

LETTER

Davisite, CaScAlSiO₆, a new pyroxene from the Allende meteorite

CHI MA* AND GEORGE R. ROSSMAN

Division of Geological and Planetary Sciences, California Institute of Technology, Pasadena, California 91125, U.S.A.

ABSTRACT

Davisite, ideally CaScAlSiO₆, is a new member of the Ca clinopyroxene group, where Sc³⁺ is dominant in the M1 site. It occurs as micro-sized crystals along with perovskite and spinel in an ultra-refractory inclusion from the Allende meteorite. The mean chemical composition determined by electron microprobe analysis is (wt%) SiO₂ 26.24, CaO 23.55, Al₂O₃ 21.05, Sc₂O₃ 14.70, TiO₂ (total) 8.66, MgO 2.82, ZrO₂ 2.00, Y₂O₃ 0.56, V₂O₃ 0.55, FeO 0.30, Dy₂O₃ 0.27, Gd₂O₃ 0.13, Er₂O₃ 0.08, sum 100.91. Its empirical formula calculated on the basis of 6 O atoms is Ca_{0.99}(Sc_{0.50}Ti_{0.16}Mg_{0.16}Ti_{0.10}Zr_{0.04}V_{0.02}³⁺Fe_{0.01}²⁺Y_{0.01})_{Σ1.00}(Si_{1.03}Al_{0.97})_{Σ2.00}O₆. Davisite is monoclinic, C2/c; *a* = 9.884 Å, *b* = 8.988 Å, *c* = 5.446 Å, β = 105.86°, *V* = 465.39 Å³, and *Z* = 4. Its electron back-scattered diffraction pattern is an excellent match to that of synthetic CaScAlSiO₆ with the C2/c structure. The strongest calculated X-ray powder diffraction lines are [*d* spacing in Å (*hkl*)]: 3.039 (100) ($\bar{2}21$), 2.989 (31) (310), 2.943 (18) ($\bar{3}11$), 2.619 (40) (002), 2.600 (26) ($\bar{1}31$), 2.564 (47) (221), 2.159 (18) ($\bar{3}31$), 2.137 (15) ($\bar{4}21$), 1.676 (20) ($\bar{2}23$), and 1.444 (18) (531). The name is for Andrew M. Davis, a cosmochemist at the University of Chicago, Illinois.

Keywords: Davisite, CaScAlSiO₆, new mineral, Sc-rich pyroxene, refractory phase, ultra-refractory inclusion, Allende meteorite

INTRODUCTION

During a nano-mineralogy investigation of the Allende meteorite, a Sc-rich pyroxene was observed in an ultra-refractory inclusion. Electron-microprobe, high-resolution SEM, electron-backscatter diffraction (EBSD), and Raman analyses have been used to characterize its composition and structure. Synthetic CaScAlSiO₆ is known (Ohashi and Ii 1978). Highly Sc-enriched pyroxenes (13–16 wt% Sc₂O₃) have been found in four Ca-,Al-rich inclusions from the Ormans, Murchison, Efremovka, and Ningqiang meteorites based on chemical analyses (Davis 1984; Davis and Hinton 1985; Simon et al. 1996; El Goresy et al. 2002; Lin et al. 2003). We report here the occurrence, composition and crystal structure of a clinopyroxene from the Allende meteorite, CaScAlSiO₆, where scandium is the dominant trivalent component in the M1 site.

MINERAL NAME AND TYPE MATERIAL

The new mineral and its name have been approved by the Commission on New Minerals, Nomenclature and Classification (IMA 2008-30). The name is for Andrew M. Davis, Professor of Cosmochemistry at the University of Chicago, born in 1950, in honor of his outstanding contributions to meteorite research. He observed a highly Sc-rich pyroxene (~15 wt% Sc₂O₃) from a meteorite in 1984 (Davis 1984). Holotype material (Caltech Section Allende12 MC2M) has been deposited in the Smithsonian Institution's National Museum of Natural History and is cataloged under USNM 7555.

* E-mail: chi@gps.caltech.edu

OCCURRENCE, ASSOCIATED MINERALS, AND ORIGIN

A fine-grained aggregate of davisite occurs with REE-rich perovskite and spinel in a single Ca-,Al-rich refractory inclusion (CAI) from the Allende meteorite (Figs. 1–2). The fractured inclusion is exposed in one polished thick section, prepared from a 1 cm Allende specimen at Caltech. The mineral occupies most of the area in this CAI, which is about 130 μm wide in the section plane, surrounded by a matrix of mostly olivine and troilite. Nearby are fragments of a likely type-II chondrule. The Allende meteorite, which fell at Pueblito de Allende, Chihuahua, Mexico, on February 8, 1969, is a CV3 carbonaceous chondrite.

APPEARANCE, PHYSICAL, AND OPTICAL PROPERTIES

The type material occurs as an aggregate. Electron back-scatter diffraction mapping reveals that the aggregate consists of crystals that are about 2–12 μm in width with different orientations. In thin section, it is transparent with a light-gray color, which may be caused by adjacent and underlying phases. Streak, luster, hardness, tenacity, cleavage, fracture, and density were not determined because of the small grain size. The density, calculated from the empirical formula, is 3.38 g/cm³. It is non-fluorescent under the beams of the electron microprobe and SEM. Optical properties were not determined because of the small grain size; *n* (calc) = 1.736. In the section, the crystal grains are irregular to subhedral. No forms or twinning were observed. The *a*:*b*:*c* ratio calculated from the unit-cell parameters is 1.0997:1:0.6059.

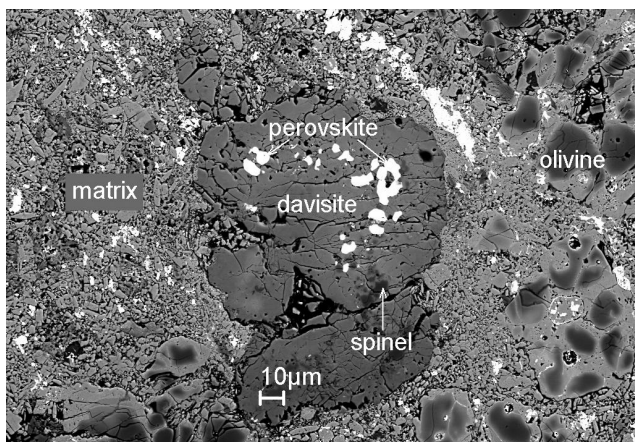


FIGURE 1. Backscatter electron image of the davisite-containing refractory inclusion in a polished section (USNM 7555) of the Allende meteorite.


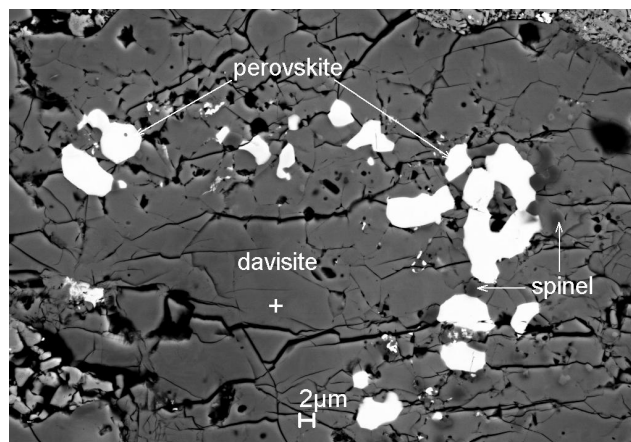


FIGURE 2. Enlarged BSE image showing davisite with perovskite and spinel (Fig. 1). The cross marks where the EBSD pattern (shown in Fig. 3) was collected.

CHEMICAL COMPOSITION

Quantitative elemental microanalyses were conducted with the JEOL 8200 electron microprobe operated at 15 kV and 25 nA in a focused beam mode. Standards for the analysis were anorthite ($\text{CaK}\alpha$, $\text{AlK}\alpha$, $\text{SiK}\alpha$), ScPO_4 ($\text{ScK}\alpha$), TiO_2 ($\text{TiK}\alpha$), zircon ($\text{ZrL}\alpha$), YPO_4 ($\text{YL}\alpha$), fayalite ($\text{FeK}\alpha$), V_2O_3 ($\text{VK}\alpha$), forsterite ($\text{MgK}\alpha$), DyPO_4 ($\text{DyL}\alpha$), GdPO_4 ($\text{GdL}\alpha$), and ErPO_4 ($\text{ErL}\alpha$). Analyses were processed with the CITZAF correction procedure (Armstrong 1995). Six individual analyses reported in Table 1 were carried out using WDS mode. No other elements with atomic number >4 were detected by WDS scans.

The empirical formula, based on 6 O atoms, is



where Ti^{3+} is calculated based on stoichiometry. The ideal, end-member formula is CaScAlSiO_6 , which requires: CaO 23.75, Sc_2O_3 29.21, Al_2O_3 21.59, SiO_2 25.45, Total 100.00 wt%.

CRYSTALLOGRAPHY

Crystallography by EBSD at a sub-micrometer scale was carried out using the methods described in Ma and Rossman (2008, 2009) with an HKL EBSD system on the ZEISS 1550VP scanning electron microscope, operated at 20 kV and 8 nA in a focused beam with a 70° tilted stage. The structure was determined and cell constants were obtained by matching the experimental EBSD pattern (Fig. 3) with the structures of synthetic CaScAlSiO_6 (Ohashi and Ii 1978), esseneite (Cosca and Peacor 1987), and orthorhombic pyroxenes (Molin 1989).

The EBSD patterns can be indexed only by the monoclinic $C2/c$ structure to give a best fit based on unit-cell data from CaScAlSiO_6 (Ohashi and Ii 1978) (Fig. 3), showing a monoclinic structure, space group: $C2/c$, $a = 9.884 \text{ \AA}$, $b = 8.988 \text{ \AA}$, $c = 5.446 \text{ \AA}$, $\beta = 105.86^\circ$, $V = 465.39 \text{ \AA}^3$, and $Z = 4$ with the mean angular deviations as low as 0.18. No errors are stated because the cell parameters are taken directly from the data of the matching CaScAlSiO_6 phase in Ohashi and Ii (1978).

X-ray powder-diffraction data ($\text{CuK}\alpha$) are calculated from

the cell parameters from Ohashi and Ii (1978) with the empirical formula from this study using Powder Cell version 2.4 (2000). The strongest X-ray powder diffraction lines are [d spacings in Å (hkl)]: 3.039 (100) (221), 2.989 (31) (310), 2.943 (18) ($3\bar{1}1$), 2.619 (40) (002), 2.600 (26) ($\bar{1}31$), 2.564 (47) (221), 2.159 (18) ($3\bar{3}1$), 2.137 (15) ($4\bar{2}1$), 1.676 (20) ($2\bar{2}3$), and 1.444 (18) (531).

SPECTROSCOPIC PROPERTIES

Raman microanalysis was carried out using the methods described in Ma and Rossman (2008, 2009). The Raman spectrum gave no indication of either H_2O or CO_2 in davisite. Raman microanalyses show that the spectrum of davisite (using a 514.5 nm laser) has intense fluorescent features and is not comparable to that of synthetic CaScAlSiO_6 (Sekita et al. 1988), which only covers a limited range, as shown in Figure 4. The intense fluorescence features are due to the significant amount of REE elements. Consequently, the identification of davisite is based on EBSD and electron-probe results only.

DISCUSSION

Davisite is a new member of the Ca clinopyroxenes (diopside group) with space group $C2/c$ (Morimoto et al. 1988), the Sc-dominant analog of esseneite ($\text{CaFe}^{3+}\text{AlSiO}_6$). Scandium is

TABLE 1. The mean analytical results of davisite

Constituent*	wt%	Range	Stand. Dev.	EPMA Standard
SiO_2	26.24	25.11–28.58	1.25	anorthite
CaO	23.55	23.37–23.65	0.10	anorthite
Al_2O_3	21.05	19.39–22.05	0.92	anorthite
Sc_2O_3	14.70	13.05–15.49	0.88	ScPO_4
TiO_2 †	8.66	8.40–8.89	0.19	TiO_2
MgO	2.82	2.20–4.03	0.65	forsterite
ZrO_2	2.00	1.66–2.15	0.18	zircon
Y_2O_3	0.56	0.51–0.60	0.03	YPO_4
V_2O_3	0.55	0.49–0.64	0.05	V_2O_5
FeO	0.30	0.27–0.33	0.02	fayalite
Dy_2O_3	0.27	0.16–0.33	0.07	DyPO_4
Gd_2O_3	0.13	0.08–0.21	0.05	GdPO_4
Er_2O_3	0.08	0.03–0.14	0.04	ErPO_4
Total	100.91			

* All listed constituents are above their detection limits at 99% confidence
† Total TiO_2 wt% recalculated to 4.64 wt% Ti_2O_3 + 3.57 wt% TiO_2 to obtain stoichiometry and valency balance, gives a new analytical total = 100.46 wt%.

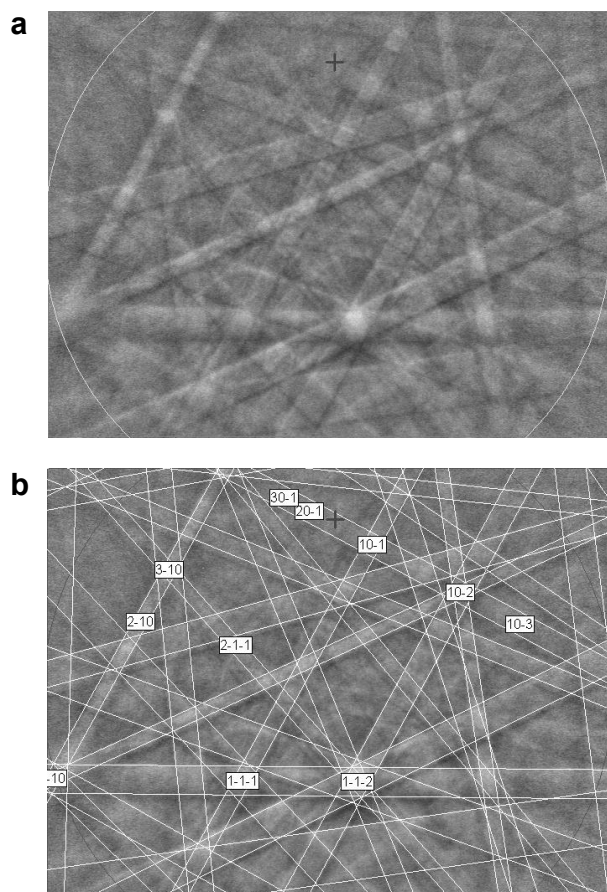


FIGURE 3. (a) EBSD pattern of the labeled davisite crystal (marked with a cross) in Figure 2; (b) the pattern perfectly indexed with the $C2/c$ CaScAlSiO_6 structure.

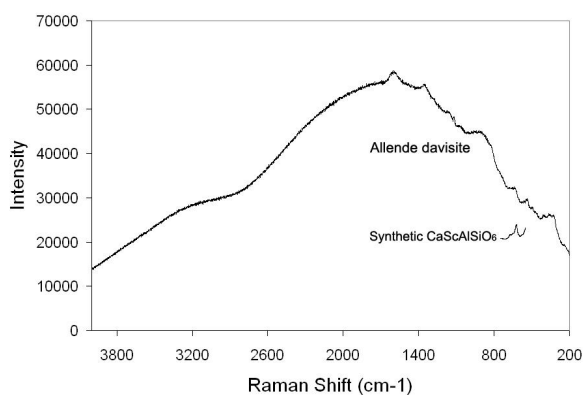


FIGURE 4. Raman spectra of davisite (this study) and synthetic CaScAlSiO_6 (Sekita et al. 1988), collected under different conditions, showing relative intensities. The spectrum for the synthetic sample covers a very limited range, and is displaced vertically from the zero line to facilitate comparison with the davisite spectrum.

a sparsely distributed element in the Earth's crust, but is significantly more abundant in the sun and primitive meteorites (Weaver and Tamey 1984; Anders and Grevesse 1989). The Allende meteorite containing 11~12 ppm (Jarosewich et al. 1987) has provided a variety of phases with high scandium contents

including oxides, pyroxenes, and perovskites in Ca-,Al-rich refractory inclusions. The newly discovered mineral allendeite ($\text{Sc}_4\text{Zr}_3\text{O}_{12}$, IMA 2007-027) and its associated Sc-stabilized tazheranite [cubic zirconia, $(\text{Zr,Sc,Ca})\text{O}_{1.75}$] from Allende are the most Sc-rich oxides found to date (Ma et al. 2009). Davisite is one of the more Sc-rich phases ever reported currently surpassed only by pretulite (ScPO_4), thortveitite [$(\text{Sc,Y})_2\text{Si}_2\text{O}_7$], kolbeckite ($\text{ScPO}_4 \cdot 2\text{H}_2\text{O}$), and the newly approved mineral allendeite.

Refractory inclusions are the first known solids formed in the solar system. Davisite is a new refractory mineral from Allende, associated with REE-rich perovskite with a formula $(\text{Ca}_{0.81}\text{Y}_{0.07}\text{Dy}_{0.03}\text{Gd}_{0.02}\text{Sc}_{0.02}\text{Na}_{0.01})(\text{Ti}_{0.94}\text{Al}_{0.03}\text{V}_{0.01}\text{Fe}_{0.01})\text{O}_3$ and Mg-Al spinel in an ultra-refractory inclusion. This fine-grained inclusion shows an irregular shape without a rim. Its mineralogy is characterized by high refractory and rare earth elements enrichment in perovskite and davisite. The inclusion is likely formed through high-temperature condensation in the solar nebula, followed by partial melting and crystallization. A more detailed geochemical investigation of refractory elements and REE in this ultra-refractory inclusion is in progress (Ma et al. in prep). It is unlikely that this CAI is associated with the nearby Type-II ferromagnesian chondrule fragments.

Other pyroxenes from CAIs in the Ornans, Murchison, Efremovka, and Ningqiang chondrites where Sc^{3+} dominates the M1 site with 44 to 56% occupancy (Davis 1984; Davis and Hinton 1985; Simon et al. 1996; El Goresy et al. 2002; Lin et al. 2003) would be davisite as well if their structure can be verified to be $C2/c$ by EBSD or other diffraction methods. Ca-pyroxenes containing up to several weight percent of Sc_2O_3 are not rare in CAIs (e.g., Simon et al. 1996; El Goresy et al. 2002; this study). It is apparent that a solid solution exists between Al-,Ti-rich diopside and davisite.

ACKNOWLEDGMENTS

The Caltech Analytical Facility at the Division of Geological and Planetary Sciences is supported, in part, by grant NSF EAR-0318518 and the MRSEC Program of the NSF under DMR-0080065. Funding from NSF grant EAR-0337816 is also acknowledged. We thank Alan Rubin and Kimberly Tait for reviewing this manuscript.

REFERENCES CITED

- Anders, E. and Grevesse, N. (1989) Abundances of the elements: Meteoritic and solar. *Geochimica et Cosmochimica Acta*, 53, 197–214.
- Armstrong, J.T. (1995) CITZAF: A package of correction programs for the quantitative electron microbeam X-ray analysis of thick polished materials, thin films, and particles. *Microbeam Analysis*, 4, 177–200.
- Cosca, M.A. and Peacor, D.R. (1987) Chemistry and structure of esseneite (CaFeAlSiO_6), a new pyroxene produced by pyrometamorphism. *American Mineralogist*, 72, 148–156.
- Davis, A.M. (1984) A scandalously refractory inclusion in Ornans. *Meteoritics*, 19, 214.
- Davis, A.M. and Hinton, R.W. (1985) Trace element abundances in OSCAR, a scandium-rich refractory inclusion from the Ornans meteorite. *Meteoritics*, 20, 633–634.
- El Goresy, A., Zinner, E., Matsunami, S., Palme, H., Spettel, B., Lin, Y., and Nazarov, M. (2002) Efremovka 101.1: A CAI with ultrarefractory REE patterns and enormous enrichments of Sc, Zr, and Y in fassaite and perovskite. *Geochimica et Cosmochimica Acta*, 66, 1459–1491.
- Jarosewich, E., Clarke Jr., R.S., and Barrows, J.N. (1987) The Allende meteorite reference sample. *Smithsonian Contributions to the Earth Sciences*, No.27.
- Lin, Y., Kimura, M., and Wang, D. (2003) Fassaite in compact type A Ca-Al-rich inclusions in the Ningqiang carbonaceous chondrite: Evidence for partial melting in the nebula. *Meteoritics and Planetary Science*, 38, 407–417.
- Ma, C. and Rossman, G.R. (2008) Barioperovskite, BaTiO_3 , a new mineral from the Benitoite Mine, California. *American Mineralogist*, 93, 154–157.
- (2009) Tistarite, Ti_2O_3 , a new refractory mineral from the Allende meteorite.

- American Mineralogist, 94, 841–844.
- Ma, C., Beckett, J.R., and Rossman, G.R. (2009) Allendeite and hexamolybdenum: Two new ultra-refractory minerals in Allende and two missing links. 40th Lunar and Planetary Science Conference, The Woodlands, Texas, Abstract 1402.
- Molin, G.M. (1989) Crystal-chemical study of cation disordering in Al-rich and Al-poor orthopyroxenes from spinel lherzolite xenoliths. *American Mineralogist*, 74, 593–598.
- Morimoto, N., Fabries, J., Ferguson, A.K., Ginzburg, I.V., Ross, M., Seifert, F.A., Zussman, J., Aoki, K., and Gottardi, G. (1988) Nomenclature of pyroxenes. *American Mineralogist*, 73, 1123–1133.
- Ohashi, H. and Ii, N. (1978) Structure of calcium scandium aluminum silicate (CaScAlSiO_6)-pyroxene. *Journal of the Japanese Association of Mineralogists, Petrologists and Economic Geologists*, 73, 267–273.
- Sekita, M., Ohashi, H., and Terada, S. (1988) Raman spectroscopic study of clinopyroxenes in the system calcium scandium aluminum silicate (CaScAlSiO_6)—calcium aluminum silicate ($\text{CaAl}_2\text{SiO}_6$). *Physics and Chemistry of Minerals*, 15, 319–322.
- Simon, S.B., Davis, A.M., and Grossman, L. (1996) A unique ultrarefractory inclusion from the Murchison meteorite. *Meteoritics and Planetary Science*, 31, 106–115.
- Weaver, B.L. and Tamey, J. (1984) Major and trace element composition of the continental lithosphere. In H.N. Pollack and V.R. Murthy, Eds., *Physics and Chemistry of the Earth*, 15, p. 39–68. Pergamon, Oxford.

MANUSCRIPT RECEIVED FEBRUARY 4, 2009

MANUSCRIPT ACCEPTED FEBRUARY 18, 2009

MANUSCRIPT HANDLED BY BRYAN CHAKOUMAKOS