



Progress of Inorganic Scintillators for Future HEP Experiments

Liyuan Zhang and Ren-Yuan Zhu

California Institute of Technology

October 30, 2024





Why Inorganic Scintillators?

arXiv: 2203.06731 and arXiv: 2203.06788



- Precision e/γ enhance physics discovery potential.
- Performance of total absorption ECAL is well understood for e/γ and jets:
 - Energy resolution achieved: $2\%/\sqrt{E} \oplus 1\%$
 - Position resolution: sub-mm can be achieved;
 - Good identification and reconstruction efficiency;
 - Excellent jet mass resolution with dual readout: C/S light or S/L gate.
- On-going Development in the Caltech HEP Crystal Lab:
 - Rad-hard LYSO:Ce crystals and LuAG:Ce ceramics: **RADiCAL for FCC-hh;**
 - Ultrafast BaF₂:Y and Lu₂O₃:Yb: **Ultrafast calorimetry and time of flight (TOF);**
 - Cost-effective ABS and DSB glasses: **CalVision for Higgs factory and HHCAL.**




L3 BGO, BaBar Csl:TI, CMS PWO and Mu2e Csl



11.4k BGO

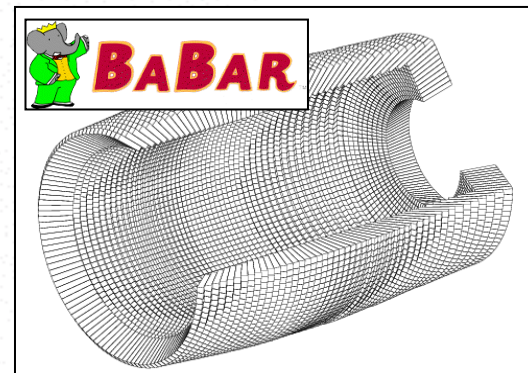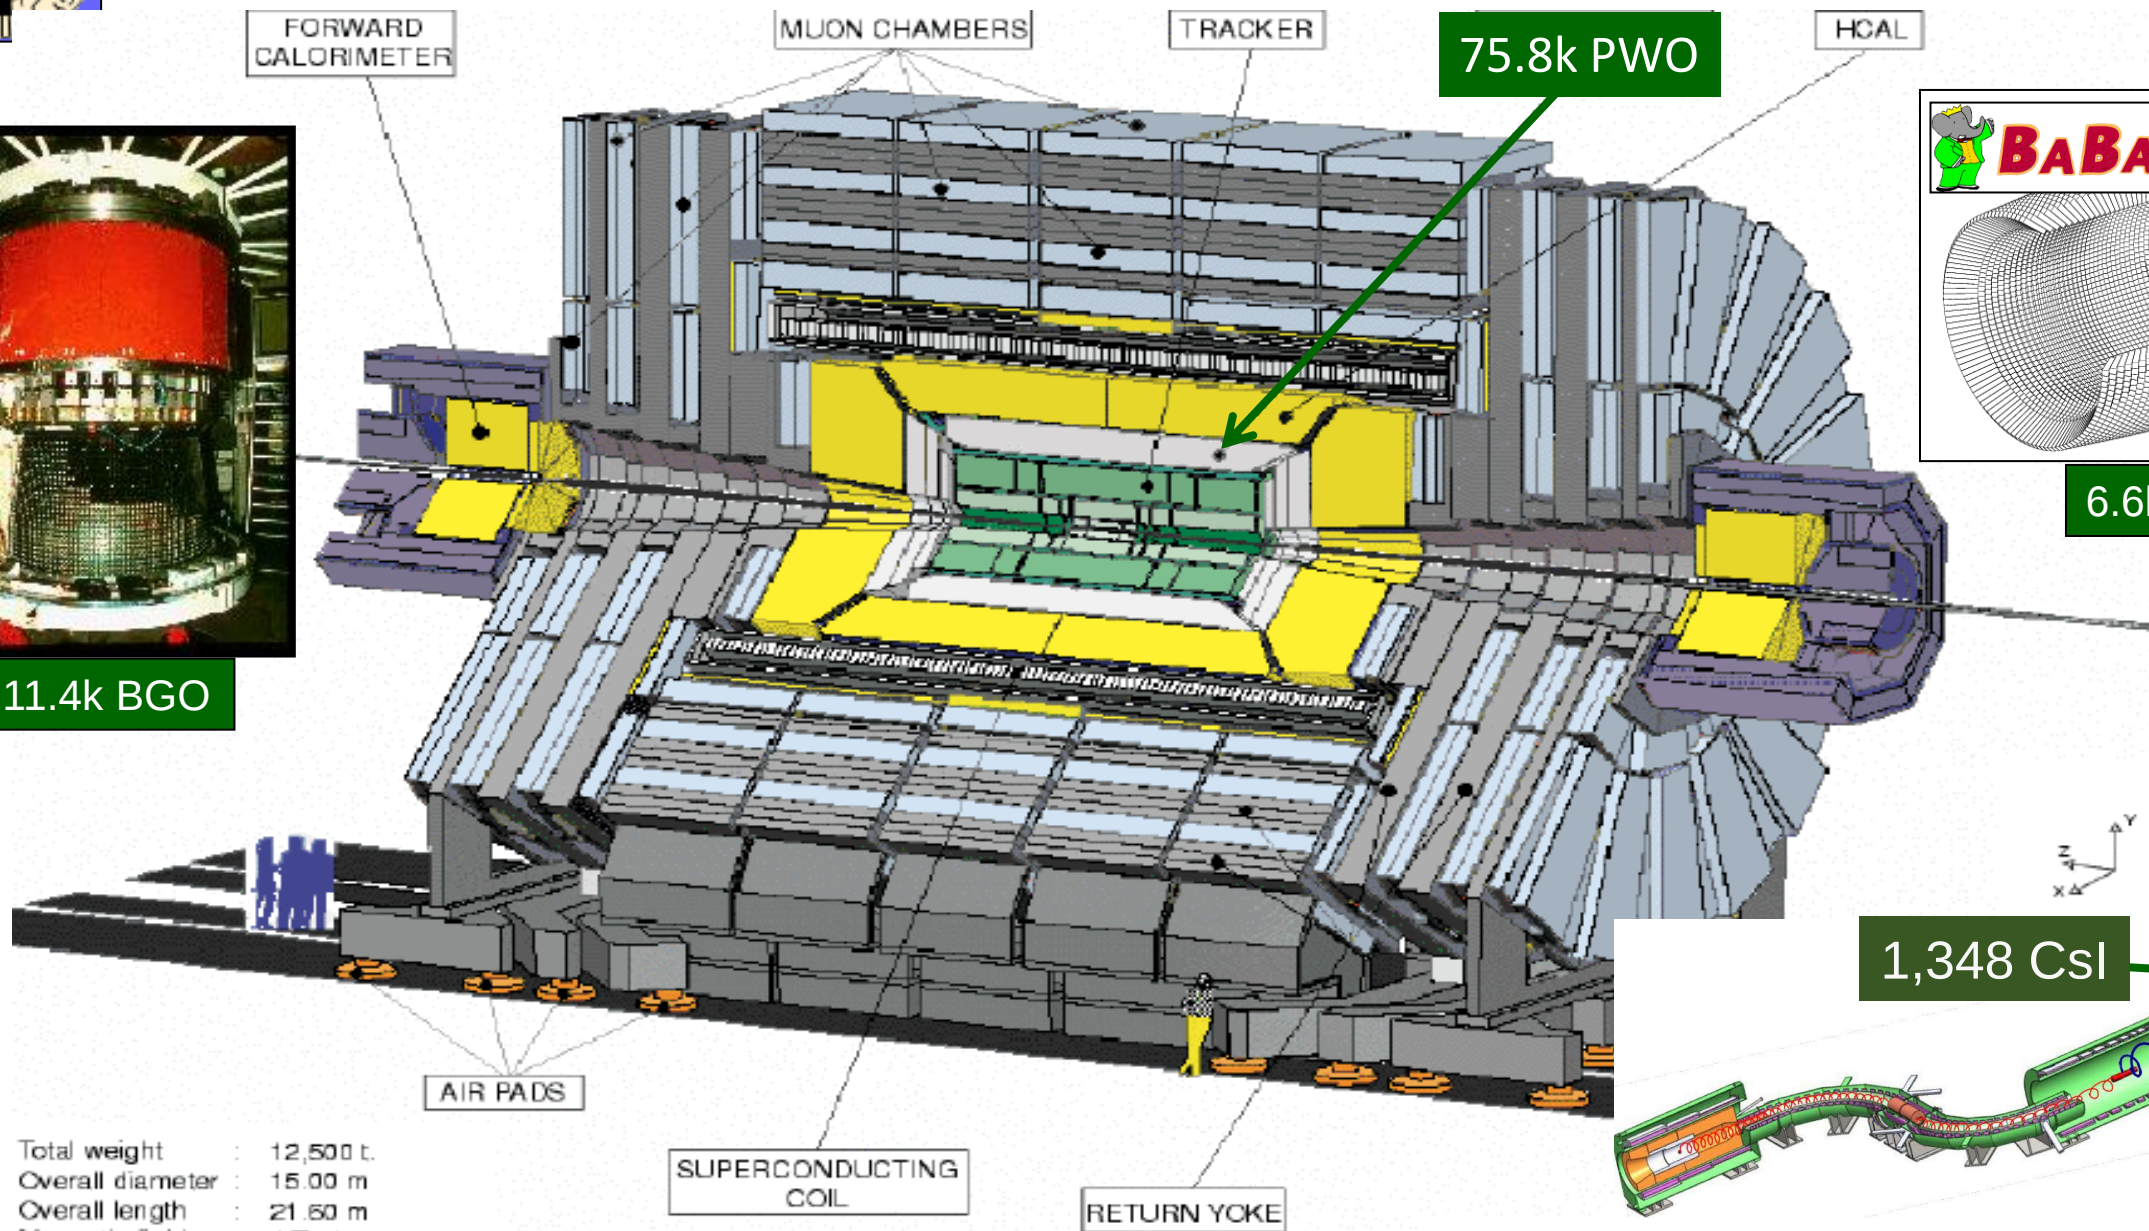

6.6k Csl:TI

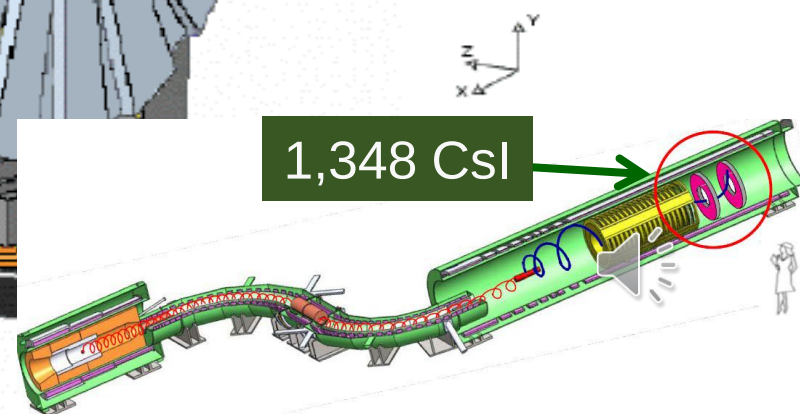



1,348 CsI

Total weight : 12,500 t.
Overall diameter : 15.00 m
Overall length : 21.60 m
Magnetic field : 4 Tesla

CMS H $\rightarrow \gamma\gamma$ and PWO Damage

M. Tornago, in Calor 2024, Tsukuba

CMS Preliminary

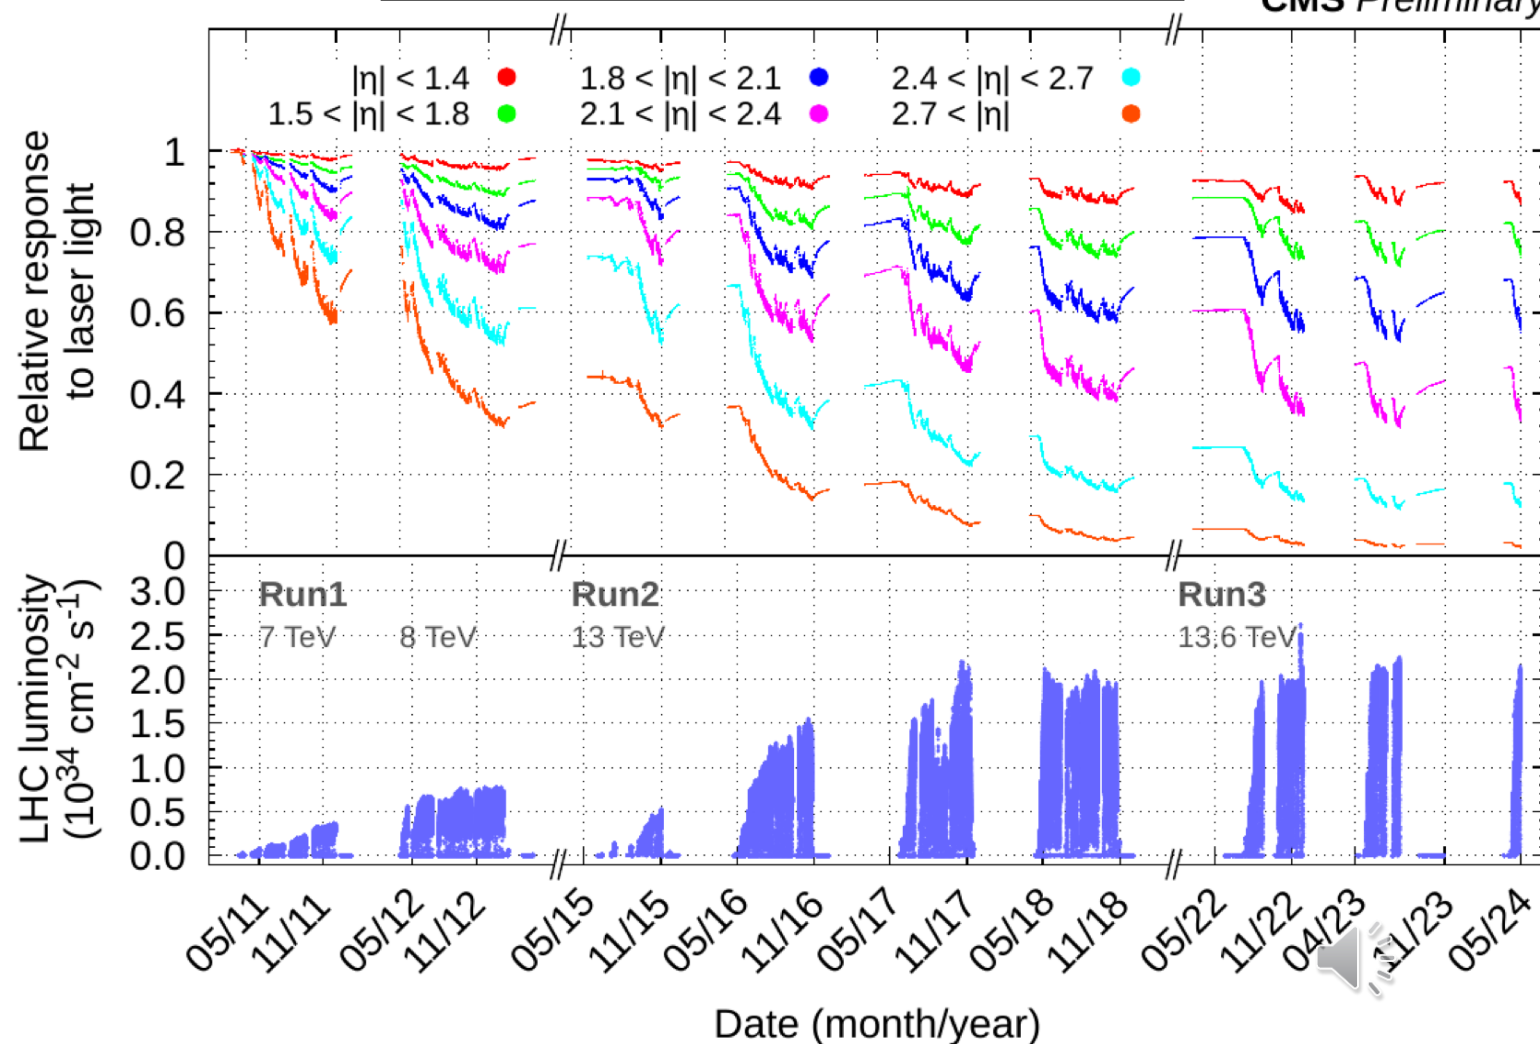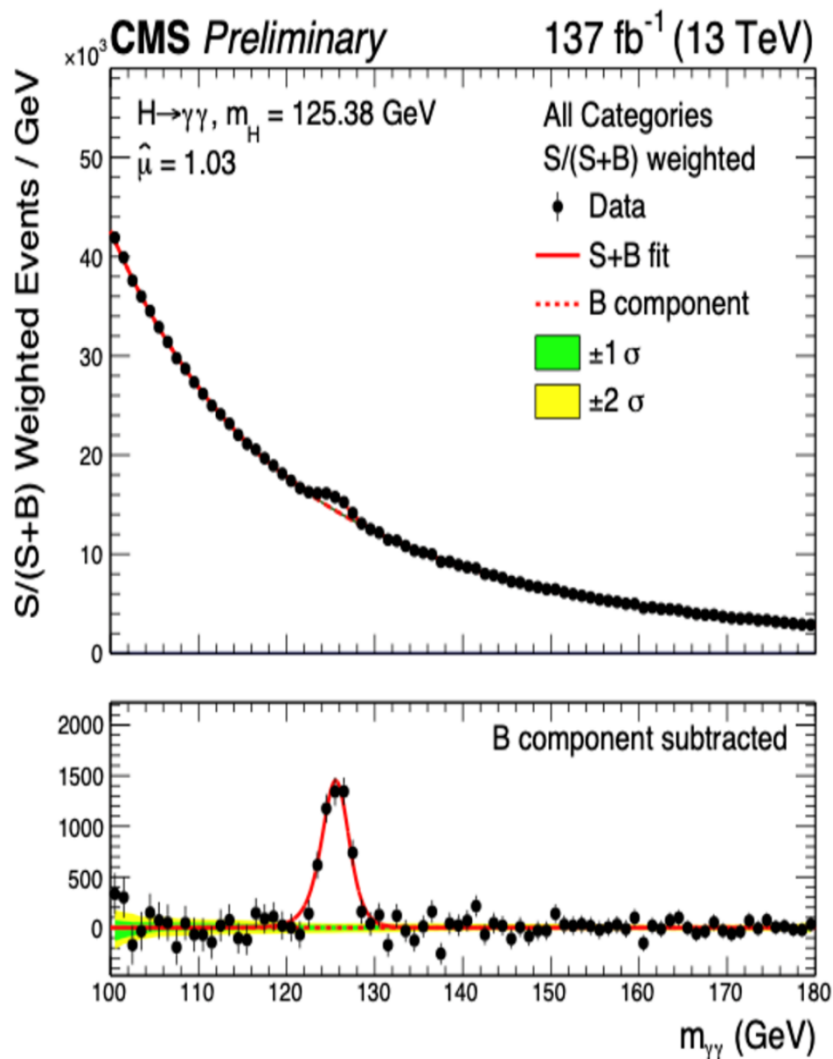




PWO damage caused by ionization dose and hadrons

PWO Damage by Ionization & Neutrons

$$\text{RIAC in PWO} = 1.4 \times 10^{-14} \times 1 \text{ MeV } n_{\text{eq}} \text{ Fluence}$$

γ -ray and neutron induced absorption explains CMS PWO monitoring data




Trans. NS. 67 (2020) 1086-1092 & http://www.its.caltech.edu/~rzhu/talks/ryz_161028_PWO_mon.pdf

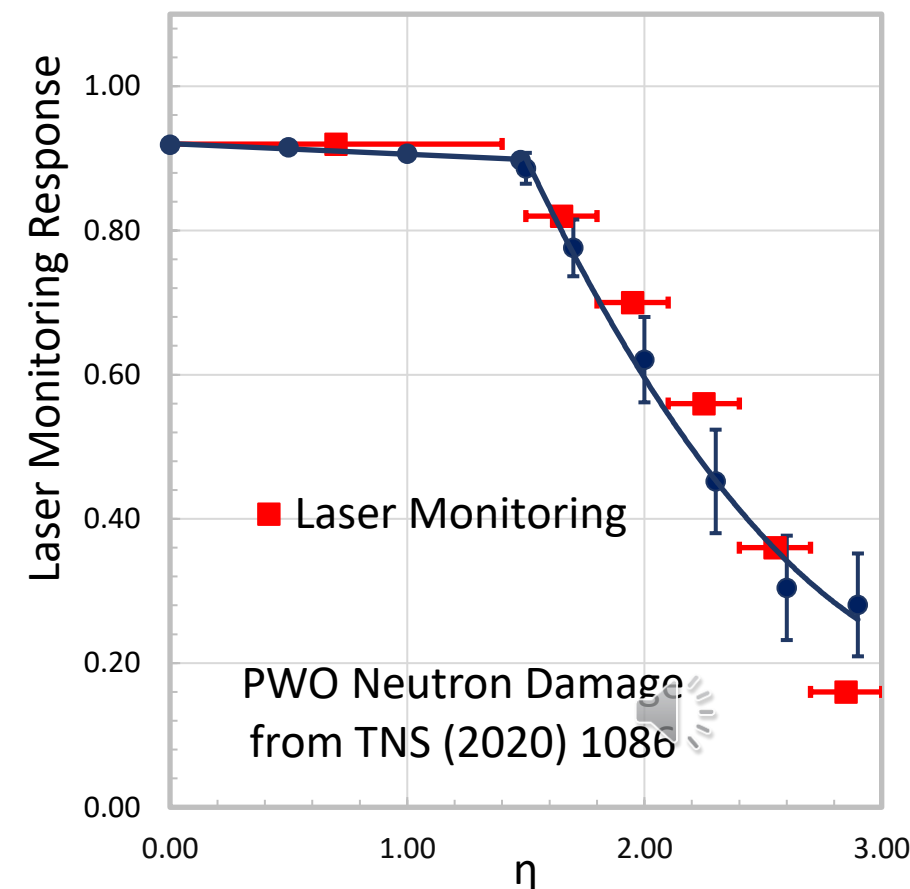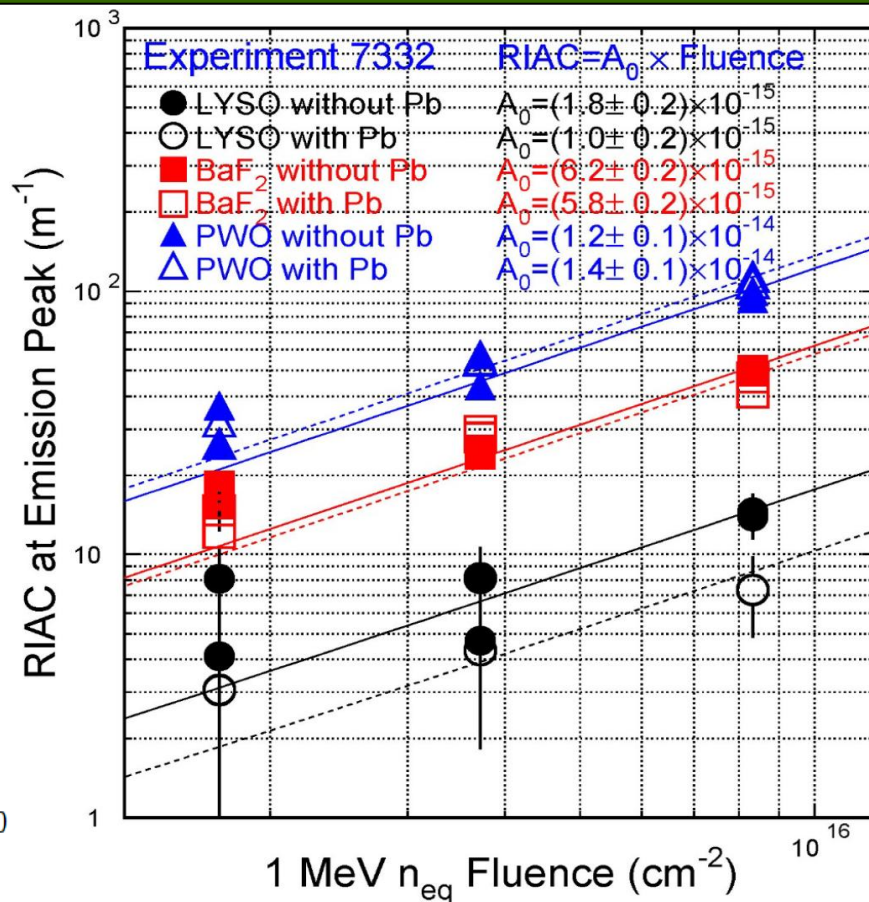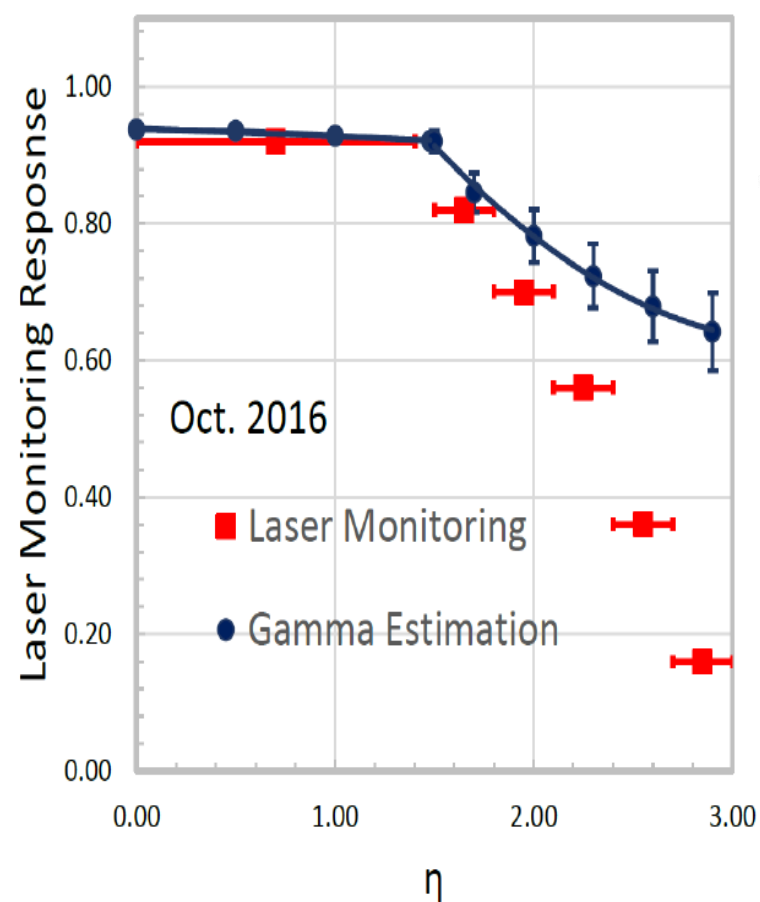

LYSO:Ce Radiation Hardness

IEEE TNS 63 (2016) 612-619

CMS BTL LYSO spec: RIAC < 3 m⁻¹ after 4.8 Mrad, 2.5 x 10¹³ p/cm² and 3.2 x 10¹⁴ n_{eq}/cm²

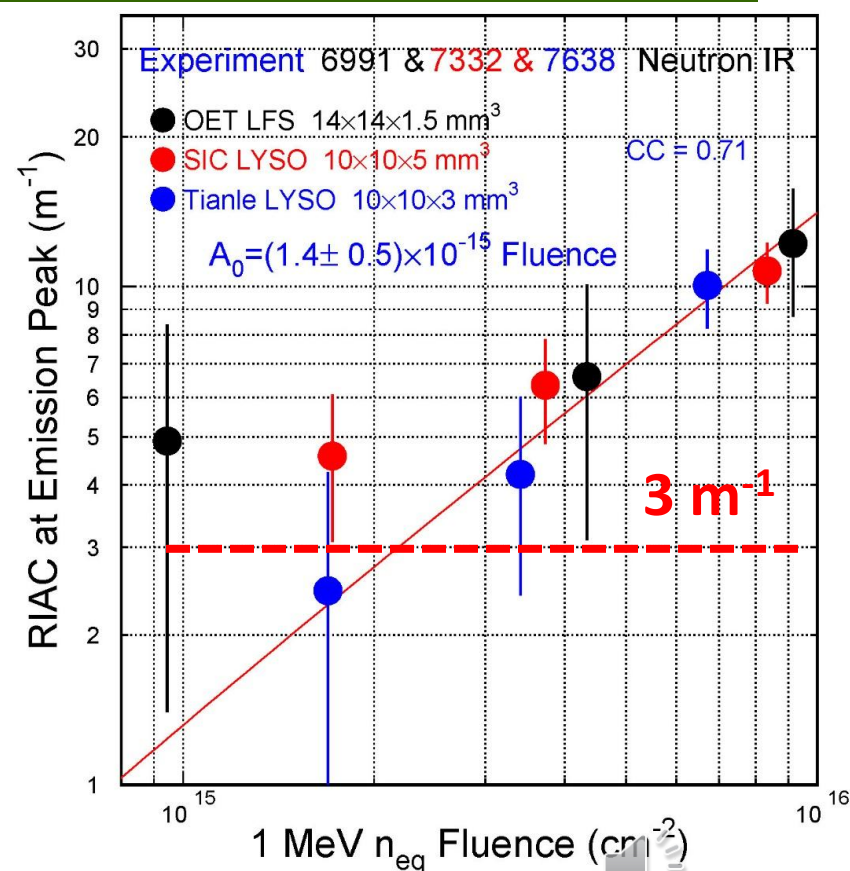
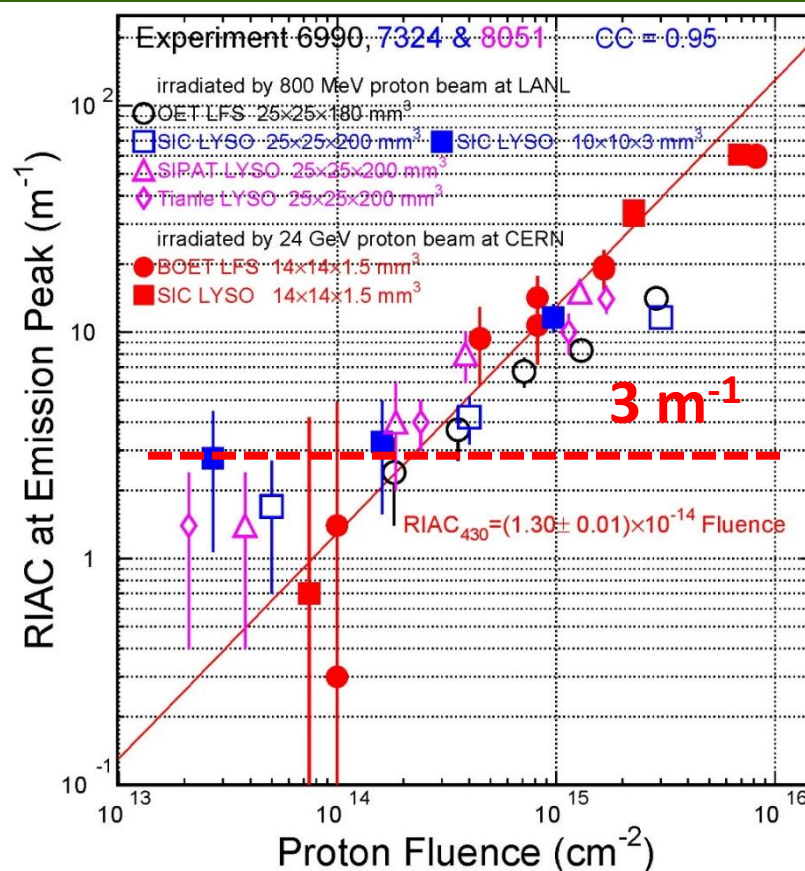
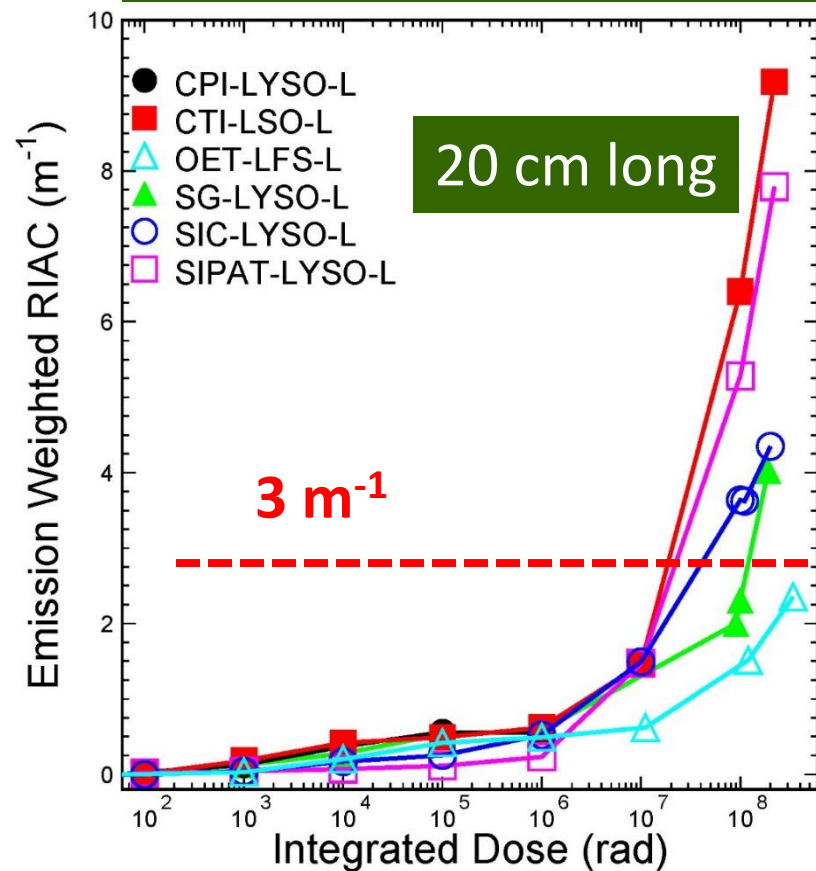


Damage induced by protons is larger than that from neutrons because of ionization energy loss in addition to displacement and nuclear breakup

LuAG:Ce Ceramics Radiation Hardness



IEEE TNS 69 (2022) 181-186

LuAG:Ce ceramics show a factor of two smaller RIAC values than LYSO:Ce up to $6.7 \times 10^{15} \text{ n}_{\text{eq}}/\text{cm}^2$ and $1.2 \times 10^{15} \text{ p}/\text{cm}^2$, promising for FCC-hh

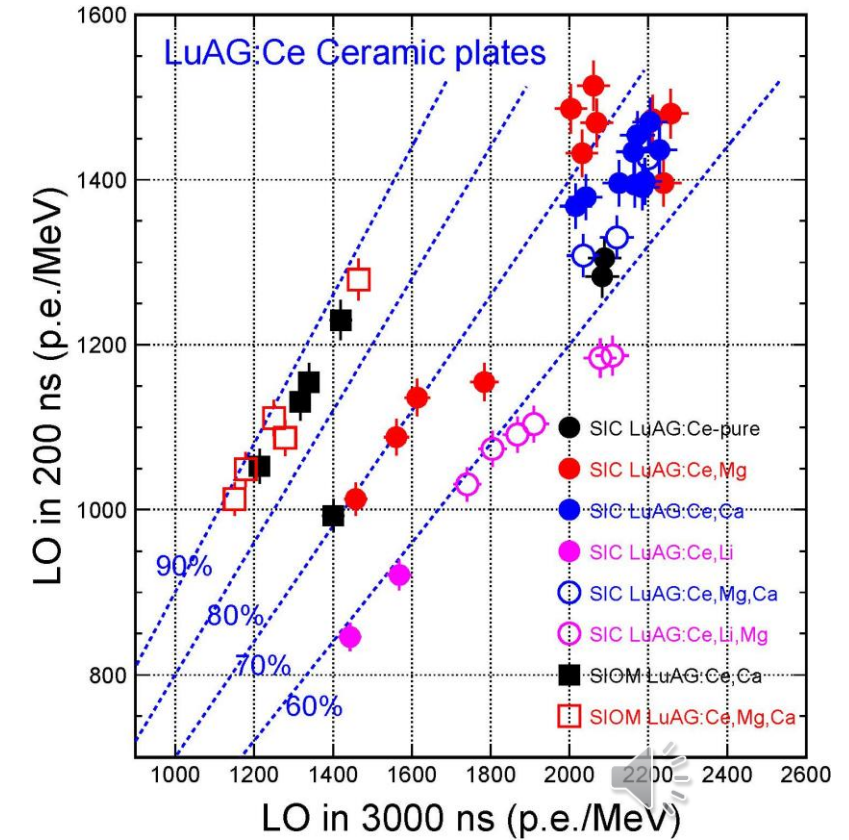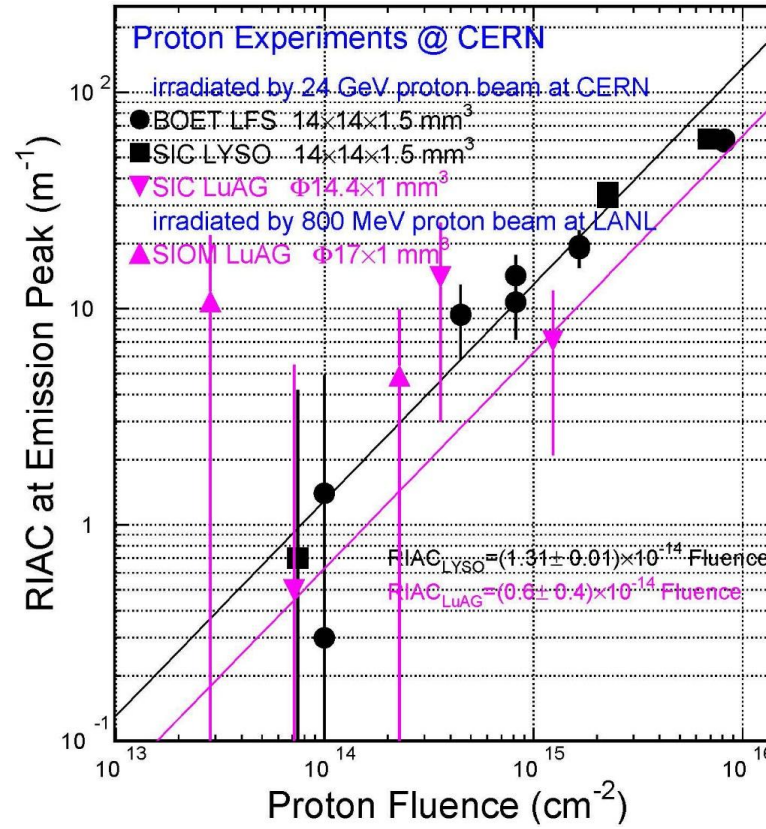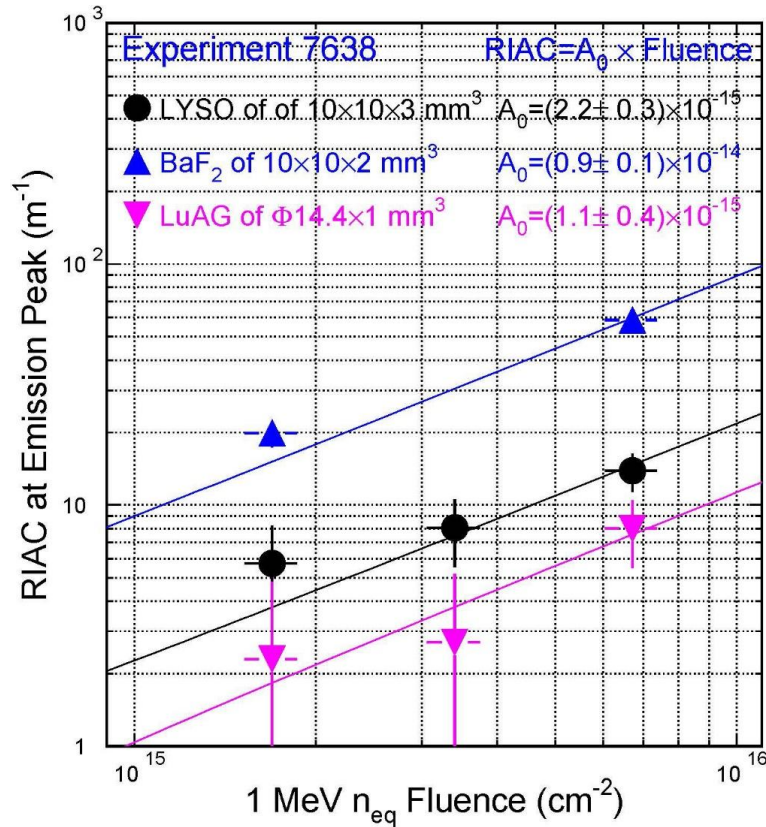


R&D on slow component suppression by Ca co-doping, and radiation hardness by $\gamma/\text{p}/\text{n}$

RADiCAL: LYSO/LuAG Shashlik ECAL



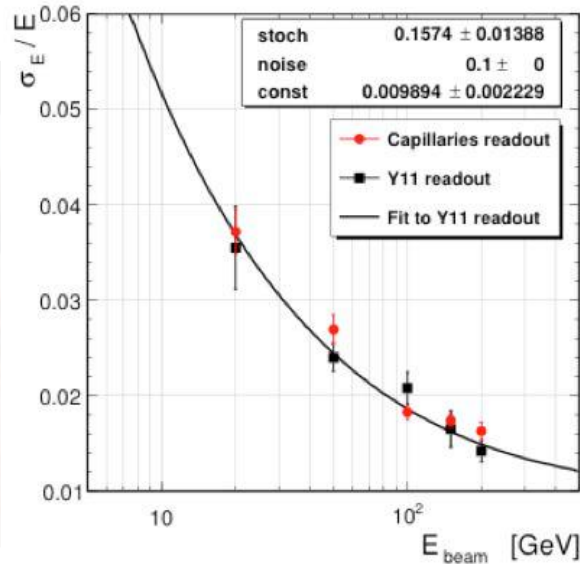
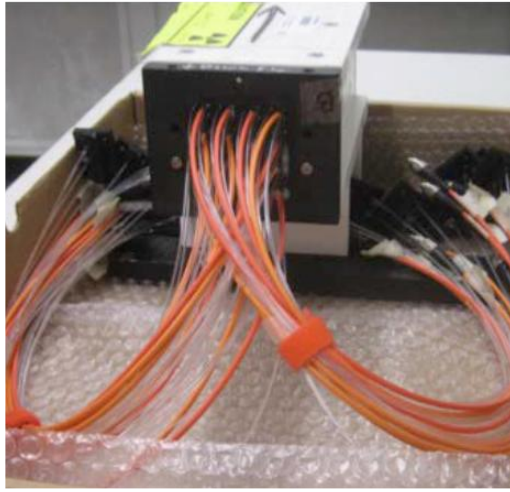


arXiv: 2203.12806

RADIation hard **CAL**orimetry
Reducing light path length to
mitigate radiation damage effect
Using radiation hard materials:
LuAG:Ce ceramics excitation
matches LYSO:Ce emission







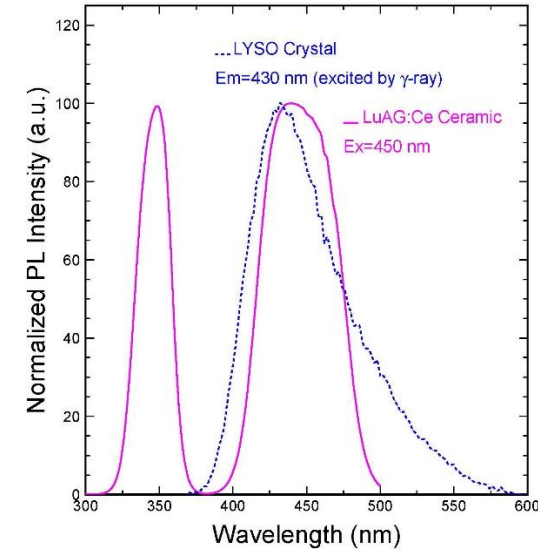


LuAG:Ce fibers

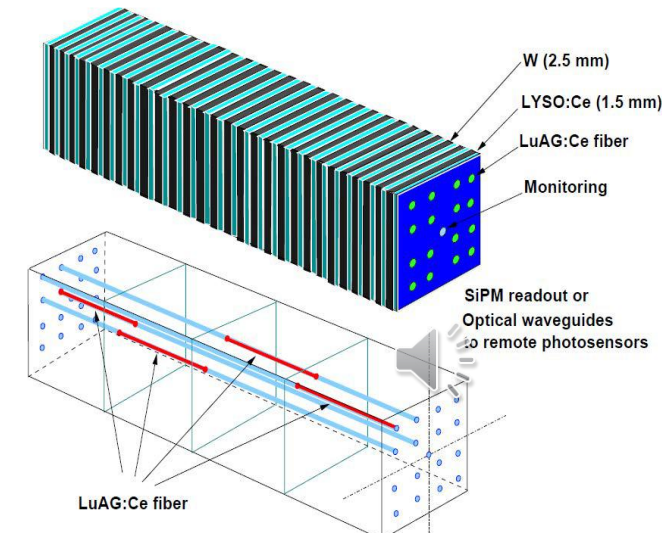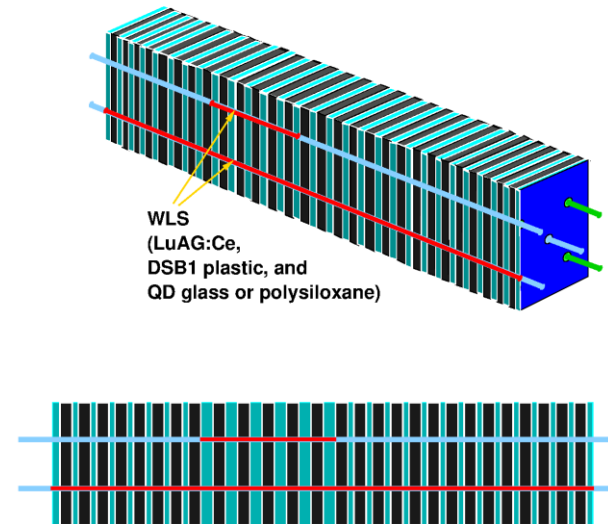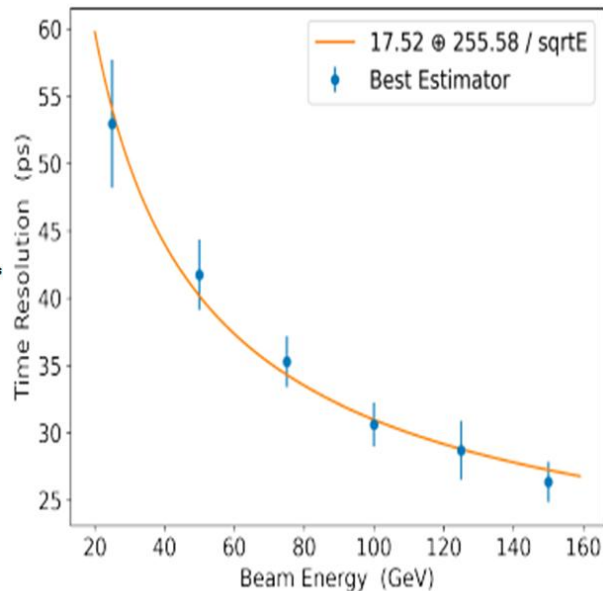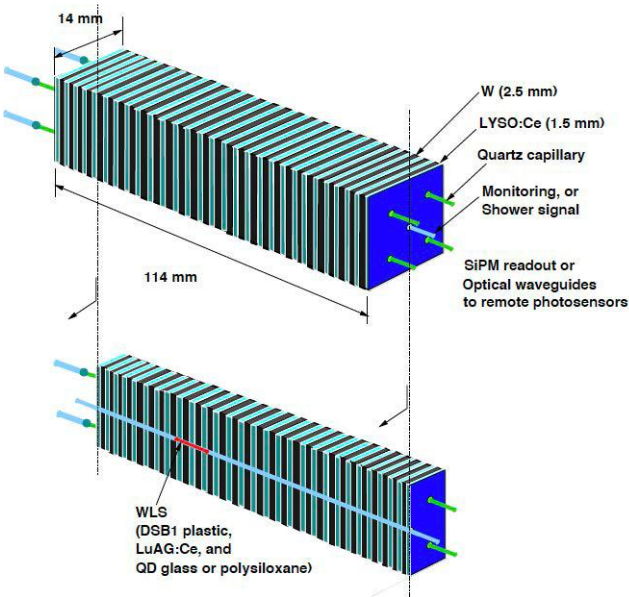

BaF₂:Y Ultrafast Calorimetry & Imaging




Increased F/S ratio observed in BaF₂:Y crystals: Proc. SPIE 10392 (2017)

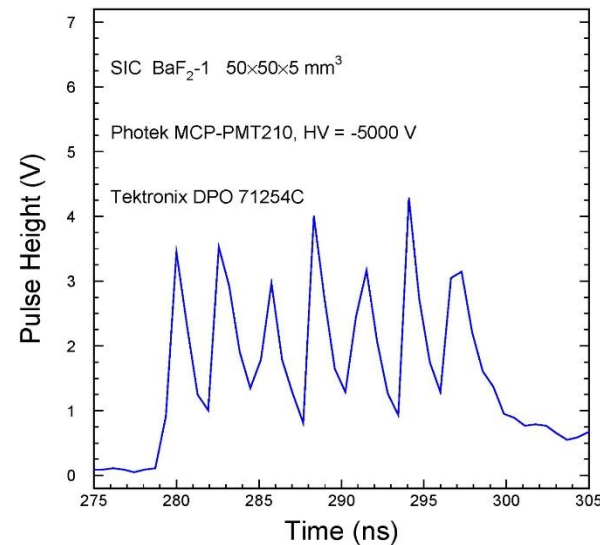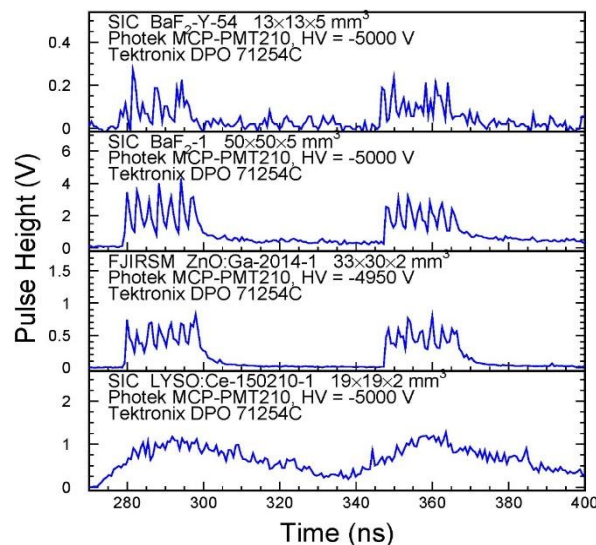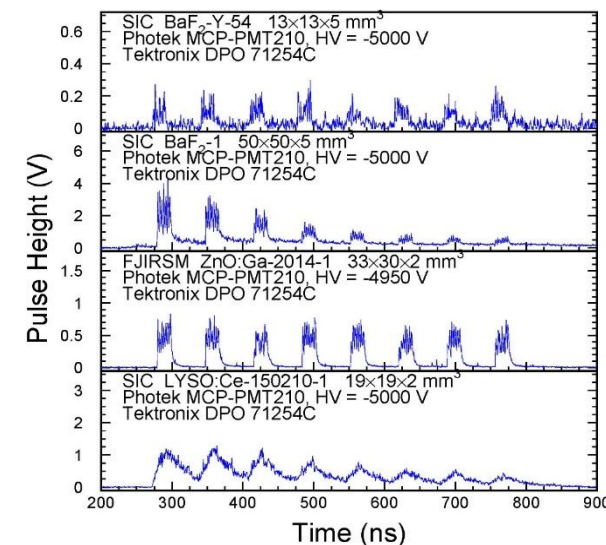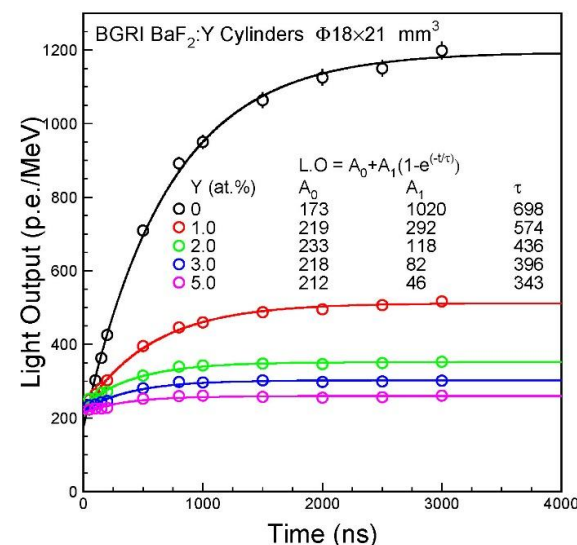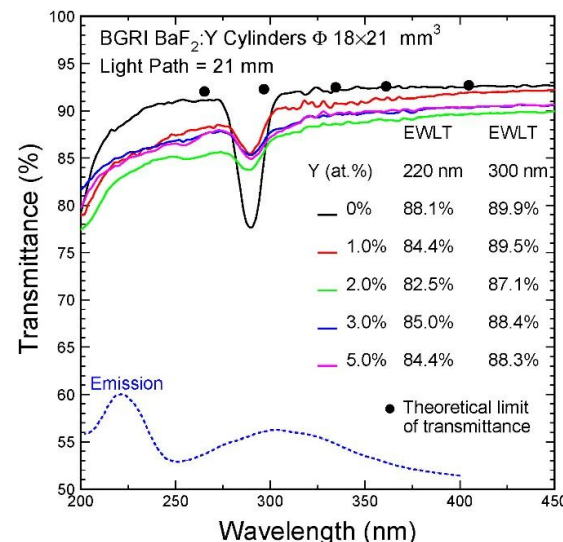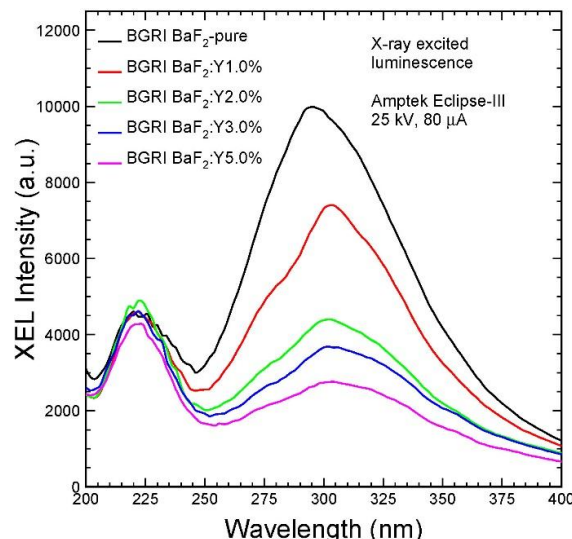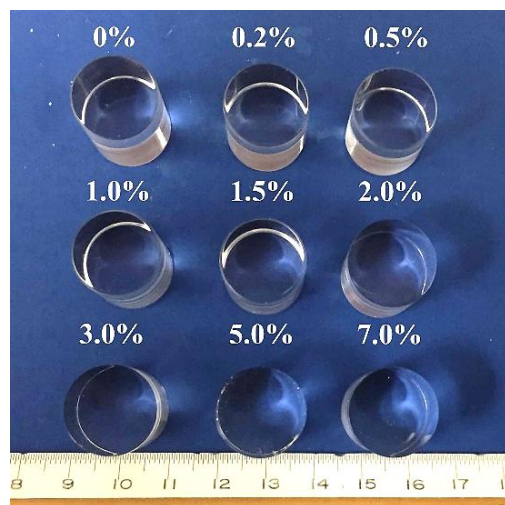

X-ray bunches with 2.83 ns spacing in septuplet are clearly resolved by ultrafast BaF₂:Y and BaF₂ crystals: for GHz Hard X-ray Imaging NIMA 240 (2019) 223-239

Novel $\text{Lu}_2\text{O}_3:\text{Yb}$ Ceramics




Instruments 2022, 6(4), 67, see Lakshmi S. Pandian paper N12-05 in this conference

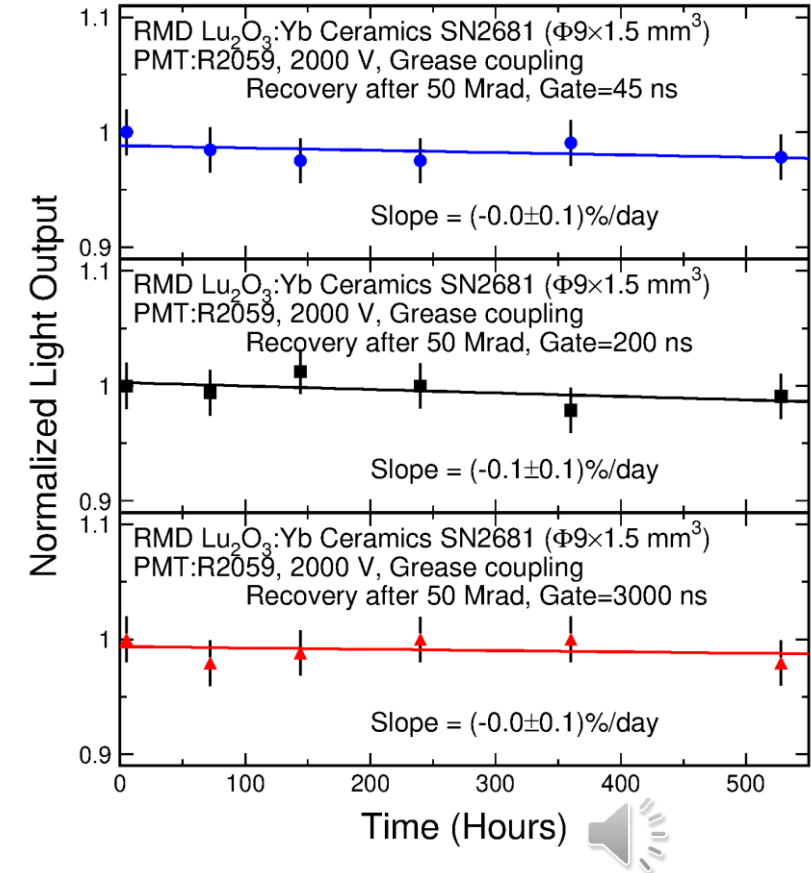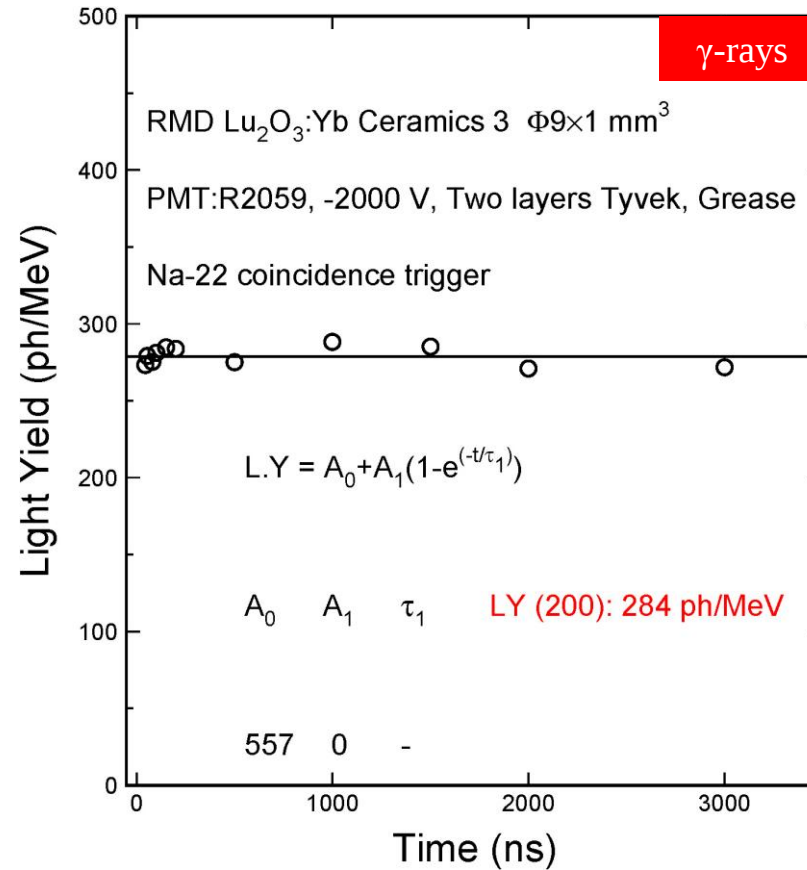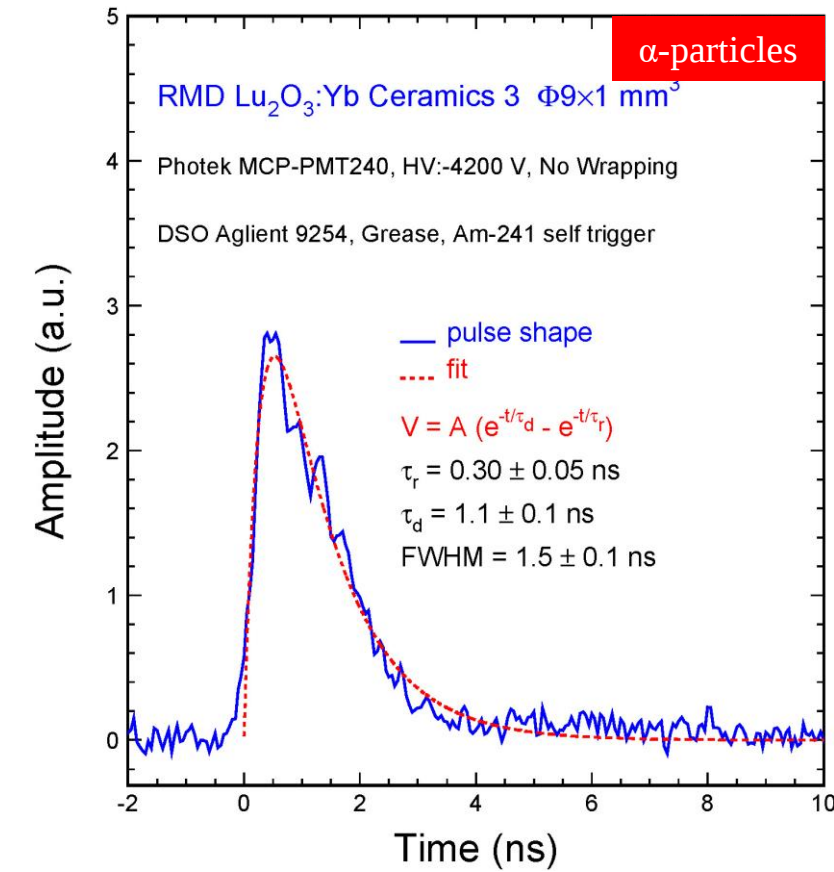



$\text{Lu}_2\text{O}_3:\text{Yb}$ ceramic (9.4 g/cc **1.1 ns**), proposed for the RADiCAL concept

CalVision: Segmented Crystal ECAL



Followed by the IDEA DR HCAL, aiming at both EM and jet resolution

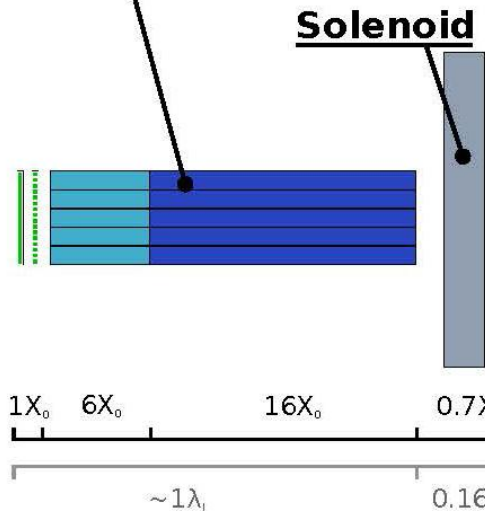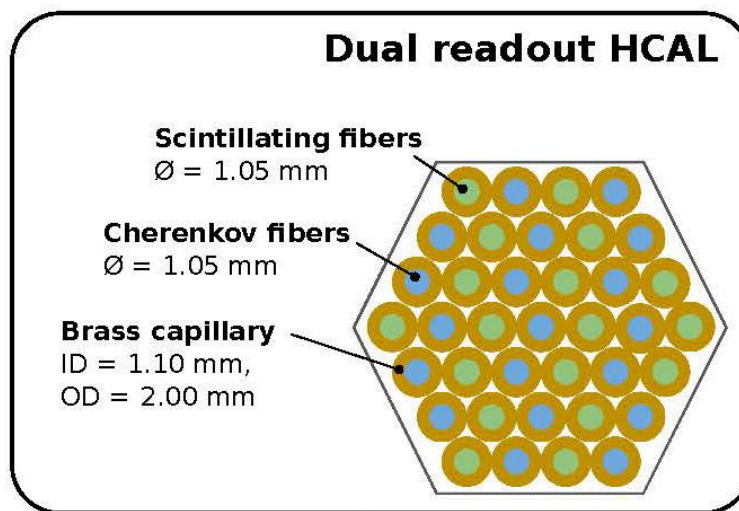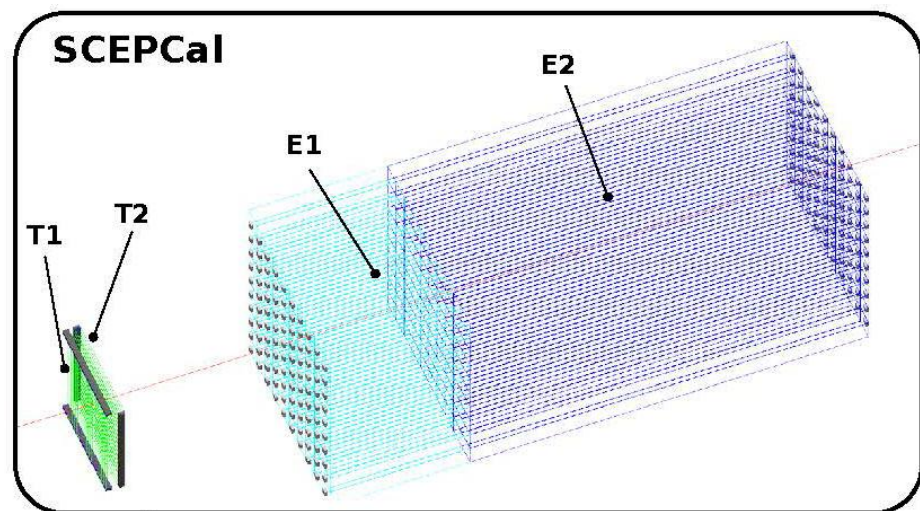


M. Lucchini et al., JINST 15 (2020) P11005

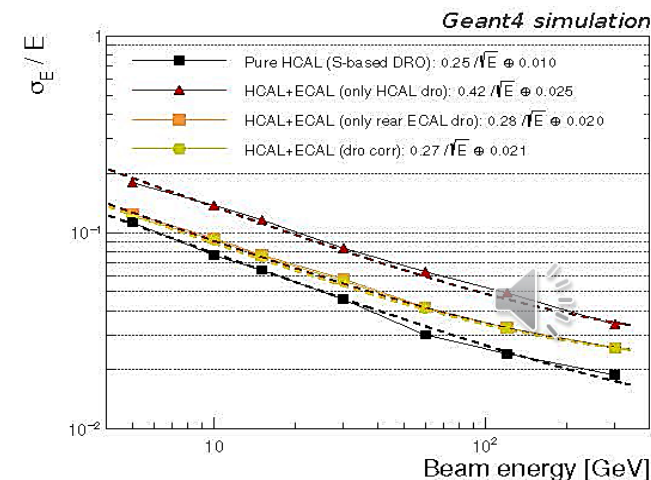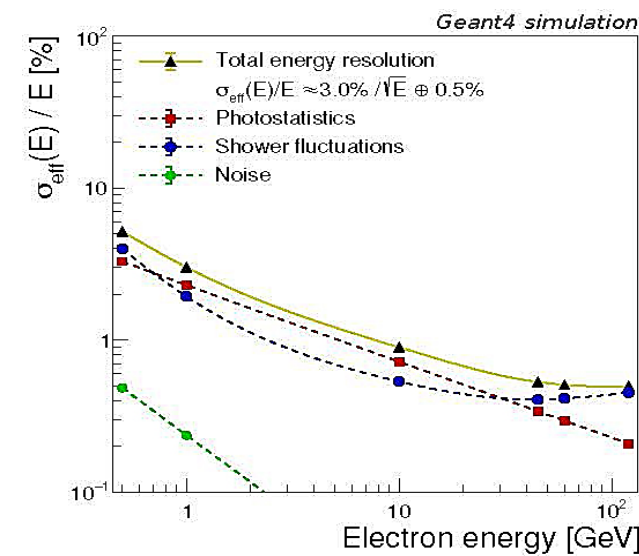


The HHCAL Concept

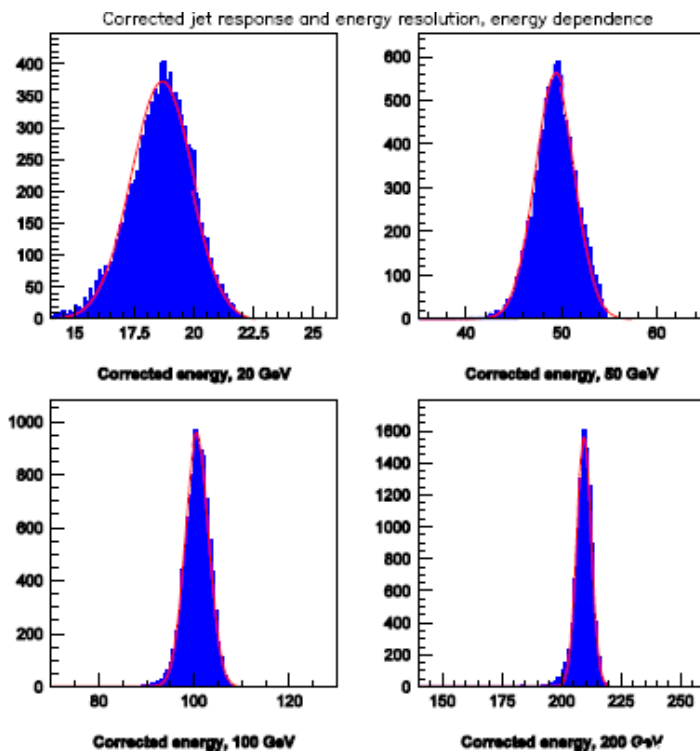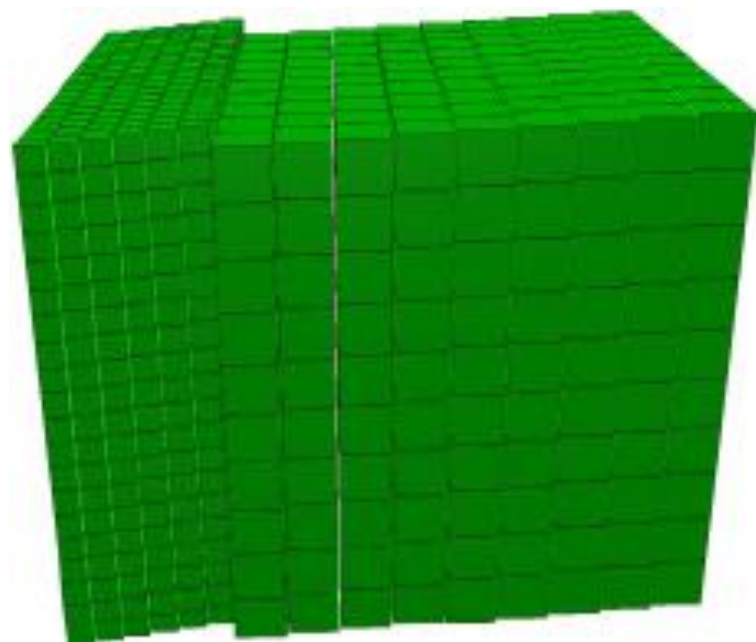

A. Para, H. Wenzel and S. McGill in Callor2012 Proceedings and A. Benaglia *et al.*, IEEE TNS **63** (2016) 574-579: a jet energy resolution at a level of $20\%/\sqrt{E}$ by HHCAL with dual readout of S/C or dual gate.
M. Demarteau, 2021 CPAD Workshop

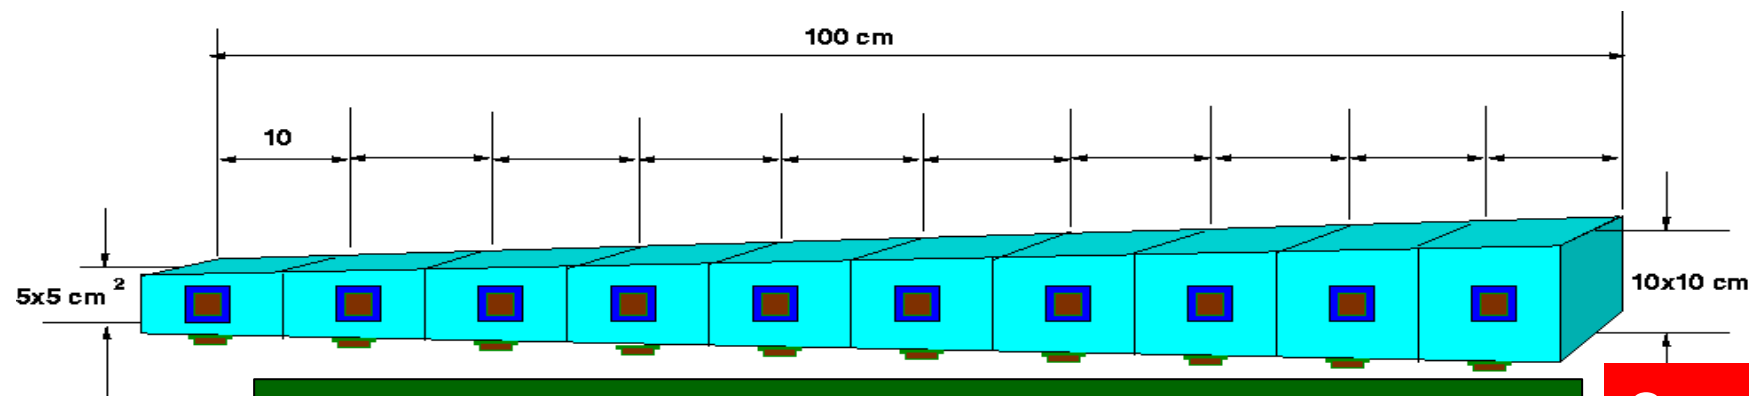






R.-Y. Zhu, ILCWS-8, Chicago: a HHCAL cell with pointing geometry

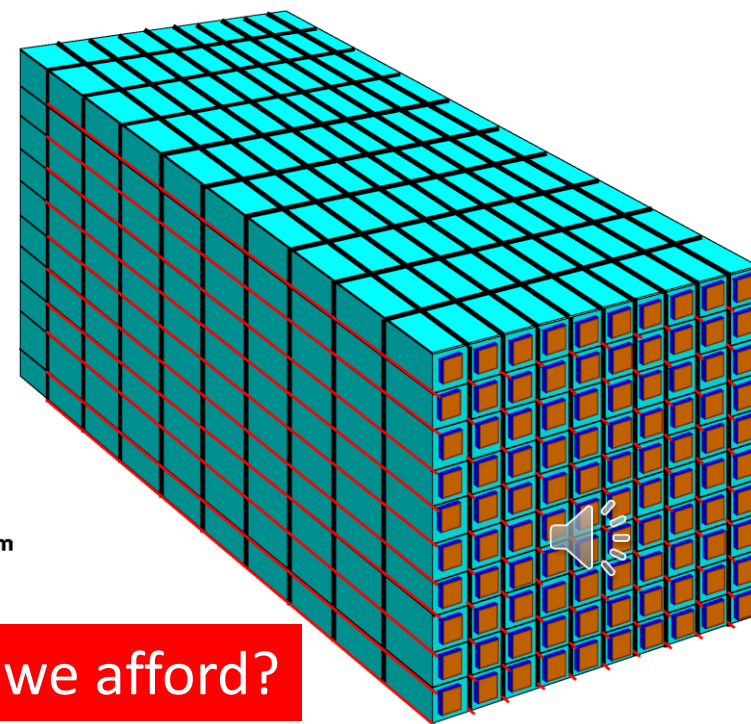

Can we afford?

ABS and DSB Glass Samples

See Liyuan Zhang, paper N12-03 in this conference

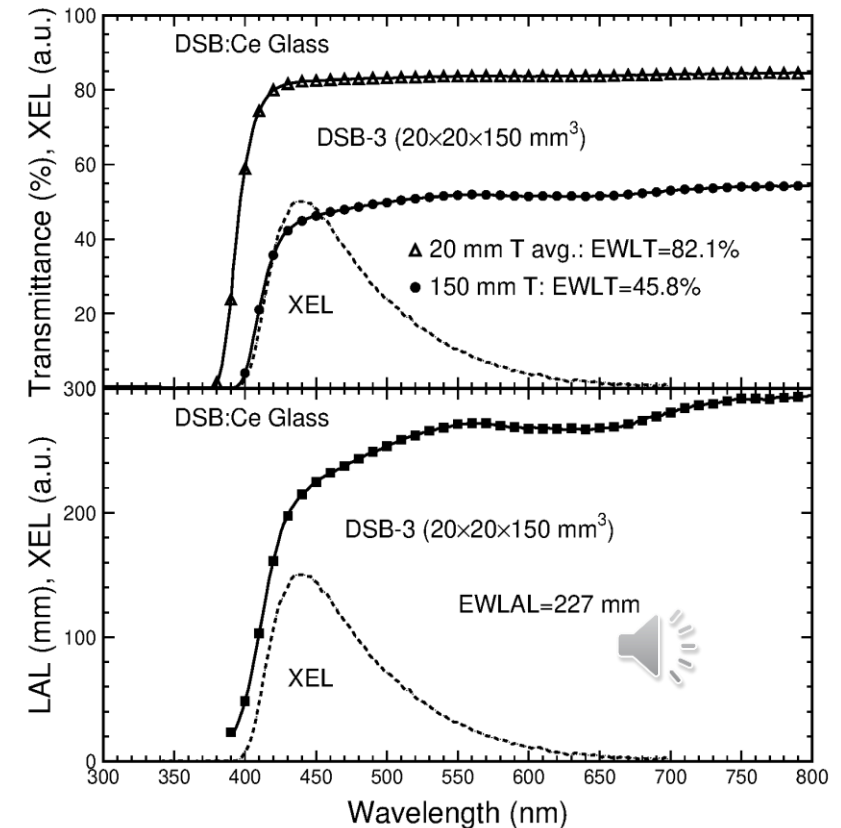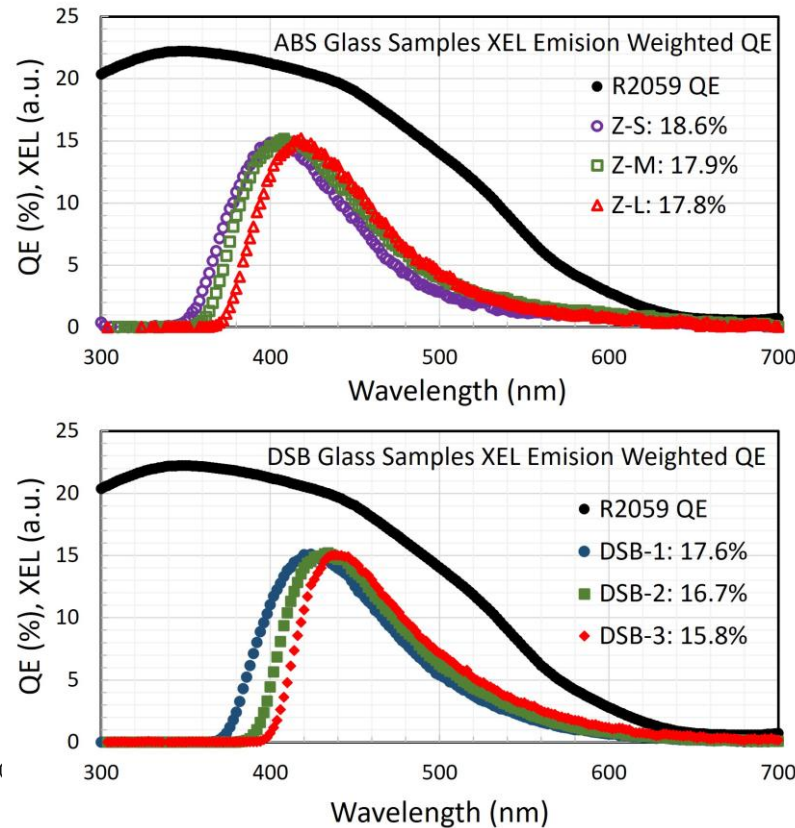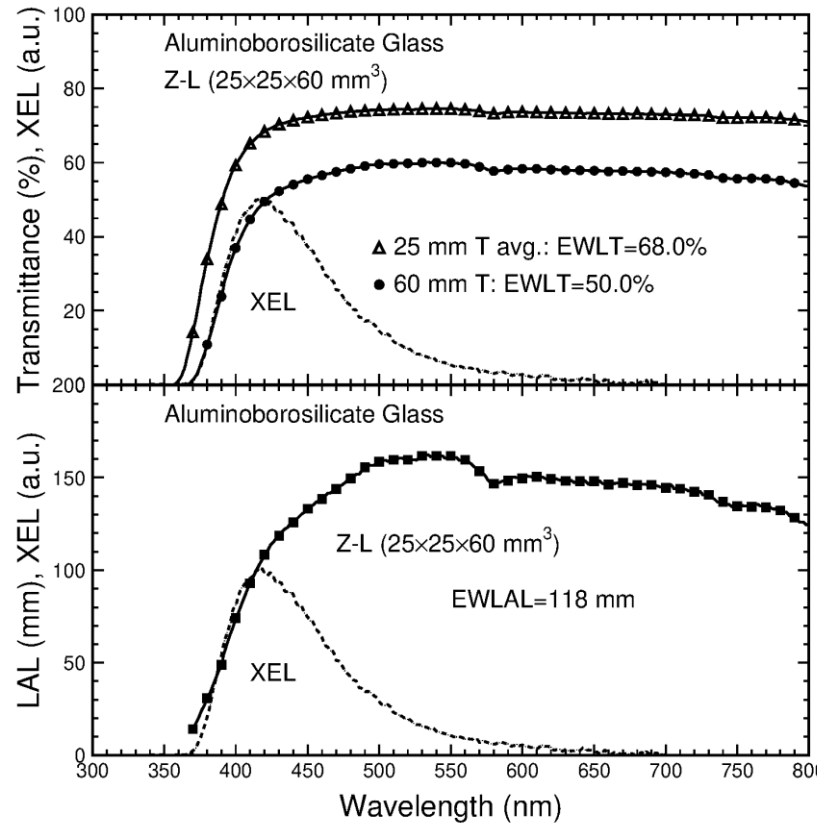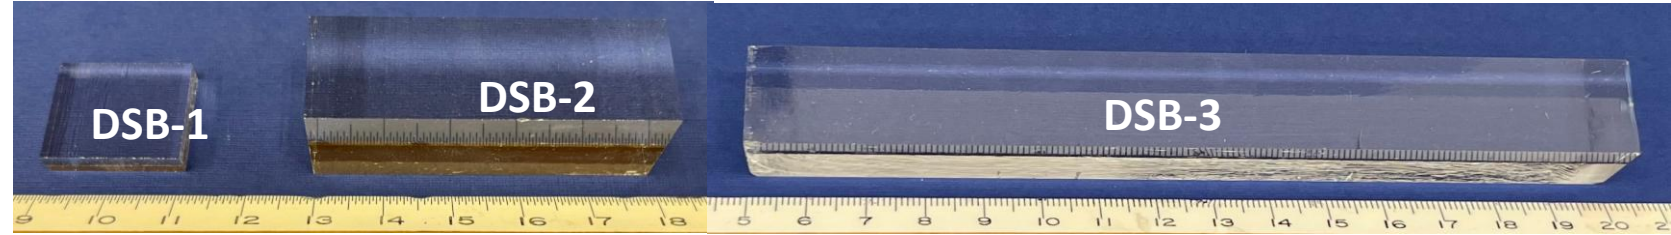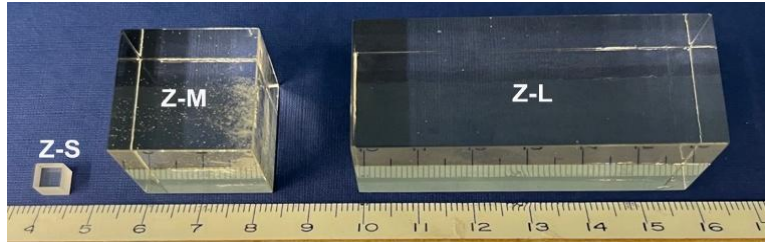



Summary

The HL-LHC and FCC-hh require fast and radiation hard inorganic scintillators. **RADiCAL** proposes an ultra-compact, fast timing and longitudinally segmented shashlik calorimeter with LuAG:Ce ceramics as wavelength shifter for LYSO:Ce crystals. R&D is on-going to suppress slow components in LuAG:Ce.

Mu2e-II considers ultrafast BaF₂:Y calorimeter. R&D is on radiation hardness of BaF₂:Y and solar-blind SiPM. Industry is developing ultrafast Lu₂O₃:Yb ceramics.

CalVision proposes a multi-readout longitudinally-segmented crystal ECAL combined with the IDEA HCAL promising excellent EM and Hadronic resolutions for the proposed Higgs factory.

Homogeneous HCAL (**HHCAL**) promises the best jet mass resolution by total absorption. Novel cost-effective heavy scintillating glass is under development.

R&D on inorganic scintillators is integrated in ECFA DRD6 WP3 and CPAD RDC9

Acknowledgements: DOE HEP Award DE-SC0011925 and DE-SC0024094



Inorganic Scintillators for HHCAL



Presented in the 1/18/2024 CalVision meeting all samples measured at Caltech

	BGO	BSO	PWO	PbF ₂	PbFCl	Sapphire:Ti	AFO:Ce Glass	DSB:Ce Glass	ABS:Ce Glass
Density (g/cm ³)	7.13	6.8	8.3	7.77	7.11	3.98	4.6	4.3	6.0
Melting point (°C)	1050	1030	1123	824	608	2040	980 ⁷	1550	?
X ₀ (cm)	1.12	1.15	0.89	0.94	1.05	7.02	2.96	2.58	1.56
R _M (cm)	2.23	2.33	2.00	2.18	2.33	2.88	2.90	3.24	2.49
λ _i (cm)	22.7	23.4	20.7	22.4	24.3	24.2	26.4	30.9	24.2
Z _{eff} value	71.5	73.8	73.6	76.7	74.7	11.1	41.4	49.5	56.6
dE/dX (MeV/cm)	8.99	8.59	10.1	9.42	8.68	6.75	6.84	6.1	8.0
Emission Peak ^a (nm)	480	470	425 420	\	420	300 750	365	420	400
Refractive Index ^b	2.15	2.68	2.20	1.82	2.15	1.76	?	?	?
LY (ph/MeV) ^c	7,500	1,500	130	\	150	7,900	450	1,360	1,150
Decay Time ^a (ns)	300	100	30 10	\	3	300 3200	40	500	 740
d(LY)/dT (%/°C) ^c	-0.9	?	-2.5	\	?	?	?	0.3	?
Cost (\$/cc)	6.0	7.0	7.5	6.0	?	0.6	2.0	2.0	<1



Fast and Ultrafast Inorganic Scintillators



arXiv: 2203.06788

	BaF ₂	BaF ₂ :Y	Lu ₂ O ₃ :Yb	YAP:Yb	YAG:Yb	ZnO:Ga	β-Ga ₂ O ₃	LYSO:Ce	LuAG:Ce	YAP:Ce	GAGG:Ce	LuYAP:Ce	YSO:Ce
Density (g/cm ³)	4.89	4.89	9.42	5.35	4.56	5.67	5.94	7.4	6.76	5.35	6.5	7.2 ^f	4.44
Melting points (°C)	1280	1280	2490	1870	1940	1975	1725	2050	2060	1870	1850	1930	2070
X ₀ (cm)	2.03	2.03	0.81	2.59	3.53	2.51	2.51	1.14	1.45	2.59	1.63	1.37	3.10
R _M (cm)	3.1	3.1	1.72	2.45	2.76	2.28	2.20	2.07	2.15	2.45	2.20	2.01	2.93
λ _i (cm)	30.7	30.7	18.1	23.1	25.2	22.2	20.9	20.9	20.6	23.1	21.5	19.5	27.8
Z _{eff}	51.0	51.0	67.3	32.8	29.3	27.7	27.8	63.7	58.7	32.8	50.6	57.1	32.8
dE/dX (MeV/cm)	6.52	6.52	11.6	7.91	7.01	8.34	8.82	9.55	9.22	7.91	8.96	9.82	6.57
λ _{peak} ^a (nm)	300 220	300 220	370	350	350	380	380	420	520	370	540	385	420
Refractive Index ^b	1.50	1.50	2.0	1.96	1.87	2.1	1.97	1.82	1.84	1.96	1.92	1.94	1.78
Normalized Light Yield ^{a,c}	42 4.8	1.7 4.8	0.95	0.19 ^d	0.36 ^d	2.6 ^d 4.0 ^d	6.5 0.5	100	35 ^e 48 ^e	9 32	190	16 15	80
Total Light yield (ph/MeV)	13,000	2,000	280	57 ^d	110 ^d	2,000 ^d	2,100	30,000	25,000 ^e	12,000	58,000	10,000	24,000
Decay time ^a (ns)	600 0.5	600 0.5	1.1 ^d	1.1 ^d	1.8 ^d	3.0 ^d 1.0 ^d	110 5.3	40	820 50	191 25	570 130	1485 36	75
LY in 1 st ns (photons/MeV)	1200	1200	170	34 ^d	46 ^d	980 ^d	43	740	240	391	400	125	318
LY in 1 st ns /Total LY (%)	9.0	64	60	60	43	49	2.0	2.5	1.2	3.3	0.7	1.4	1.3
40 keV Att. Leng. (1/e, mm)	0.106	0.106	0.127	0.314	0.439	0.407	0.394	0.185	0.251	0.314	0.319	0.214	0.334

^a top/bottom row: slow/fast component; ^b at the emission peak; ^c normalized to LYSO:Ce; ^d excited by Alpha particles; ^e 0.3 Mg at% co-doping; ^f Lu_{0.7}Y_{0.3}AlO₃:Ce.



Crystals Used in HEP Calorimeters



Crystal	NaI:TI	CsI:TI	CsI	BaF ₂	BGO	LYSO:Ce	PWO	PbF ₂
Density (g/cm ³)	3.67	4.51	4.51	4.89	7.13	7.40	8.3	7.77
Melting Point (°C)	651	621	621	1280	1050	2050	1123	824
Radiation Length (cm)	2.59	1.86	1.86	2.03	1.12	1.14	0.89	0.93
Molière Radius (cm)	4.13	3.57	3.57	3.10	2.23	2.07	2.00	2.21
Interaction Length (cm)	42.9	39.3	39.3	30.7	22.8	20.9	20.7	21.0
Refractive Index ^a	1.85	1.79	1.95	1.50	2.15	1.82	2.20	1.82
Hygroscopicity	Yes	Slight	Slight	No	No	No	No	No
Luminescence ^b (nm) (at peak)	410	550	420 310	300 220	480	402	425 420	-
Decay Time ^b (ns)	245	1220	30 6	650 0.9	300	40	30 10	-
Light Yield ^{b,c} (photons/MeV)	38,000	63,000	1,400 420	13,680 1,560	8,000	32,000	114 40	-
d(LY)/dT ^b (%/ °C)	-0.2	0.4	-1.4	-1.9 0.1	-0.9	-0.2	-2.5	-
Experiment	Crystal Ball	BaBar BELLE BES III	KTev Mu2e	TAPS Mu2e-II	L3 BELLE	COMET CMS BTL PIONEER	CMS ALICE PANDA ePIC	A4 G-2

a. at emission peak; b. up/low row: slow/fast component; c. with QE of readout device taken out.