



Gamma-ray Induced Radiation Damage up to 340 Mrad in Various Scintillation Crystals

Fan Yang, Liyuan Zhang, Ren-Yuan Zhu

California Institute of Technology


Nov 4, 2015



Introduction



- **Gamma-ray induced radiation damage in large size crystal scintillators was investigated for BaF_2 , BGO, CeF_3 , pure CsI, LSO/LYSO/LFS and PWO.**
- **Irradiations were carried out at the total ionization dose (TID) facility of Jet Propulsion Laboratory (JPL) up to 340 Mrad with a dose rate up to 1 Mrad/h.**
- **Long crystal samples were hosted in an aluminum box of ten inch square. The box was inserted in a square throat of 10" x 10" x 13.5" facing a group of Co-60 γ -ray sources. The entire body of crystals was uniformly irradiated.**

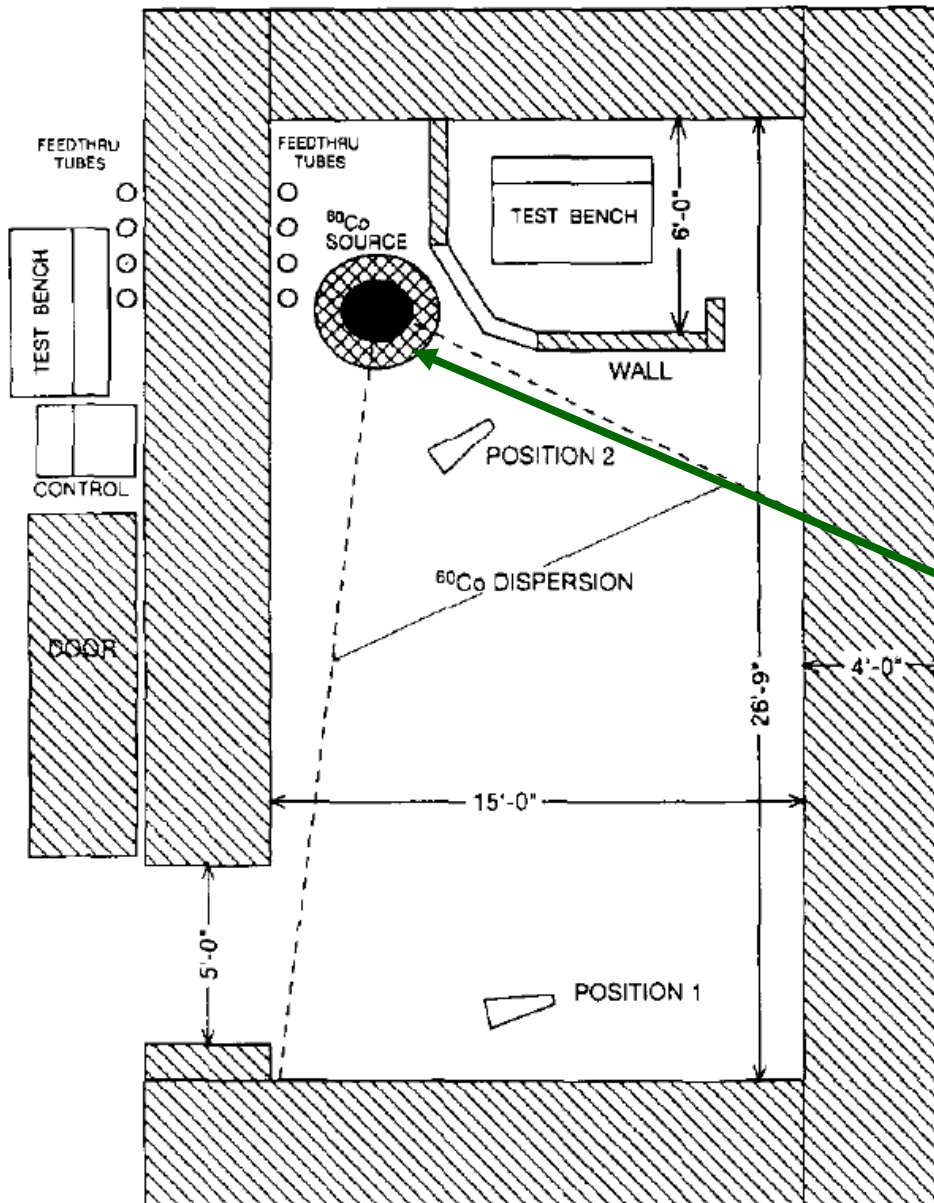

A group of high intensity ^{60}Co sources provides a variable dose rate up to 1 Mrad/h in an opening throat of 10" x 10" x 13.5".

Irradiation was carried out in step: 10 Mrad first, followed by several 100 Mrad steps over weekends.

The time between the end of each irradiation and the measurements at Caltech is less than 30 minutes.




ID	Dimension (mm)
CeF₃	33×32×191
BaF₂	20×20×250
PWO	28.5²×30²×220
BGO	25×25×200
LYSO	25×25×200
Pure CsI	50×50×200

Experiments


Longitudinal Transmittance (LT) and Light Output (LO) were measured at room temperature before and after each irradiation step.

Gamma-Ray Induced Damage in 20 cm Long LYSO/LSO Crystals

No damage in scintillation mechanism

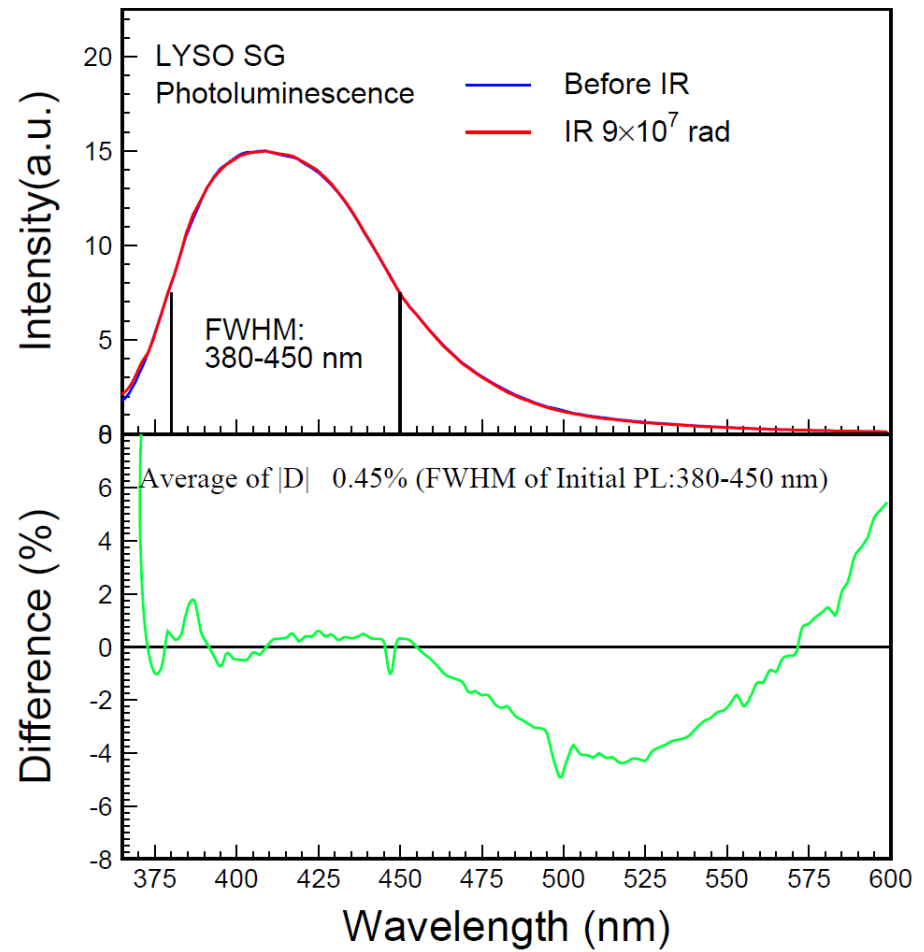


No recovery: dose rate independent

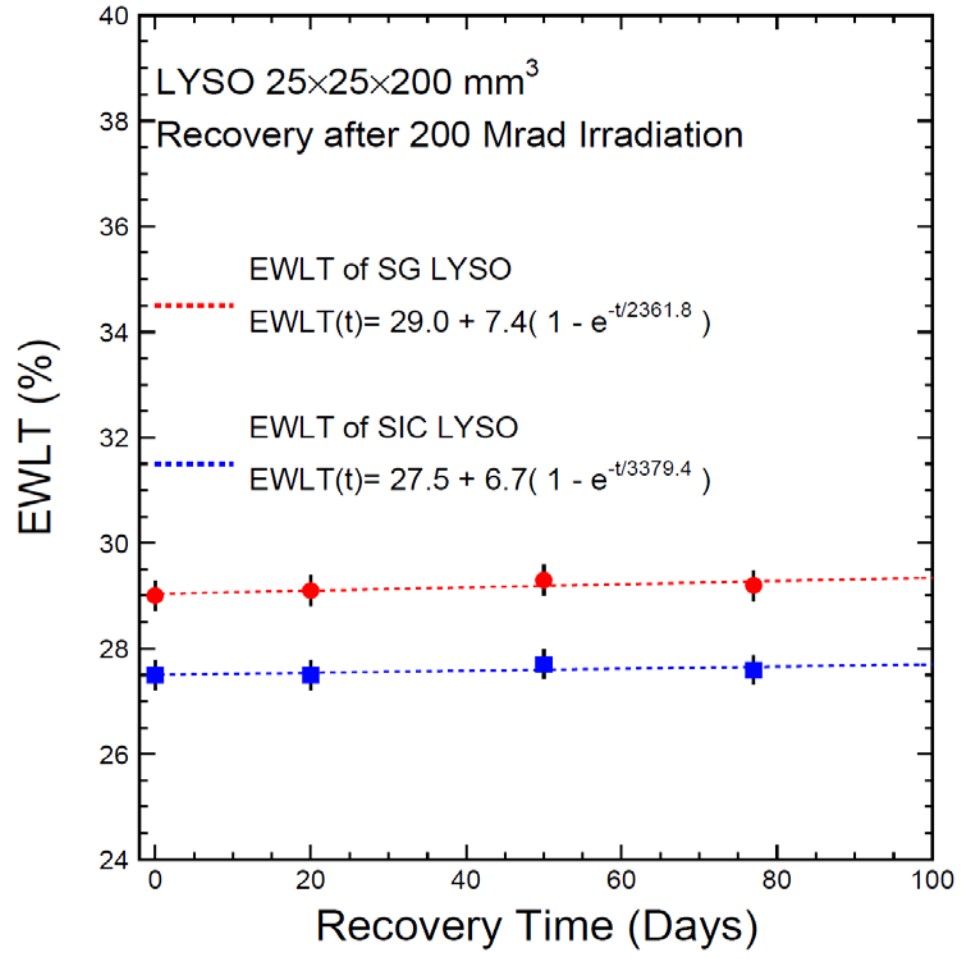

Radiation damage in BaF₂ and pure CsI is also dose rate independent

LYSO/LSO/LFS: Radiation Damage in Longitudinal Transmittance (LT)

The best sample: 77% EWLT after 100 Mrad

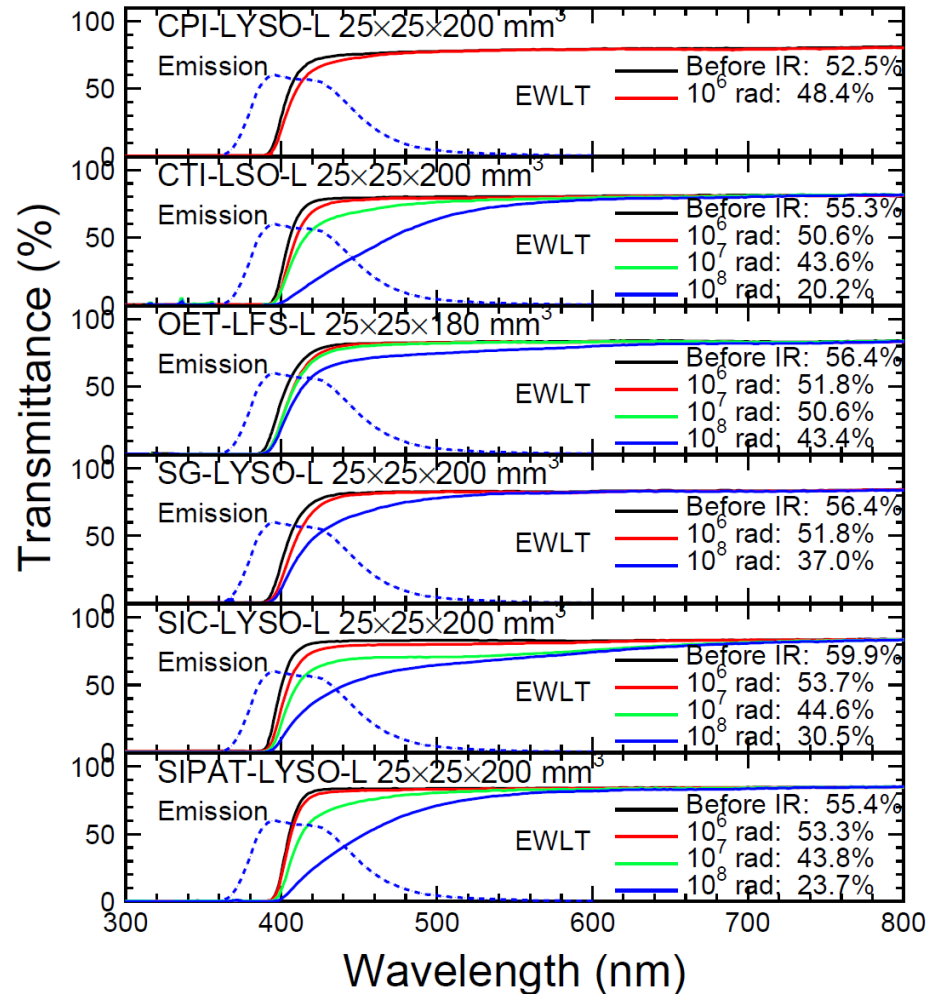

EWLT or emission weighted longitudinal transmittance is defined as:

$$EWLT = \frac{\int LT(\lambda)Em(\lambda)d\lambda}{\int Em(\lambda)d\lambda}$$

RIAC or radiation induced absorption coefficient is defined as:


$$RIAC = \frac{1}{l} \ln \frac{T_0(\lambda)}{T(\lambda)}$$

EWRIAC or emission weighted radiation induced absorption coefficient is defined as:

$$EWRIAC = \frac{\int RIAC(\lambda)Em(\lambda)d\lambda}{\int Em(\lambda)d\lambda}$$

LYSO/LSO/LFS: Normalized EWLT and LO vs. Dose and LO vs. EWLT



The best sample: 58% light output after 340 Mrad

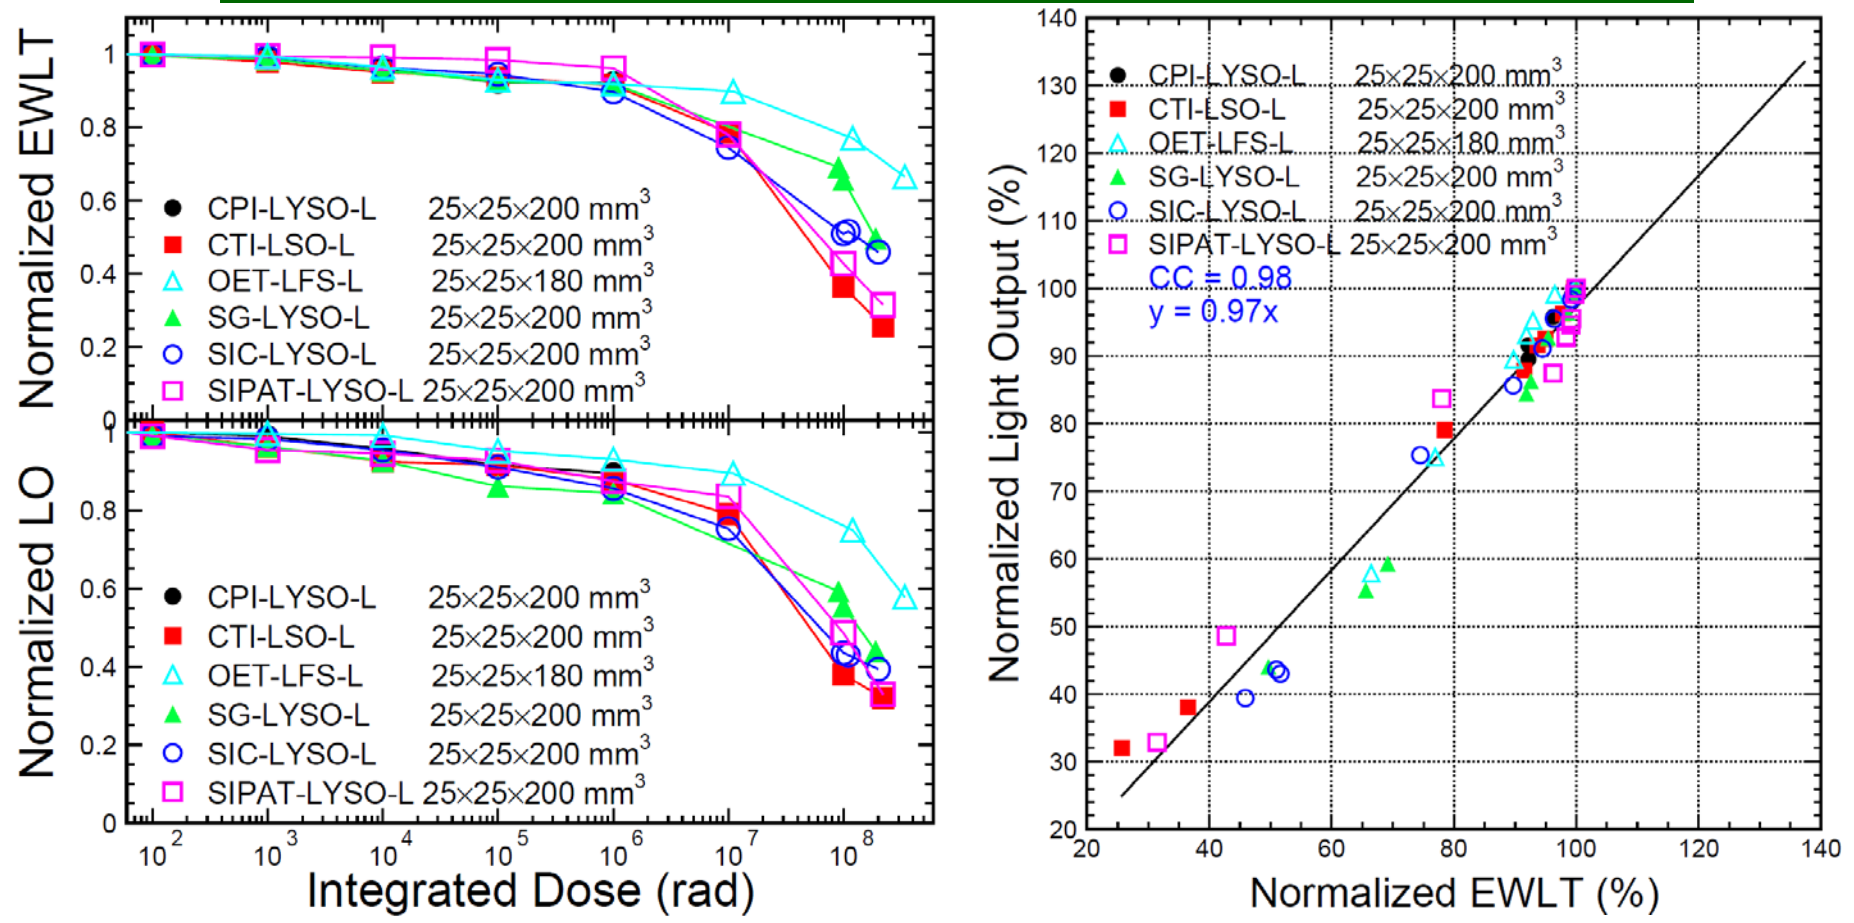

Good correlation between LO and EWLT: LO loss is caused by absorption


LYSO/LSO/LFS: EWRIAC vs. Dose and Normalized LO vs. EWRIAC

EWRIAC in the best sample is 0.62, 1.5 and 2.4 m⁻¹ after 10, 120 and 340 Mrad

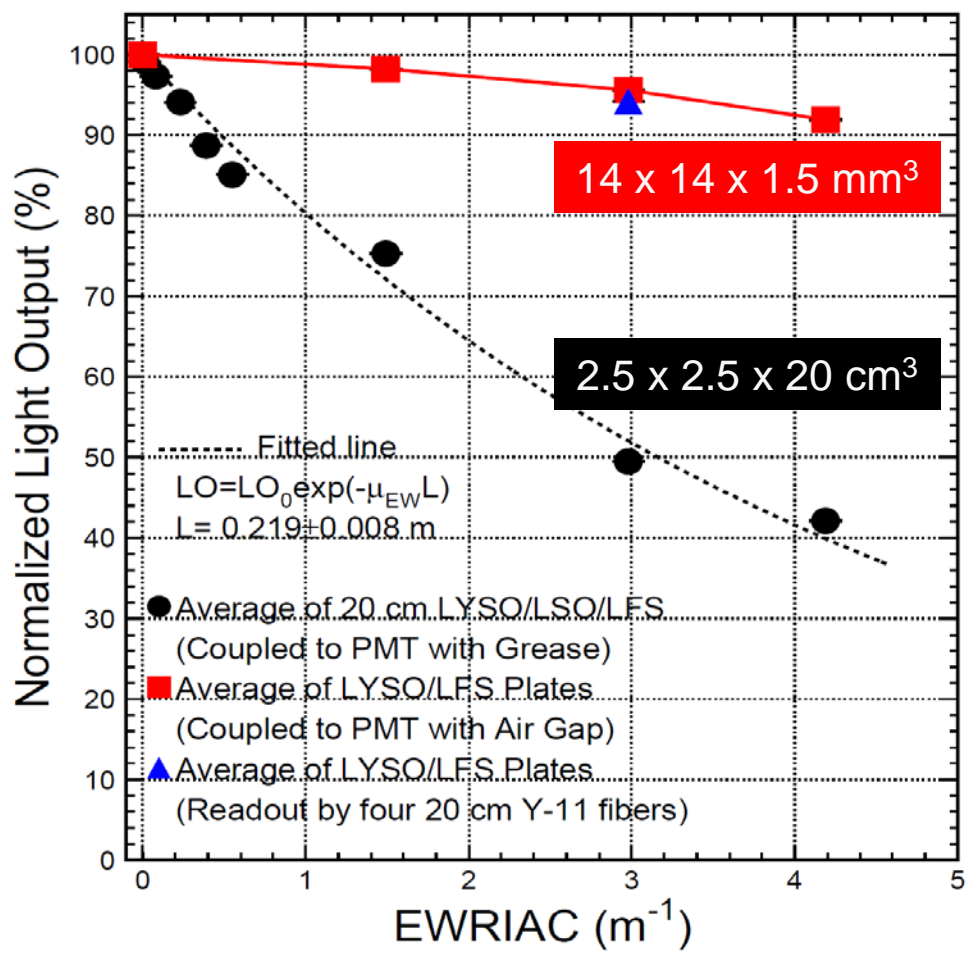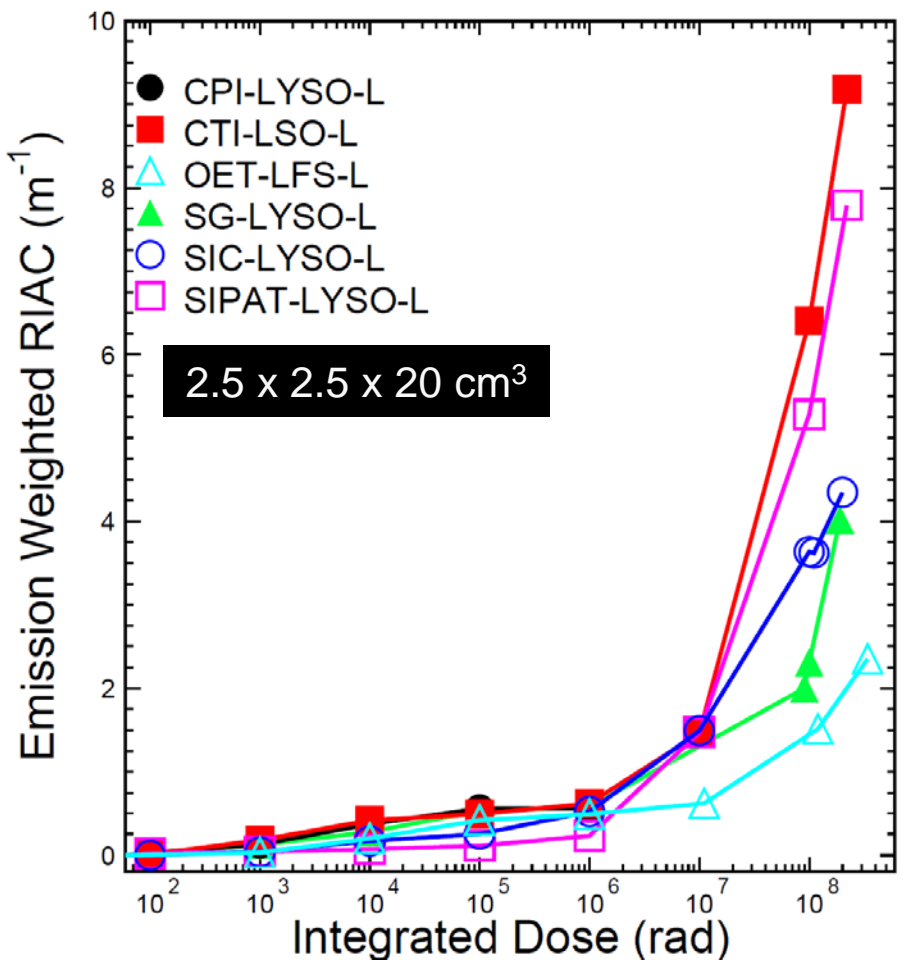

With EWRIAC of 3 m⁻¹, LO losses in 14x14x1.5 mm plates and 20 cm long crystals are 4%/6% for direct/WLS readout and 50%



BaF₂: Longitudinal Transmittance

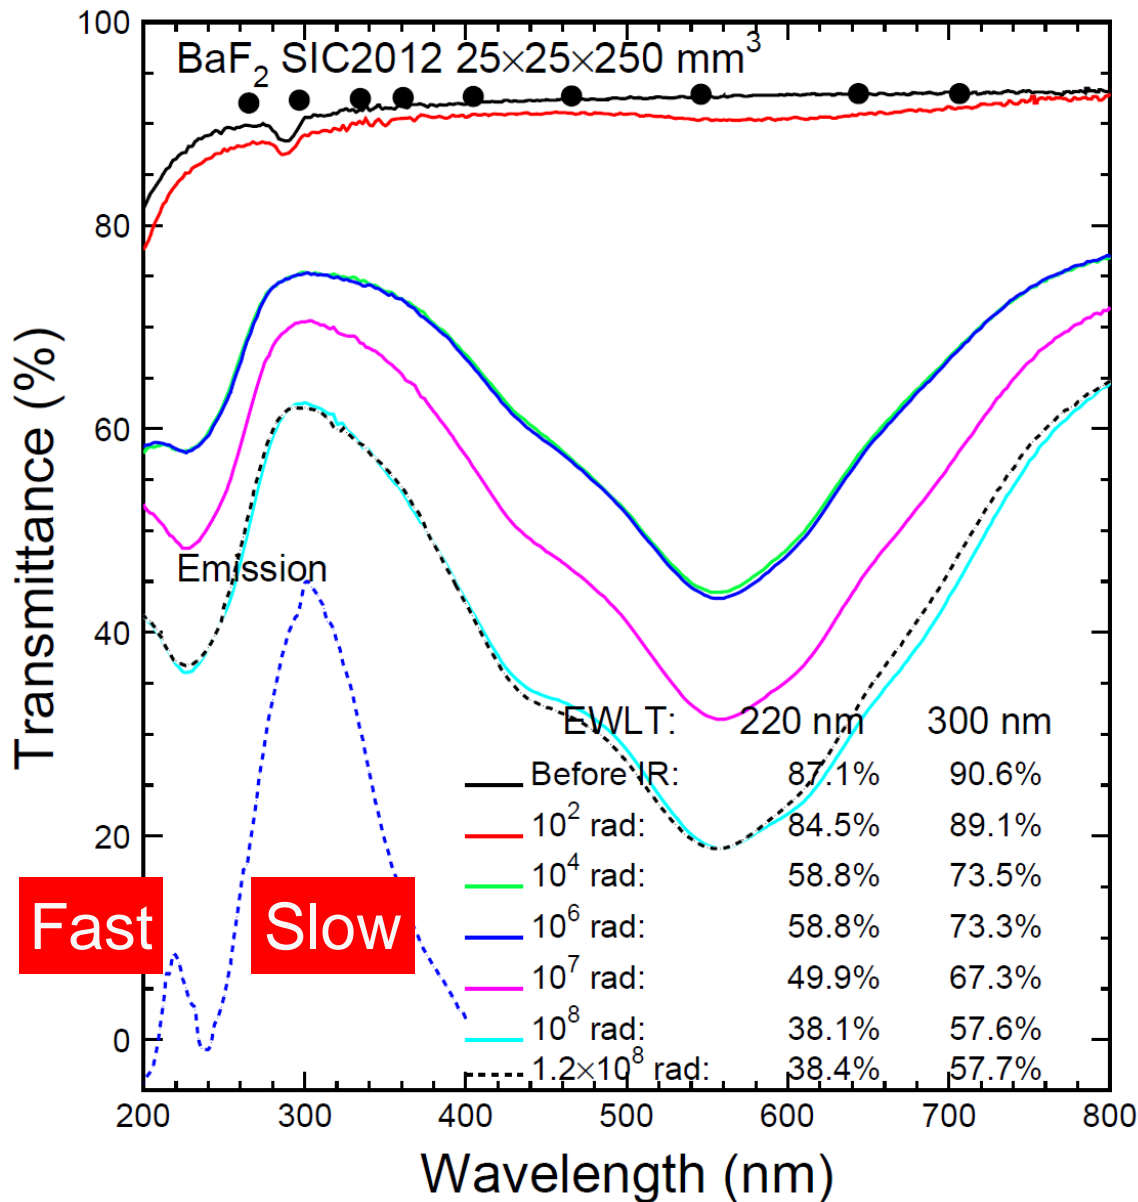

Transmittance damage: 44% and 64% EWLT for the fast and slow scintillation component respectively after 120 Mrad

BaF₂: Normalized EWLT and LO



Consistent damage in crystals from three vendors

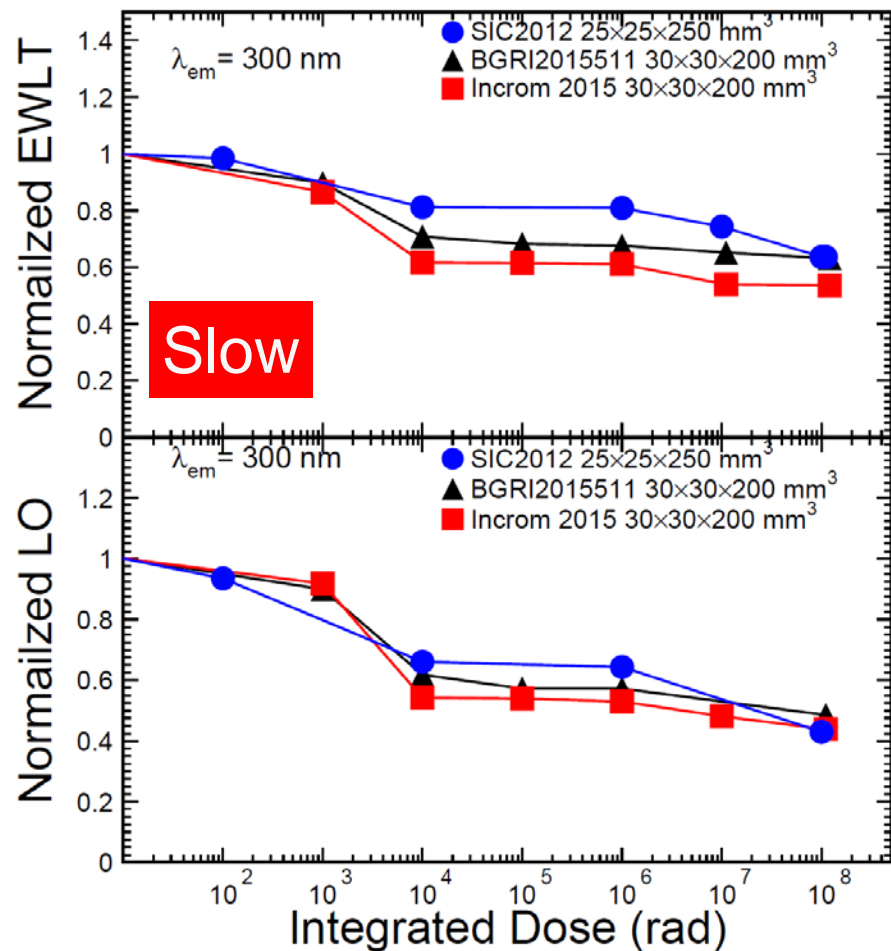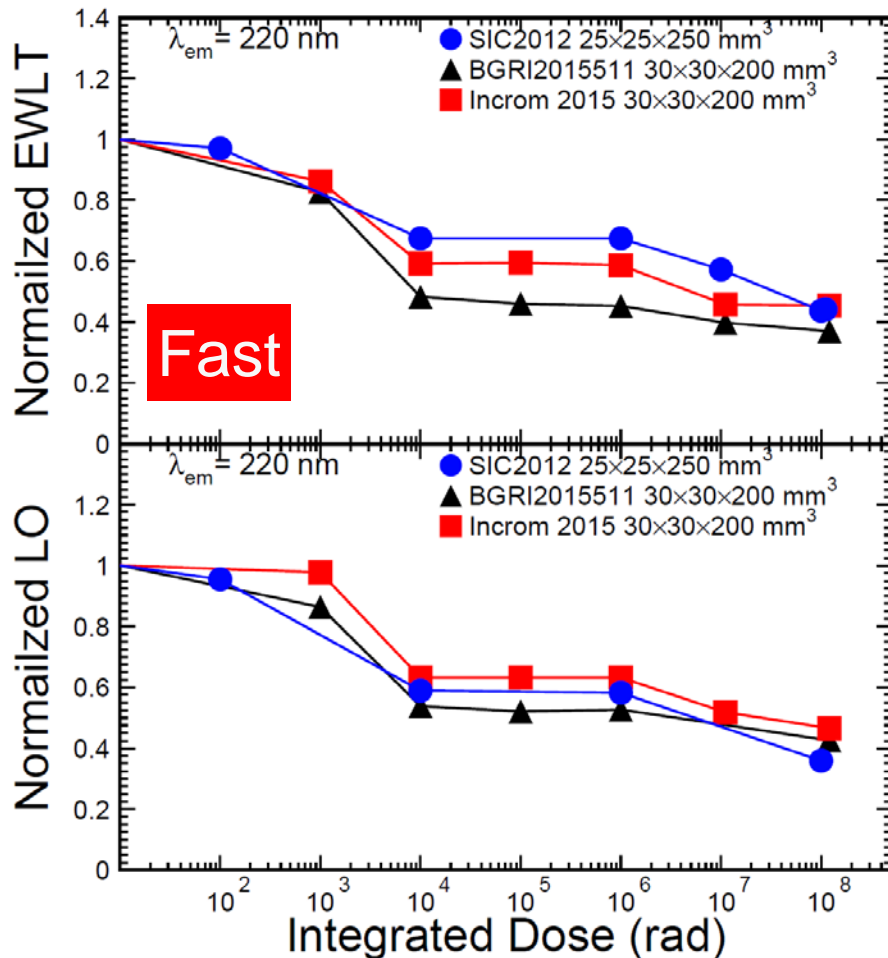

40%/45% LO for the fast/slow component after 120 Mrad

Pure CsI: Normalized EWL/LO and RIAC @ Emission Peak



Consistent damage in crystals from two vendors

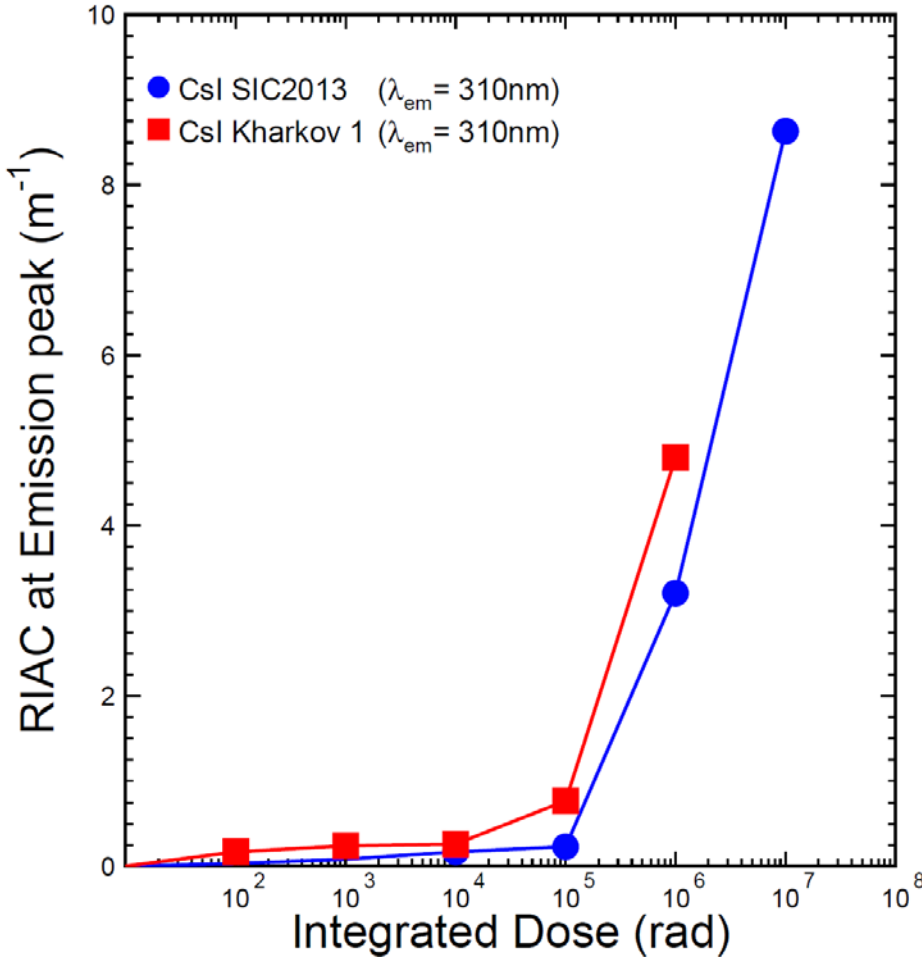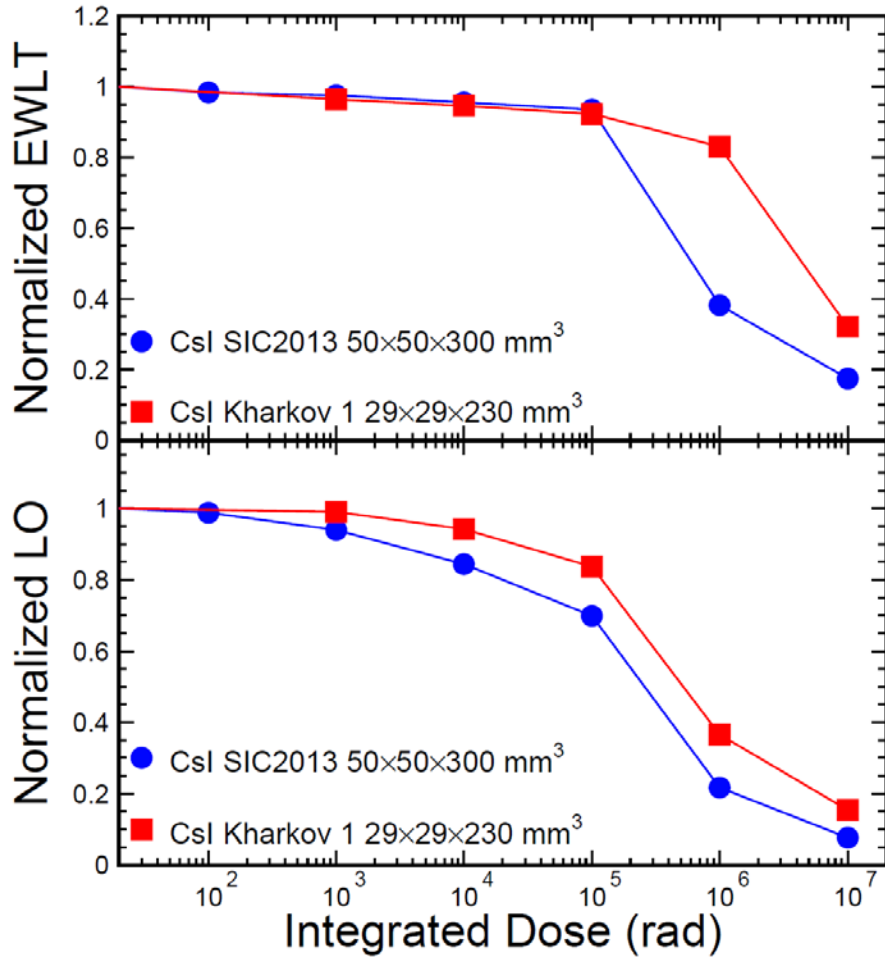

No significant damage in LO up to 100 krad

CeF₃: Damage & Recovery



Damage in CeF₃ recovers at room temperature, so is dose rate dependent

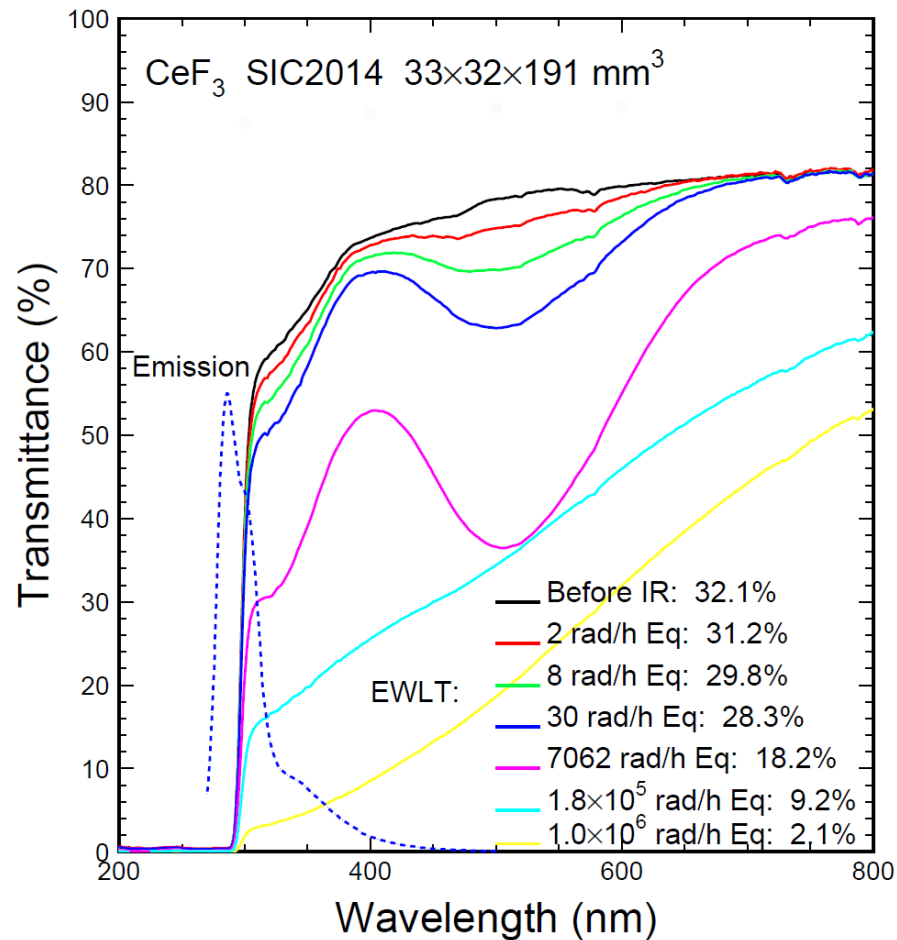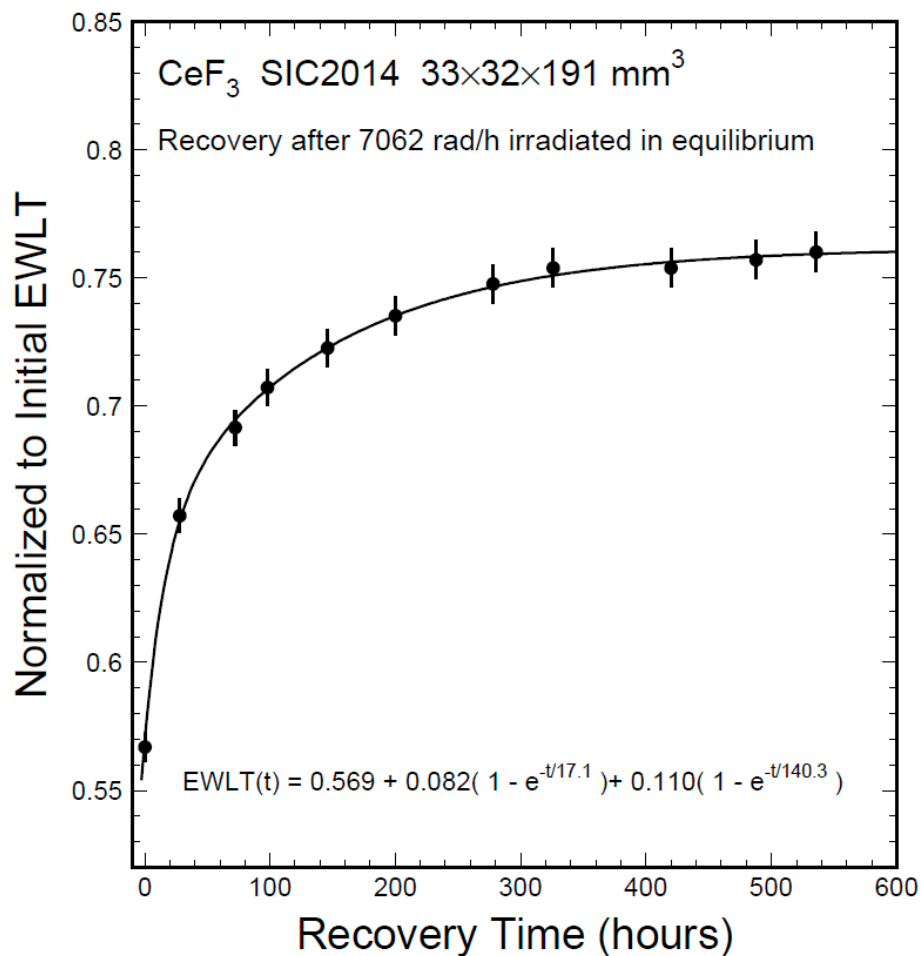

Radiation damage in BGO and PWO is also dose rate dependent



CeF₃: Normalized EWLT and LO

Irradiation carried out under a dose rate until reaching equilibrium
 Dose rate dependent damage observed in both EWLT and LO

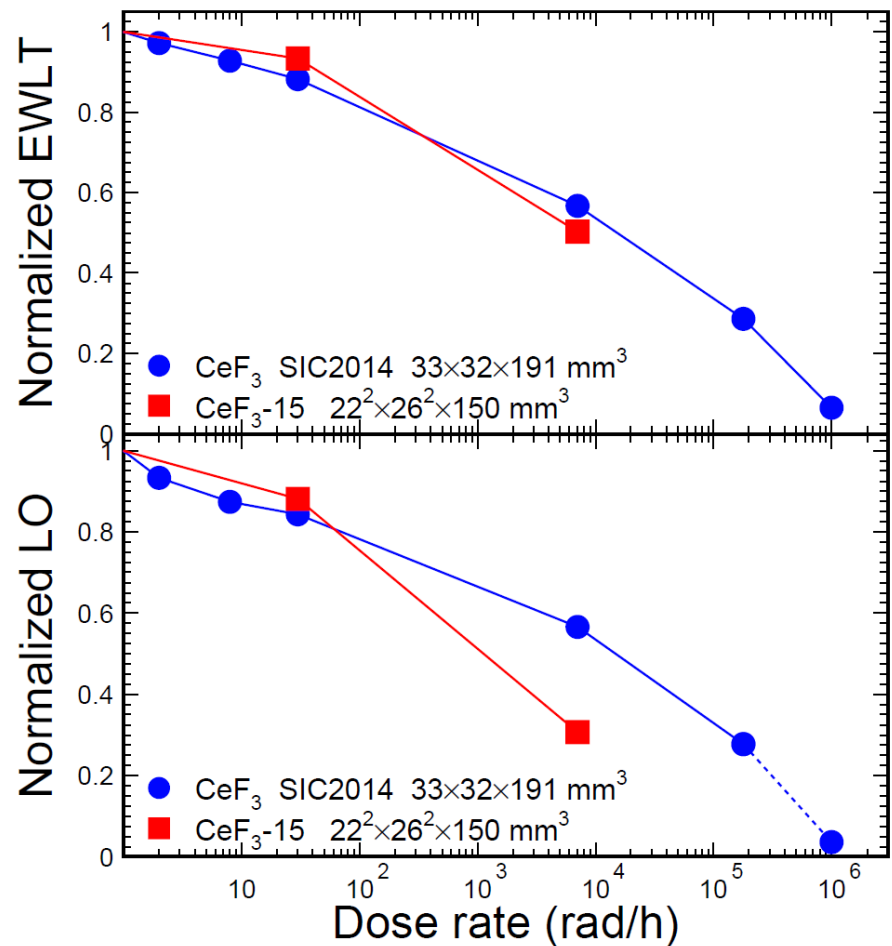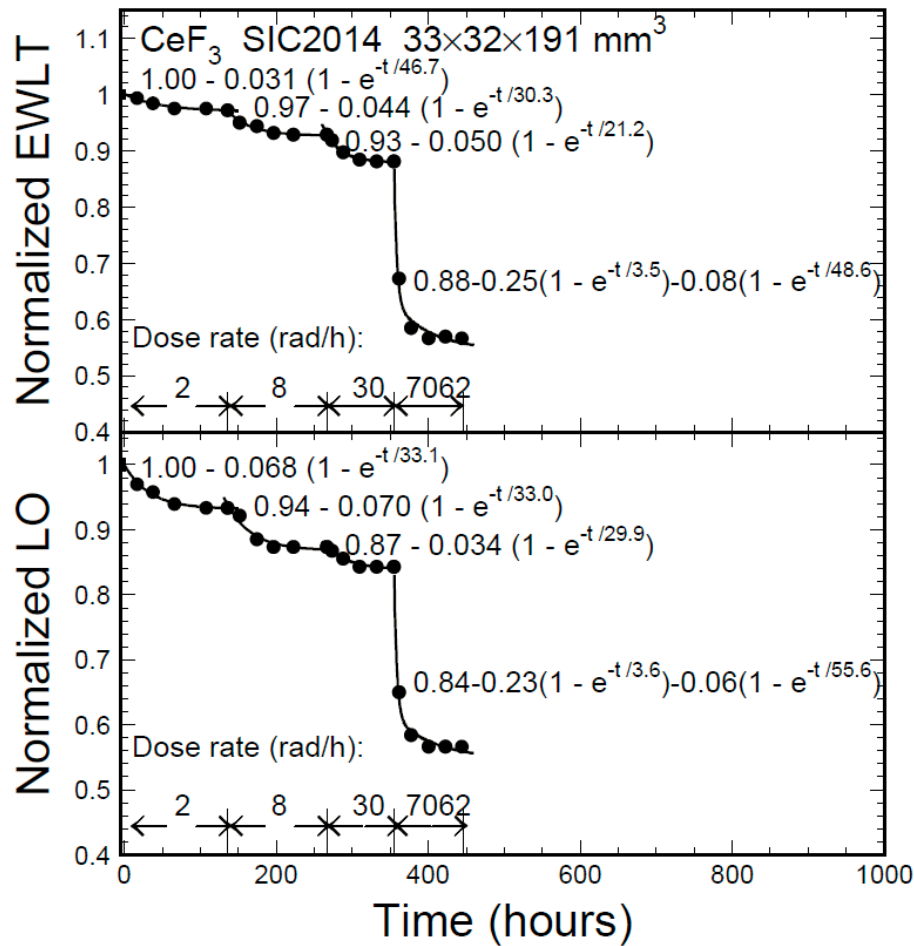

LO is too low to be measured under 1 Mrad/h in equilibrium



Dose rate dependent damage in crystals from two vendors

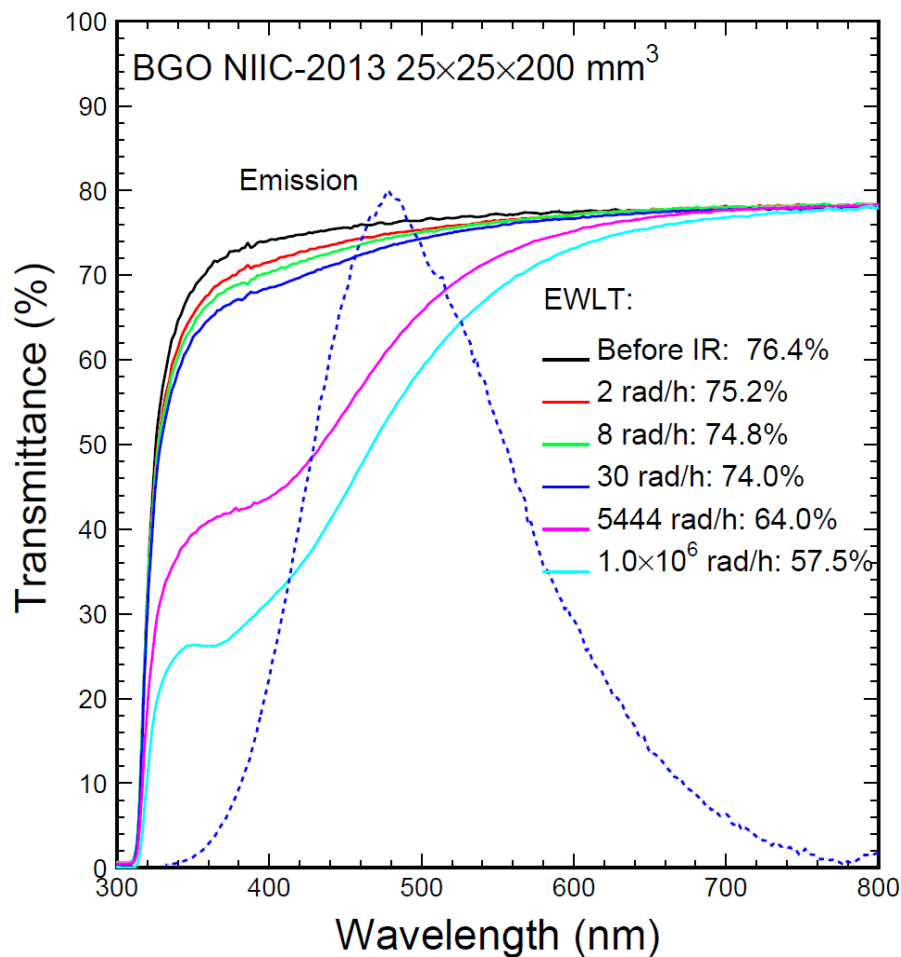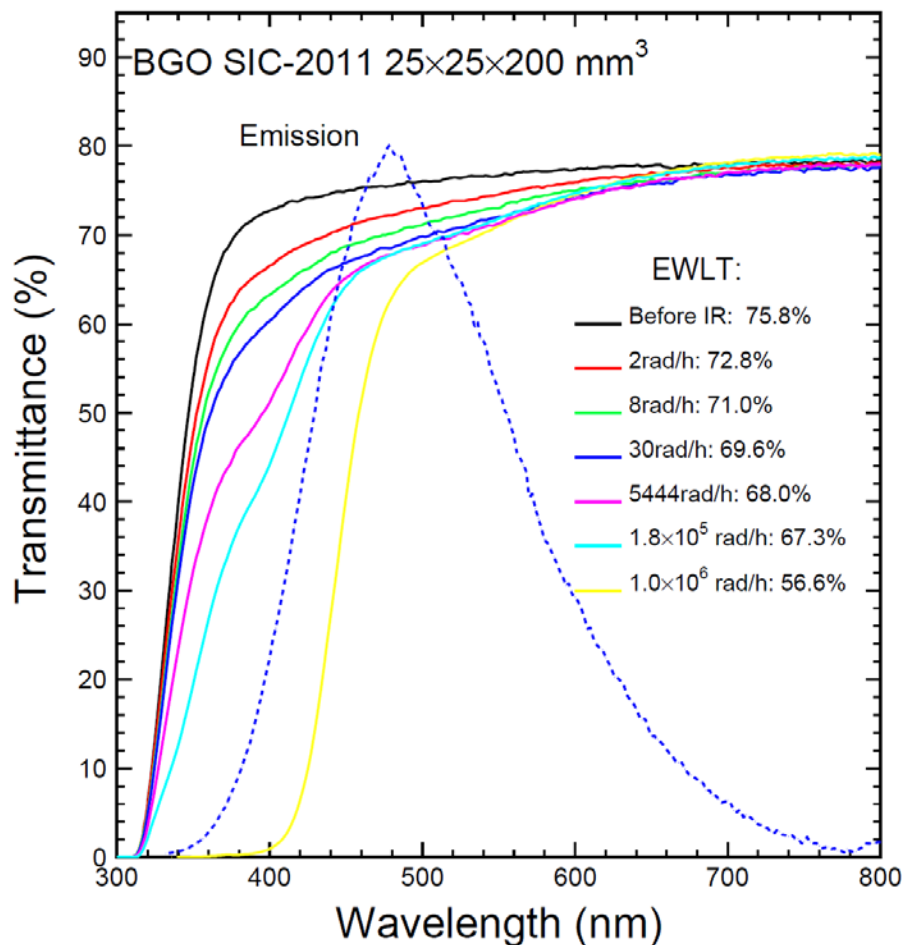

75% EWLT under 1 Mrad/h

BGO: Normalized EWLT and LO



Dose rate dependent damage observed in both EWLT and LO

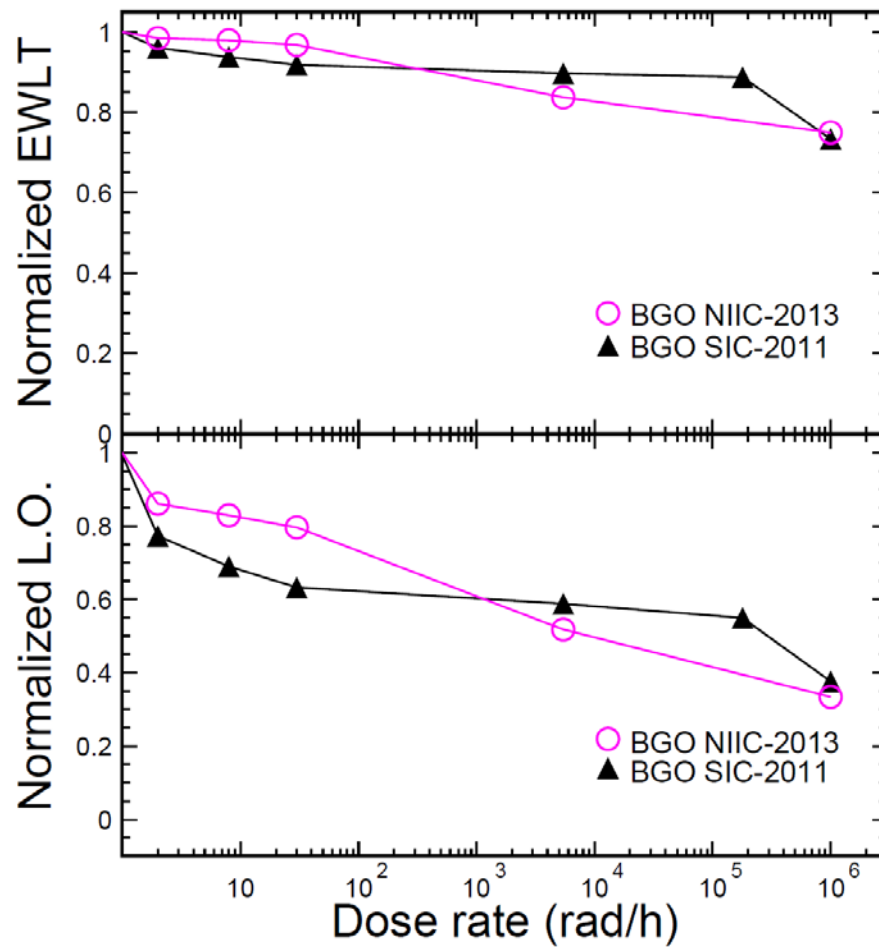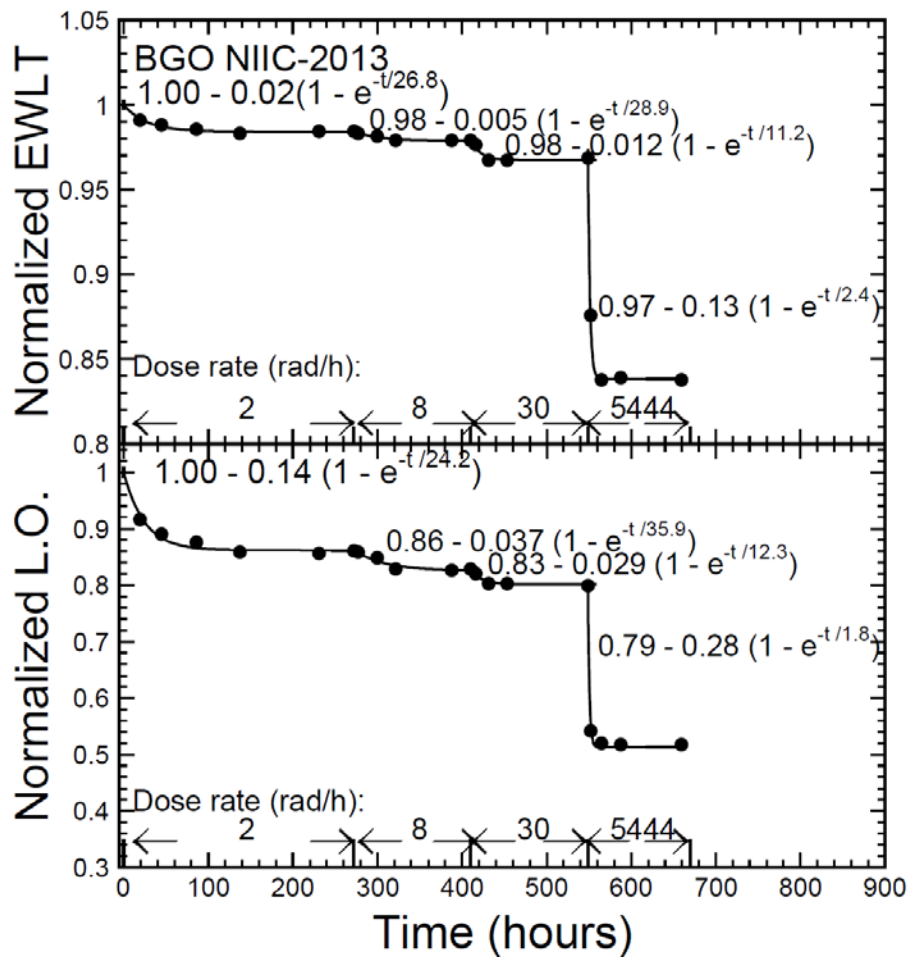

35% light output under 1 Mrad/h for both vendors

PWO : Damage & Recovery



Dose rate dependent damage observed in both EWLT and LO

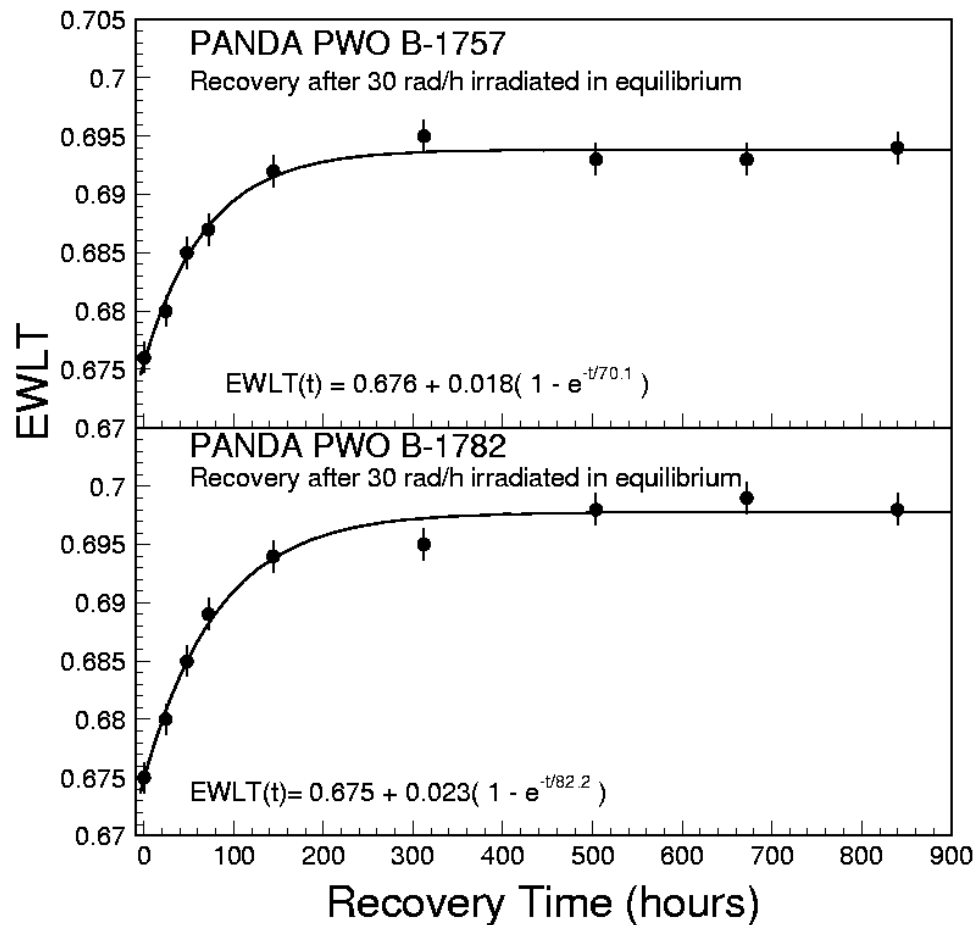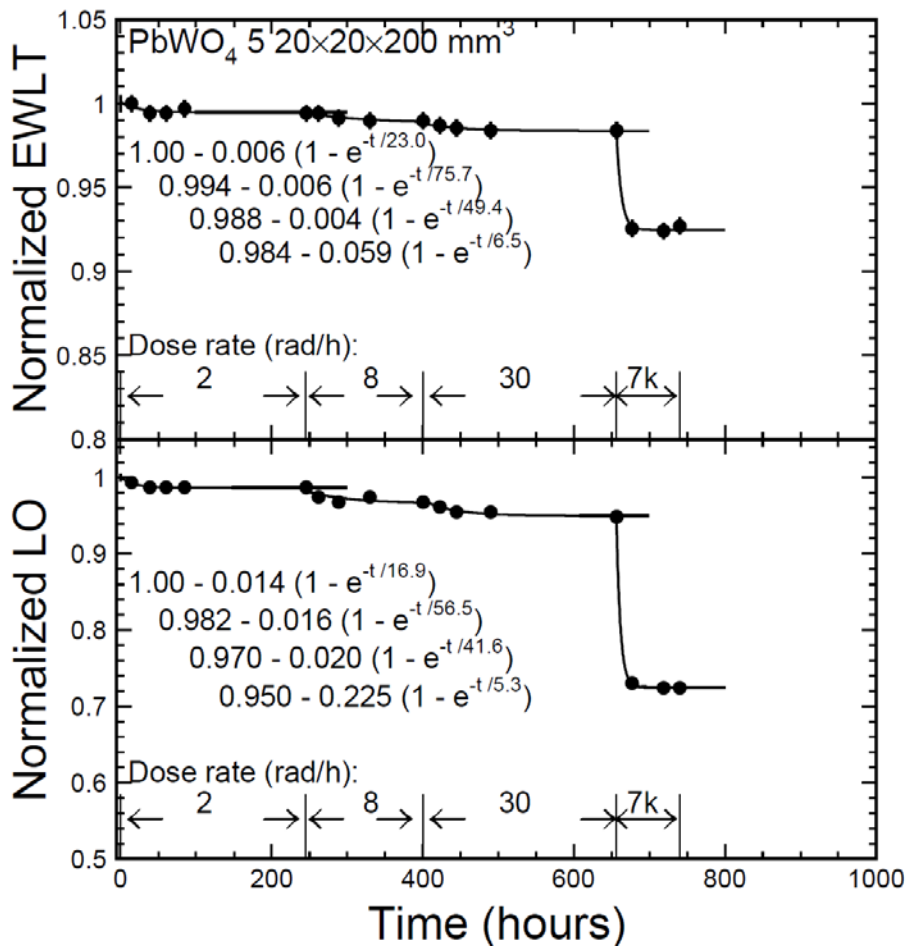

Recovery is not complete because of deep color centers

PWO: Normalized EWLT/LO and EWRIAC vs. Dose Rate



Damage in PWO crystals is diverse, so quality control is important

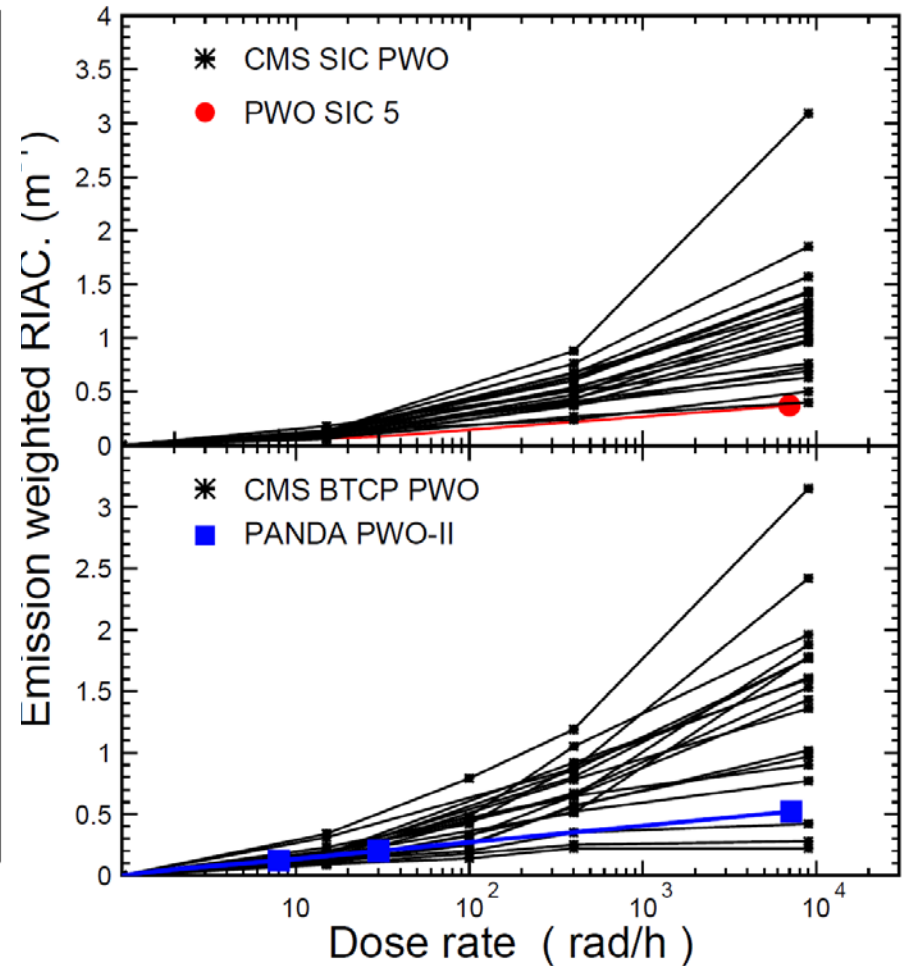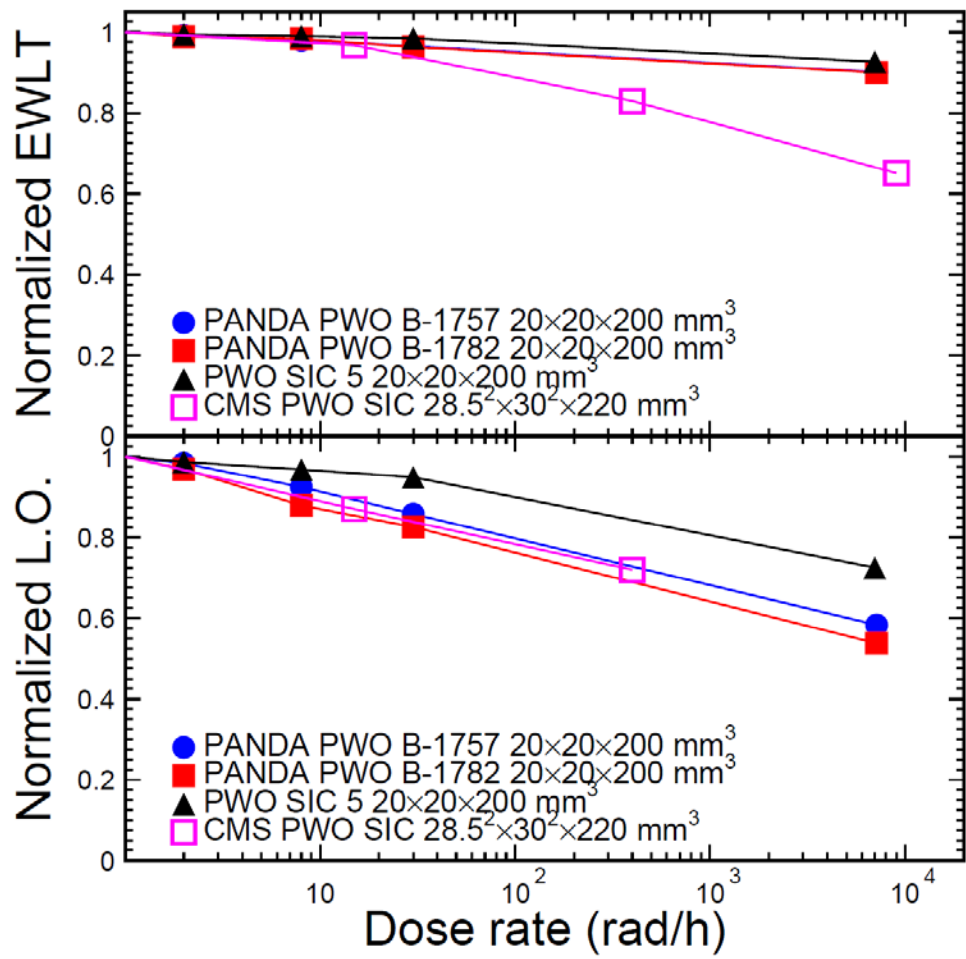

PWO-II for Panda and PWO 5 for JLAB are better than CMS PWO



All Crystals: RIAC @ Emission Peak

Pure CsI is good below 100 krad; LYSO and BaF₂ are good beyond 1 Mrad
 BGO shows small radiation induced absorption up to 1 Mrad/h

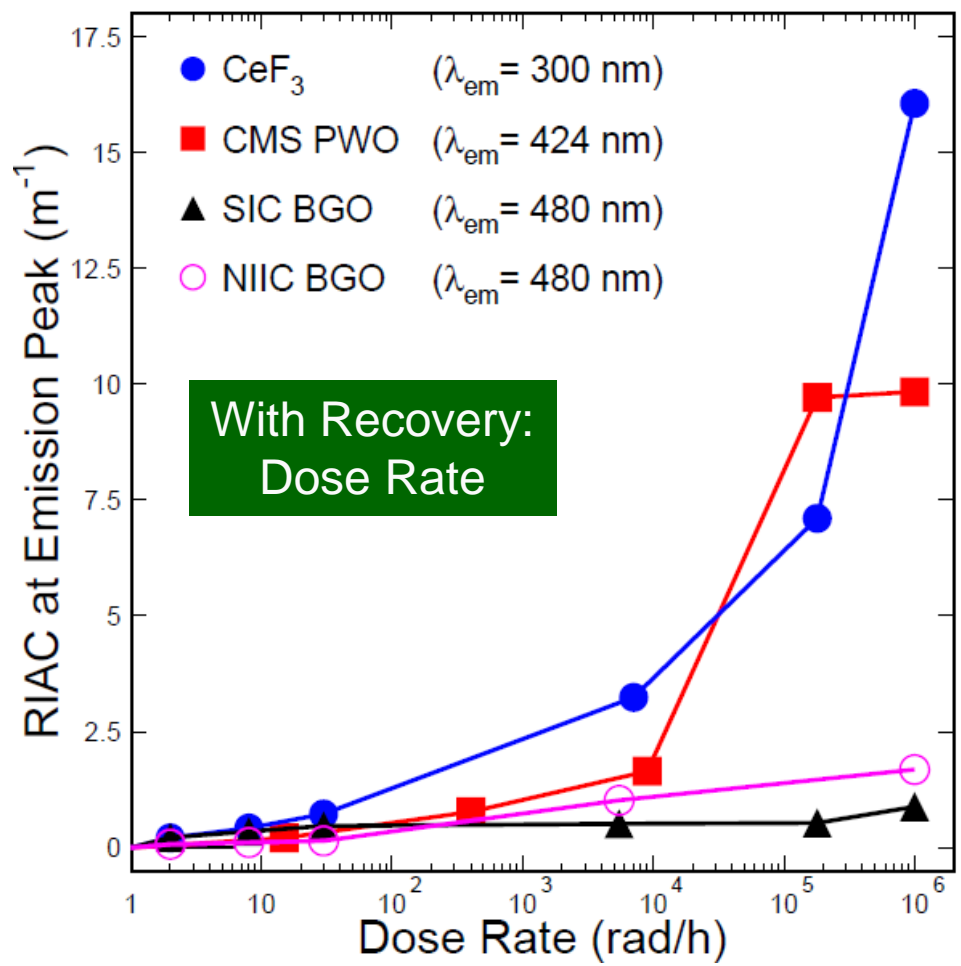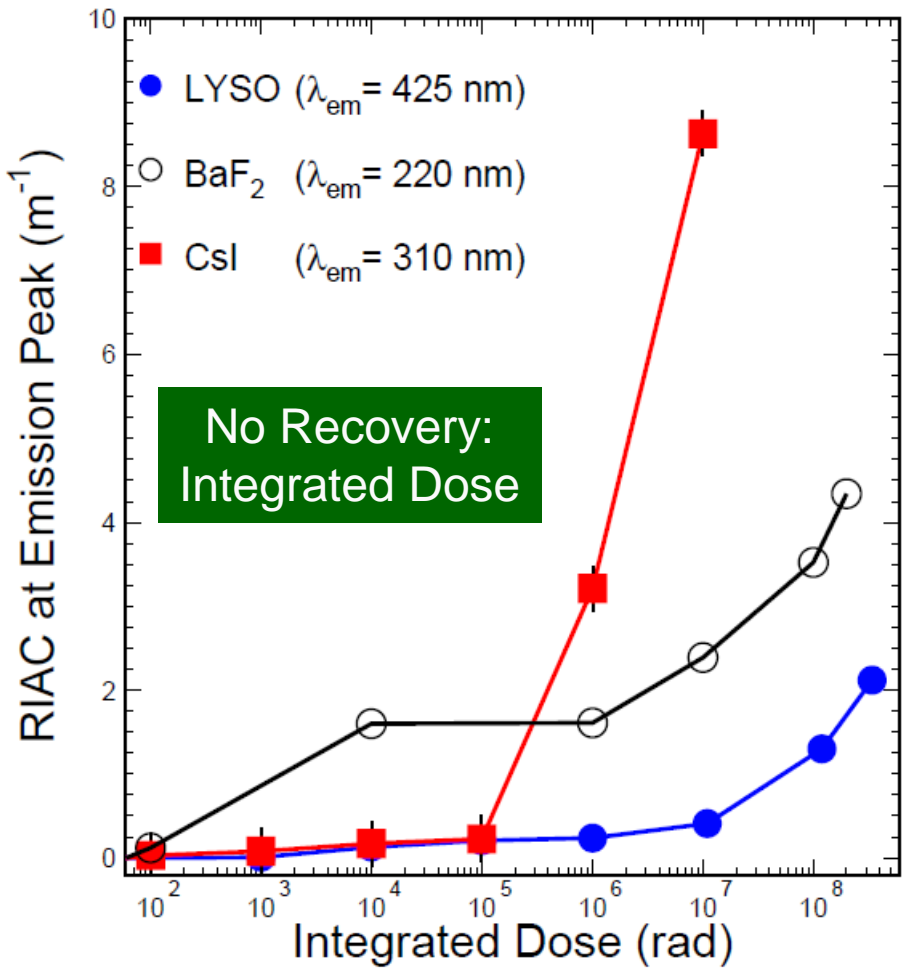

All Crystals: RIAC and LO

Ignoring dose rate dependence, the values of RIAC at the emission peak and normalized LO shown as a function of the integrated dose

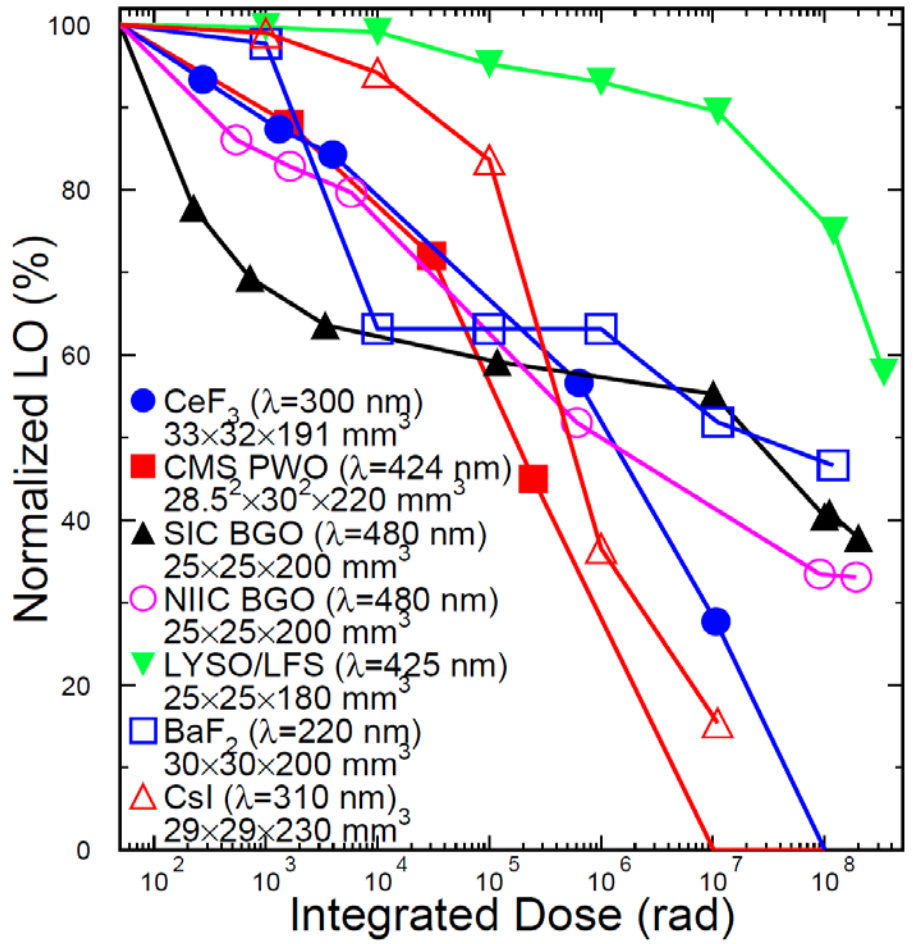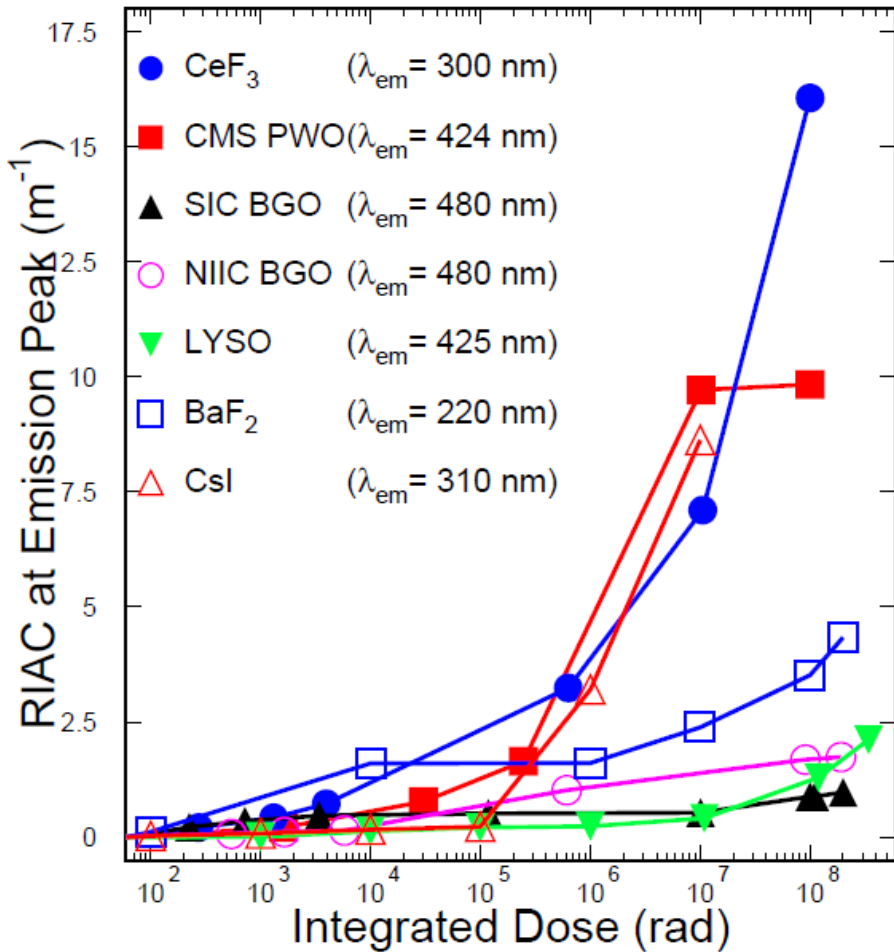

LYSO crystals show the best radiation hardness up to 340 Mrad



Summary



- Gamma-ray induced damage in various scintillating crystals of about 20 cm long was investigated up to 340 Mrad.
- Damage in LYSO/LSO/LFS crystals from six vendors was measured. The best sample shows 58% light output after 340 Mrad.
- Damage in BaF₂ crystals from three vendors is consistent. 40%/45% LO is observed after 120 Mrad for the fast/slow component.
- Damage in pure CsI crystals from two vendors is consistent. Good radiation hardness is observed below 100 krad.
- Damage in CeF₃, BGO and PWO recovers at room temperature, so is dose rate dependent. The quality of the large size CeF₃ crystals grown 20 years ago is worse than PWO and BGO.
- Damage in BGO crystals from two vendors was measured. 35% light output is observed in both crystals under a dose rate of 1 Mrad/h.
- Damage in PWO crystals is diverse. Two PWO-II crystals for Panda and one PWO 5 crystal for JLAB are better than CMS PWO.
- LYSO/LSO/LFS crystals show the best radiation hardness among all scintillation crystals up to 340 Mrad.