


# Precision Crystal Calorimeters in High Energy Physics: Past, Present and Future

**Ren-Yuan Zhu**

California Institute of Technology





# Physics with Crystal Calorimeters




Charmonium system observed by CB through Inclusive photons

$H \rightarrow \gamma\gamma$  at LHC

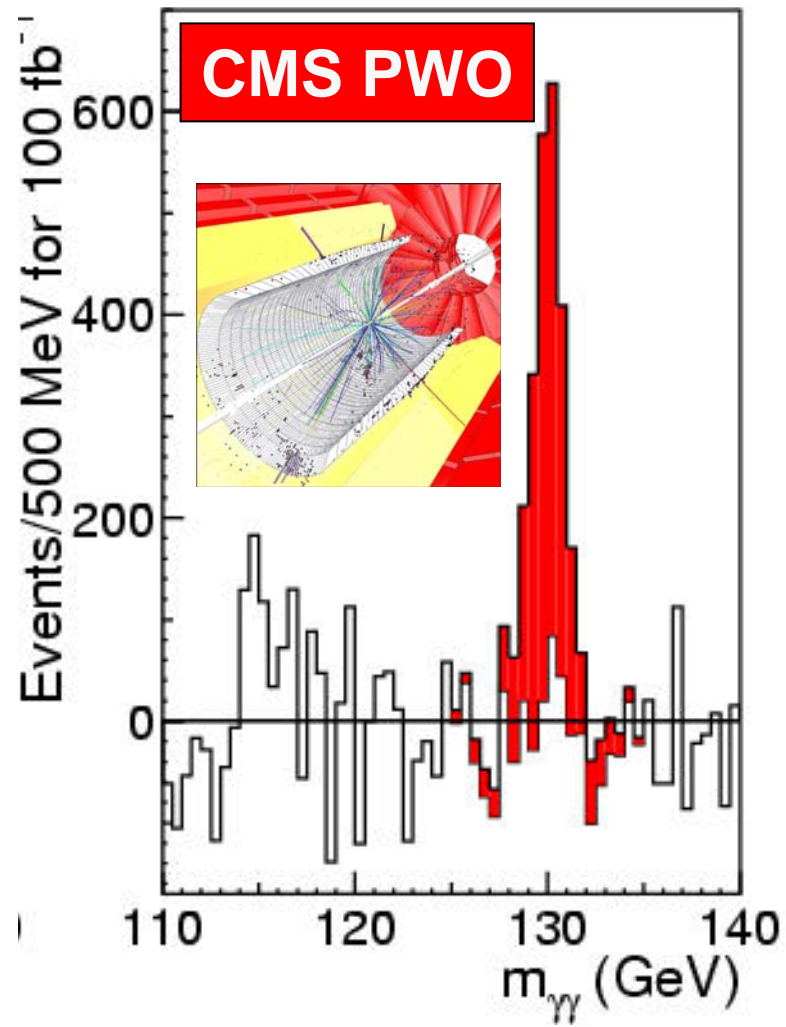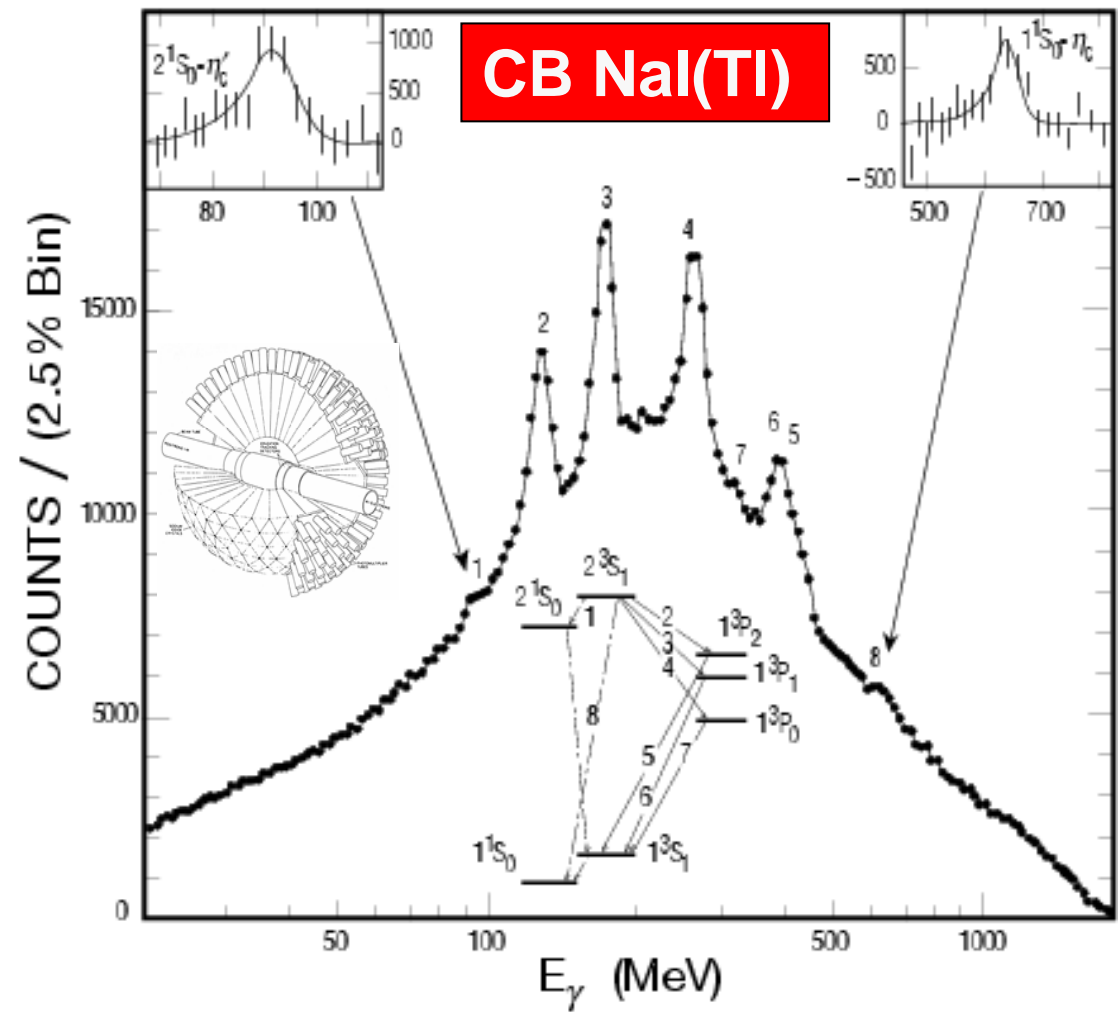



# Mass Produced Crystals





Crystal	Nal(Tl)	CsI(Tl)	CsI	BaF <sub>2</sub>	BGO	PWO(Y)	LSO(Ce)	GSO(Ce)
Density (g/cm <sup>3</sup> )	3.67	4.51	4.51	4.89	7.13	8.3	7.40	6.71
Melting Point (°C)	651	621	621	1280	1050	1123	2050	1950
Radiation Length (cm)	2.59	1.86	1.86	2.03	1.12	0.89	1.14	1.38
Molière Radius (cm)	4.13	3.57	3.57	3.10	2.23	2.00	2.07	2.23
Interaction Length (cm)	42.9	39.3	39.3	30.7	22.8	20.7	20.9	22.2
Refractive Index <sup>a</sup>	1.85	1.79	1.95	1.50	2.15	2.20	1.82	1.85
Hygroscopicity	Yes	Slight	Slight	No	No	No	No	No
Luminescence <sup>b</sup> (nm) (at peak)	410	550	420 310	300 220	480	425 420	402	440
Decay Time <sup>b</sup> (ns)	230	1250	30 6	630 0.9	300	30 6	40	60
Light Yield <sup>b,c</sup> (%)	100	165	3.6 1.1	36 3.4	21	0.29 .083	83	30
d(LY)/dT <sup>b</sup> (%/°C)	~0	0.3	-0.6	-2 ~0	-1.6	-1.9	~0	-0.1
Experiment	Crystal Ball	CLEO BaBar BELLE BES III	KTeV	TAPS (L*) (GEM)	L3 BELLE PANDA?	CMS ALICE PrimEx PANDA?	-	-


a. at peak of emission; b. up/low row: slow/fast component; c. PMT QE taken out.



# Crystal Density: Radiation Length

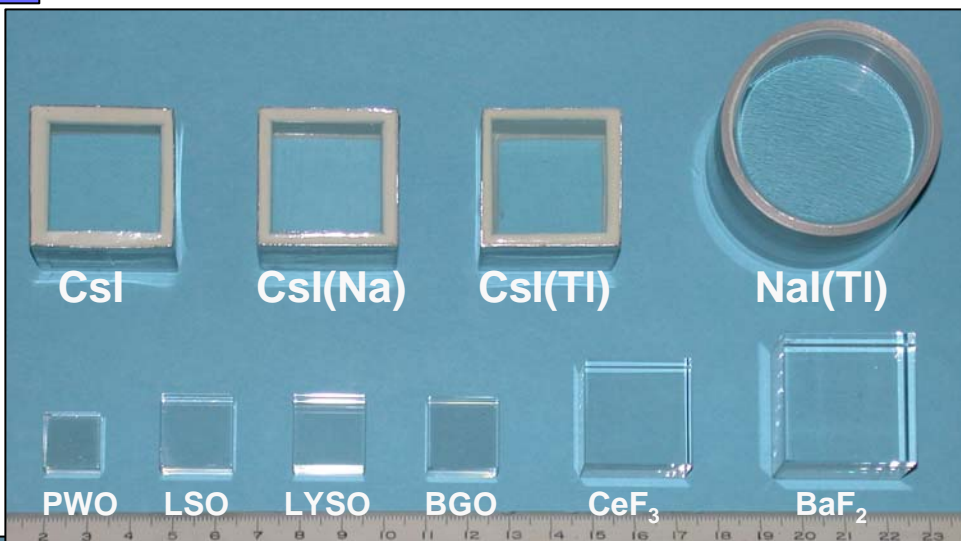


1.5  $X_0$  Samples:  
Hygroscopic Halides  
Non-hygroscopic

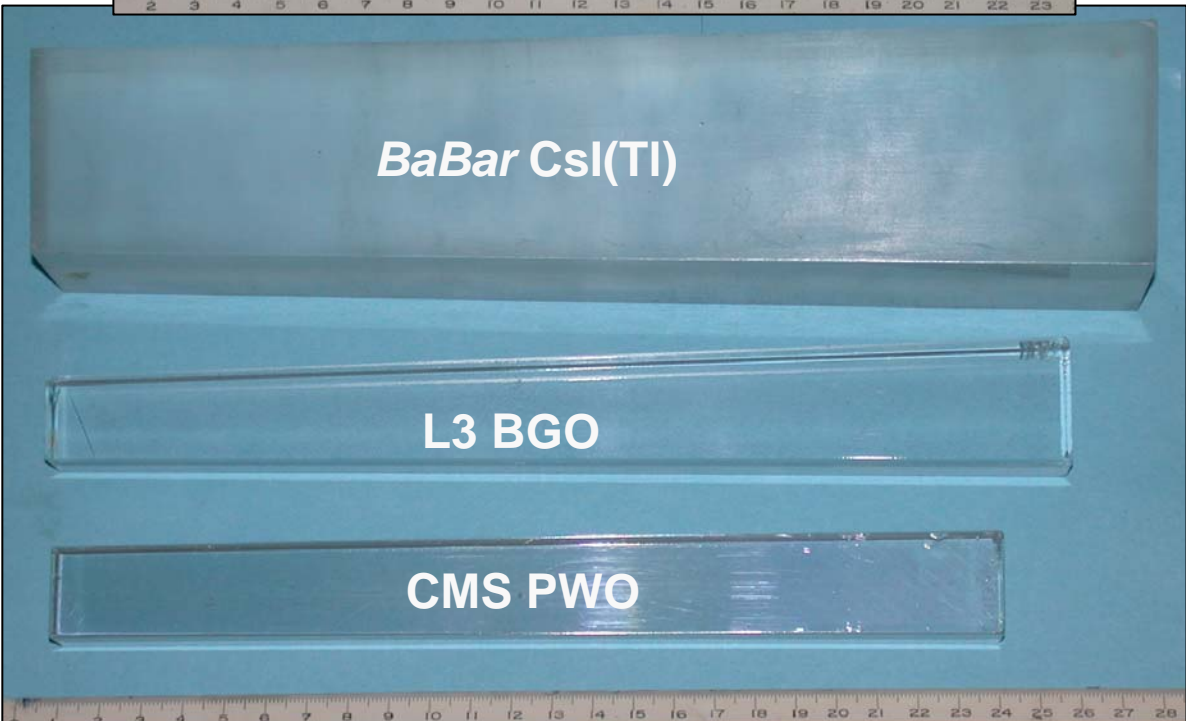

Full Size Crystals:  
*BaBar* Csl(Tl): 16  $X_0$   
L3 BGO: 22  $X_0$   
CMS PWO(Y): 25  $X_0$




# Excitation, Emission & Transmission



$$T_s = (1 - R)^2 + R^2(1 - R)^2 + \dots = (1 - R)/(1 + R), \text{ with}$$


$$R = \frac{(n_{crystal} - n_{air})^2}{(n_{crystal} + n_{air})^2}$$

Theoretical limit of transmittance: NIM A333 (1993) 422

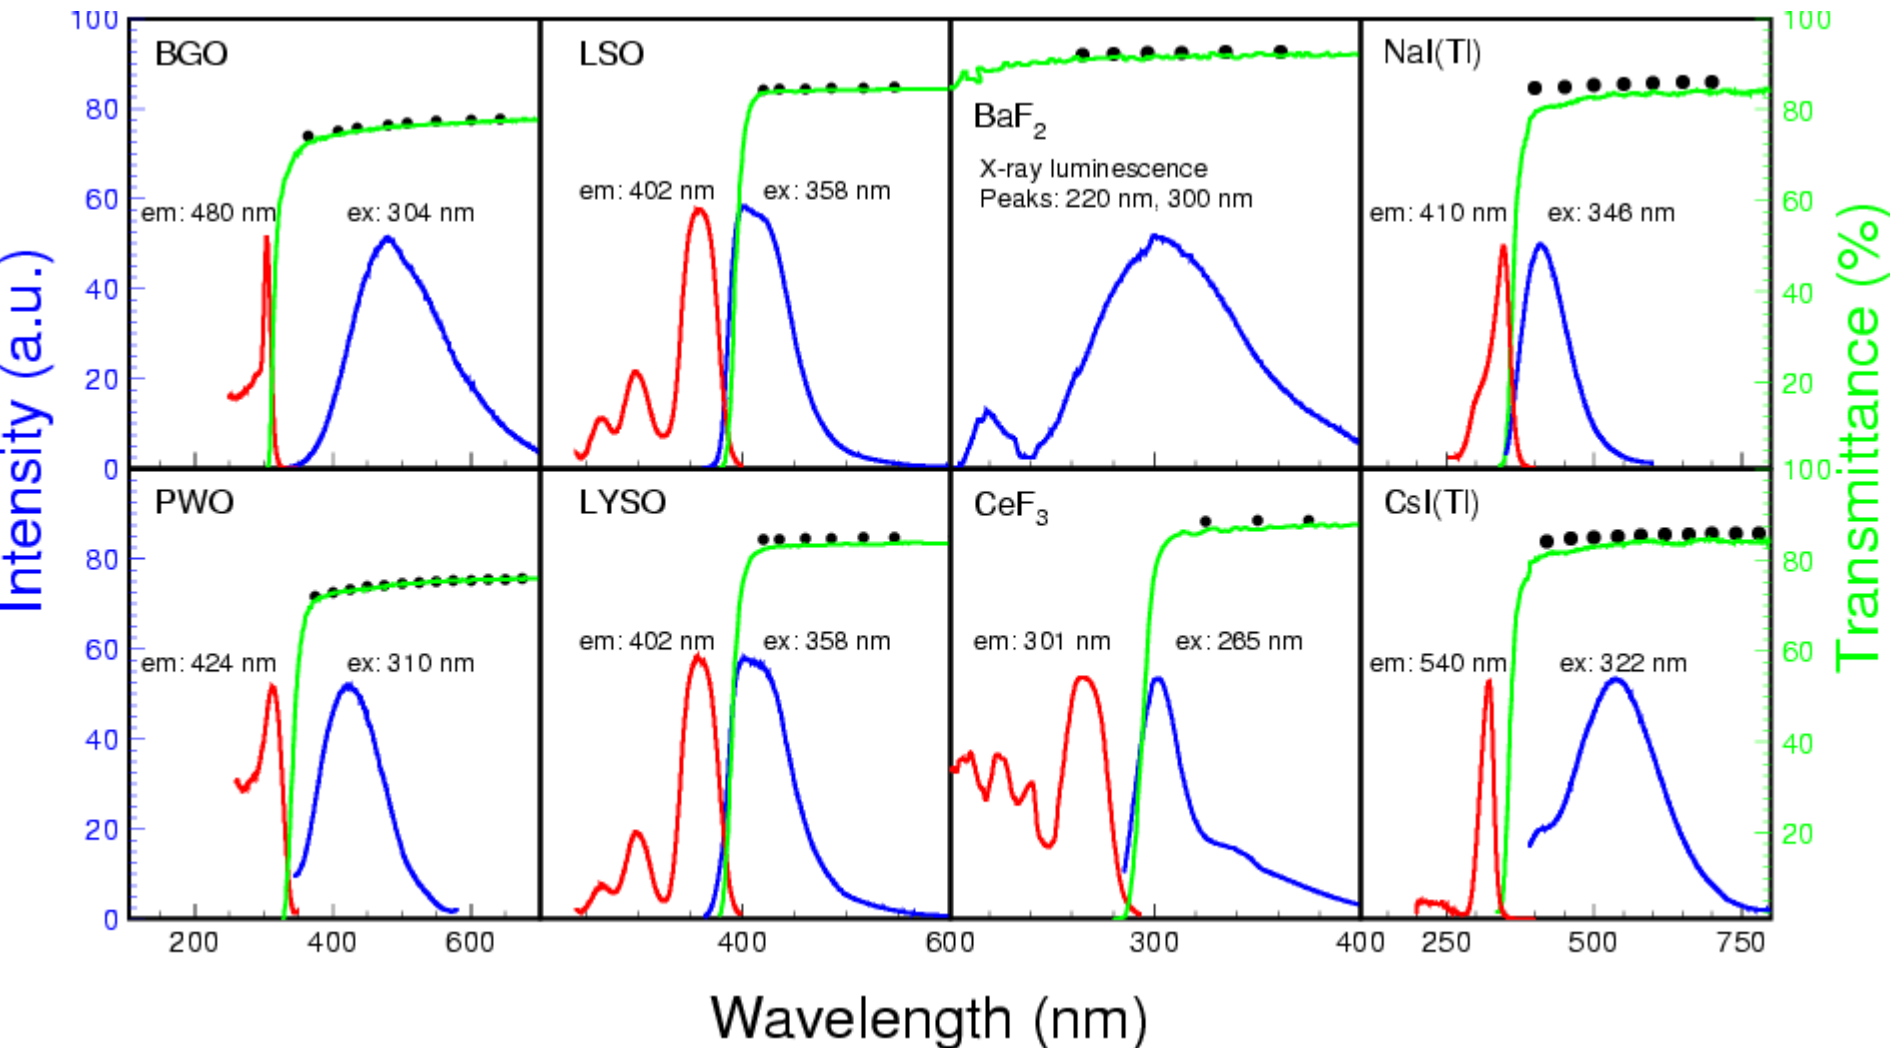





# Scintillation Light Decay Time



Recorded with an Agilent 6052A digital scope


## Fast Scintillators

## Slow Scintillators

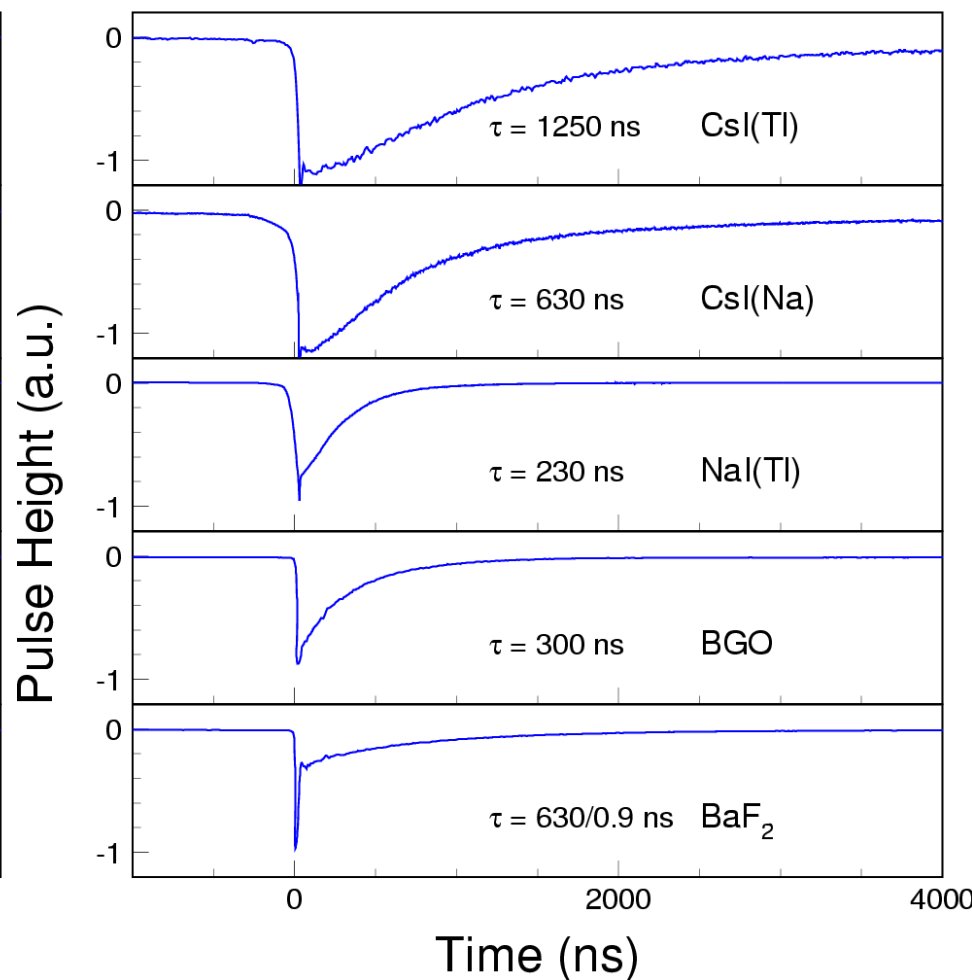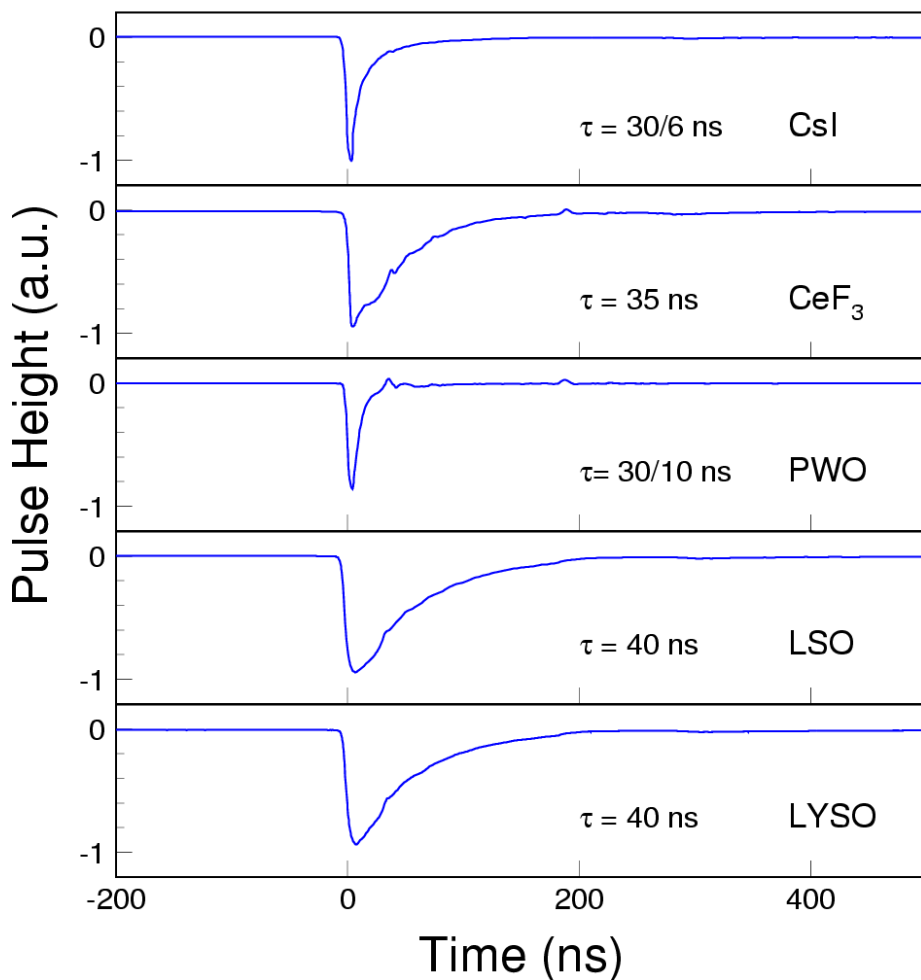




# Scintillation Light Output




Measured with a Philips XP2254B PMT (multi-alkali cathode)  
 p.e./MeV: LSO/LYSO is 6 & 230 times of BGO & PWO respectively

## Fast Scintillators

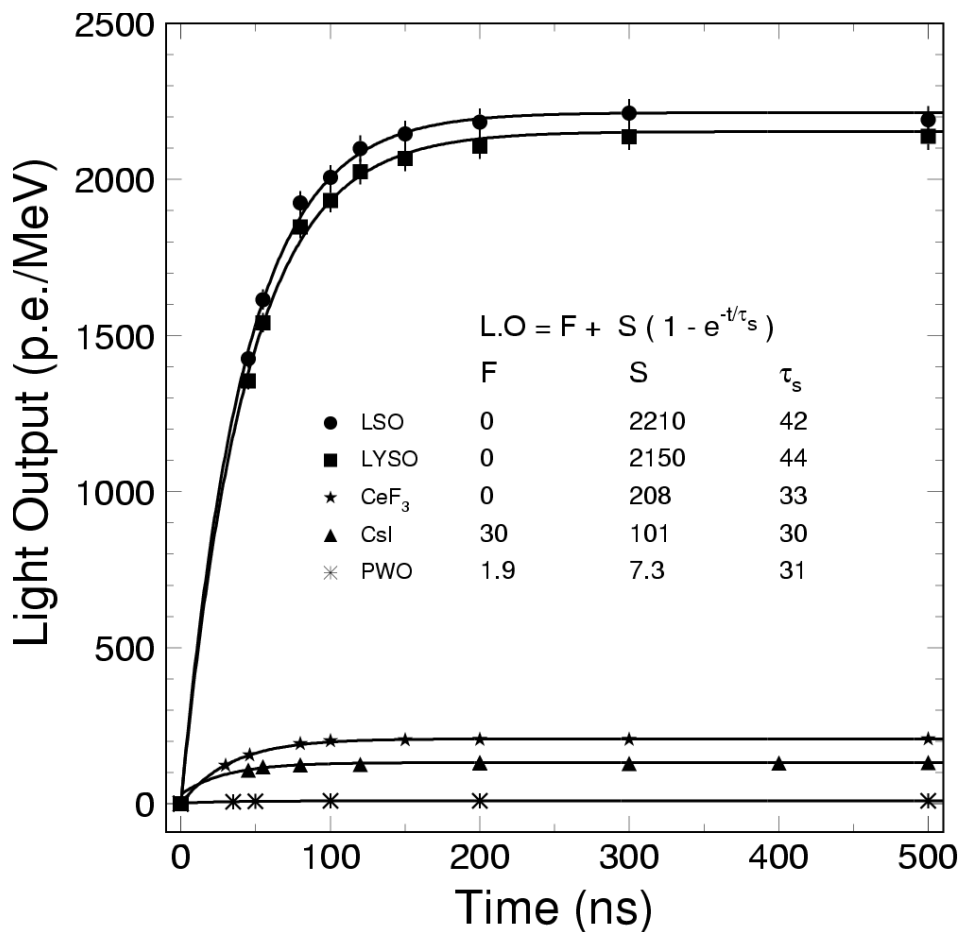


## Slow Scintillators


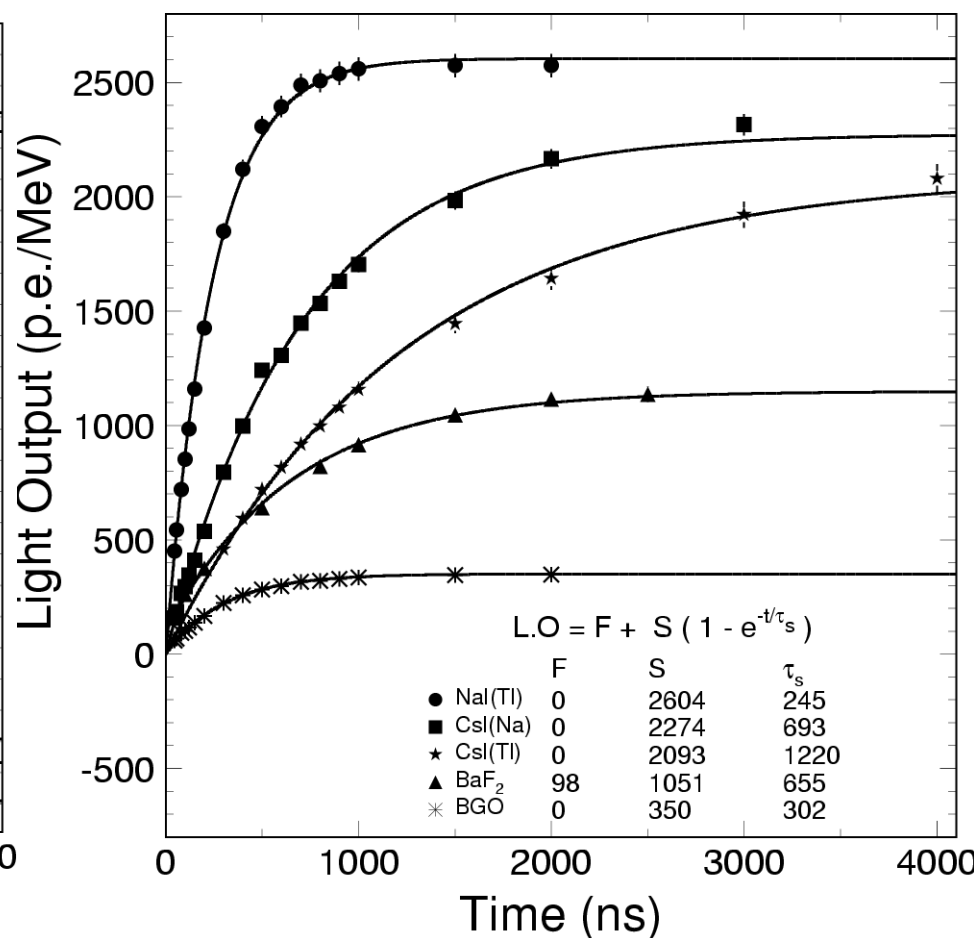




# Emission Weighted PMT Q.E.




Taking out QE, L.O. of LSO/LYSO is 4/200 times BGO/PWO  
Hamamatsu S8664-55 APD has QE 75% for LSO/LYSO

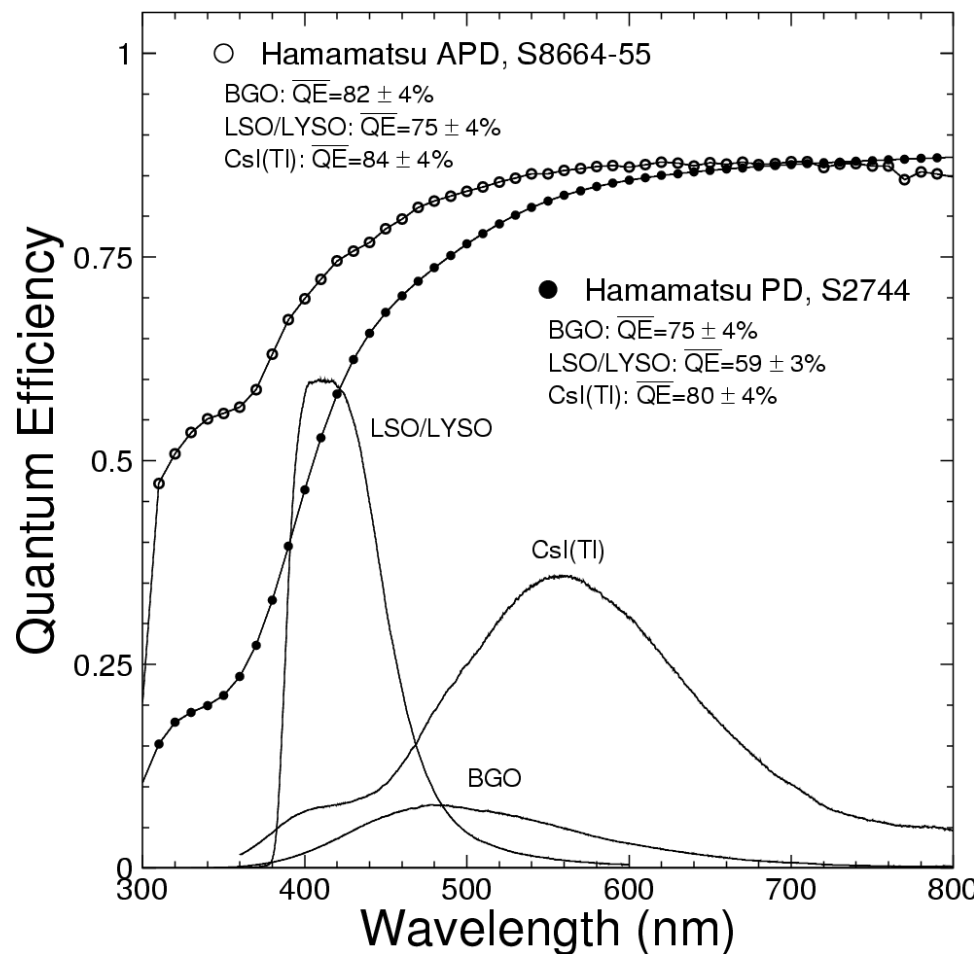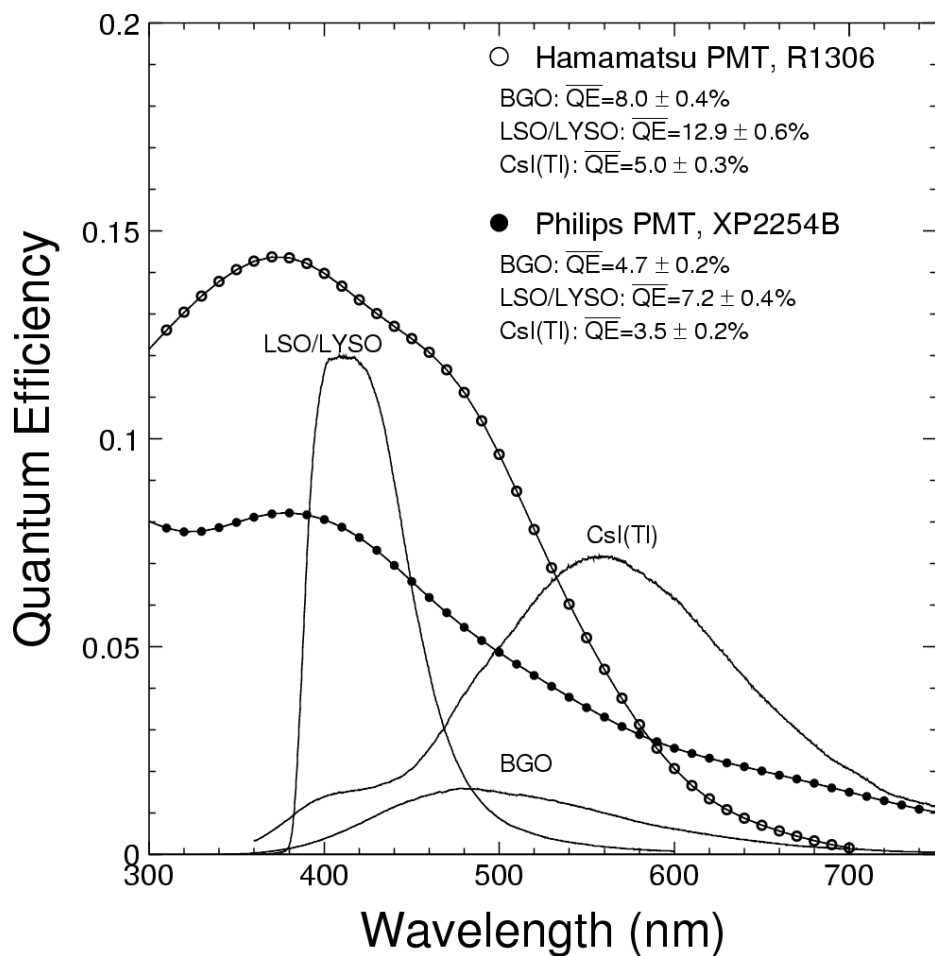






# BGO, LSO & LYSO Samples




2.5 x 2.5 x 20 cm ( $18 X_0$ )


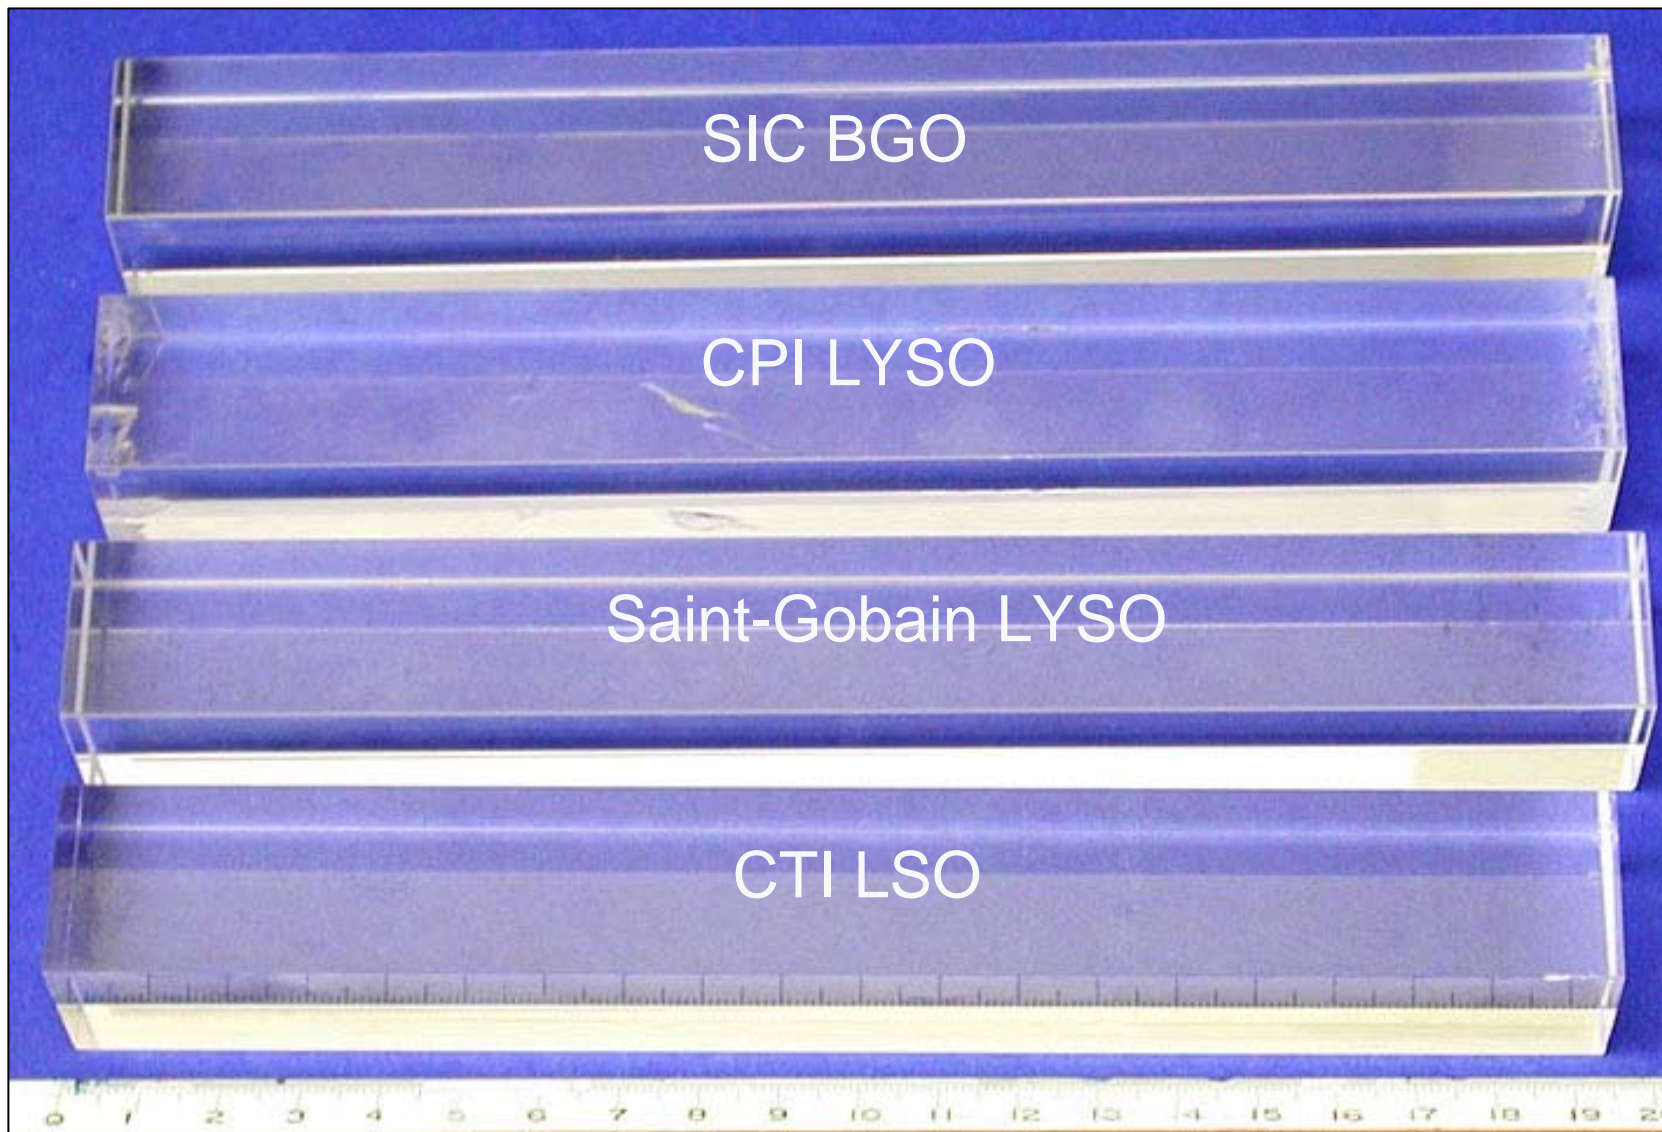




# LSO/LYSO with PMT Readout




~10% FWHM resolution for  $^{22}\text{Na}$  source (0.51 MeV)  
1,200 p.e./MeV, 5/230 times of BGO/PWO

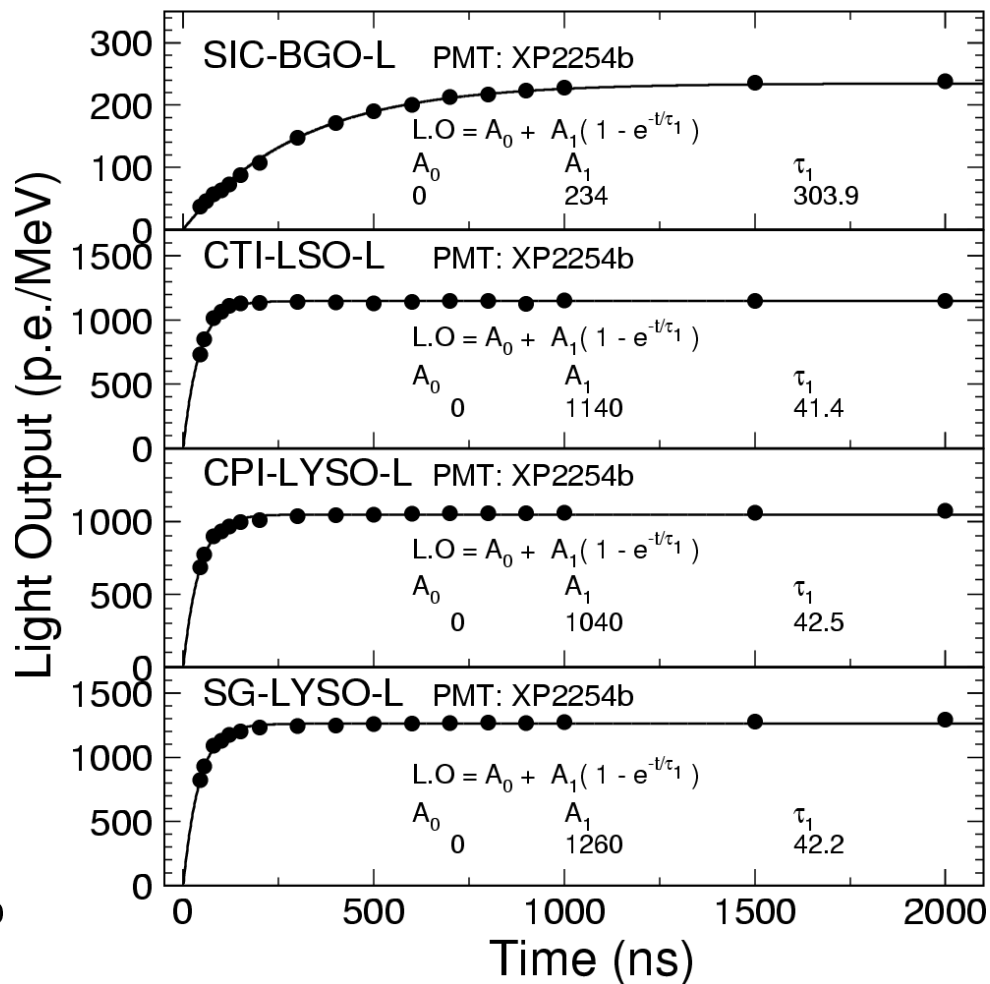
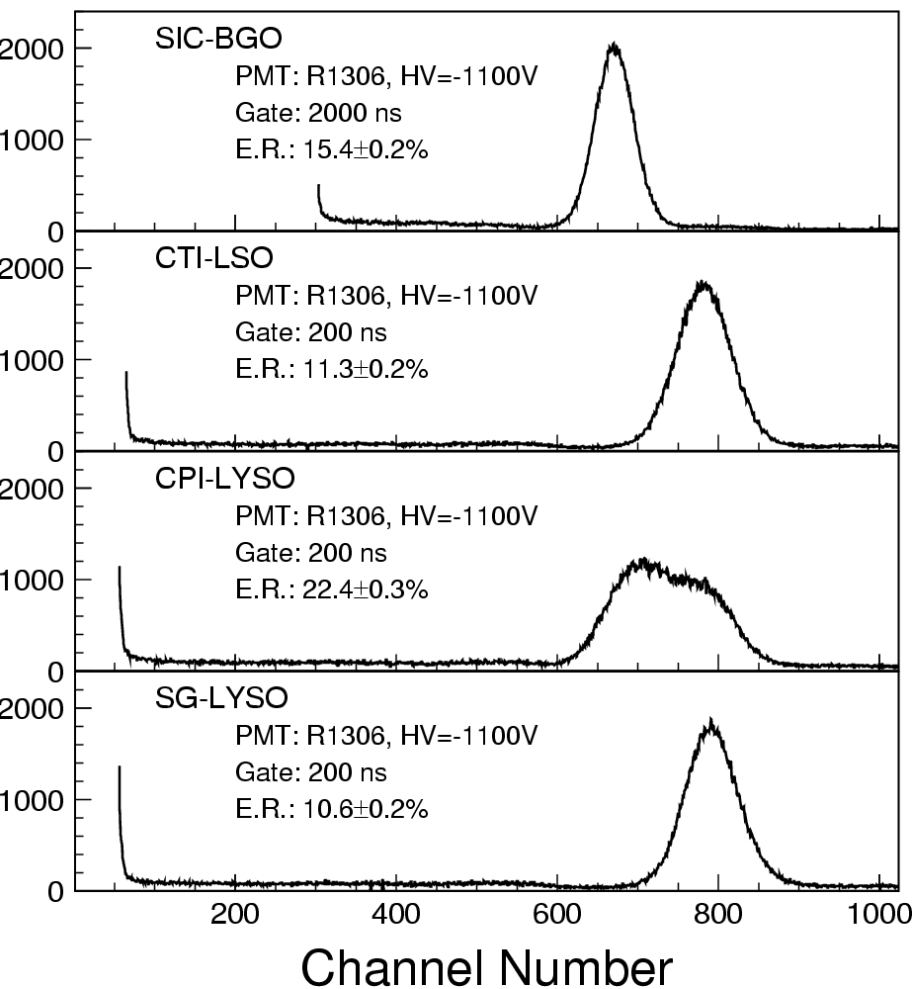




# LSO/LYSO with APD Readout




L.O.: 1,500 p.e./MeV, 4/200 times of BGO/PWO  
Readout Noise: <40 keV

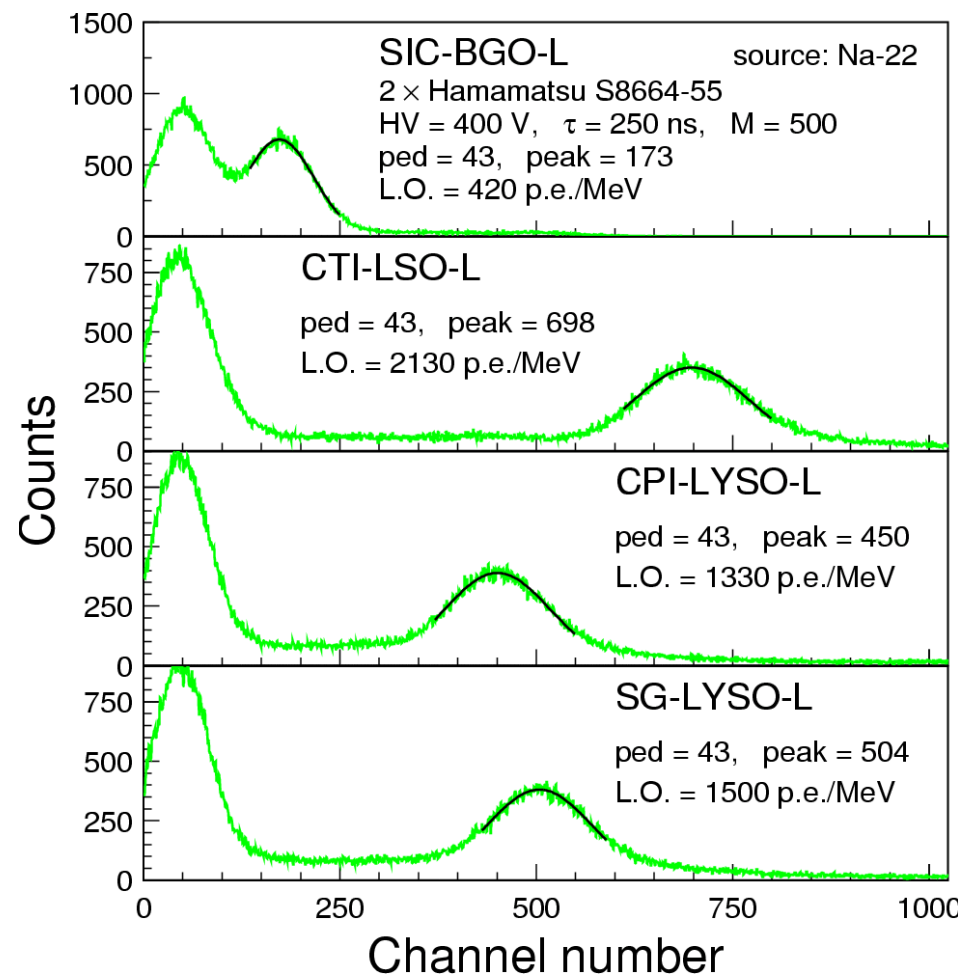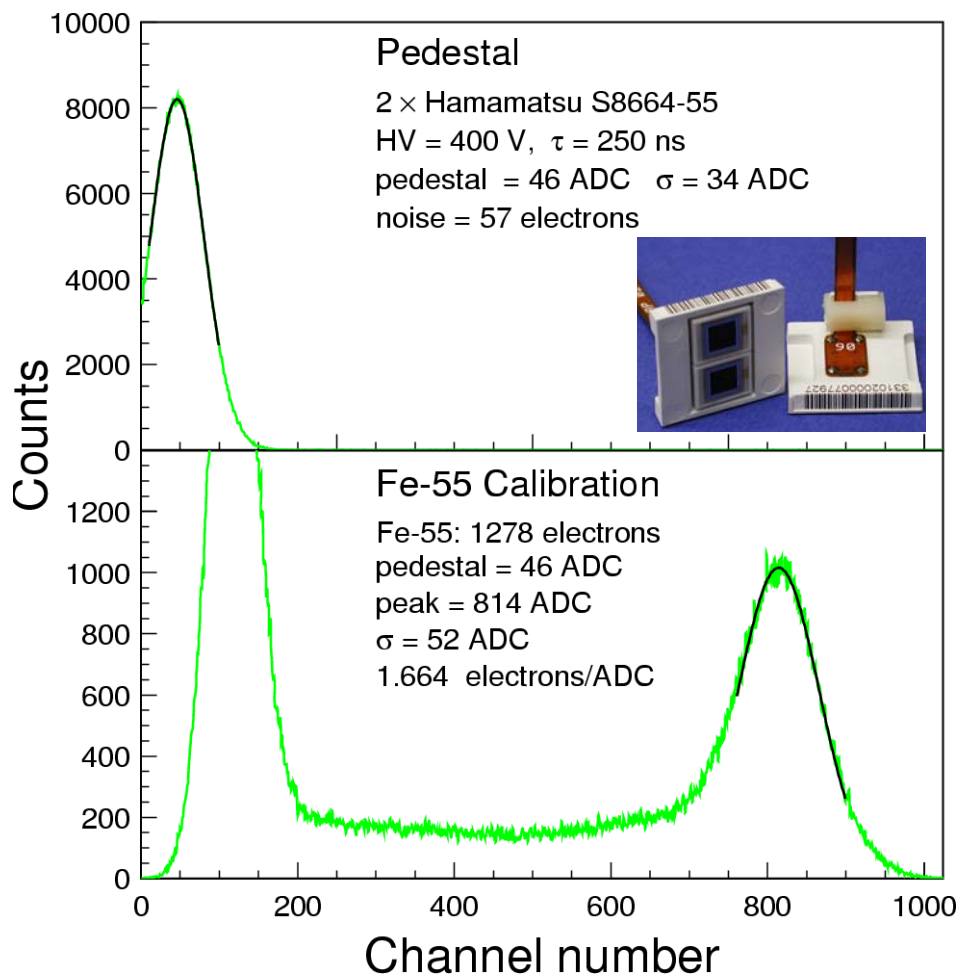



# Crystal Calorimeters in HEP



Date	75-85	80-00	80-00	80-00	90-10	94-10	94-10	95-20
Experiment	C. Ball	L3	CLEO II	C. Barrel	KTeV	<i>BaBar</i>	BELLE	CMS
Accelerator	SPEAR	LEP	CESR	LEAR	FNAL	SLAC	KEK	CERN
Crystal Type	NaI(Tl)	BGO	CsI(Tl)	CsI(Tl)	CsI	CsI(Tl)	CsI(Tl)	PbWO <sub>4</sub>
B-Field (T)	-	0.5	1.5	1.5	-	1.5	1.0	4.0
$r_{inner}$ (m)	0.254	0.55	1.0	0.27	-	1.0	1.25	1.29
Number of Crystals	672	11,400	7,800	1,400	3,300	6,580	8,800	76,000
Crystal Depth ( $X_0$ )	16	22	16	16	27	16 to 17.5	16.2	25
Crystal Volume (m <sup>3</sup> )	1	1.5	7	1	2	5.9	9.5	11
Light Output (p.e./MeV)	350	1,400	5,000	2,000	40	5,000	5,000	2
Photosensor	PMT	Si PD	Si PD	WS <sup>a</sup> +Si PD	PMT	Si PD	Si PD	APD <sup>a</sup>
Gain of Photosensor	Large	1	1	1	4,000	1	1	50
$\sigma_N$ /Channel (MeV)	0.05	0.8	0.5	0.2	small	0.15	0.2	40
Dynamic Range	10 <sup>4</sup>	10 <sup>5</sup>	10 <sup>4</sup>	10 <sup>4</sup>	10 <sup>4</sup>	10 <sup>4</sup>	10 <sup>4</sup>	10 <sup>5</sup>


**Future crystal calorimeters in HEP:**

**PANDA at GSI: PWO or BGO?**



**LSO/LYSO for a Super B Factory or ILC?**



# L3 BGO Resolution






Contribution	“Radiative”+Intrinsic	Temperature	Calibration	Overall
Barrel	0.8%	0.5%	0.5%	1.07%
Endcaps	0.6%	0.5%	0.4%	0.88%

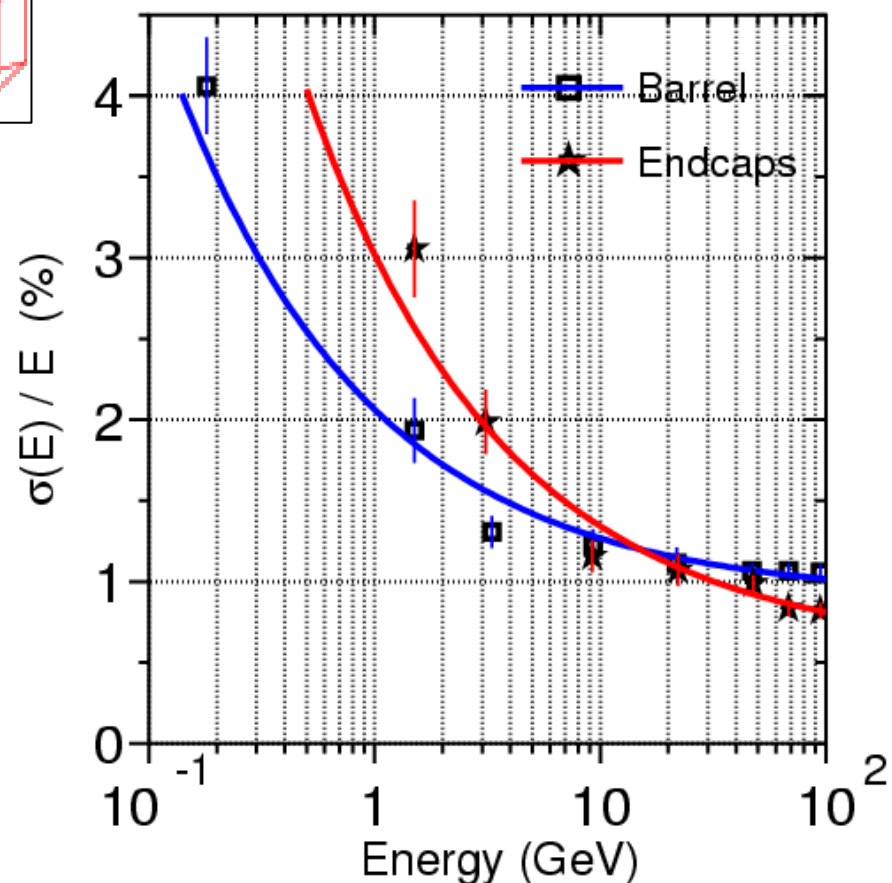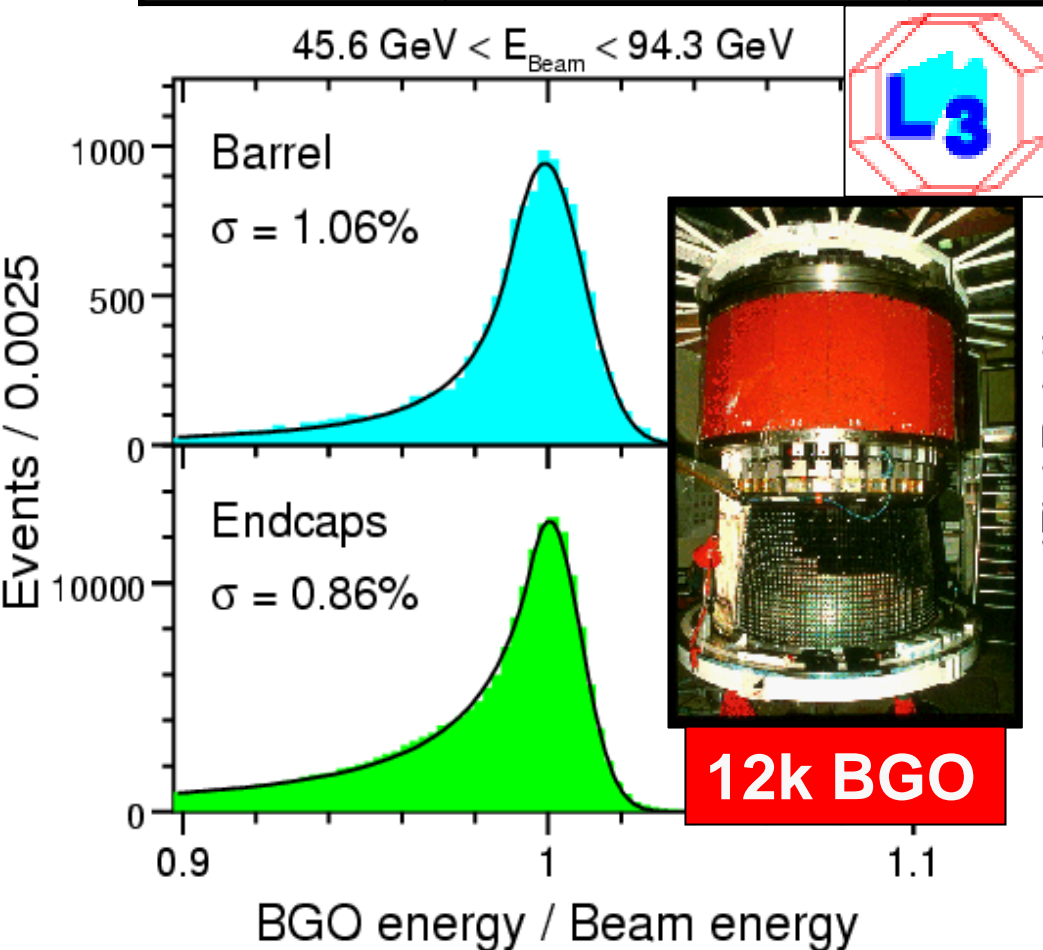




# KTeV CsI Position Resolution

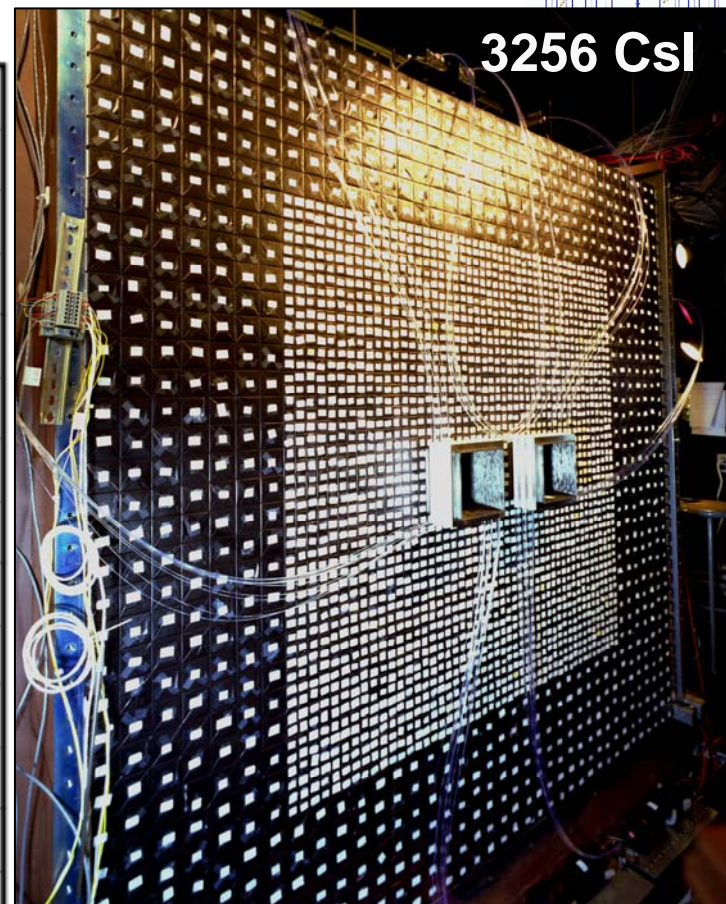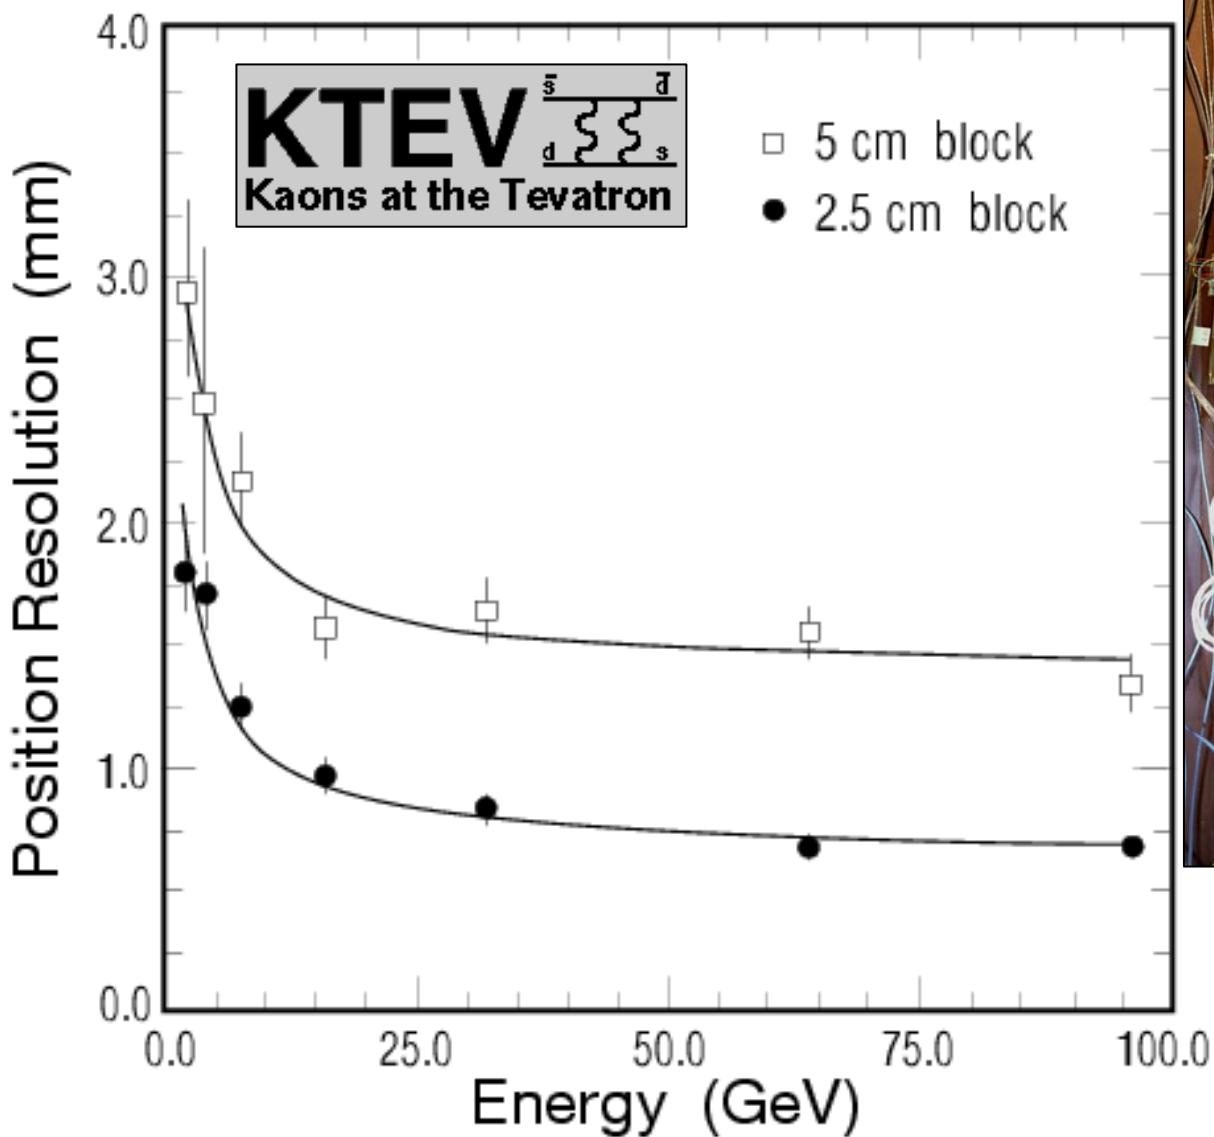

Sub mm position resolution.  
L3 BGO & CMS  
PWO: 0.3 mm.




# PWO Crystal ECAL Resolution



## Crystal Aging & Radiation Damage?

See talks by Paramatti, Mao, Adi & Daskalakis


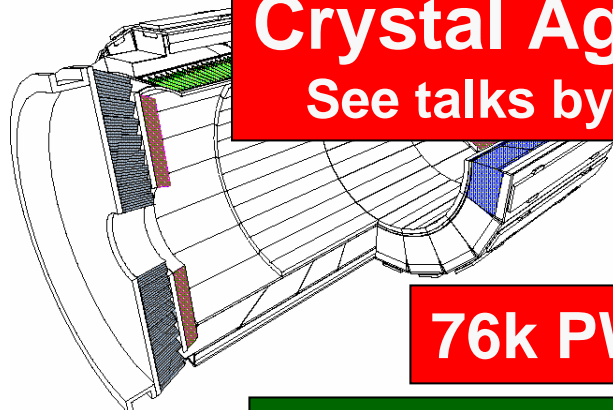


**76k PWO**



measured resolution  
 $\sigma(E)/E < 1\%$  if  $E > 25$  GeV  
 $\sigma(E)/E \sim 0.5\%$  at 120 GeV


**Designed Resolution**

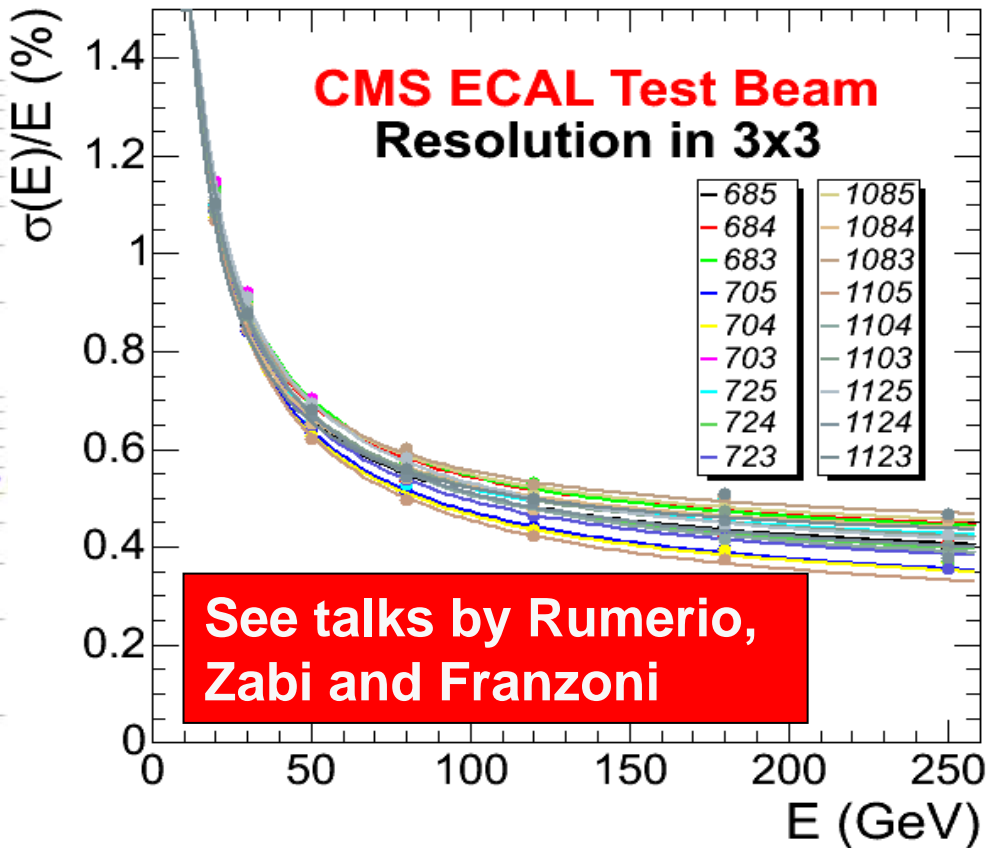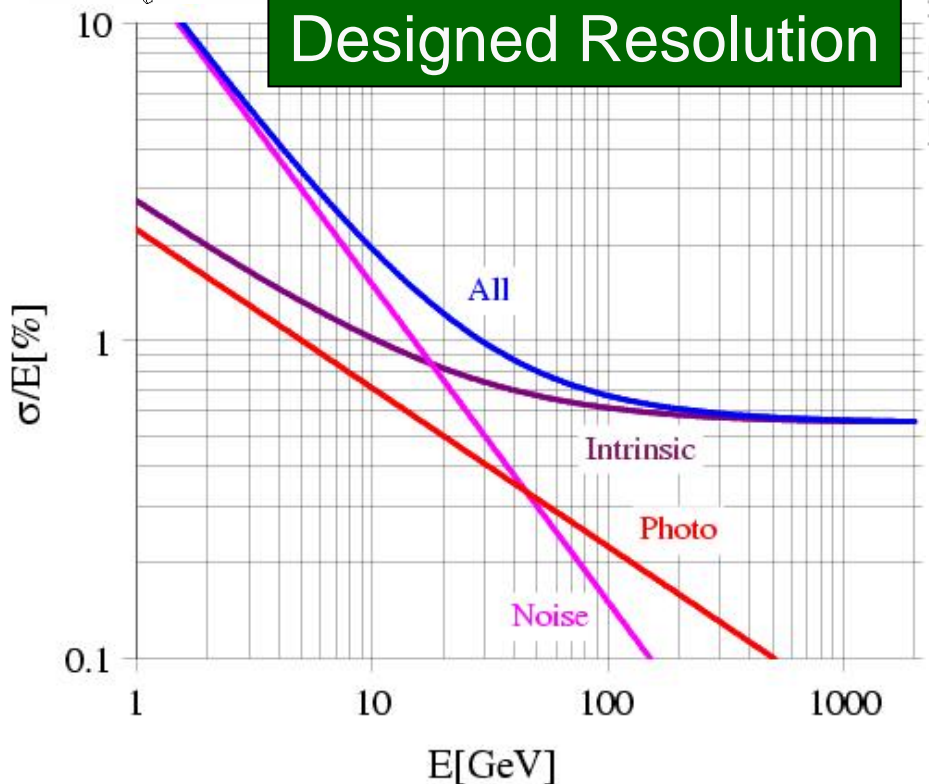

See talks by Rumerio, Zabi and Franzoni





# Crystal Degradation *in situ*



L3 BGO degrades 6 – 7% in 7 years


*BaBar* CsI(Tl): 1 - 3 % per year

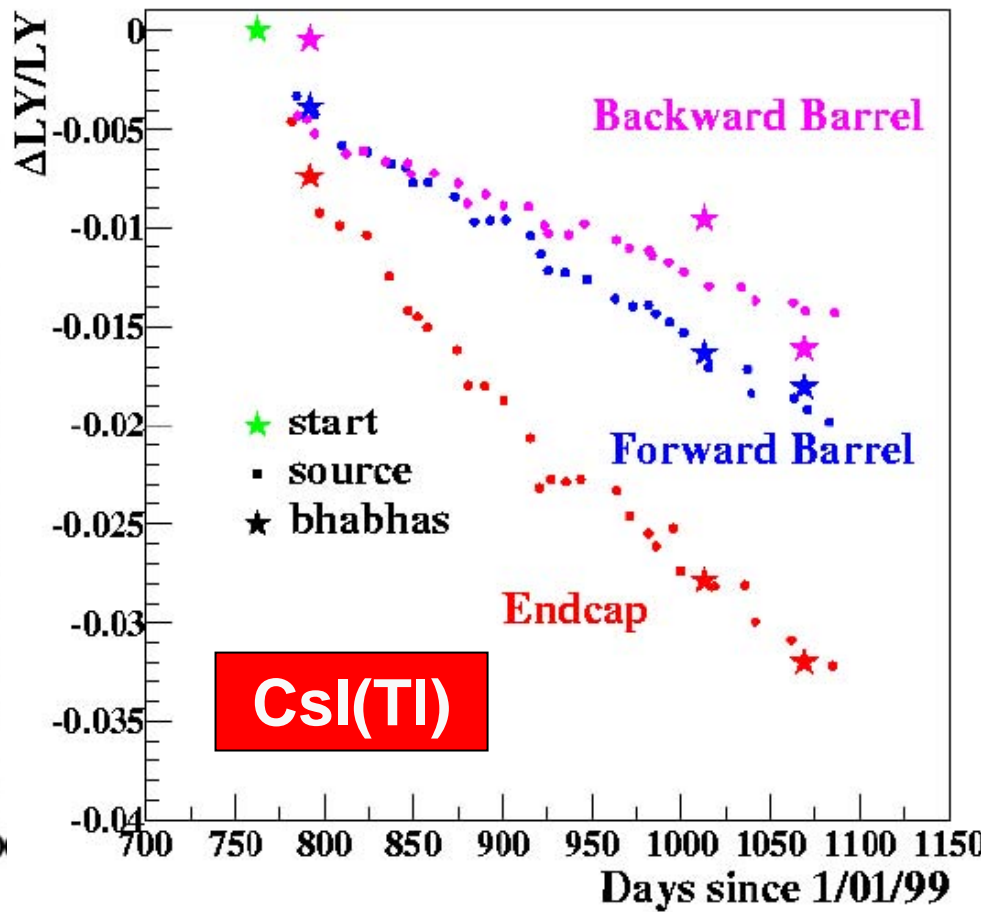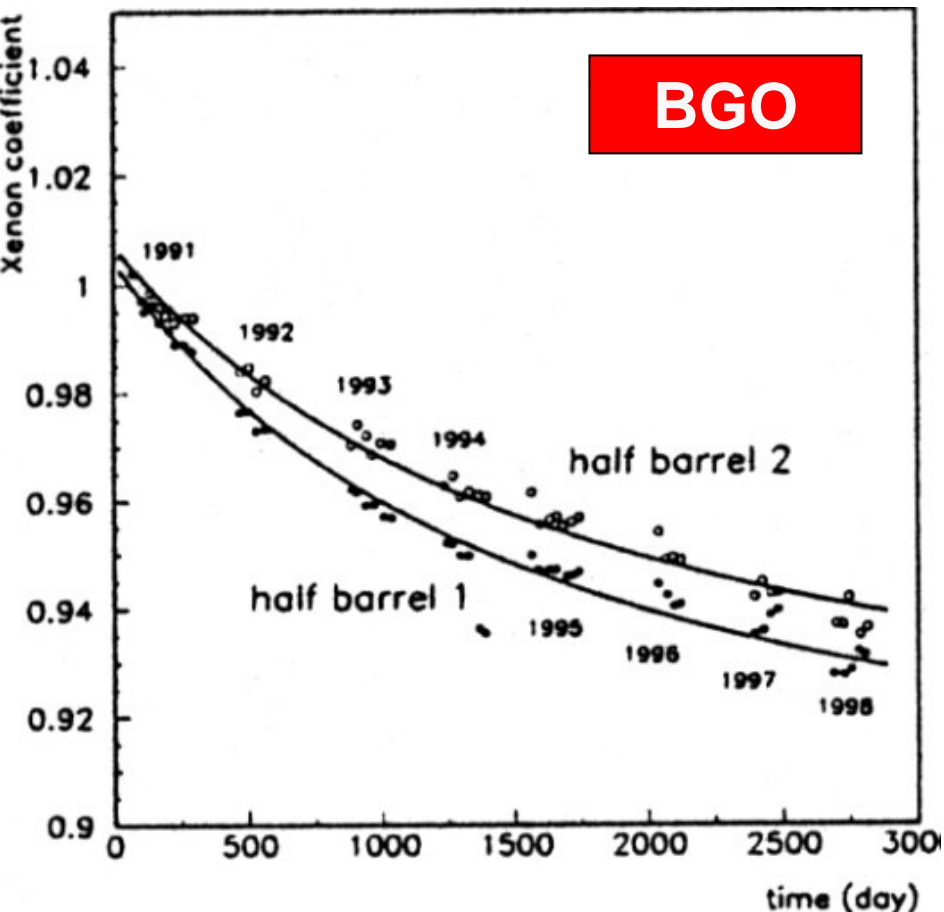





# Effects of Radiation Damage




- Induced absorption caused by color center formation:
  - reduced light attenuation length and thus light output, and maybe
  - degraded of light response uniformity (LRU).
- Induced phosphorescence:
  - increase readout noise.
- Reduced scintillation light yield:
  - reduce light output and degrade light response uniformity.



Item	CsI(Tl)	CsI	BaF <sub>2</sub>	BGO	PbWO <sub>4</sub>
Color Centers	Yes	Yes	Yes	Yes	Yes
Fluorescence	Yes	Yes	Yes	Yes	Yes
Scintillation	No	No	No	No	No
Recover @RT	Slow	Slow	No	Yes	Yes
<b>Dose Rate Dependence</b>	No	No	No	Yes	Yes
Thermal Annealing	No/Yes	No/Yes	Yes	Yes	Yes
Optical Bleaching	No/Yes	No/Yes	Yes	Yes	Yes



# Radiation Induced Absorption




Measured with Hitachi U-3210 Photospectrometer

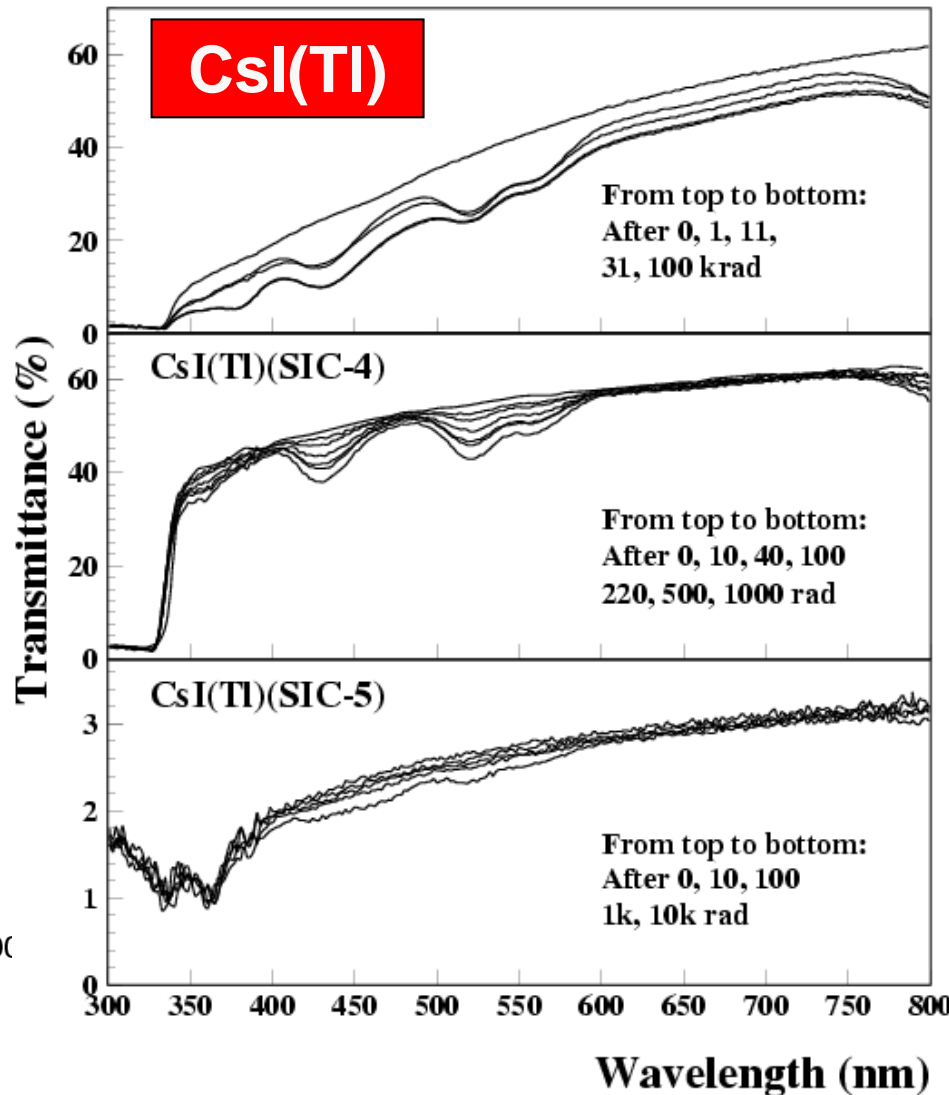
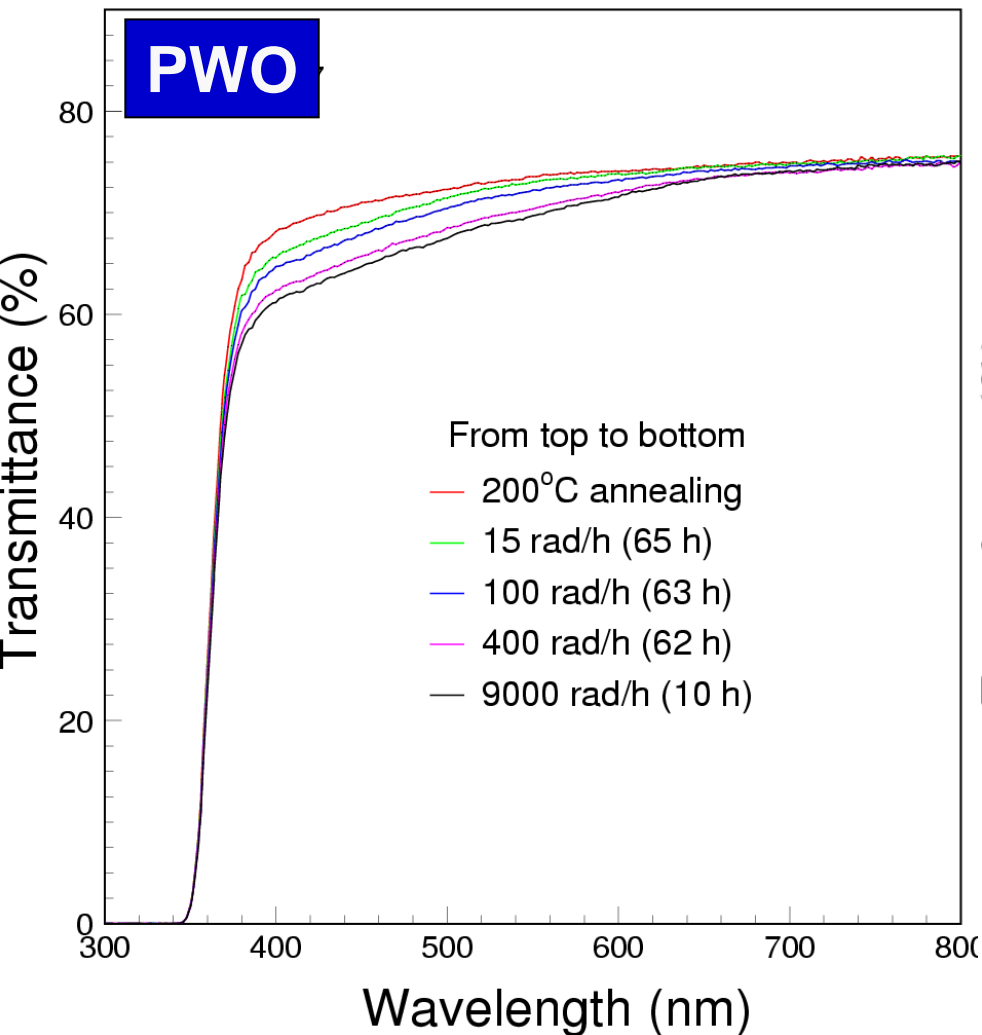




# SIMS Study & CsI(Tl) Improvement




Secondary Ion Mass Spectroscopy revealed depth profile of oxygen contamination; Oxygen control improves CsI(Tl) quality

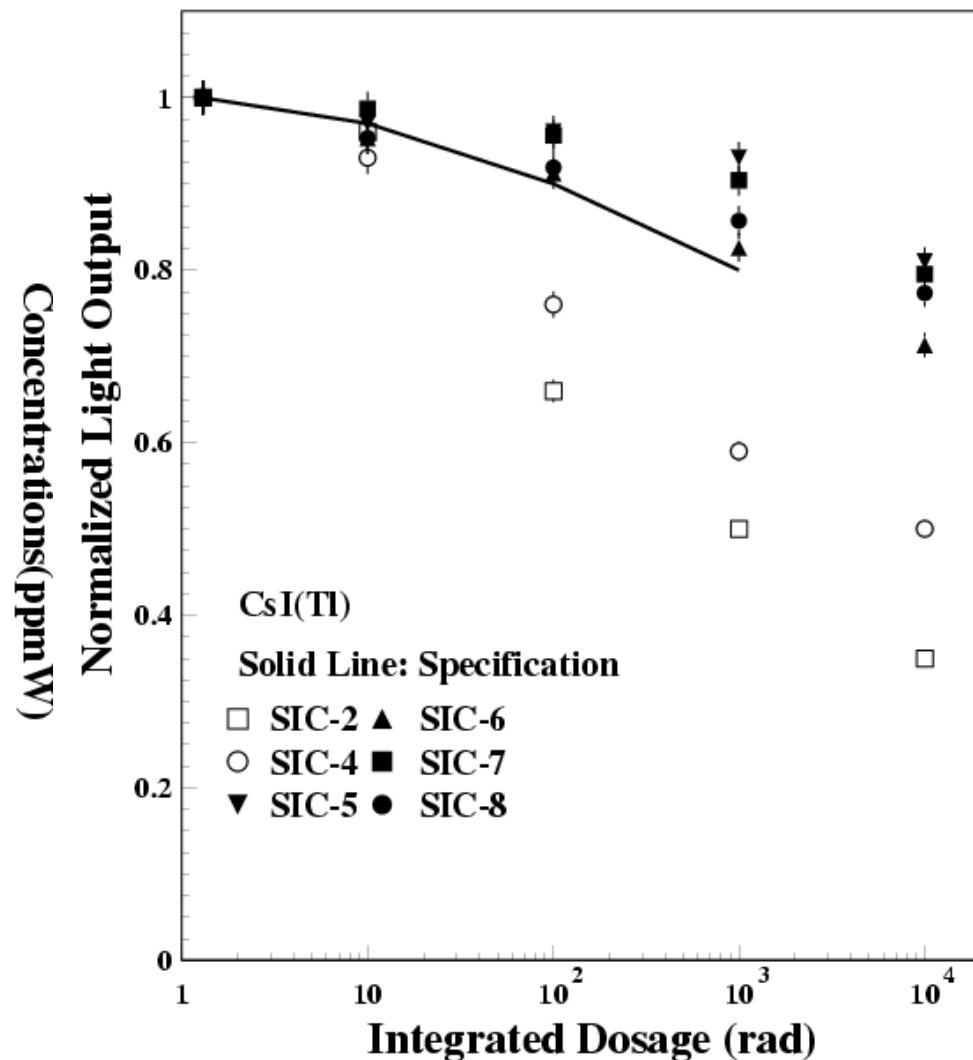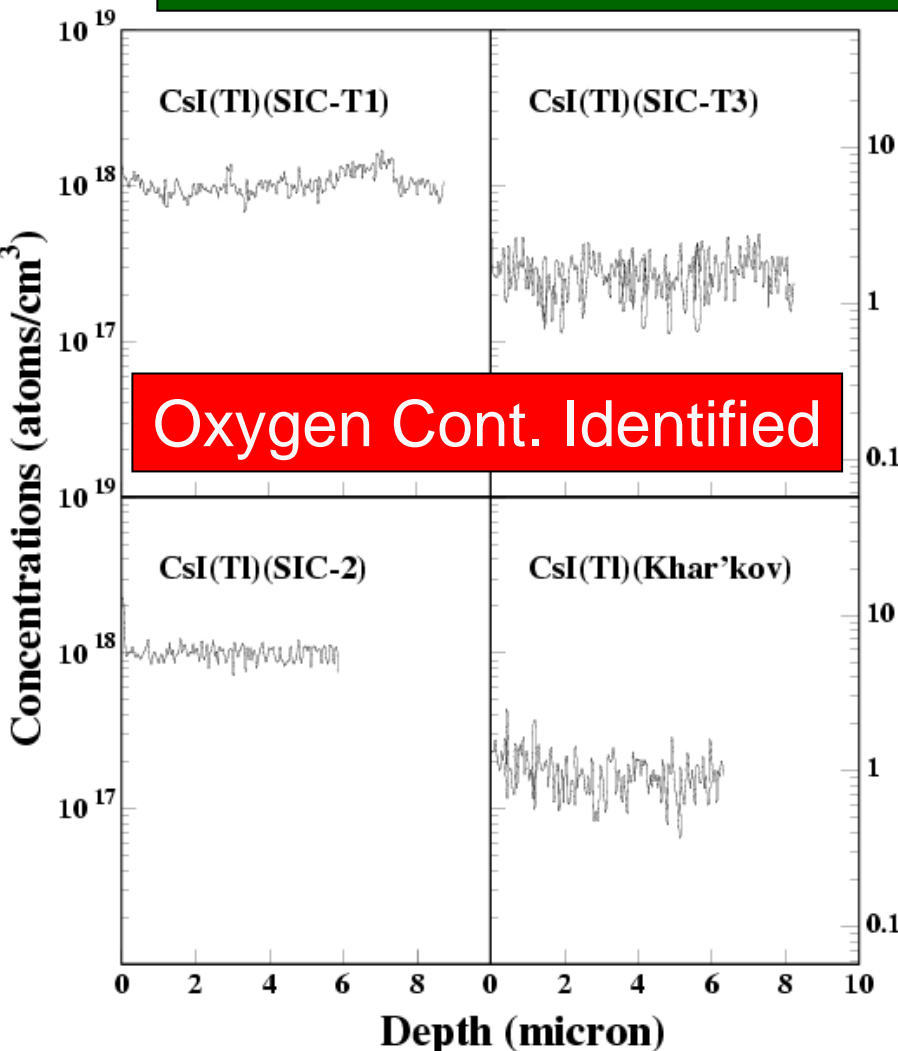




# TEM/EDS Study on PWO Crystals



TOPCON-002B scope, 200 kV, 10  $\mu$ A, 5 to 10 nm black spots identified  
JEOL JEM-2010 scope and Link ISIS EDS localized Stoichiometry Analysis

**X-ray**

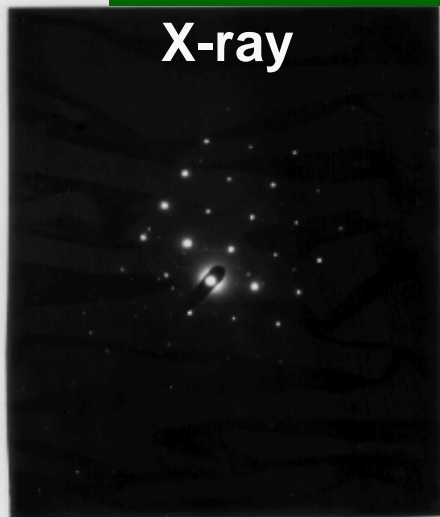

**Good PWO**




Atomic Fraction (%) in  $\text{PbWO}_4$


As Grown Sample

Element	Black Spot	Peripheral	Matrix <sub>1</sub>	Matrix <sub>2</sub>
O	1.5	15.8	60.8	63.2
W	50.8	44.3	19.6	18.4
Pb	47.7	39.9	19.6	18.4

**Bad PWO**

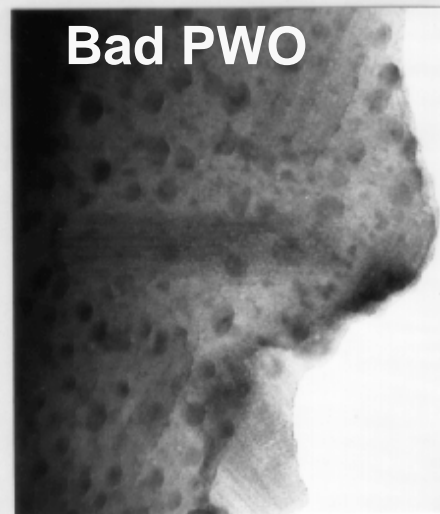

**Bad PWO**

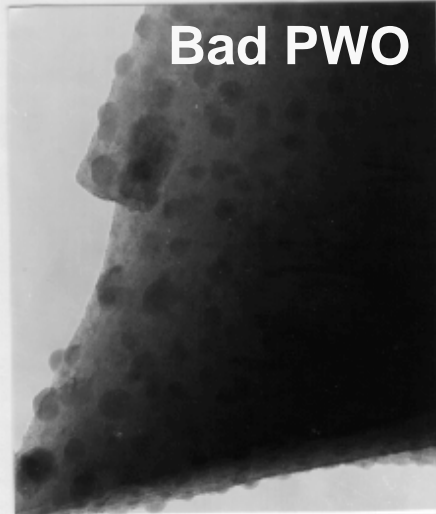


The Same Sample after Oxygen Compensation

Element	Point <sub>1</sub>	Point <sub>2</sub>	Point <sub>3</sub>	Point <sub>4</sub>
O	59.0	66.4	57.4	66.7
W	21.0	16.5	21.3	16.8
Pb	20.0	17.1	21.3	16.5

**Oxygen Vacancies Identified**



# BGO/PWO Quality Improvement





Nucl. Instr. and Meth. A302 (1991) 69

Nucl. Instr. and Meth. A480 (2002) 470


BGO damage recovery after 2.5 krad

PWO damage at different dose rate

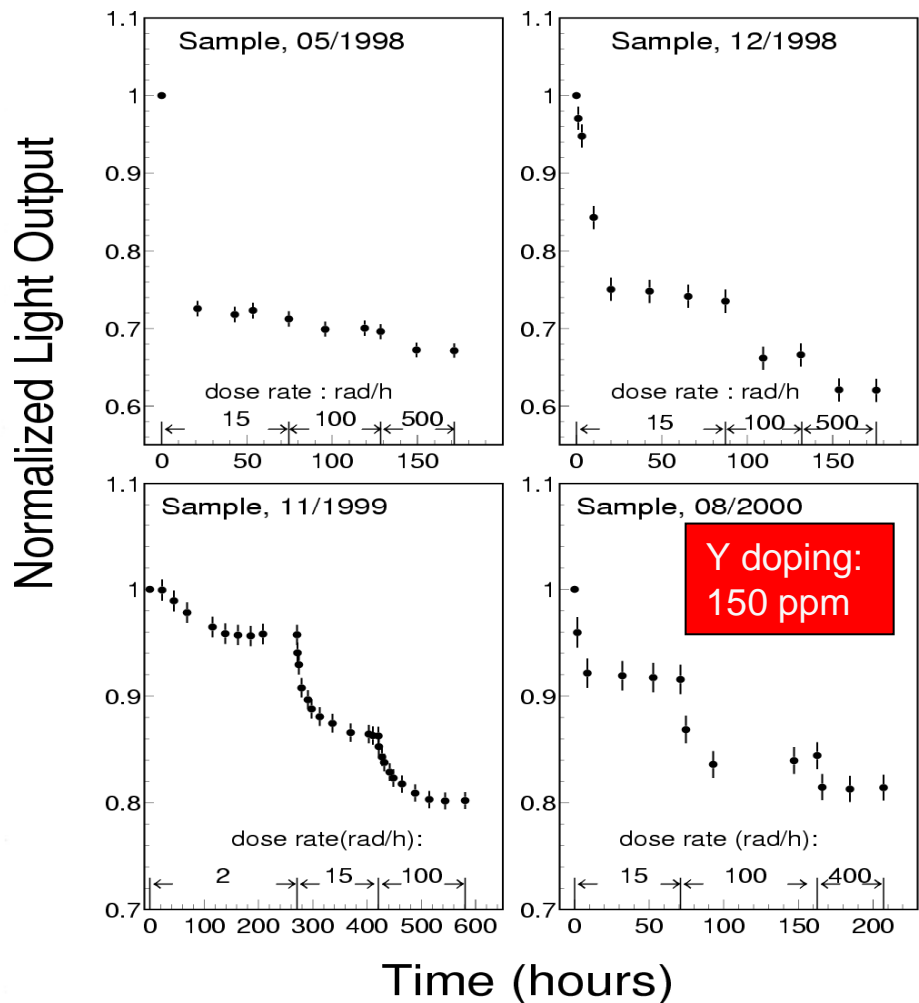
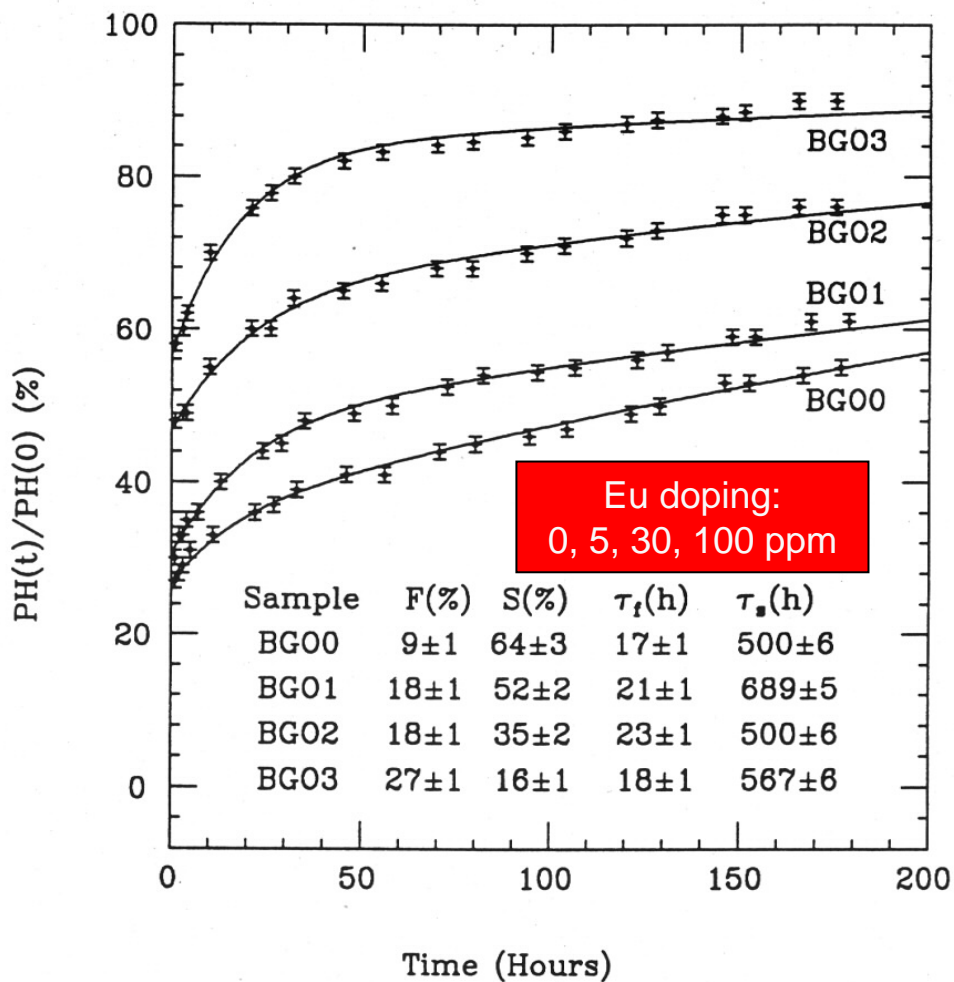




# LYSO Transmittance Damage




LT @ 430 nm shows 6 and 3% increase under 2 rad/h, followed by 6 and 5% degradation under 9 krad/h for CPI and SG samples respectively

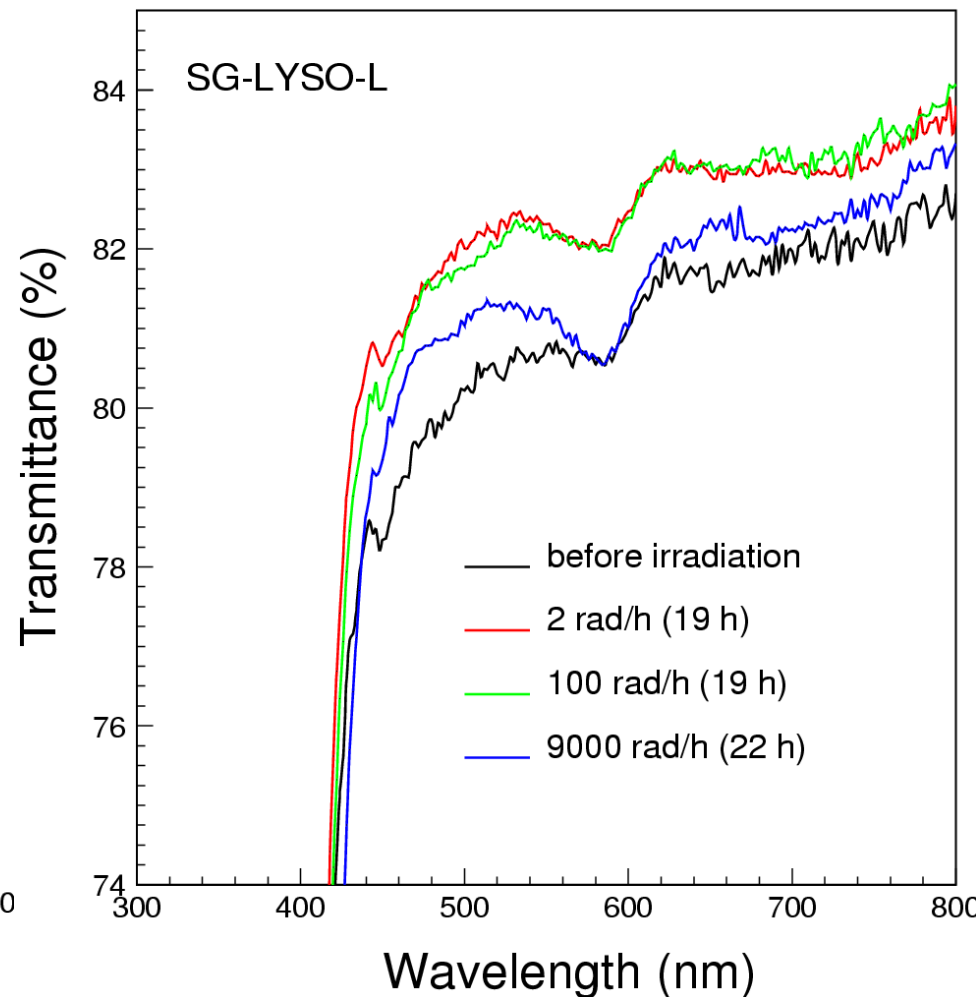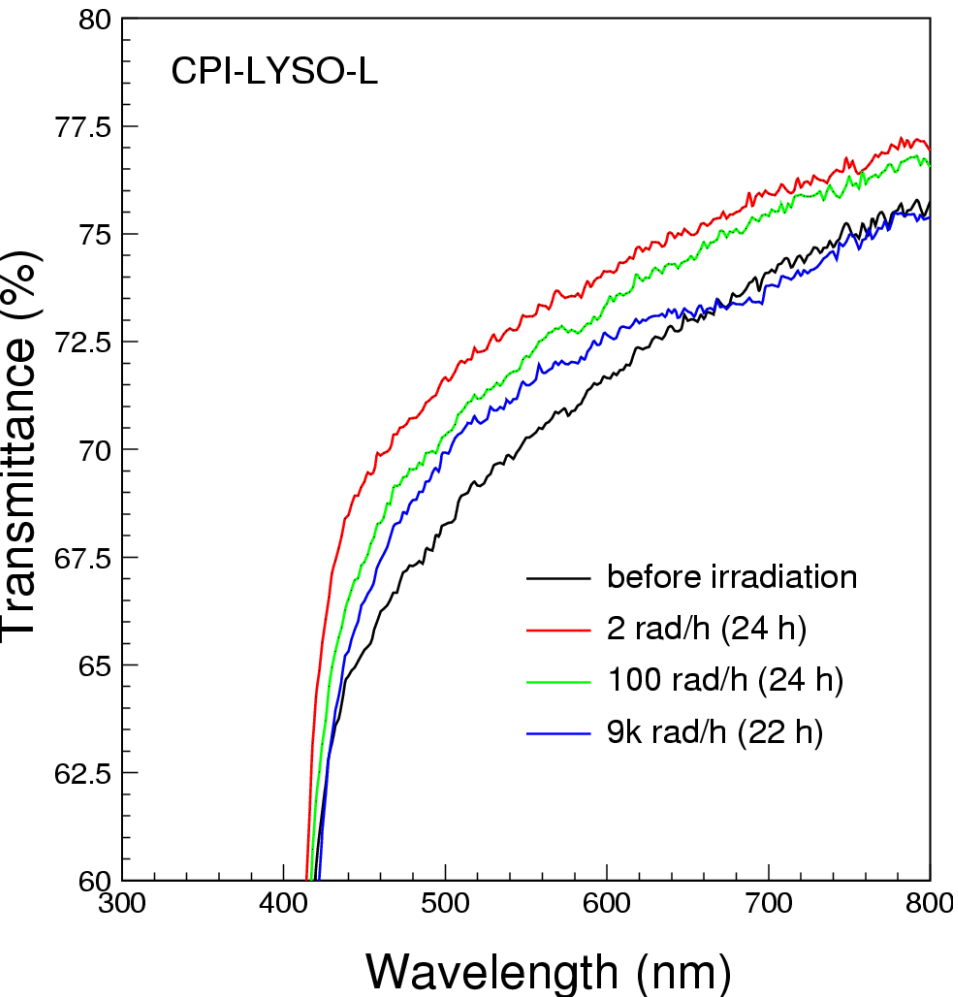



# LSO/LYSO ECAL Performance




- Less demanding to the environment because of small temperature coefficient.
- Radiation damage is less an issue as compared to the CMS PWO ECAL.
- A better energy resolution,  $\sigma(E)/E$ , at low energies than L3 BGO and CMS PWO because of its high light output and low readout noise:

$$2.0\% / \sqrt{E} \oplus 0.5\% \oplus .001/E$$



# Summary




- Because of total absorption, precision crystal calorimetry provides the best possible energy and position resolutions for electrons and photons as well as good  $e/\gamma$  identification and reconstruction efficiencies.
- Progress has been made in understanding crystal radiation damage and improving qualities of mass produced crystals.
- An LSO/LYSO crystal calorimeter will provide excellent energy resolution over a large dynamic range down to MeV level for future HEP and NP experiments.





# LAL affects LRU



Nucl. Instr. And Meth. A413 (1998) 297


Ray-Tracing simulation for CMS PWO crystals shows no change in LRU if LAL is longer than 3.5 crystal length

Light collection efficiency, fit to a linear function of distance to the small end of the crystal, was determined with two parameters: the light collection efficiency at the middle of the crystal and the uniformity.

LAL (cm)	20	40	60	80	200
Large Area Photo Detector, covering 100% back face					
$\eta_m$ (%)	$9.5 \pm 2$	$15.7 \pm 4$	$19.2 \pm 5$	$21.6 \pm 6$	$26.9 \pm 7$
$\delta$ (%)	$23 \pm 1$	$-4.6 \pm 8$	$-11 \pm 1$	$-15 \pm 1$	$-15 \pm 1$
$\phi 5$ mm Photo Detector, covering 3.7% back face					
$\eta_m$ (%)	$.38 \pm .04$	$.74 \pm .08$	$1.1 \pm .1$	$1.4 \pm .2$	$3.0 \pm .3$
$\delta$ (%)	$23 \pm 4$	$-3.5 \pm 4$	$-12 \pm 4$	$-16 \pm 4$	$-17 \pm 3$
$\frac{\eta_m(\phi 5mm)}{\eta_m(Full)}$ (%)	4.0	4.7	5.7	6.5	11





# PWO Radiation Damage




No damage in scintillation mechanism

No damage in resolution if light attenuation length > 1 m

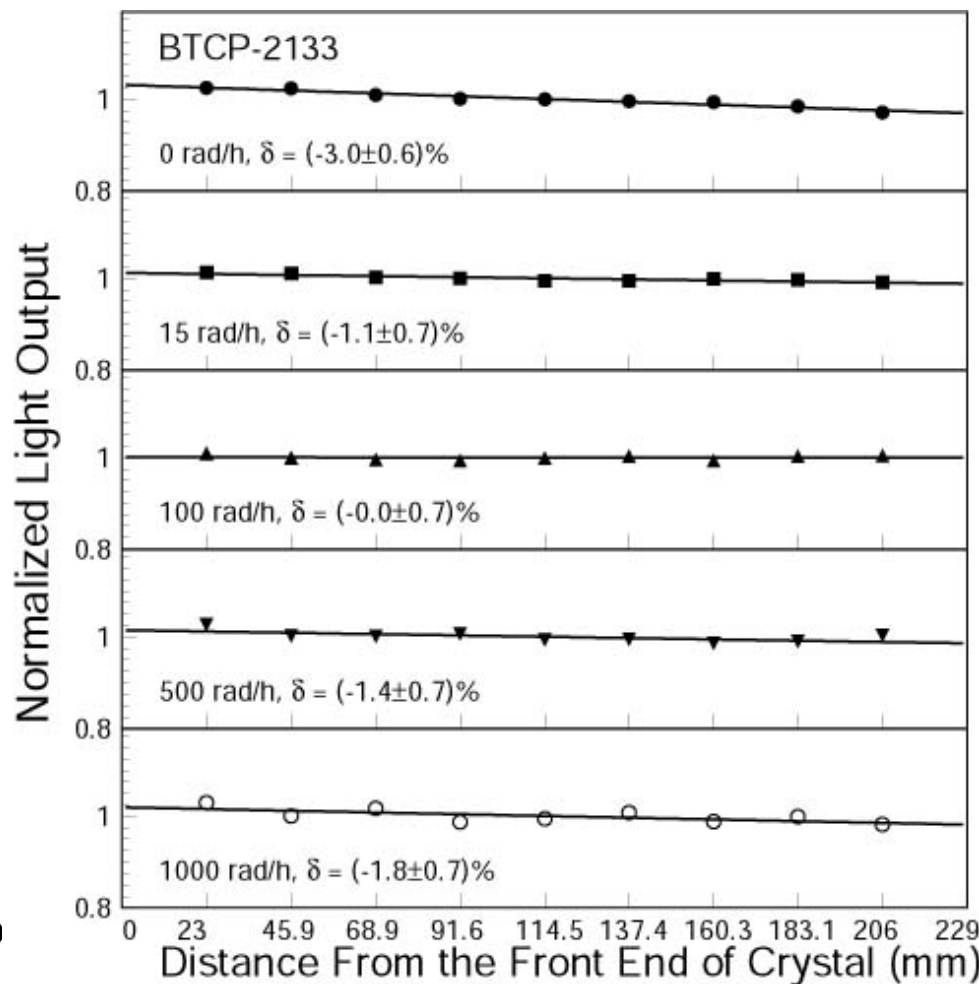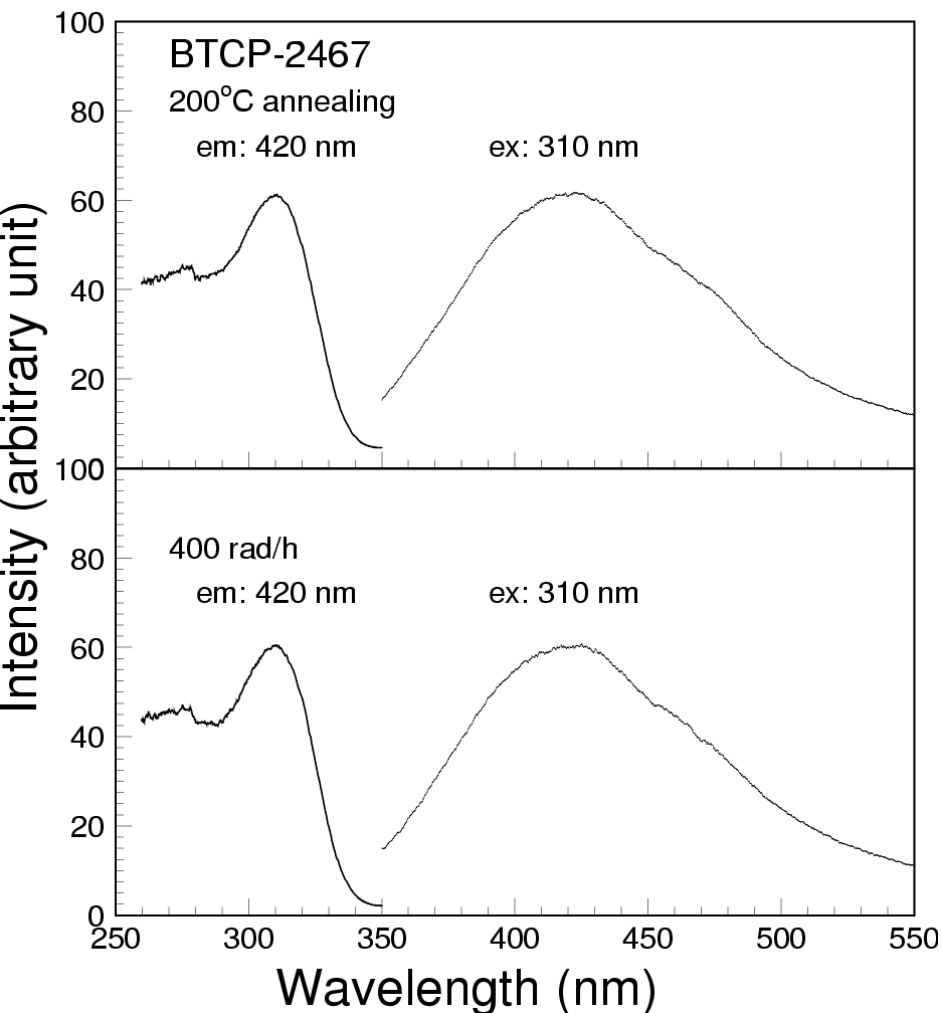



# Dose Rate Dependence




IEEE Trans. Nucl. Sci., Vol. 44 (1997) 468-476

$$dD = \sum_{i=1}^n \{-a_i D_i dt + (D_i^{all} - D_i) b_i R dt\}$$

$$D = \sum_{i=1}^n \left\{ \frac{b_i R D_i^{all}}{a_i + b_i R} [1 - e^{-(a_i + b_i R)t}] + D_i^0 e^{-(a_i + b_i R)t} \right\}$$


- $D_i$ : color center density in units of  $m^{-1}$ ;
- $D_i^0$ : initial color center density;
- $D_i^{all}$  is the total density of trap related to the color center in the crystal;
- $a_i$ : recovery constant in units of  $hr^{-1}$ ;
- $b_i$ : damage constant in units of  $kRad^{-1}$ ;
- $R$ : the radiation dose rate in units of  $kRad/hr$ .

$$D_{eq} = \sum_{i=1}^n \frac{b_i R D_i^{all}}{a_i + b_i R}$$

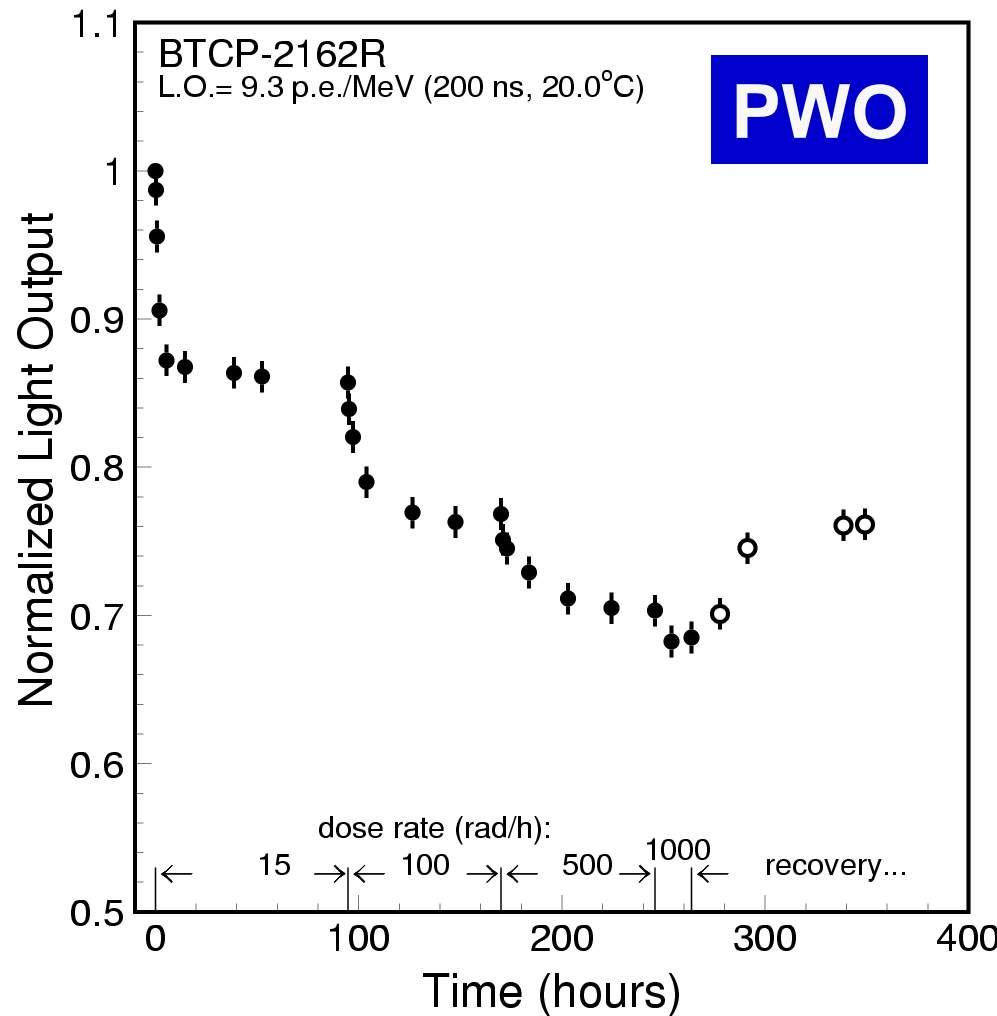





# No Dose Rate Dependence



No/slow recovery: no/less dose rate dependence


**BaF<sub>2</sub>**

**CsI(Tl)**

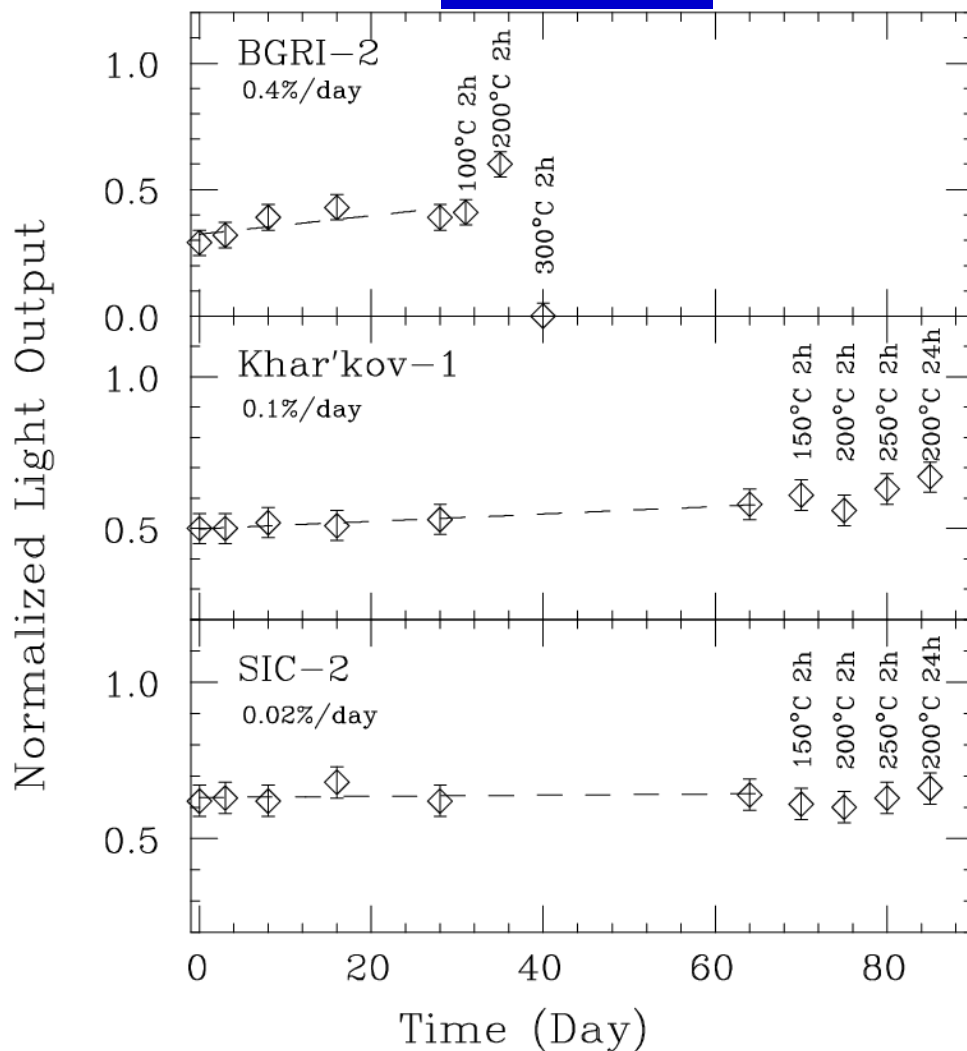
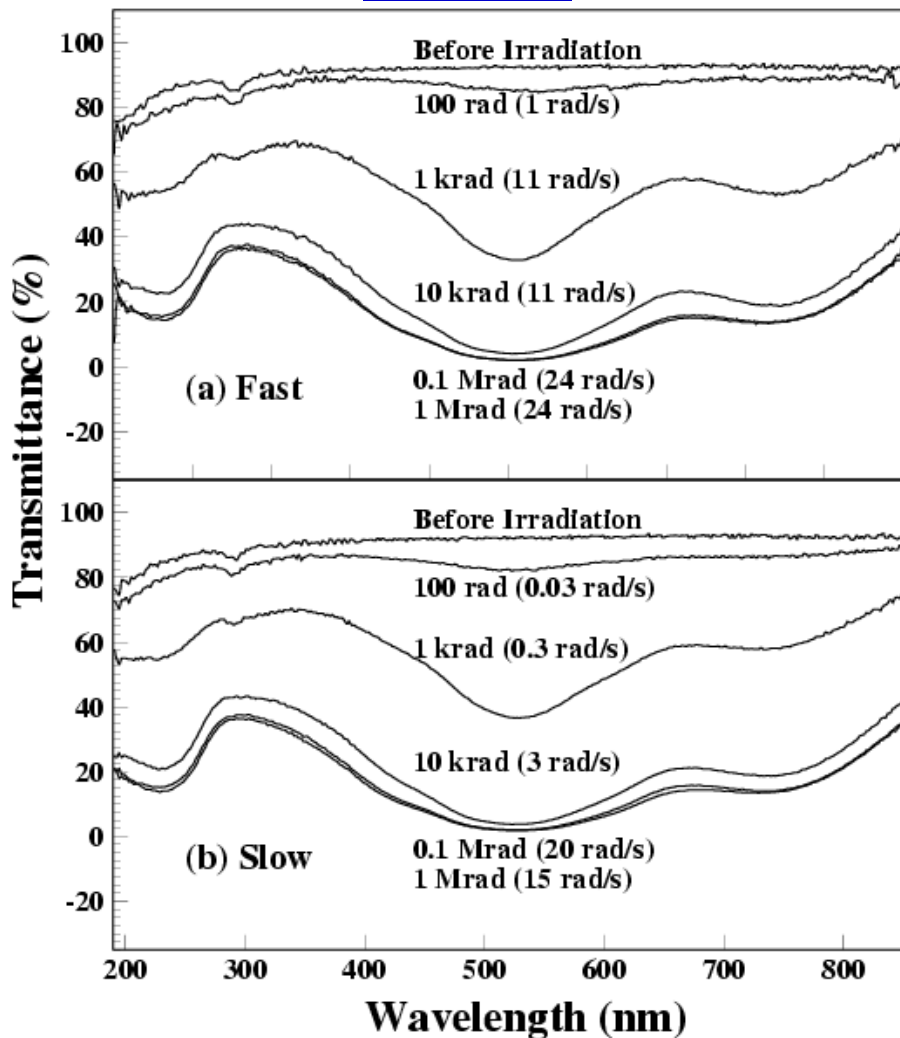




# Radiation Induced Phosphorescence




Phosphorescence peaked at 430 nm  
with decay time constant of 2.5 h observed

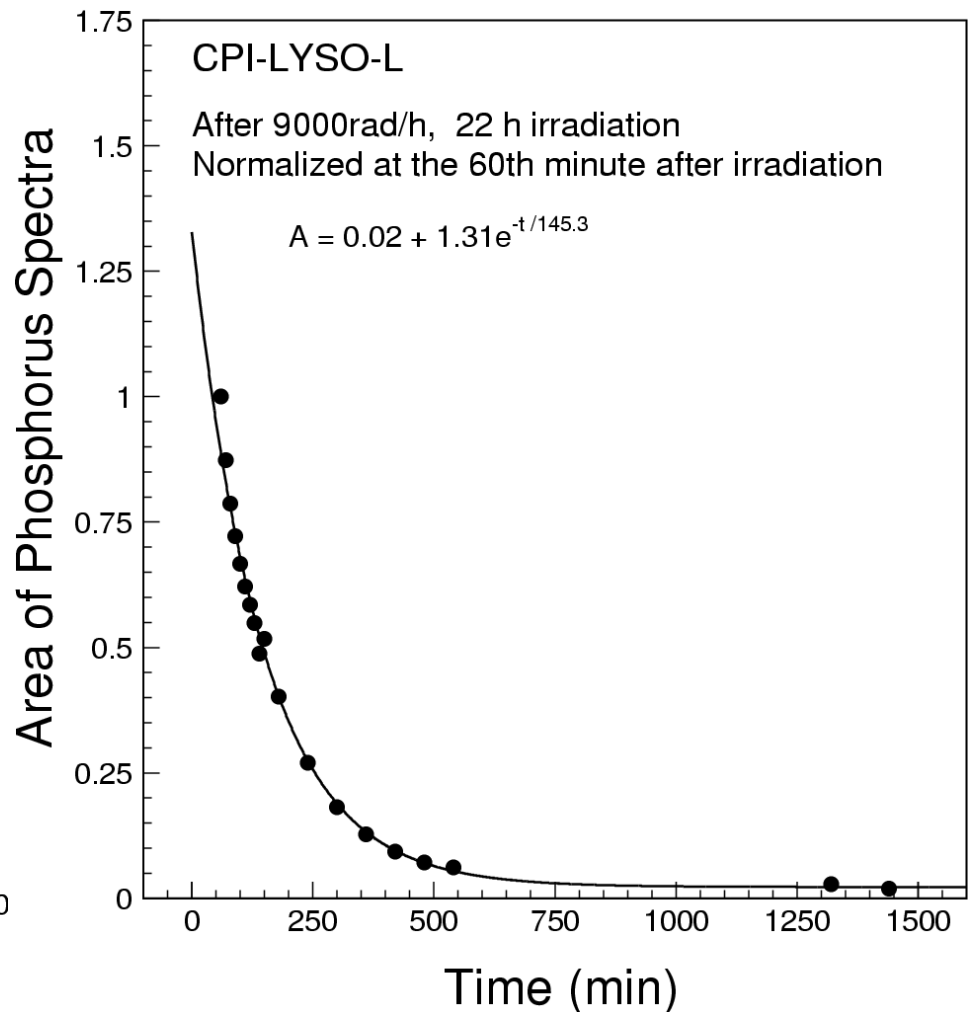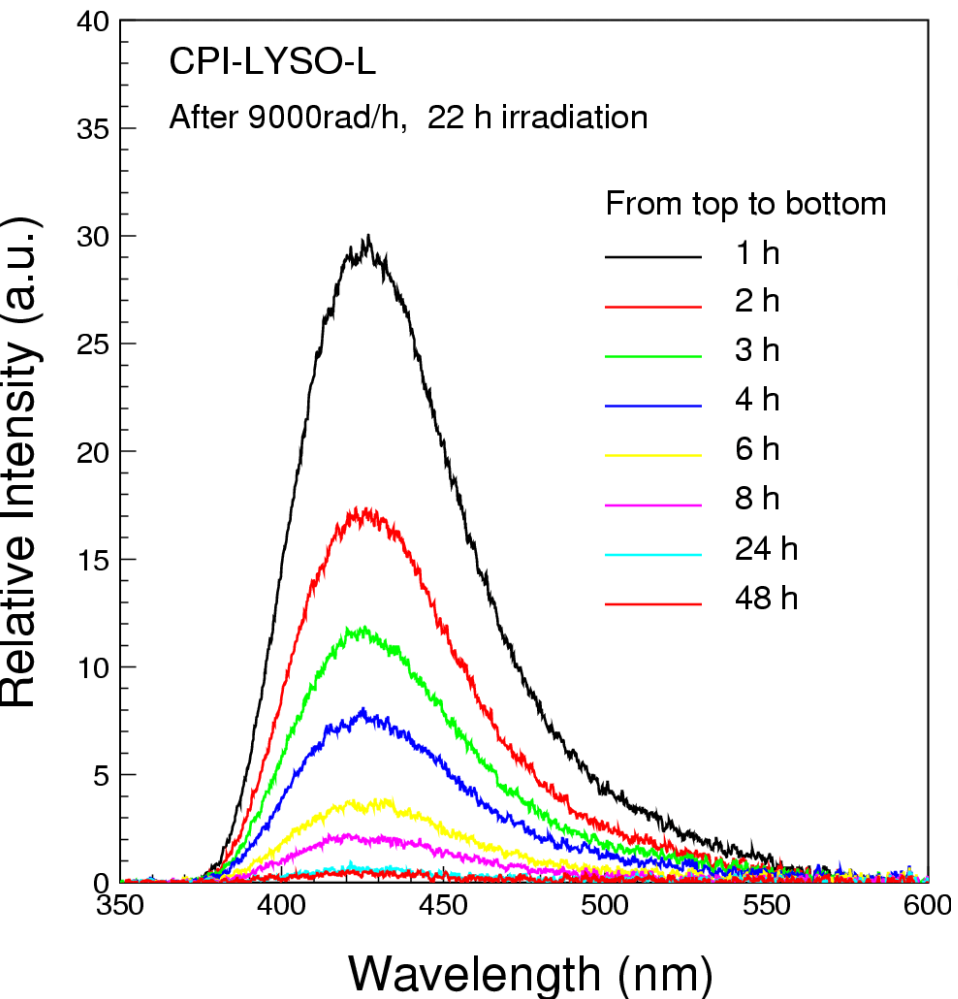




# $\gamma$ -ray Induced Readout Noise



Sample ID	L.Y. p.e./MeV	F $\mu$ A/rad/h	$Q_{15 \text{ rad/h}}$ p.e.	$Q_{500 \text{ rad/h}}$ p.e.	$\sigma_{15 \text{ rad/h}}$ MeV	$\sigma_{500 \text{ rad/h}}$ MeV
CPI	1,480	41	$6.98 \times 10^4$	$2.33 \times 10^6$	0.18	1.03
SG	1,580	42	$7.15 \times 10^4$	$2.38 \times 10^6$	0.17	0.97

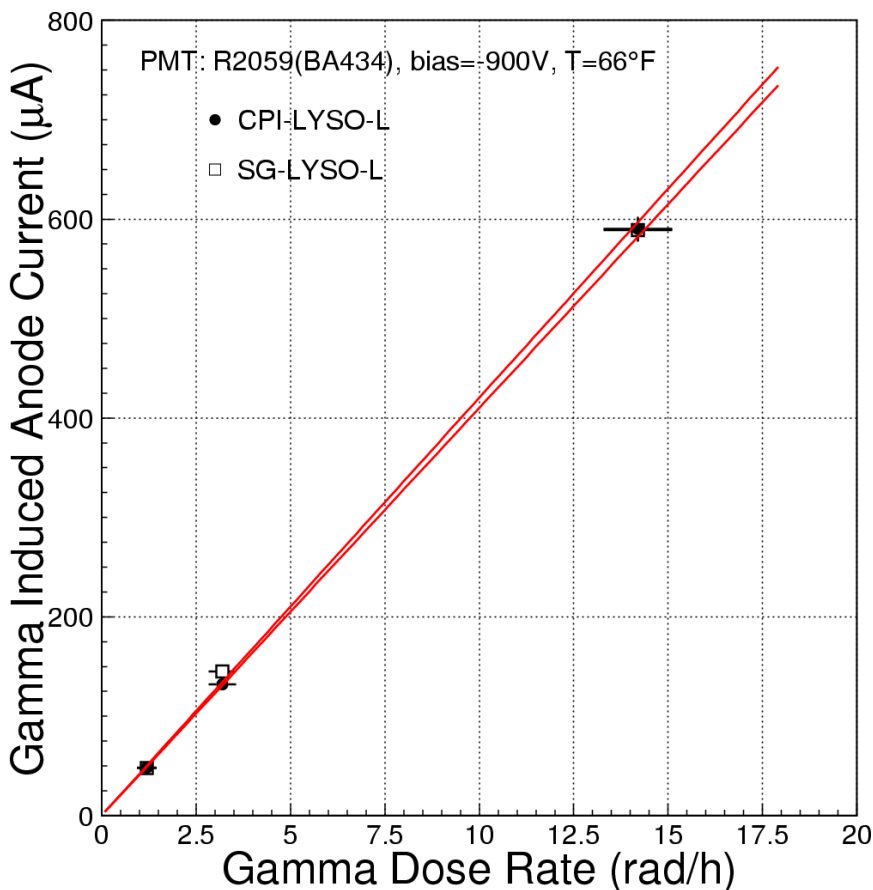

$\gamma$ -ray induced PMT anode current can be converted to the photoelectron numbers ( $Q$ ) integrated in 100 ns gate. Its statistical fluctuation contributes to the readout noise ( $\sigma$ ).