



---

# Ultrafast Inorganic Scintillators for Future HEP and Imaging Applications

**Ren-Yuan Zhu**

**California Institute of Technology**

March 14, 2023



# Inorganic Scintillators for HEP




## Crystal Calorimetry Physics

- Precision photons and electrons enhance HEP discovery potential.
- Crystal performance well understood:
  - Best possible energy and position resolution;
  - Good  $e/\gamma$  identification and reconstruction efficiency;
  - Excellent jet mass resolution with dual readout.
- Challenges at future HEP Experiments:
  - Rad-hard LYSO:Ce/LuAG:Ce for HL-LHC and FCC-hh;
  - Ultrafast BaF<sub>2</sub>:Y/Lu<sub>2</sub>O<sub>3</sub>:Yb to break the ps timing barrier and for ultrafast calorimetry;
  - Cost-effective crystals for the proposed Higgs factory.


Charmonium system observed by CB through Inclusive photons

CB NaI(Tl)

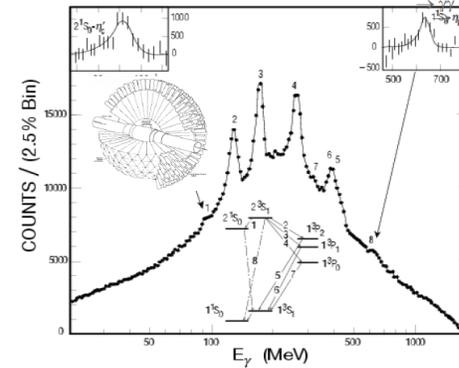

Higgs ->  $\gamma\gamma$  by CMS through reconstructing photon pairs

CMS PWO



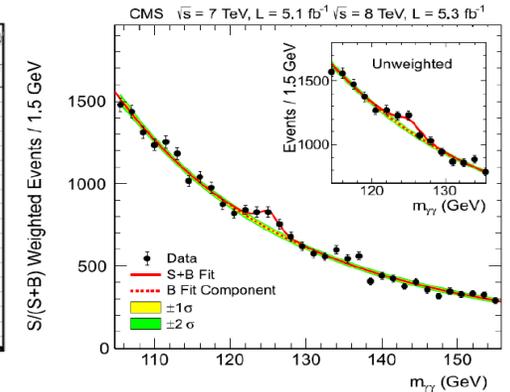


## LYSO:Ce Crystals for CMS BTL

NIMA 824 (2016) 726-728

IEEE TNS 64 (2017) 665-672, 65 (2018) 1018-1024

IEEE TNS 67 (2020) 1086-1092

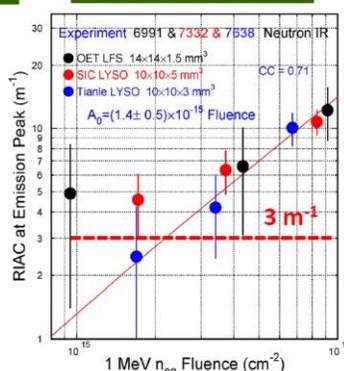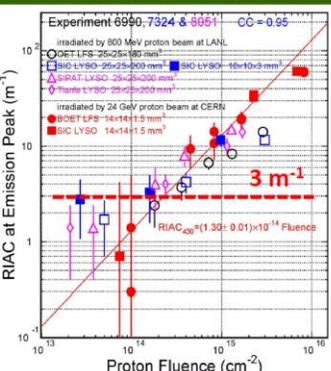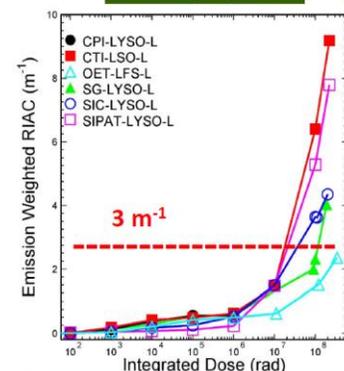

arXiv: 2203.06731 and arXiv: 2203.06788

Crystals damaged by both proton and neutron. Damage by proton is larger than that from neutrons because of ionization energy loss in addition to displacement and nuclear breakup





# Inorganic Scintillators for Imaging

TNS 65 (2018) 2097; NIM A 940 (2019) 223; TNS 67 (2020) 1086

- Pixelized detector is standard in medical industry. Laser slicing & micropore provide excellent coverage and position resolution.
- Ultrafast scintillators are needed for GHz Hard X-Ray Imaging at Future FEL facilities.

Performance	Type I imager	Type II imager
X-ray energy	up to 30 keV	42-126 keV
Frame-rate/inter-frame time	0.5 GHz / 2 ns	3 GHz / 300 ps
Number of frames per burst	≥ 10	10 - 30
X-ray detection efficiency	above 50%	above 80%
Pixel size/pitch	≤ 300 μm	< 300 μm
Dynamic range	10 <sup>3</sup> X-ray Photons/pixel/frame	≥ 10 <sup>4</sup> X-ray Photons/pixel/frame
Pixel format	64 × 64 <sup>a</sup> (scalable to 1 Mpix)	1 Mpix

- Detection efficiency for hard X-ray requires bulk detector; 2 ns and 300 ps inter-frame time requires ultrafast sensor.

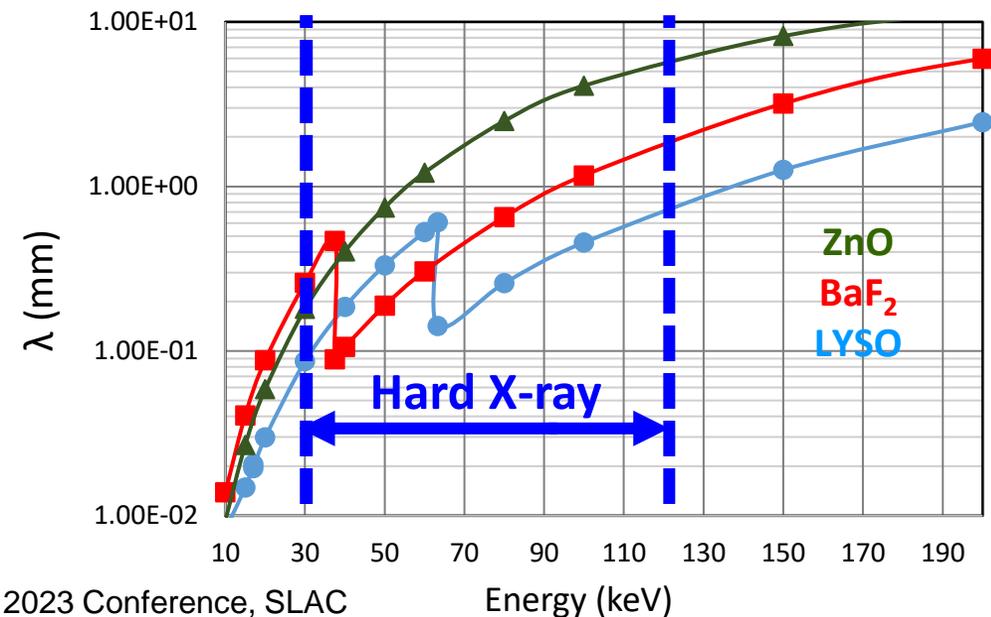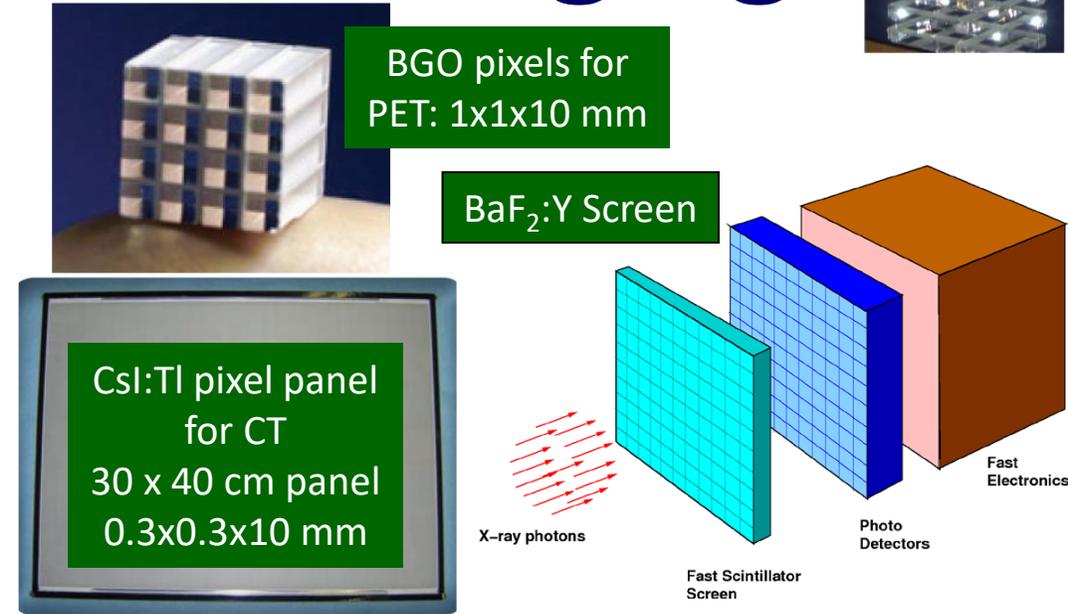



# 2019 DOE Basic Research Needs Study Priority Research Directions for Calorimetry



- Enhance calorimetry energy resolution for precision electroweak mass and missing-energy measurements;
- Advance calorimetry with spatial and timing resolution and radiation hardness to master high-rate environments;
- Develop **ultrafast** media to improve background rejection in calorimeters and particle identification detectors.

DOE 2019: <https://www.osti.gov/servlets/purl/1659761>

ECFA 2021: <https://cds.cern.ch/record/2784893>

Snowmass 2021: <https://arxiv.org/abs/2209.14111>

Fast/**ultrafast**, radiation hard and cost-effective inorganic scintillators






# Challenge: Radiation Damage at LHC



F. Ferri, Calor 2022, <https://indico.cern.ch/event/847884/timetable/#20220515>

[http://www.its.caltech.edu/~rzhu/talks/ryz\\_161028\\_PWO\\_mon.pdf](http://www.its.caltech.edu/~rzhu/talks/ryz_161028_PWO_mon.pdf)

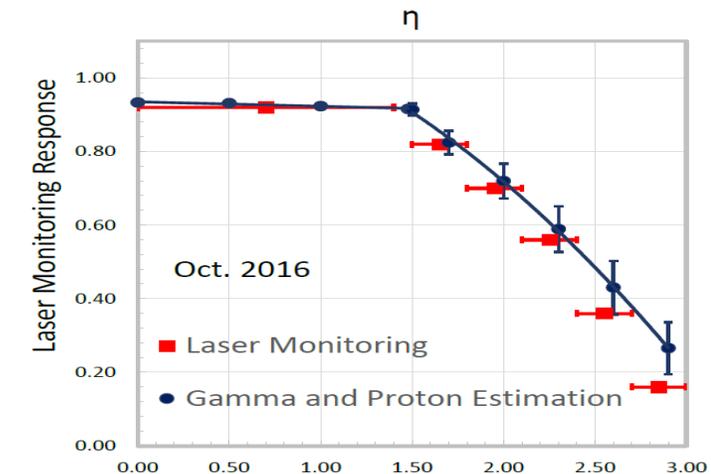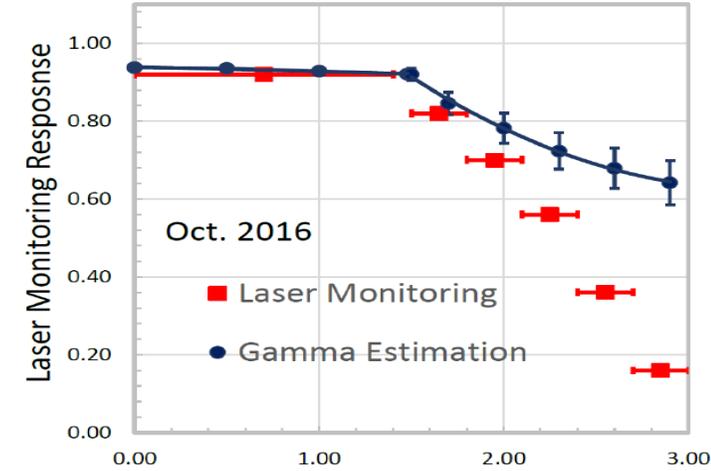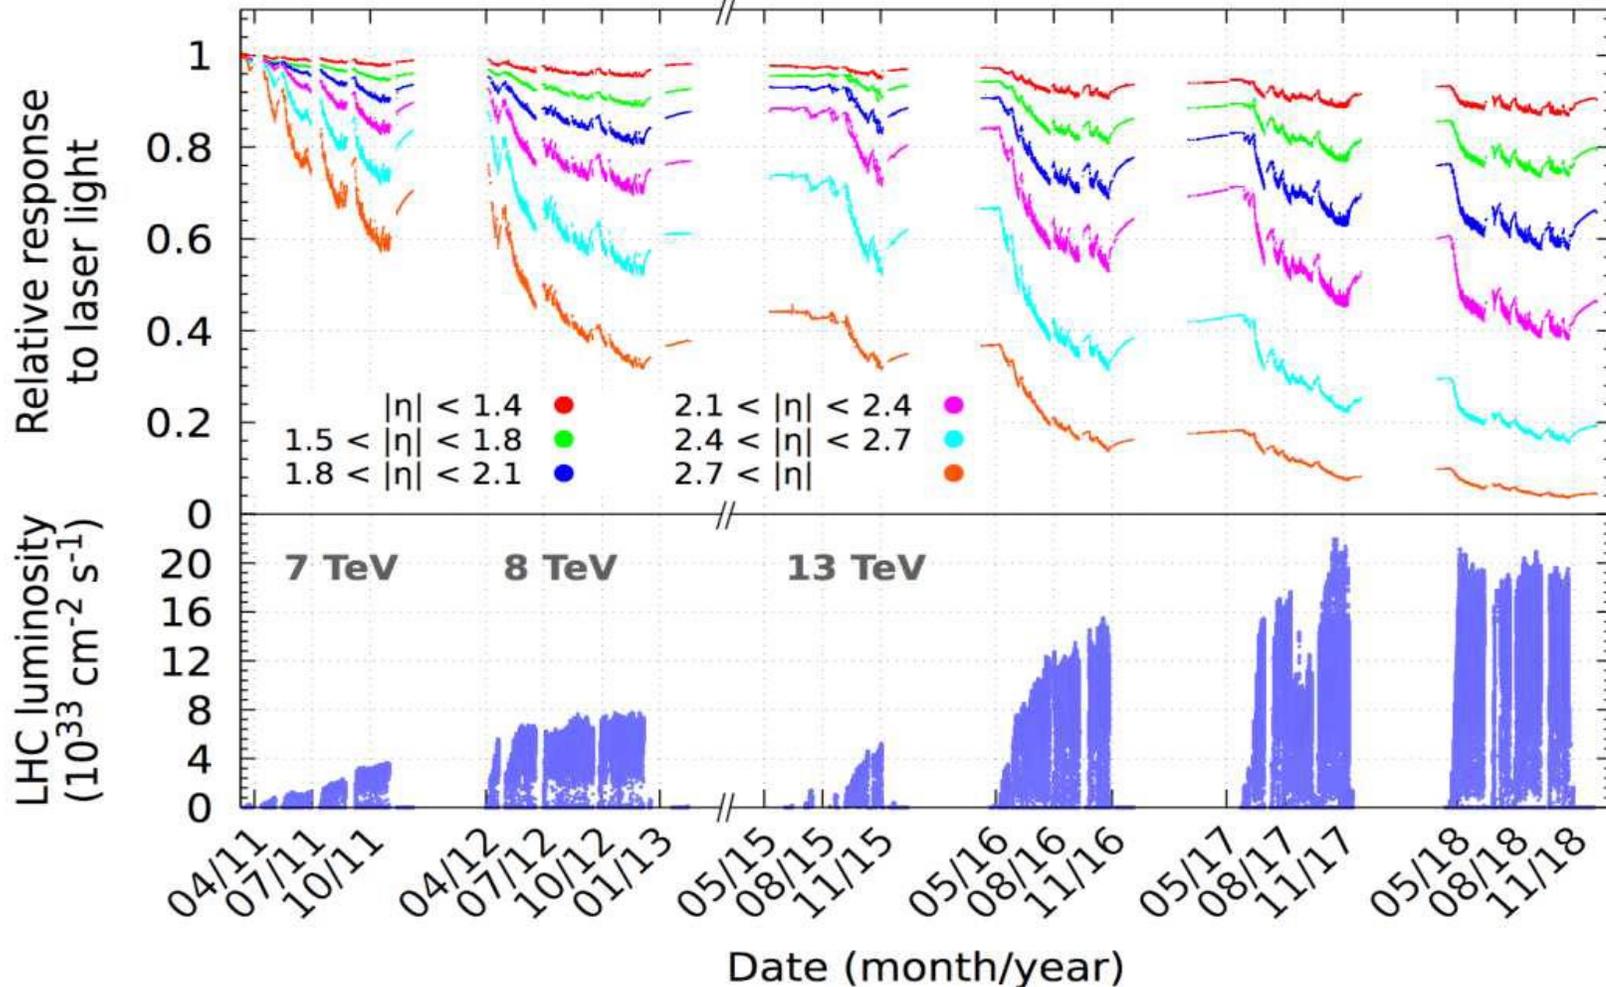

Use materials with monotonic damage:  $\text{BaF}_2$ , CsI,  $\text{LYSO:Ce}$ ,  $\text{LuAG:Ce}$

Neutron damage?



# Expected Radiation for CMS ECAL



CMS Barrel/Endcaps: 4.8/68 Mrad,  $2.5/21 \times 10^{13}$  p/cm<sup>2</sup> &  $3.2/24 \times 10^{14}$  n<sub>eq</sub>/cm<sup>2</sup>

CMS MTD	$\eta$	n <sub>eq</sub> (cm <sup>-2</sup> )	n <sub>eq</sub> Flux (cm <sup>-2</sup> s <sup>-1</sup> )	Proton (cm <sup>-2</sup> )	p Flux (cm <sup>-2</sup> s <sup>-1</sup> )	Dose (Mrad)	Dose rate (rad/h)
Barrel	0.00	2.5E+14	2.8E+06	2.2E+13	2.4E+05	2.7	108
Barrel	1.15	2.7E+14	3.0E+06	2.4E+13	2.6E+05	3.8	150
<b>Barrel</b>	<b>1.45</b>	<b>2.9E+14</b>	<b>3.2E+06</b>	<b>2.5E+13</b>	<b>2.8E+05</b>	<b>4.8</b>	<b>192</b>
Endcap	1.60	2.3E+14	2.5E+06	2.0E+13	2.2E+05	2.9	114
Endcap	2.00	4.5E+14	5.0E+06	3.9E+13	4.4E+05	7.5	300
Endcap	2.50	1.1E+15	1.3E+07	9.9E+13	1.1E+06	26	1020
<b>Endcap</b>	<b>3.00</b>	<b>2.4E+15</b>	<b>2.7E+07</b>	<b>2.1E+14</b>	<b>2.3E+06</b>	<b>68</b>	<b>2700</b>


Much higher at FCC-hh: up to 0.1/500 Grad and  $3/500 \times 10^{16}$  n<sub>eq</sub>/cm<sup>2</sup> at EMEC/EMF  
Aleksa *et al.*, Calorimeters for the FCC-hh CERN-FCCPHYS-2019-0003, Dec 23, 2019



# CMS Barrel Timing Detector for HL-LHC








To face challenge of pileup at HL-LHC by using 4D tracking in space and time

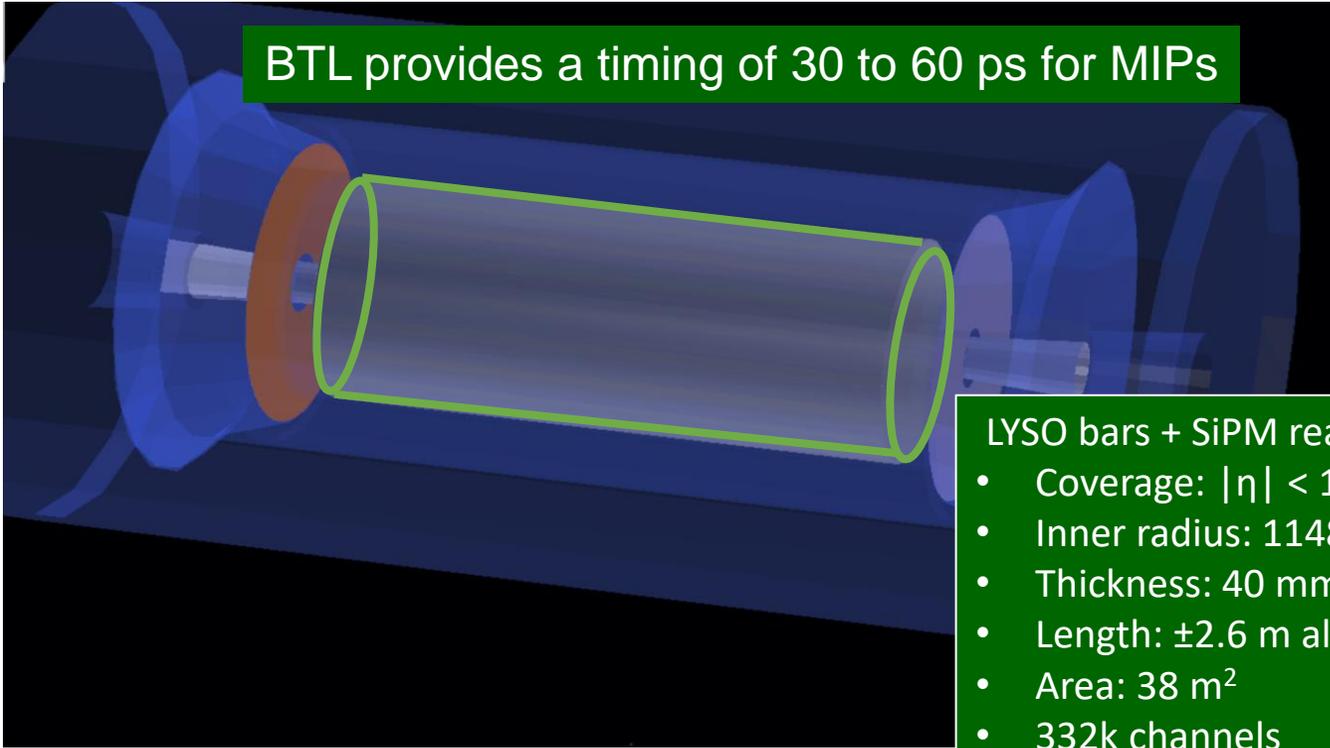

BTL provides a timing of 30 to 60 ps for MIPs

- LYSO bars + SiPM readout
- Coverage:  $|\eta| < 1.45$
- Inner radius: 1148 mm
- Thickness: 40 mm
- Length:  $\pm 2.6$  m along z
- Area: 38 m<sup>2</sup>
- 332k channels

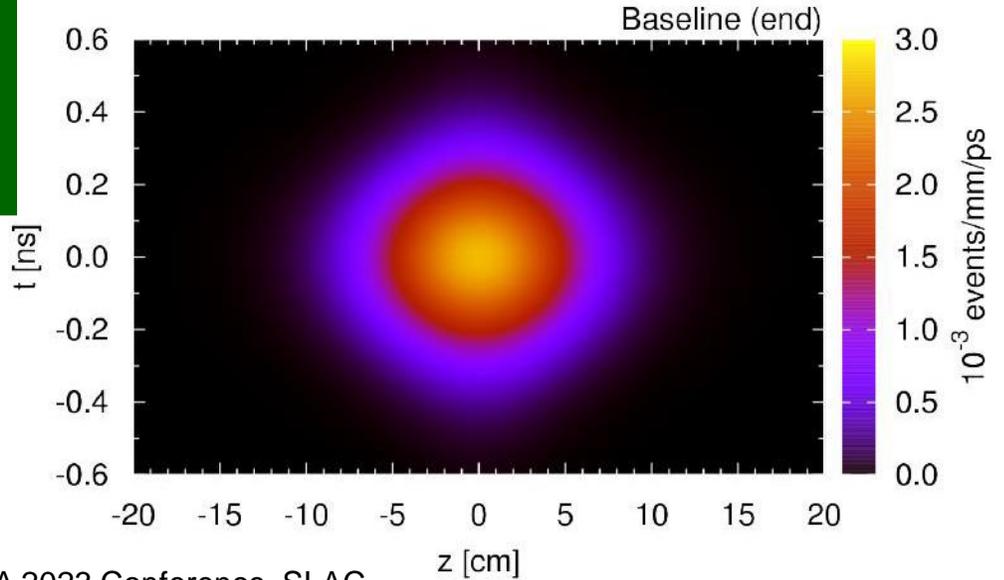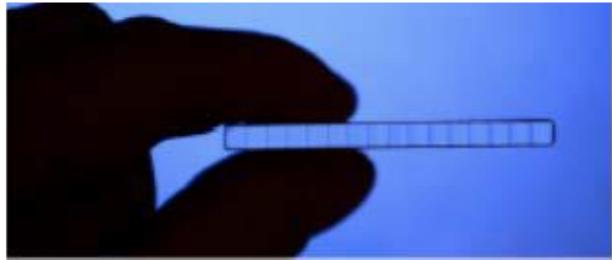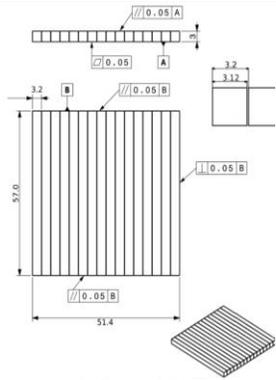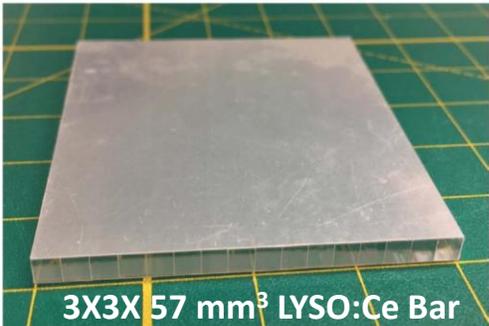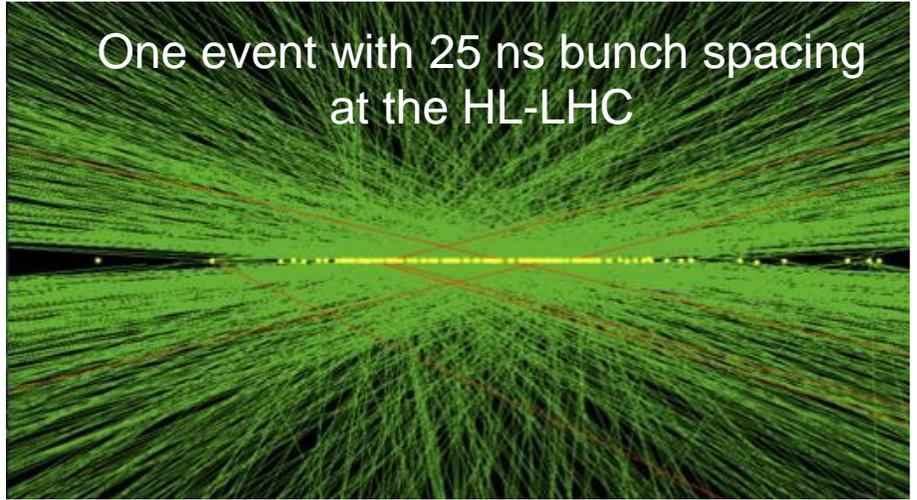






# LYSO:Ce Radiation Hardness



IEEE TNS 63 (2016) 612-619

CMS LYSO spec: RIAC < 3 m<sup>-1</sup> after 4.8 Mrad, 2.5 x 10<sup>13</sup> p/cm<sup>2</sup> and 3.2 x 10<sup>14</sup> n<sub>eq</sub>/cm<sup>2</sup>

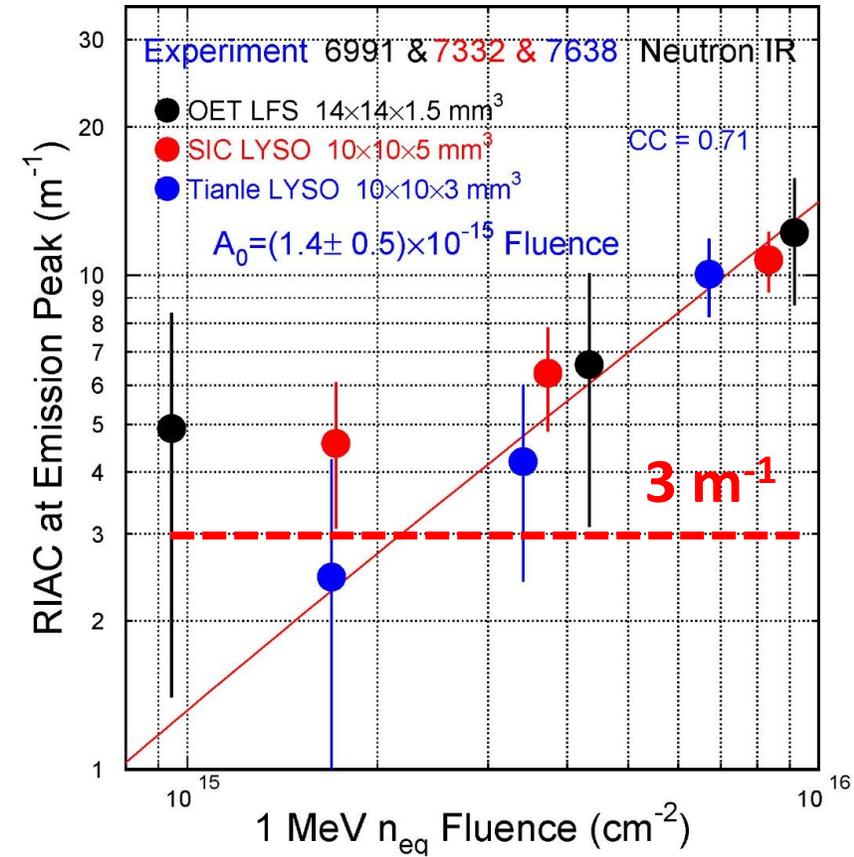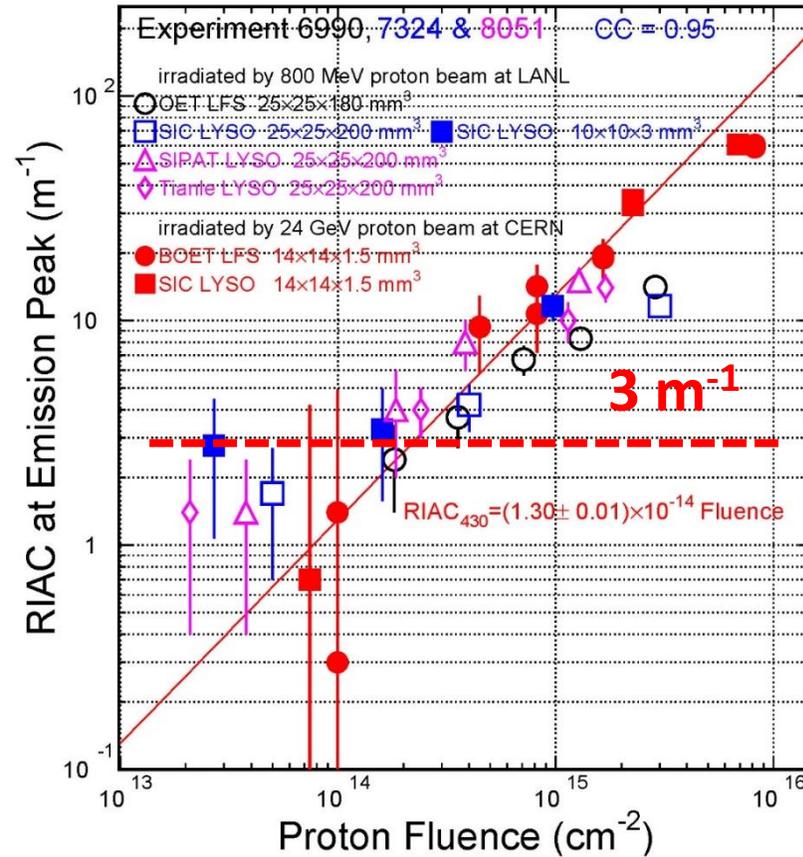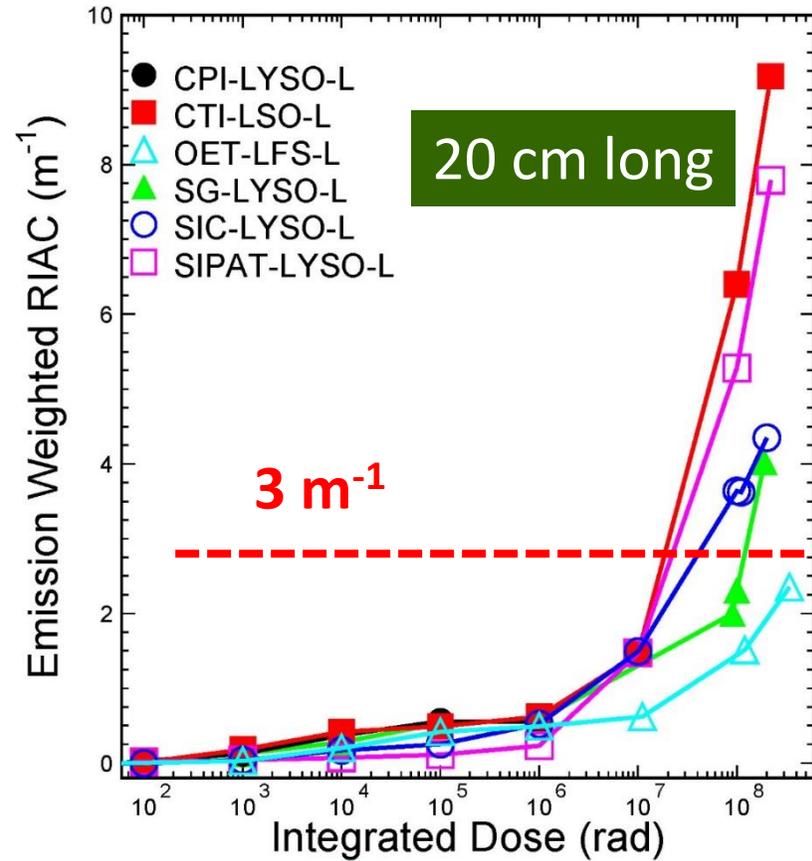

Damage induced by protons is larger than that from neutrons  
Due to ionization energy loss in addition to displacement and nuclear breakup






# LuAG:Ce Ceramics Radiation Hardness



IEEE TNS 69 (2022) 181-186


LuAG:Ce ceramics show a factor of two smaller RIAC values than LYSO:Ce up to  $6.7 \times 10^{15}$   $n_{eq}/cm^2$  and  $1.2 \times 10^{15}$   $p/cm^2$ , promising for FCC-hh

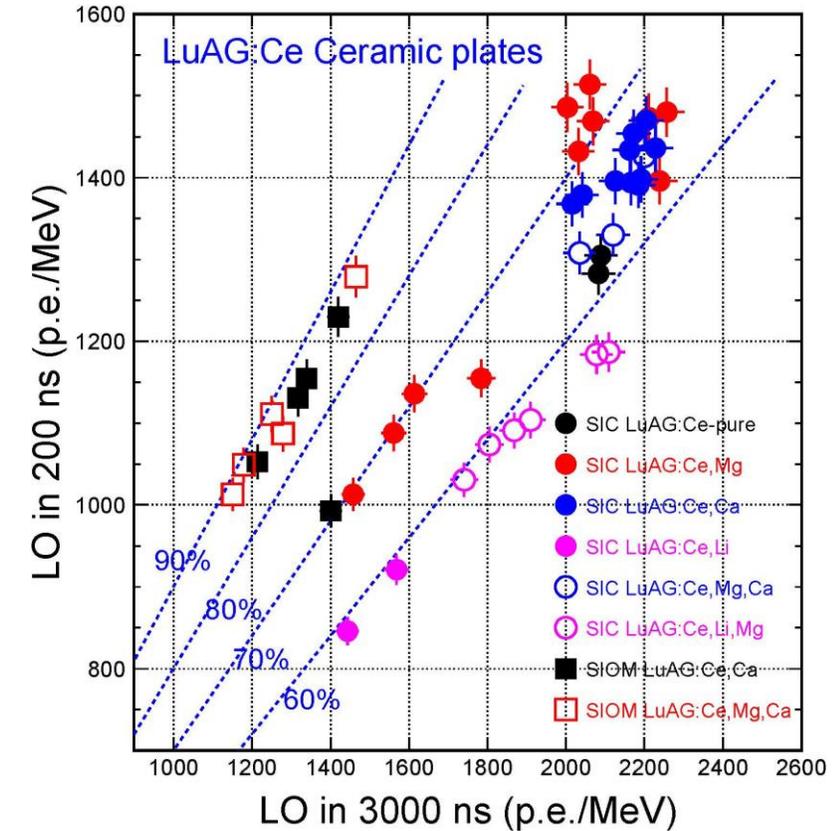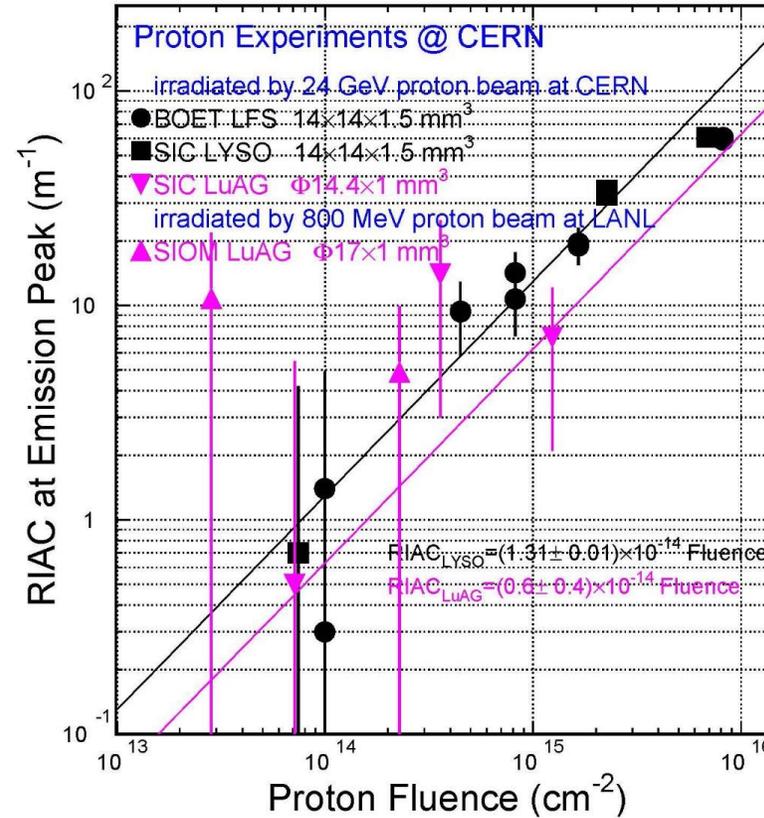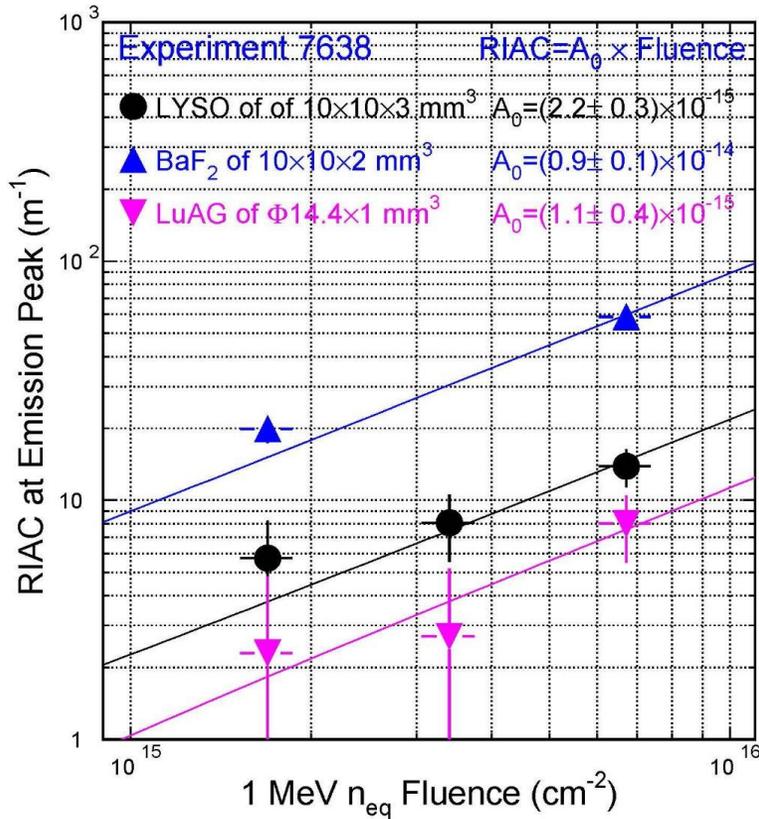

R&D on slow component suppression by Ca co-doping, and radiation hardness by  $\gamma/p/n$






# RADiCAL: LYSO/LuAG Shashlik ECAL

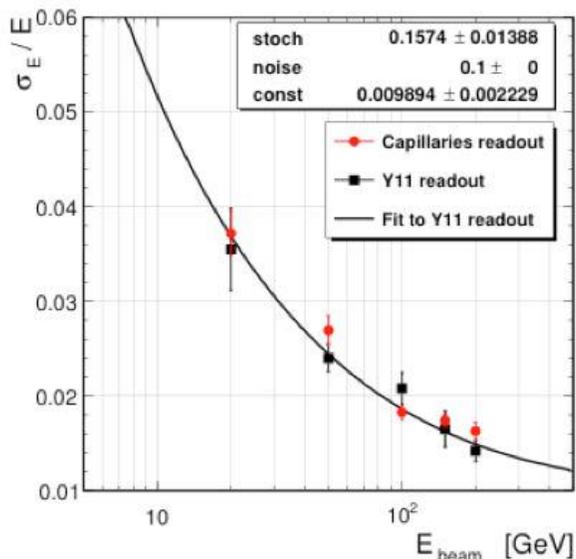


arXiv: 2203.12806 (N35-6)

**RADI**ation hard **CAL**orimetry  
 Reducing light path length to mitigate radiation damage effect  
 Using radiation hard materials:  
 LuAG:Ce ceramics excitation matches LYSO:Ce emission

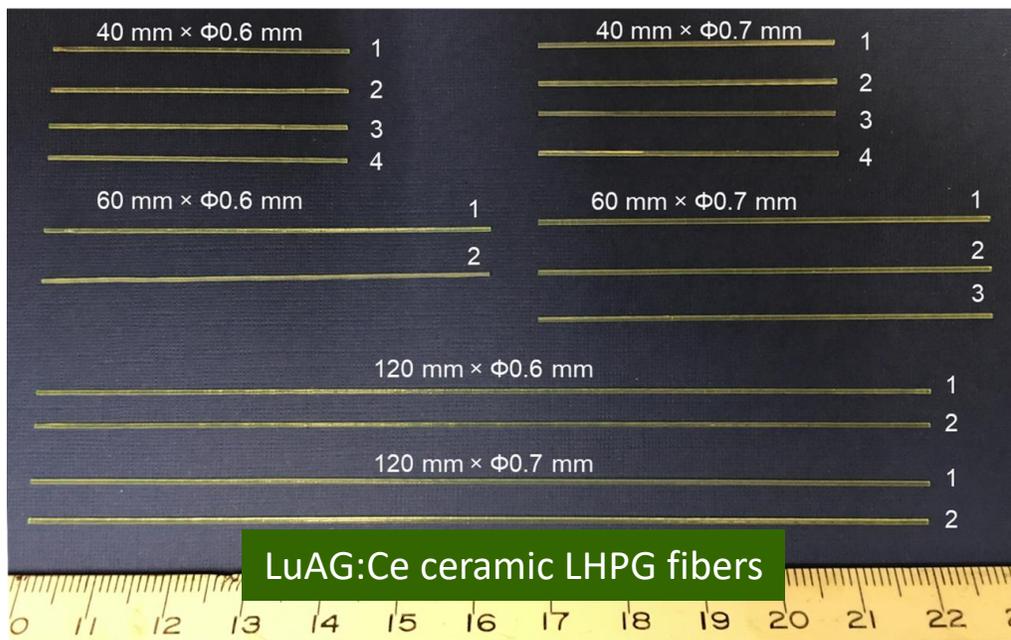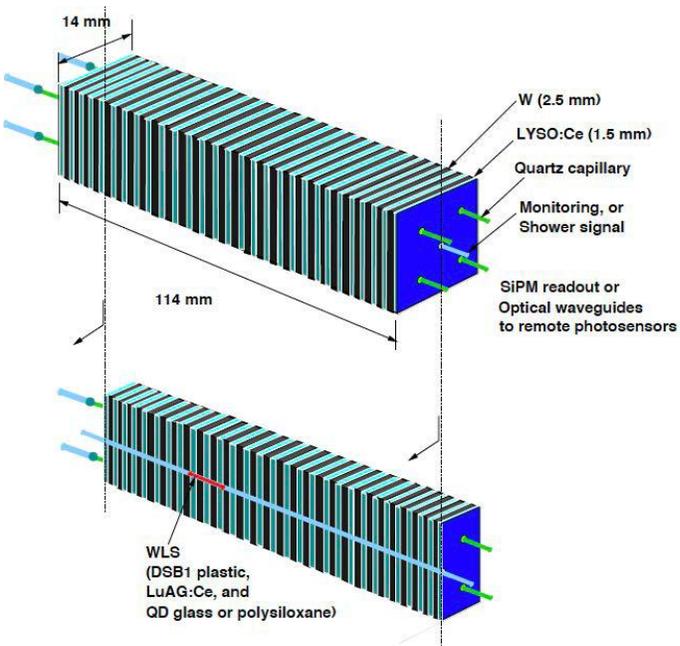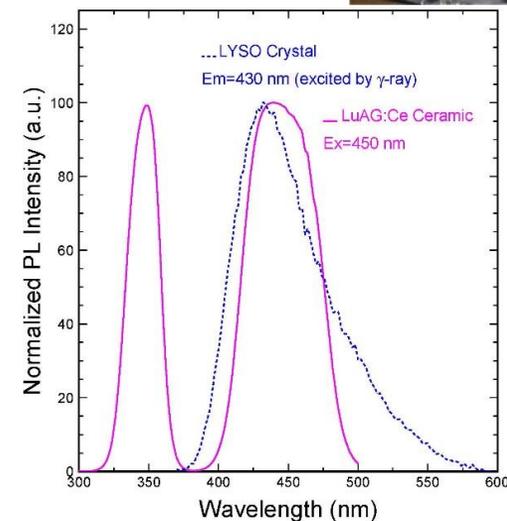


LuAG:Ce ceramic LHPG fibers


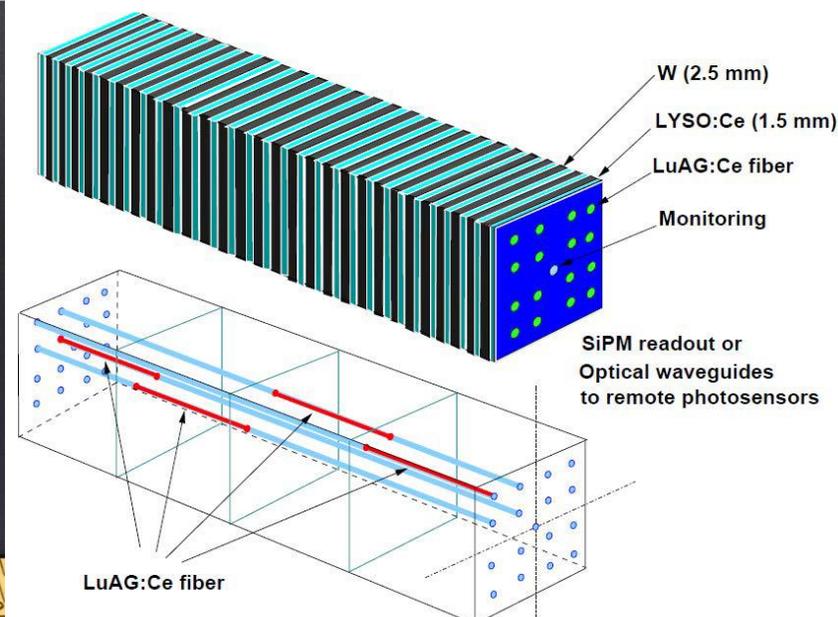




# LuAG:Ce Fiber Light Output and Uniformity

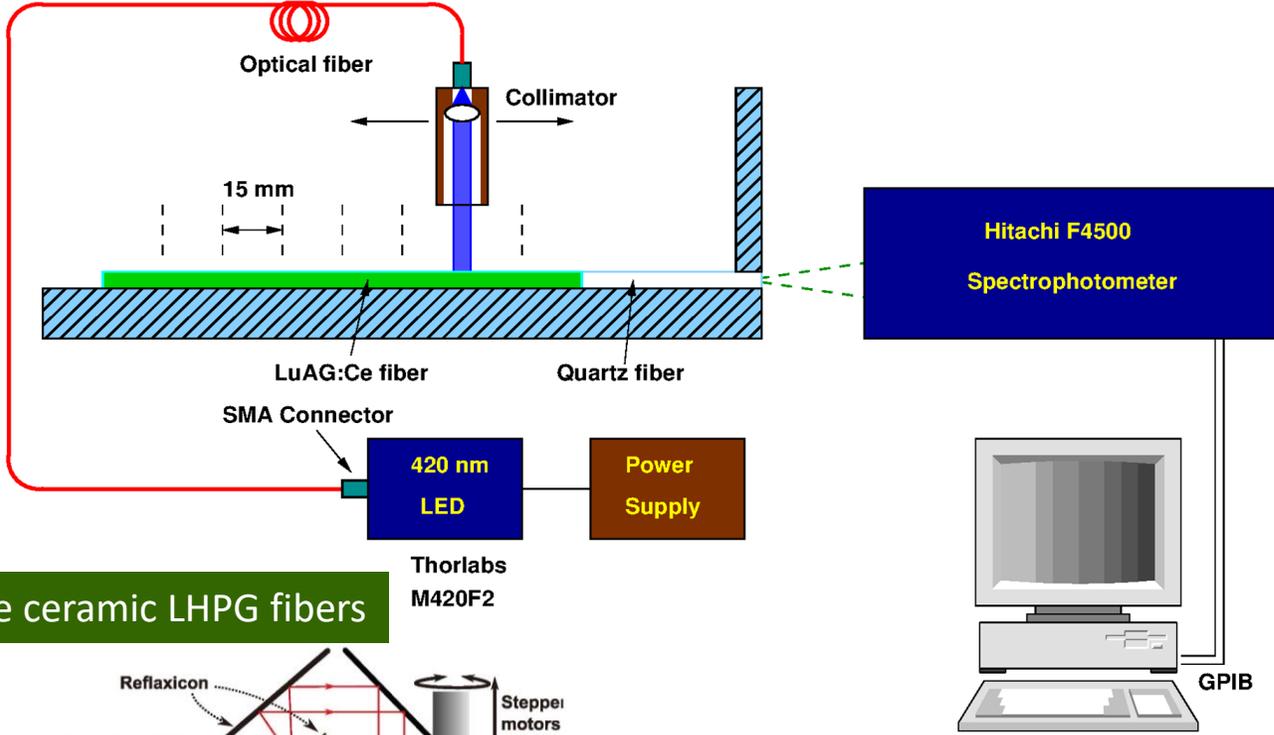

LuAG:Ce ceramic LHPG fibers

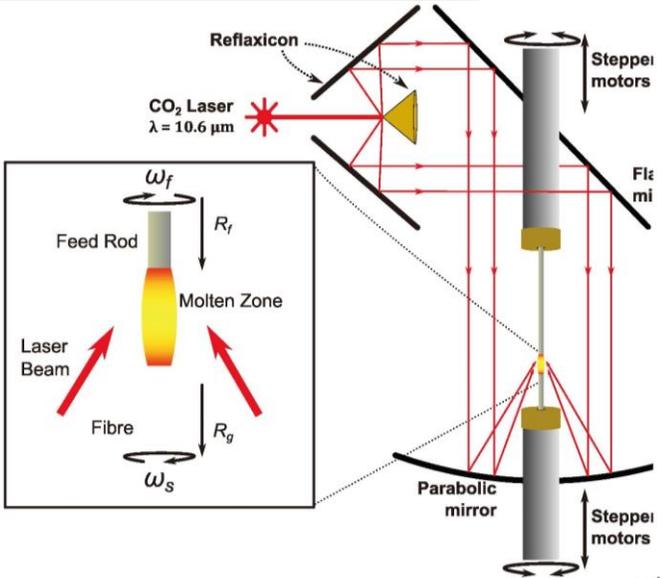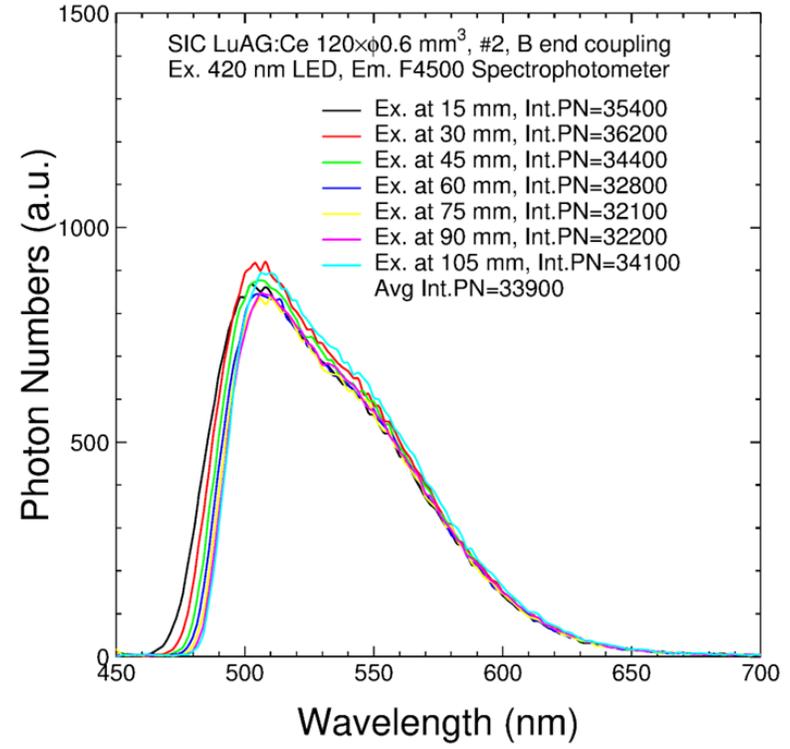

Excellent uniformity observed for  $\Phi 0.6 \times 120 \text{ mm}^3$  LuAG:Ce ceramic fibers excited by a 420 nm LED at different longitudinal location, with a solid coupling to a quartz fiber, mimicking its application in RADiCAL Calorimetry



# Ultrafast BaF<sub>2</sub>:Y Calorimeter for Mu2e-II




Use ultrafast material to mitigate pile-up

• Energy resolution	$\sigma < 5\%$ (FWHM/2.36) @ 100 MeV
• Time resolution	$\sigma < 500$ ps
• Position resolution	$\sigma < 10$ mm
• Radiation hardness	
• Crystals	1 kGy/yr and a total of $10^{12}$ n <sub>-1</sub> MeV equivalent/cm <sup>2</sup> total
• Photosensors	$3 \times 10^{11}$ n <sub>-1</sub> MeV equivalent/cm <sup>2</sup> total

Mu2e-I: 1,348 CsI of 34 x 34 x 200 mm<sup>3</sup>

CsI+SiPM

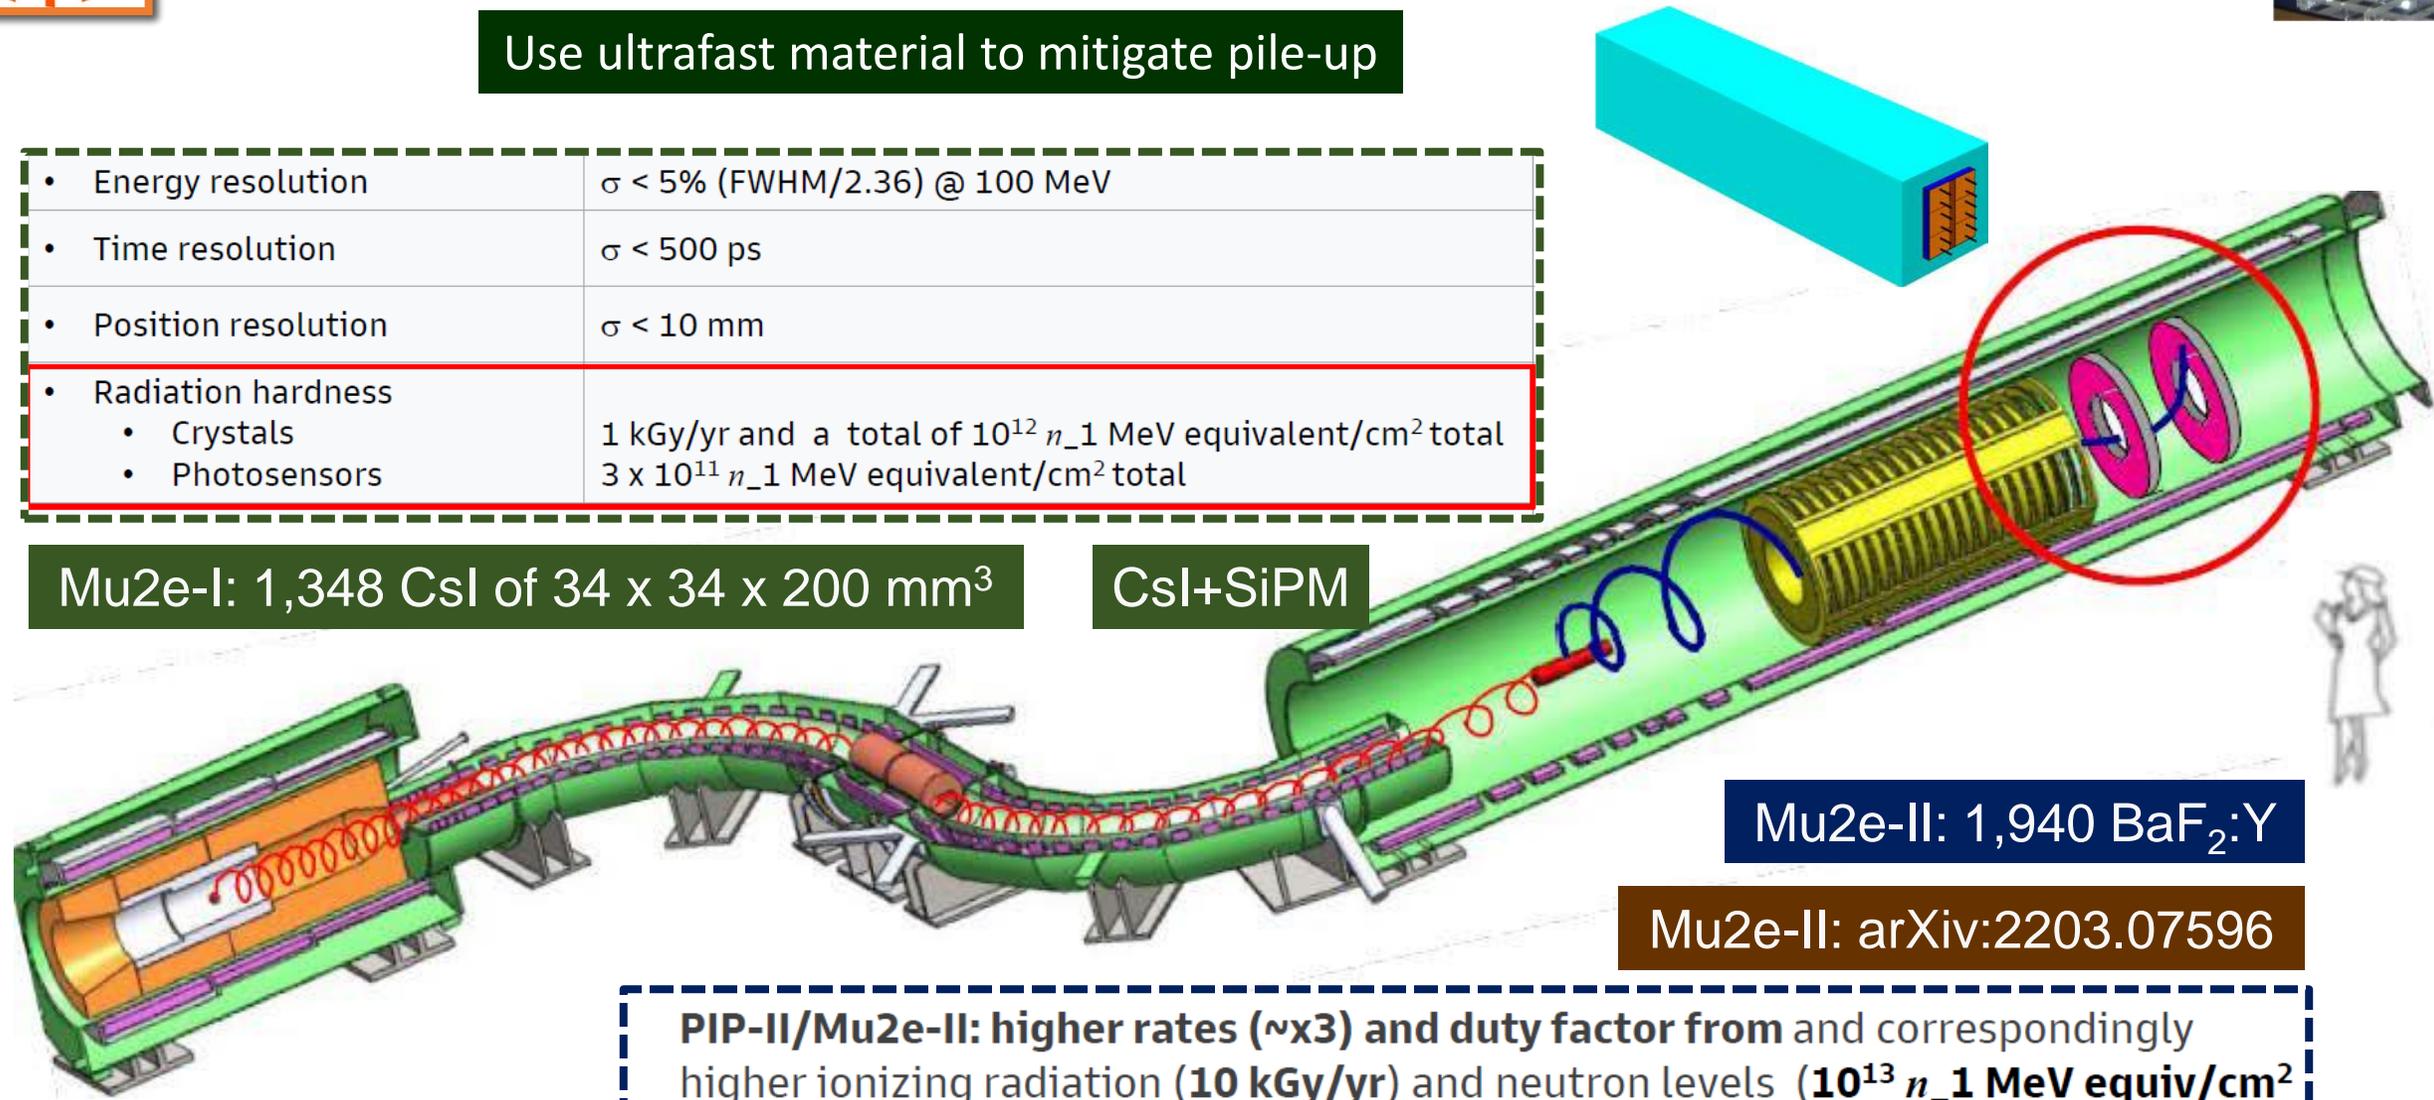

Mu2e-II: 1,940 BaF<sub>2</sub>:Y

Mu2e-II: arXiv:2203.07596

**PIP-II/Mu2e-II: higher rates (~x3) and duty factor from and correspondingly higher ionizing radiation (10 kGy/yr) and neutron levels (10<sup>13</sup> n<sub>-1</sub> MeV equiv/cm<sup>2</sup> total), which are particularly important at the inner radius of disk 1**



# Ultrafast and Radiation Hard BaF<sub>2</sub>









IEEE TNS NS 67, NO. 6 (2020) 1014-1019

NIMA 340 (1994) 442-457

BaF<sub>2</sub> has an ultrafast scintillation component @ 220 nm with **0.5 ns** decay time and a much larger slow component @ 300 nm with 600 ns decay time.  
Slow suppression may be achieved by rare earth doping, and/or solar-blind photo-detectors

BaF<sub>2</sub> shows saturated damage from 10 krad to 100 Mrad, indicating good radiation resistance against  $\gamma$ -rays  
BaF<sub>2</sub> also survives after proton irradiation up to  $9.7 \times 10^{14}$  p/cm<sup>2</sup>, and neutron irradiation up to  $8.3 \times 10^{15}$  n<sub>eq</sub>/cm<sup>2</sup>

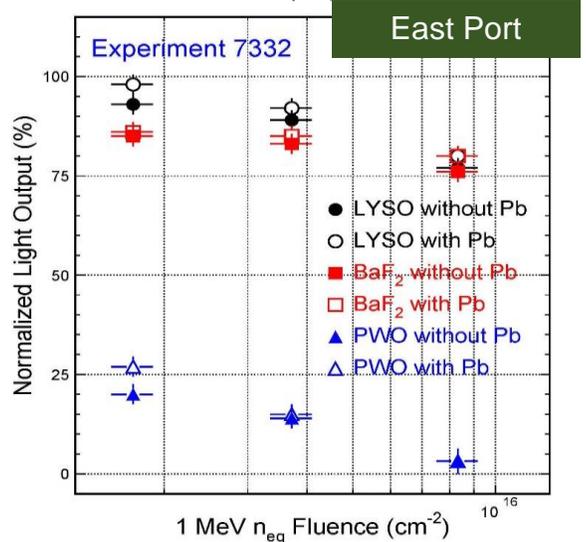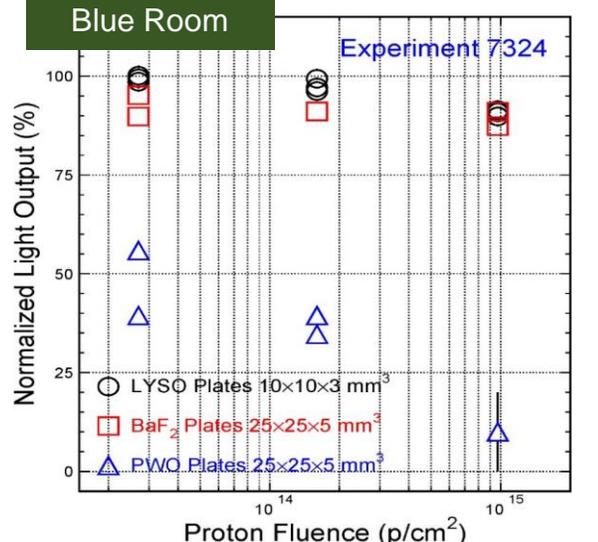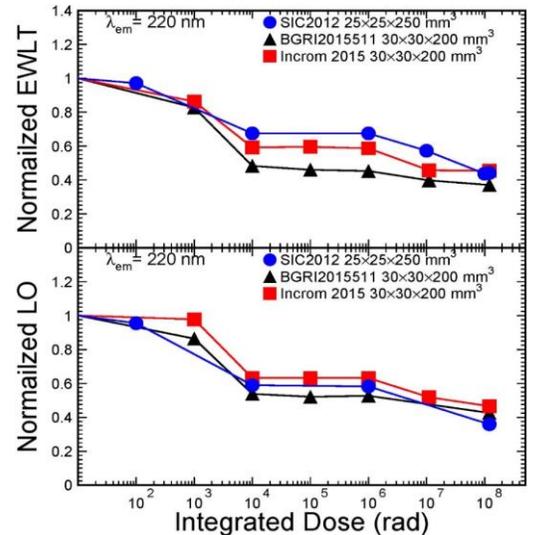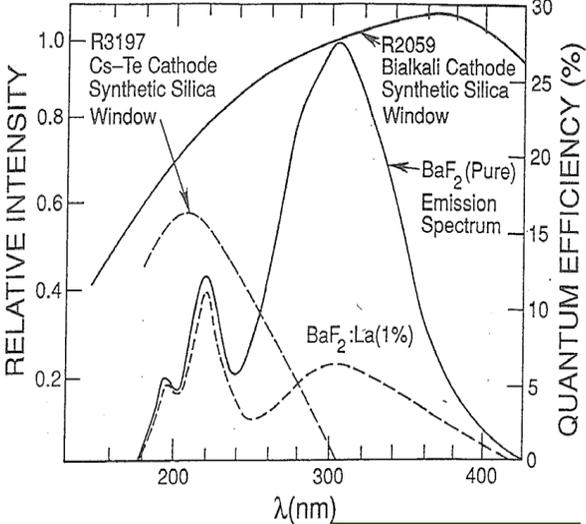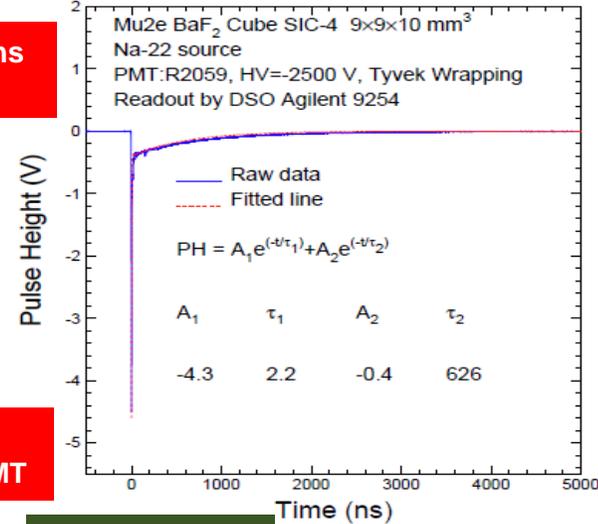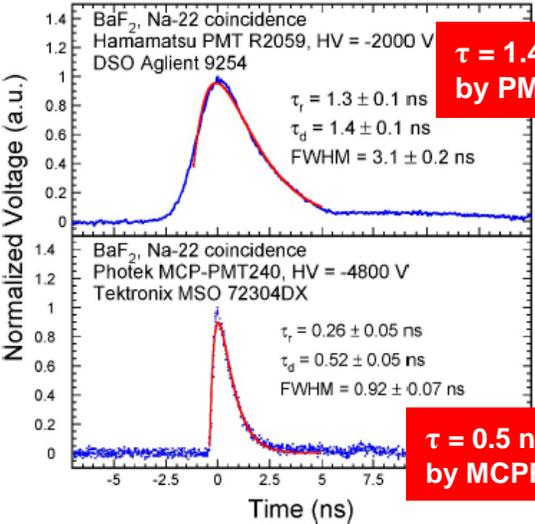

IEEE TNS 63 (2016) 612-619

IEEE TNS 65 (2018) 1086-1092








IEEE TNS 67 (2020) 1018-1024



# BaF<sub>2</sub>:Y for Calorimetry & Imaging



Increased F/S ratio observed in BGRI BaF<sub>2</sub>:Y crystals: Proc. SPIE 10392 (2017)

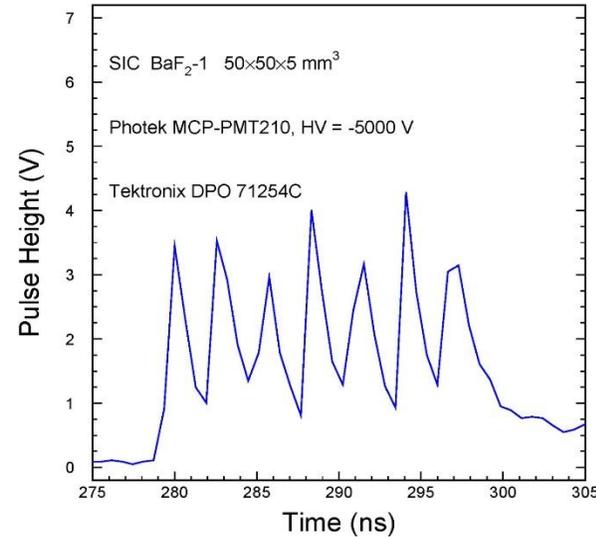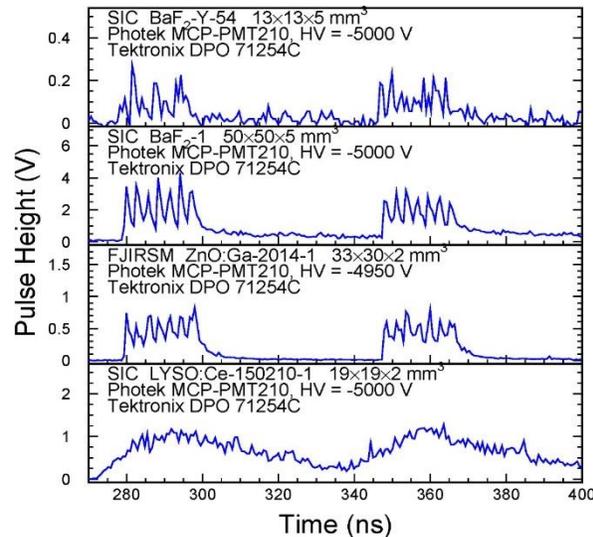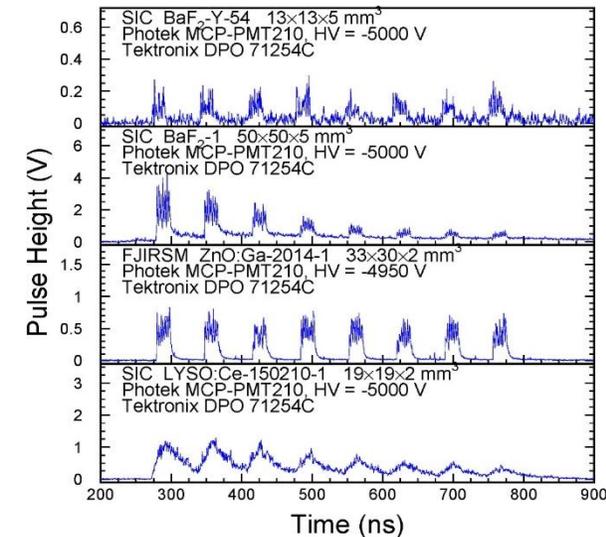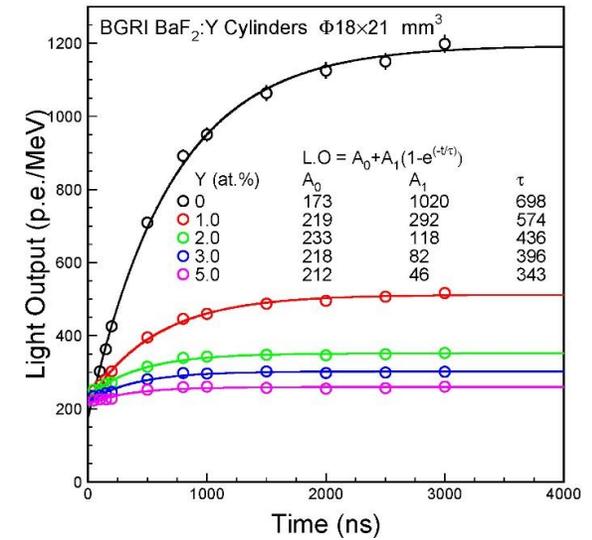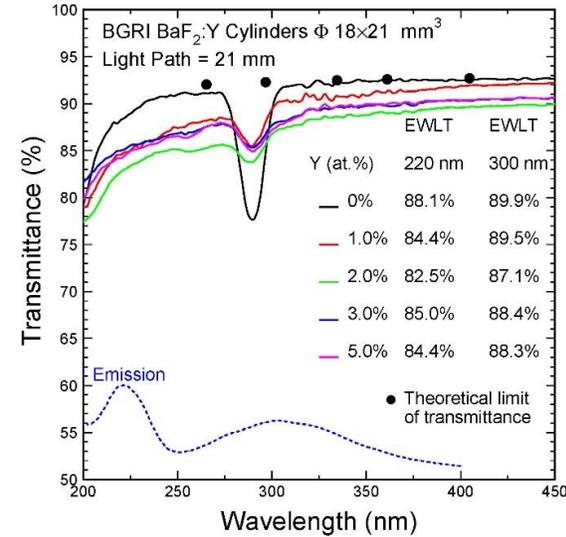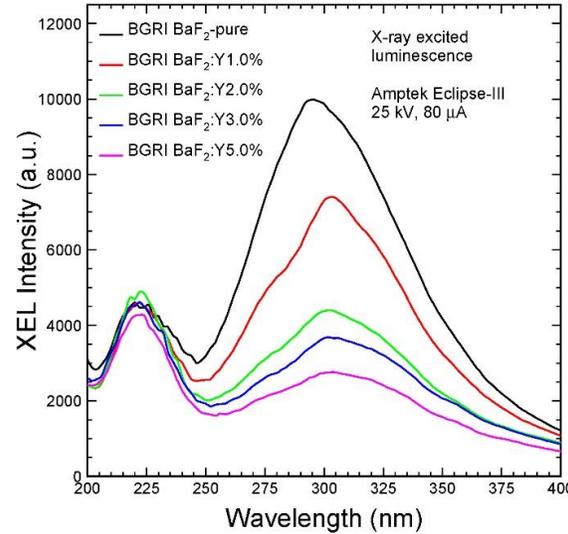
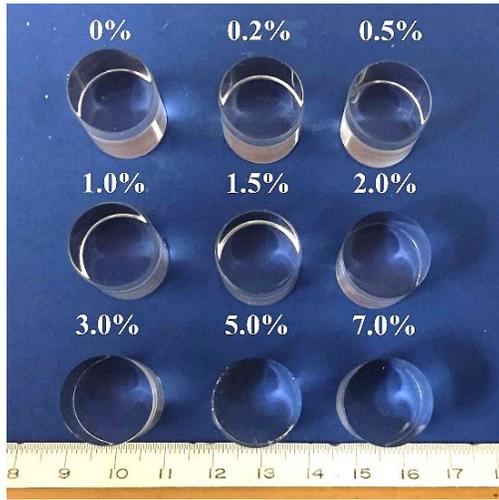


X-ray bunches with 2.83 ns spacing in septuplet are clearly resolved by ultrafast BaF<sub>2</sub>:Y and BaF<sub>2</sub> crystals: for GHz Hard X-ray Imaging NIMA 240 (2019) 223-239

# A Puzzle of Long Decay Observed at APS



NIM A 940 (2019) 223–229

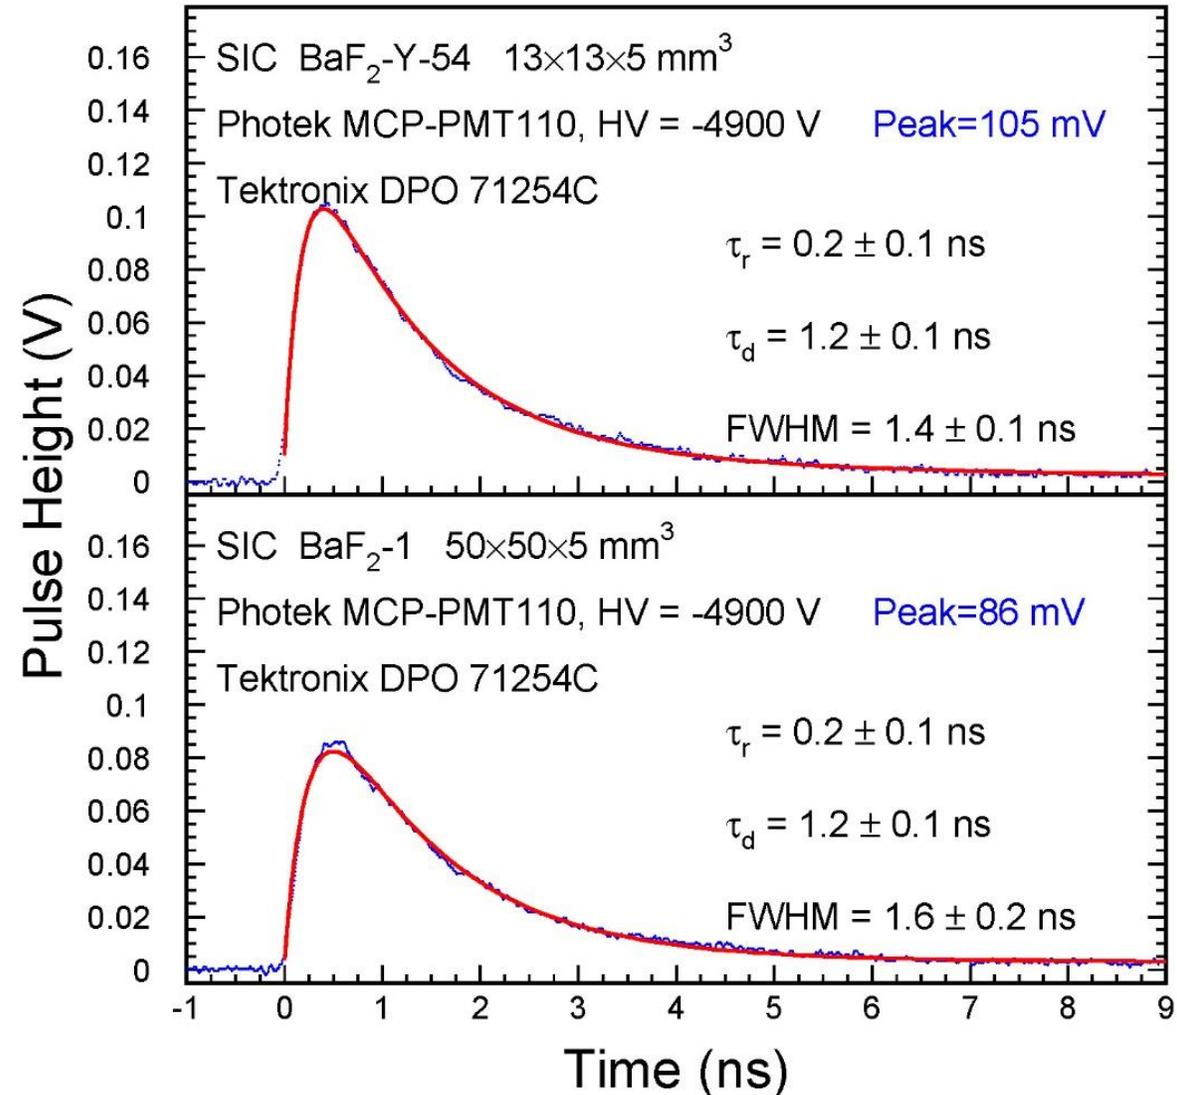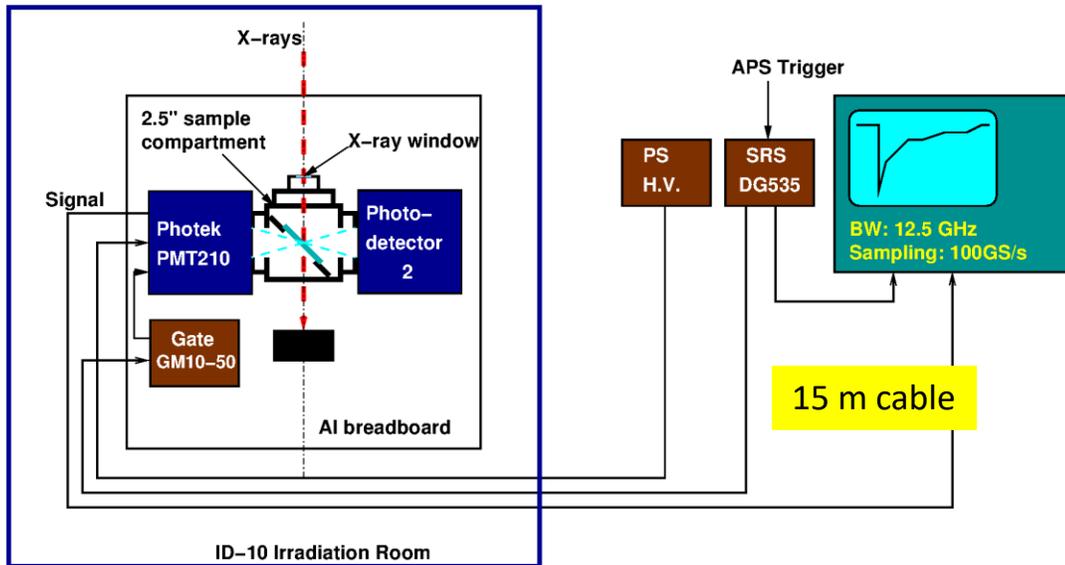


The decay time of BaF<sub>2</sub> measured at APS for septuplet X-ray bunches with 2.83 ns spacing is longer than 1 ns. This is suspected to be caused by the 15 m long cable used between the MCP-PMT and the MSO




# An MCP-PMT 240-Based Test Bench




## Na-22 Coincidence Trigger

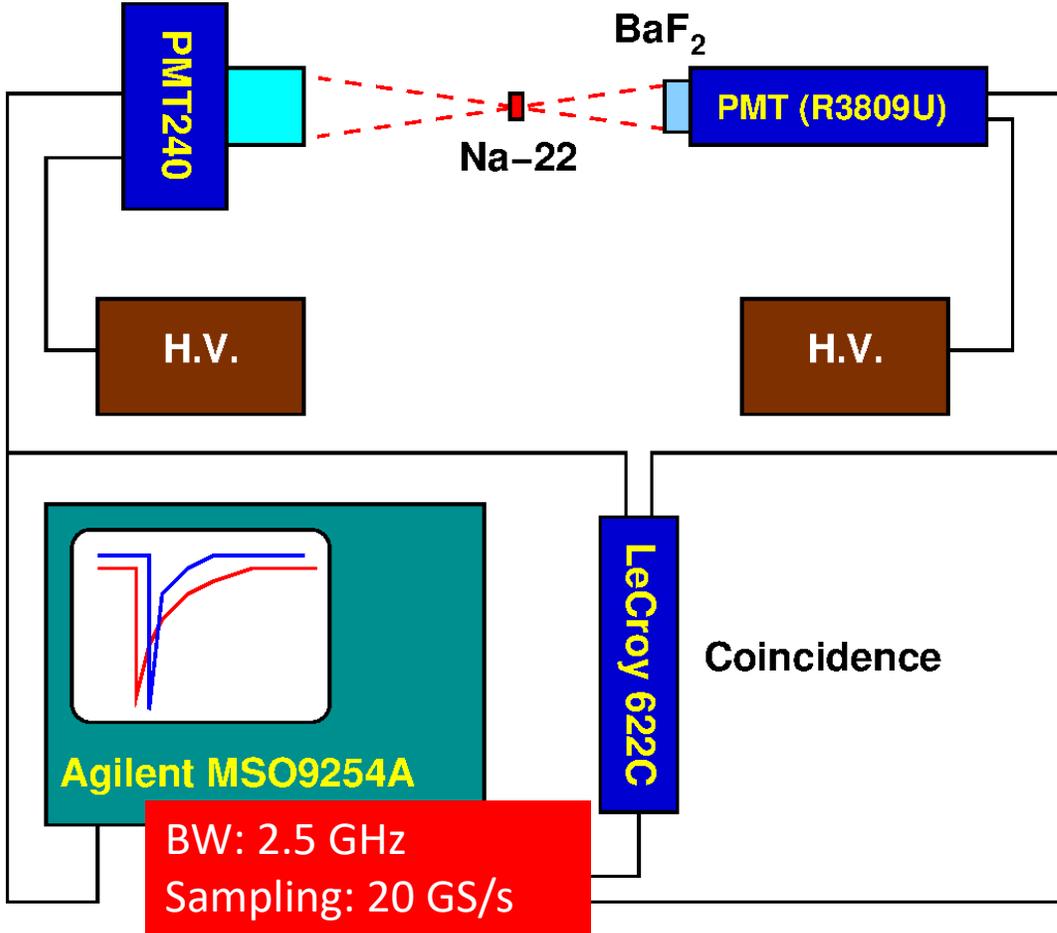

## Am-241 Self Trigger

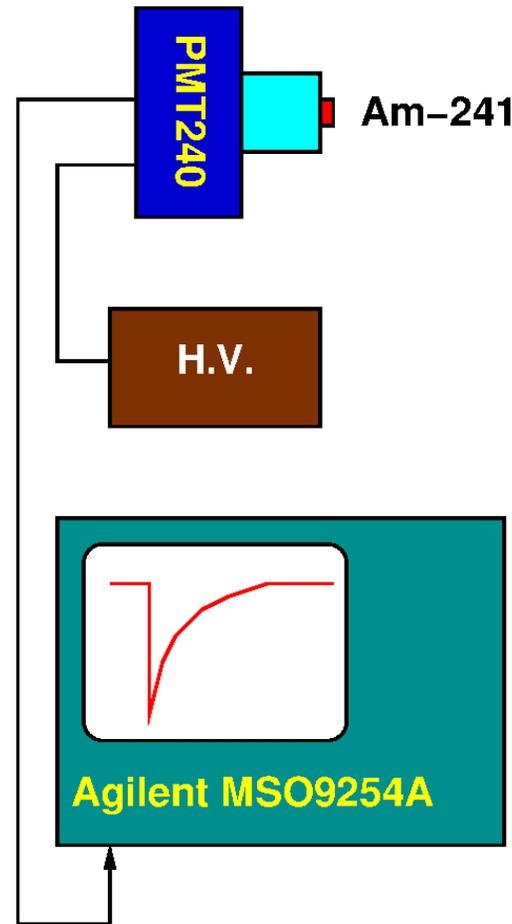

P. Rodny, CRC Press,  
Boca Raton, FL, USA, 2020

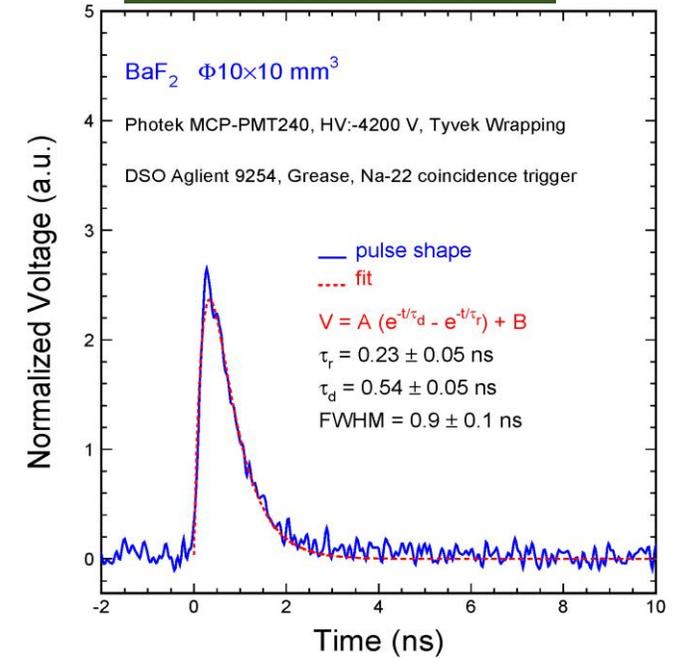

Fitting:

$$V = A(e^{-\frac{t}{\tau_d}} - e^{-\frac{t}{\tau_r}}) + B$$

B: background noise  
or very slow component,  
 $\tau_r$ : rise time,  $\tau_d$ : decay time.

Rise, decay and FWHM obtained by fitting temporal response





# MCP-PMT 240 Temporal Response






A fit to response of the Photek MCP-PMT 240 for pico-second laser pulses shows both the rise and FWHM consistent with the specification

Photodetector	Active diameter (mm)	Spectral range (nm)	Peak Sen. (nm)	Gain	Rise time (ns)	FWHM (ns)
<b>Photek MCP-PMT 240</b>	<b>40</b>	<b>160-850</b>	<b>280-450</b>	<b><math>1 \times 10^6</math></b>	<b>0.180</b>	<b>0.82</b>
Hamamatsu MCP-PMT R3809U-50	11	160-850	430	$3 \times 10^5$	0.160	0.30
Photek MCP-PMT 110	10	160-850	280-450	$1 \times 10^4$	0.065	0.11
Photek MCP-PMT 210	10	160-850	280-450	$1 \times 10^6$	0.085	0.15
Hamamatsu PMT R2059	46	160-650	450	$2 \times 10^7$	1.3	

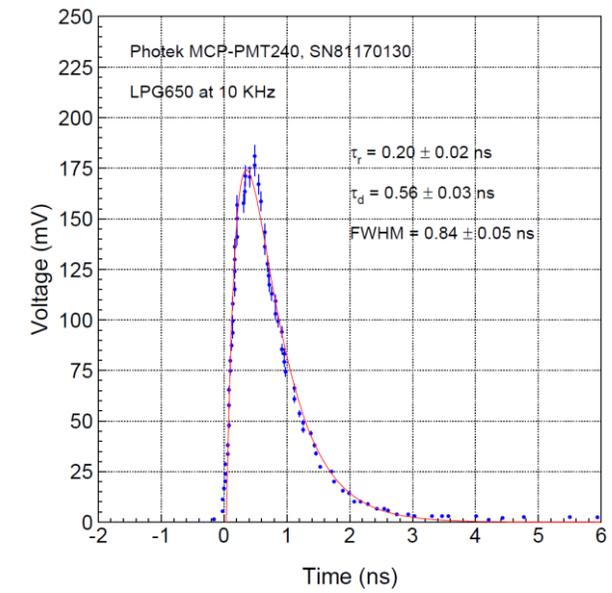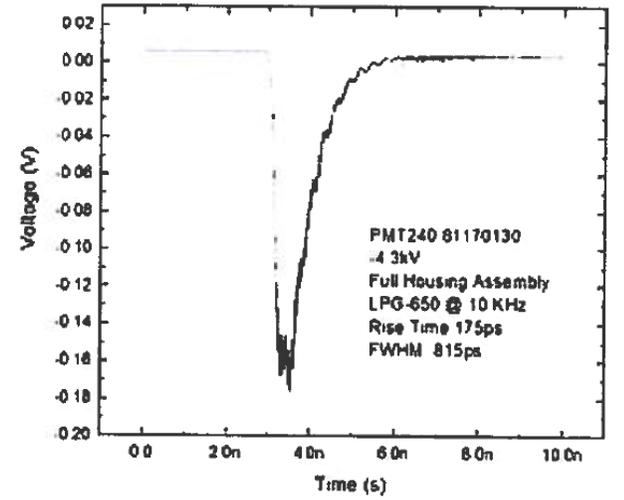






# Temporal Response: BaF<sub>2</sub> & BaF<sub>2</sub>:Y

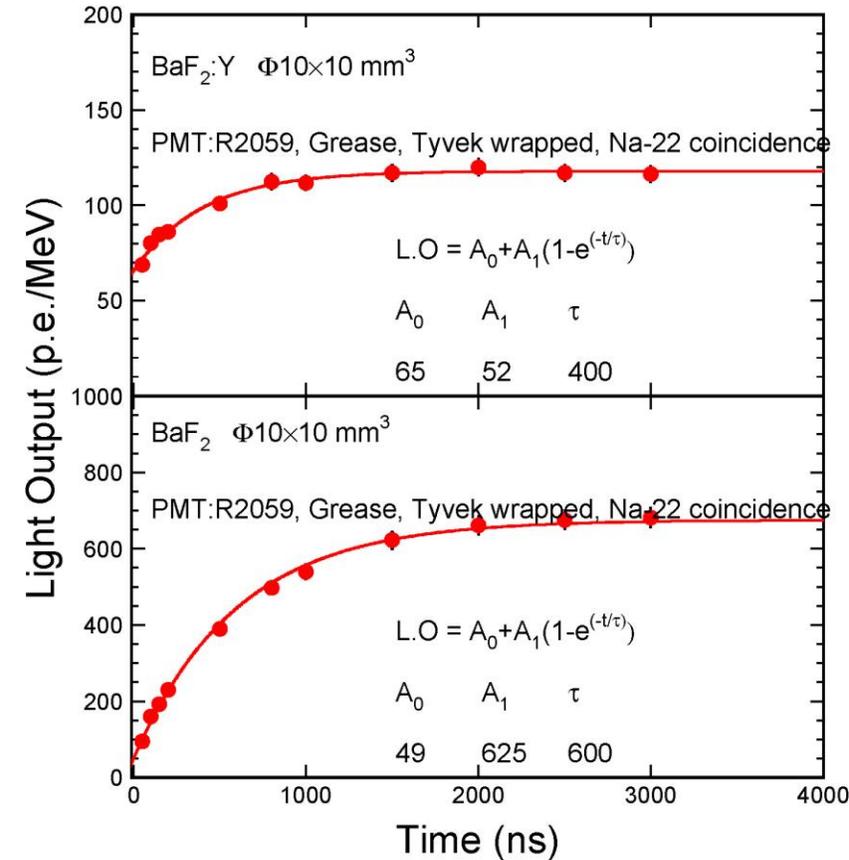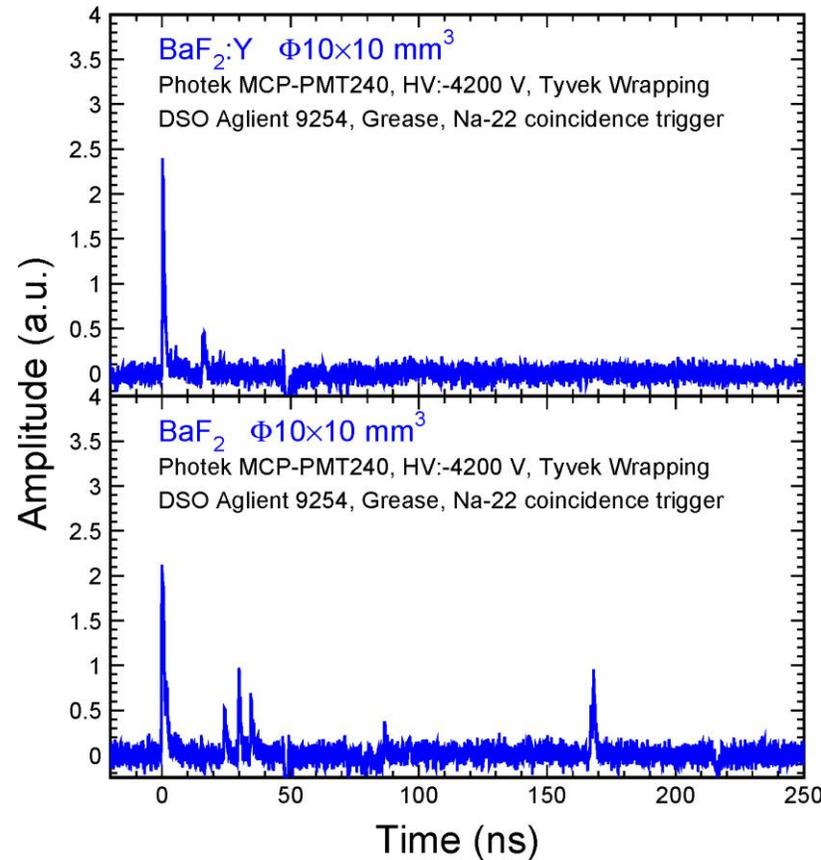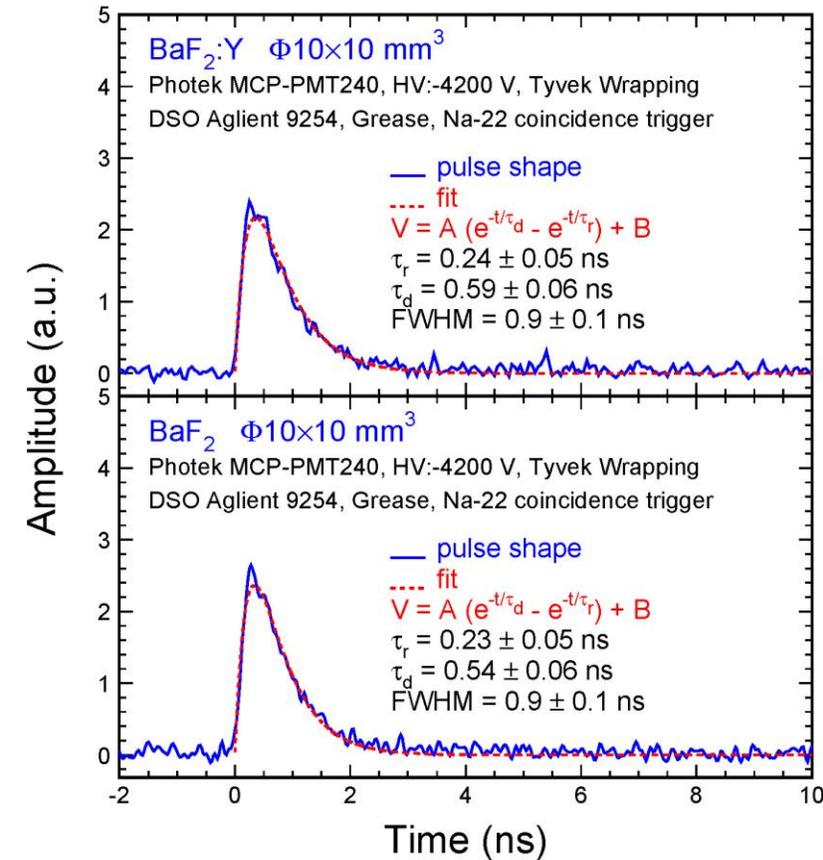

Ultrafast response of 0.2/0.6/0.8 ns observed for BaF<sub>2</sub> and BaF<sub>2</sub>:Y crystals  
 The response is consistent with the Photek MCP-PMT 240 specification






# Temporal Response: $\text{Lu}_2\text{O}_3:\text{Yb}$ Ceramics

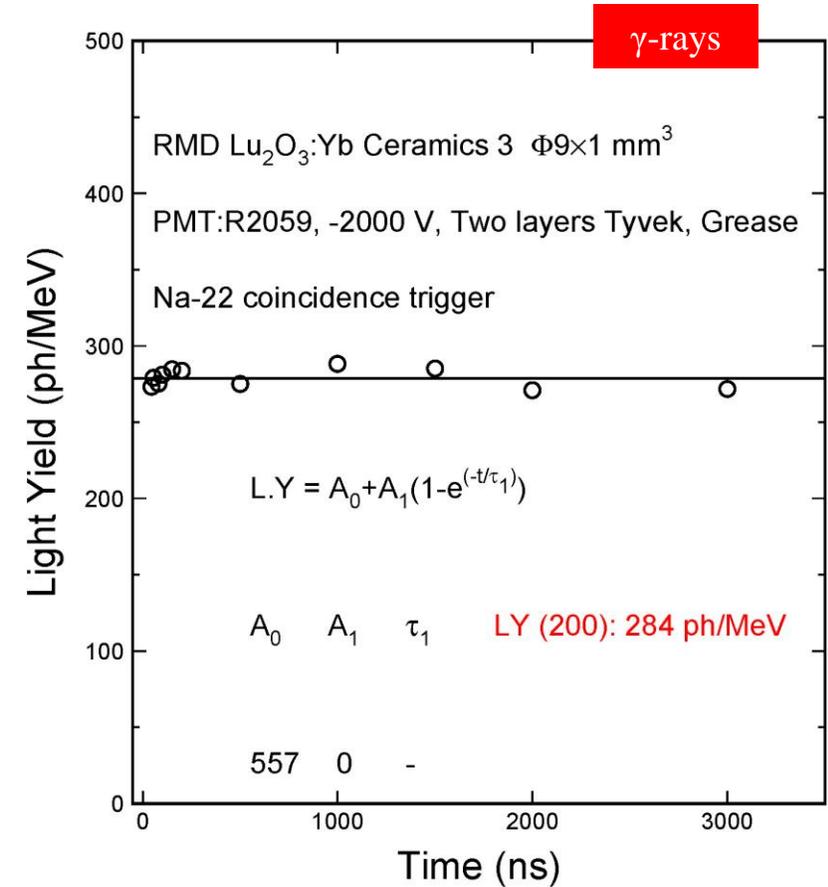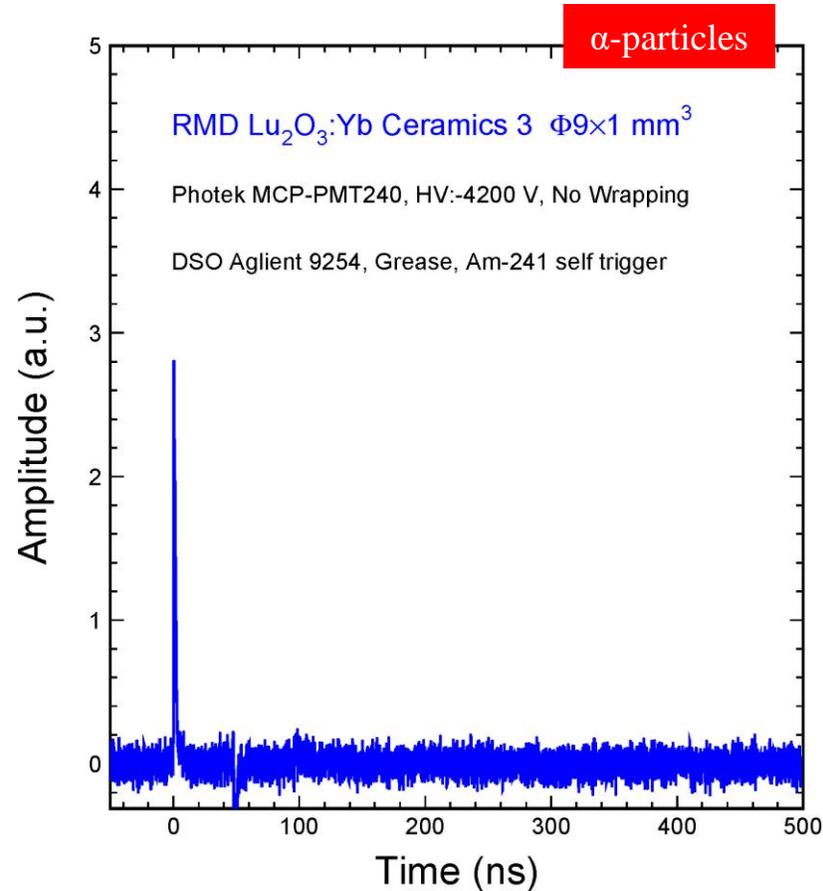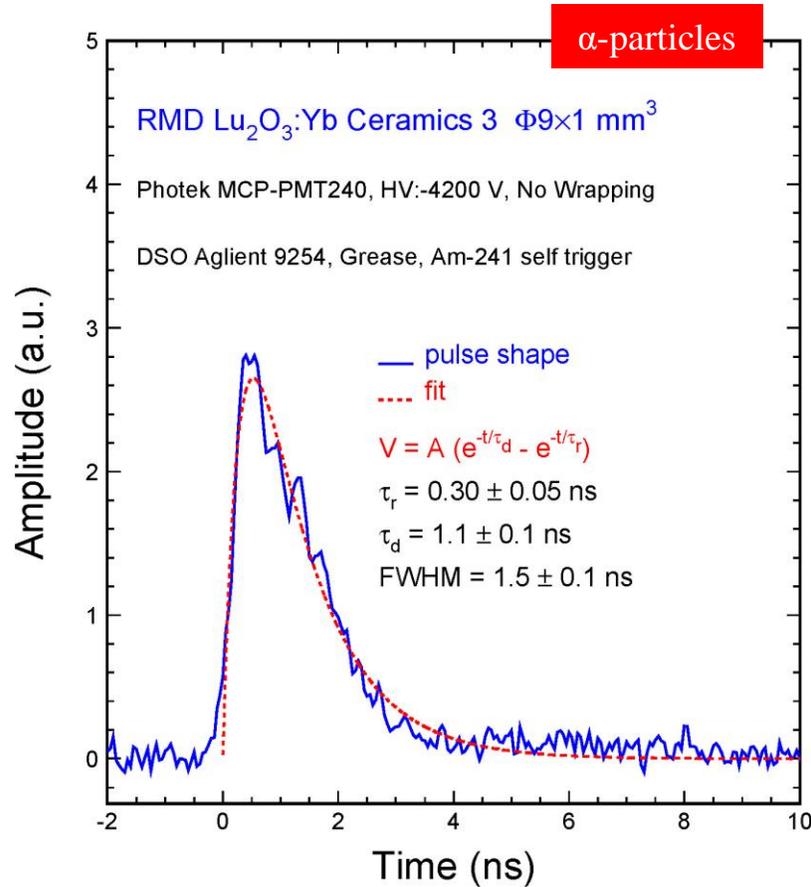

$\text{Lu}_2\text{O}_3:\text{Yb}$  ceramic of 9.4 g/cc shows an ultrafast decay time of 1.1 ns by Am-241 with negligible slow component observed in integrated light output measurement



# Temporal Response of YAP:Yb & YAG:Yb

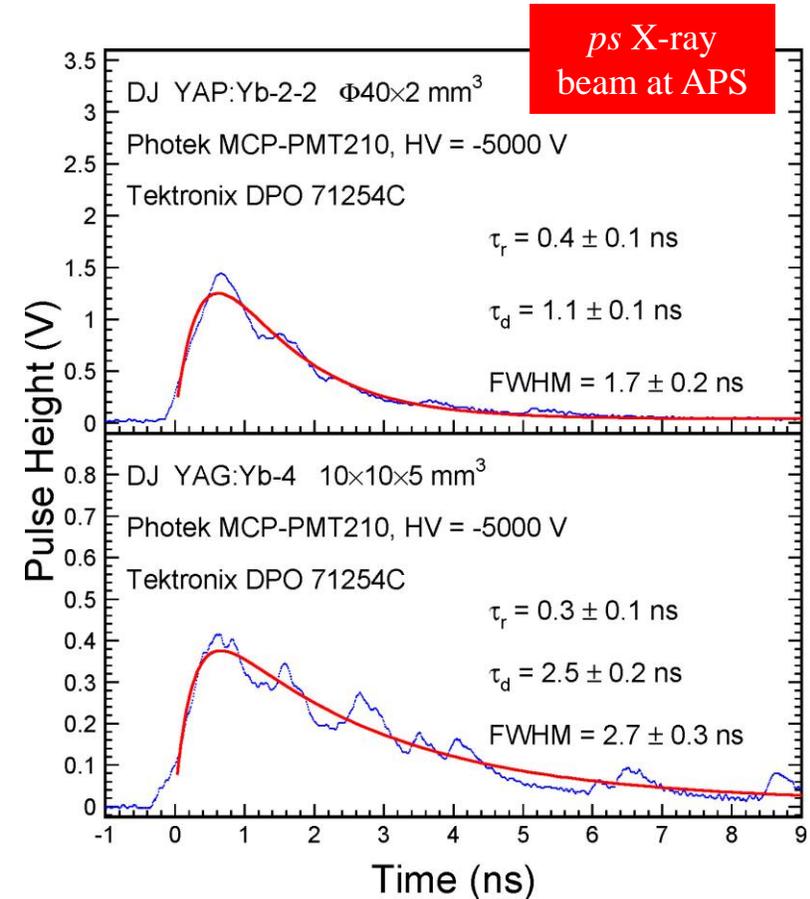
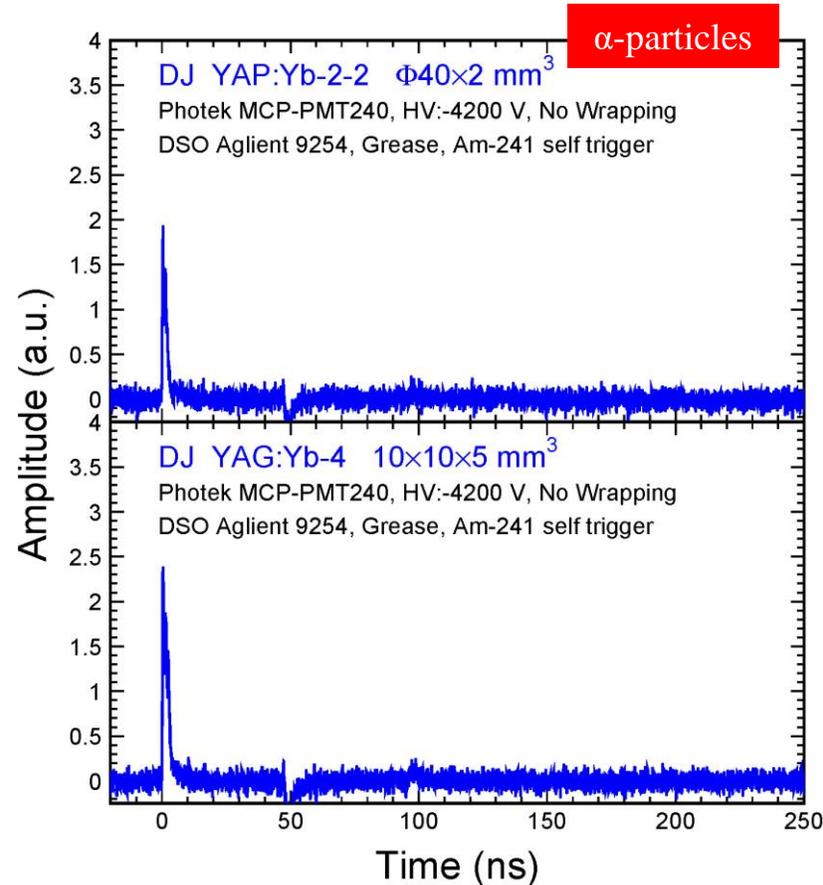
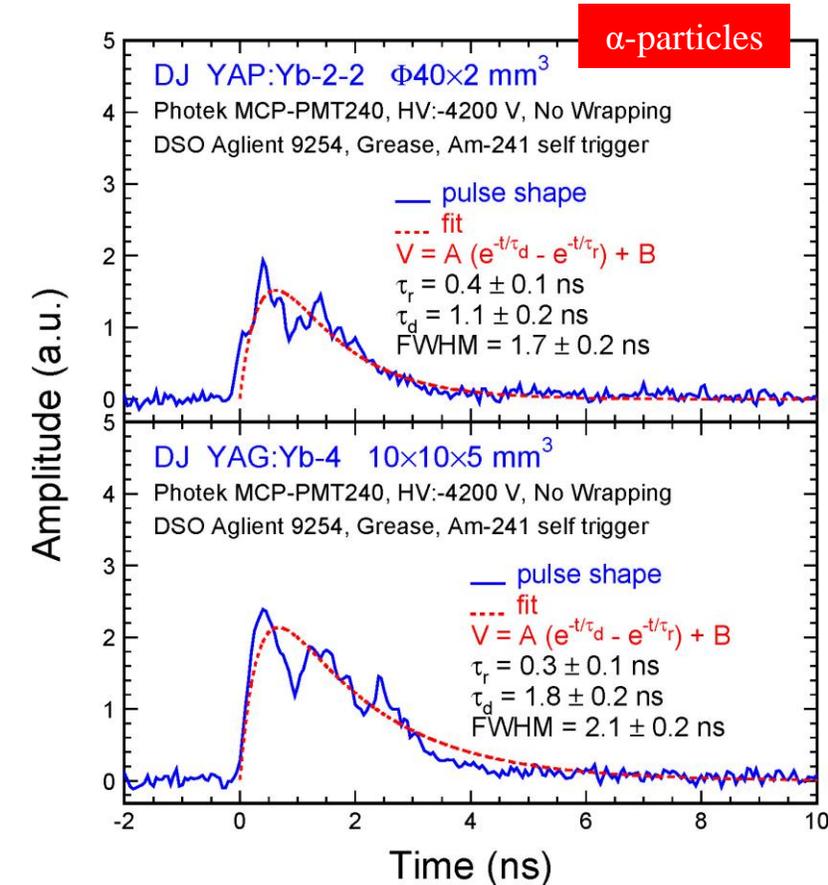


NIM A 940 (2019) 223–229

YAP:Yb & YAG:Yb show a decay time of 1.1 ns and 1.8 ns by Am-241 with negligible slow component



# Temporal Response of ZnO:Ga

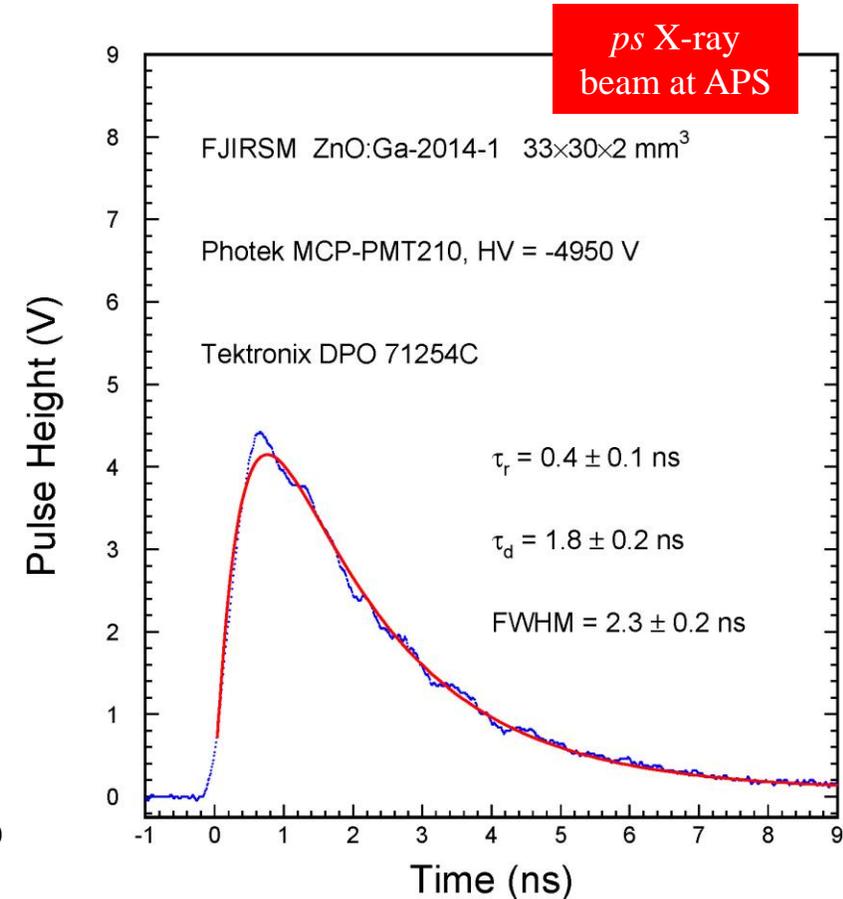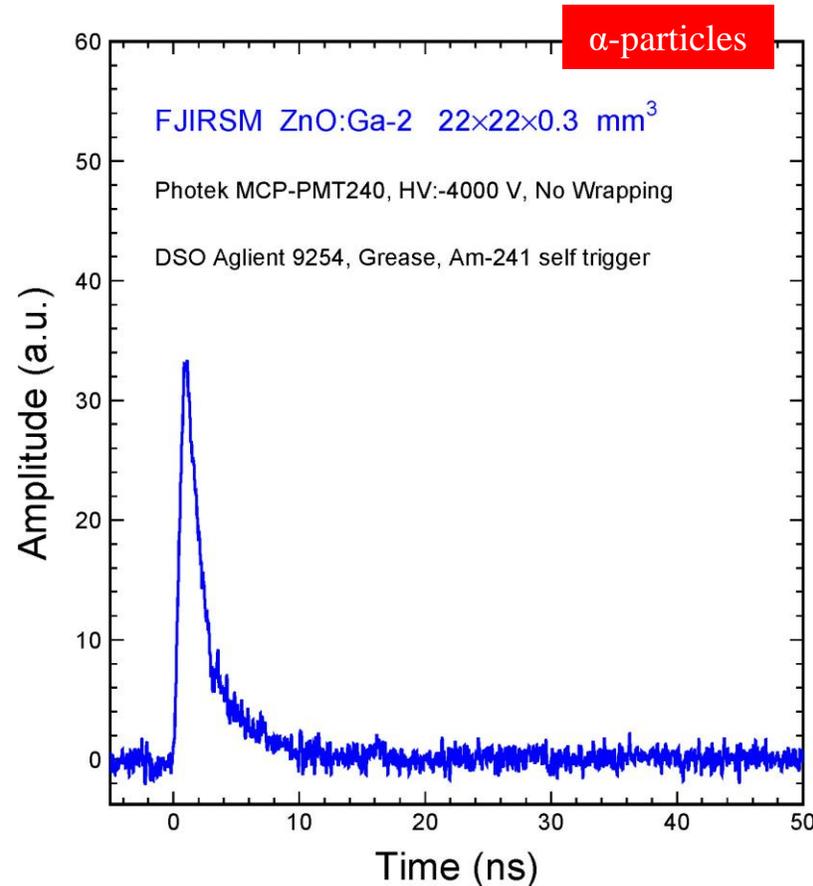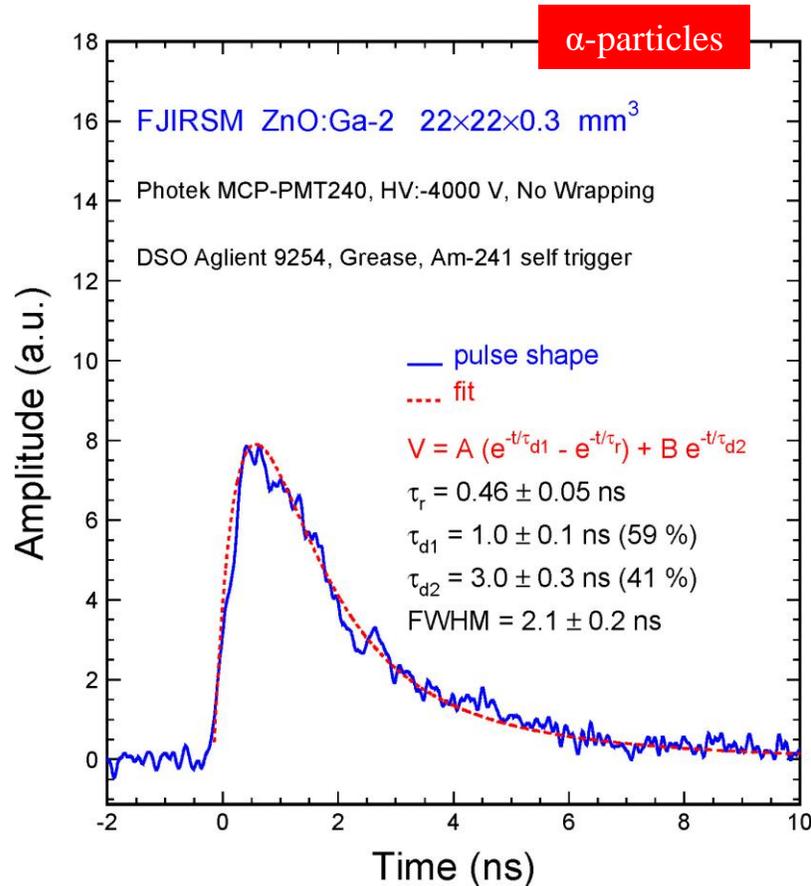



ZnO:Ga shows decay time of 1.0/3.0 ns by Am-241 with negligible slow component



# The Instrument Response Function




$$Fit(t) = f[V(t) * IRF(t)] = \int_{-\infty}^{+\infty} V(\tau) * IRF(t - \tau) d\tau$$

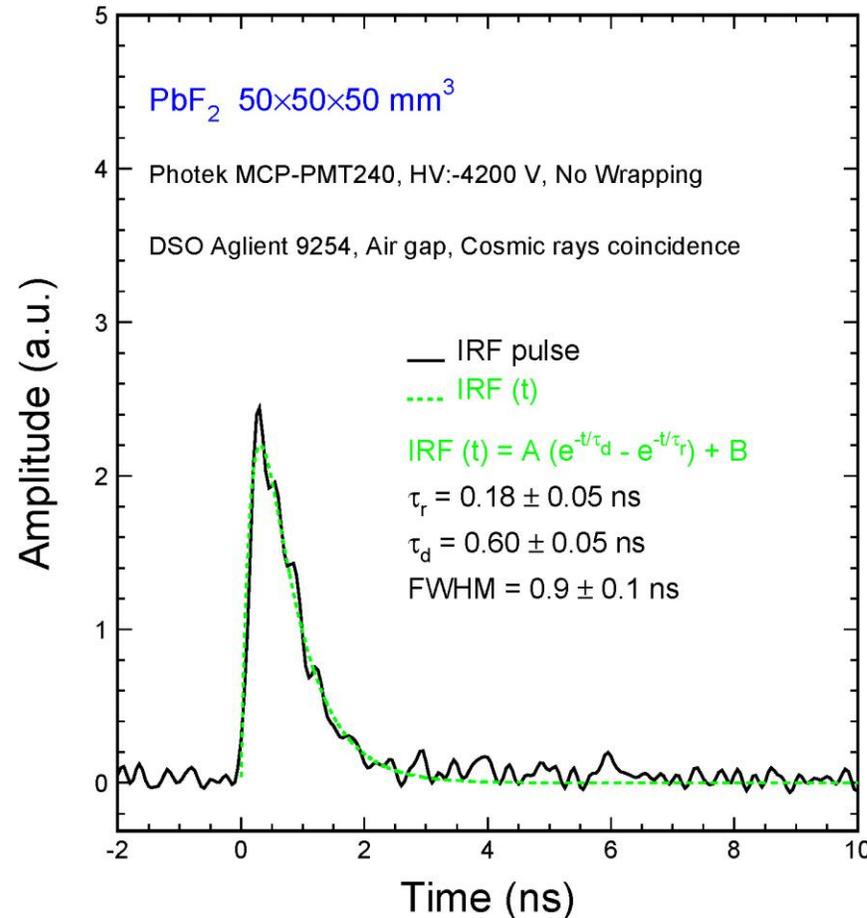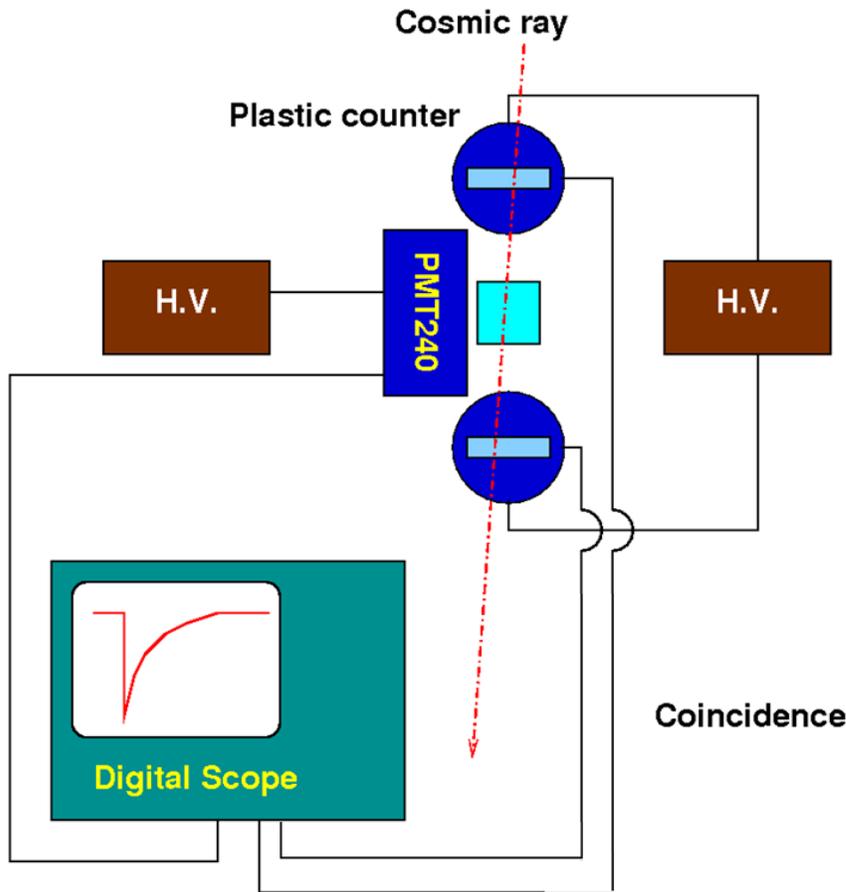

Intrinsic ultrafast response time can be extracted by taking out the IRF of the set-up. It was measured by fitting Cerenkov light pulse from a PbF<sub>2</sub> crystal, which agrees well with Photek spec.



# Intrinsic Decay Time of $\text{Lu}_2\text{O}_3:\text{Yb}$

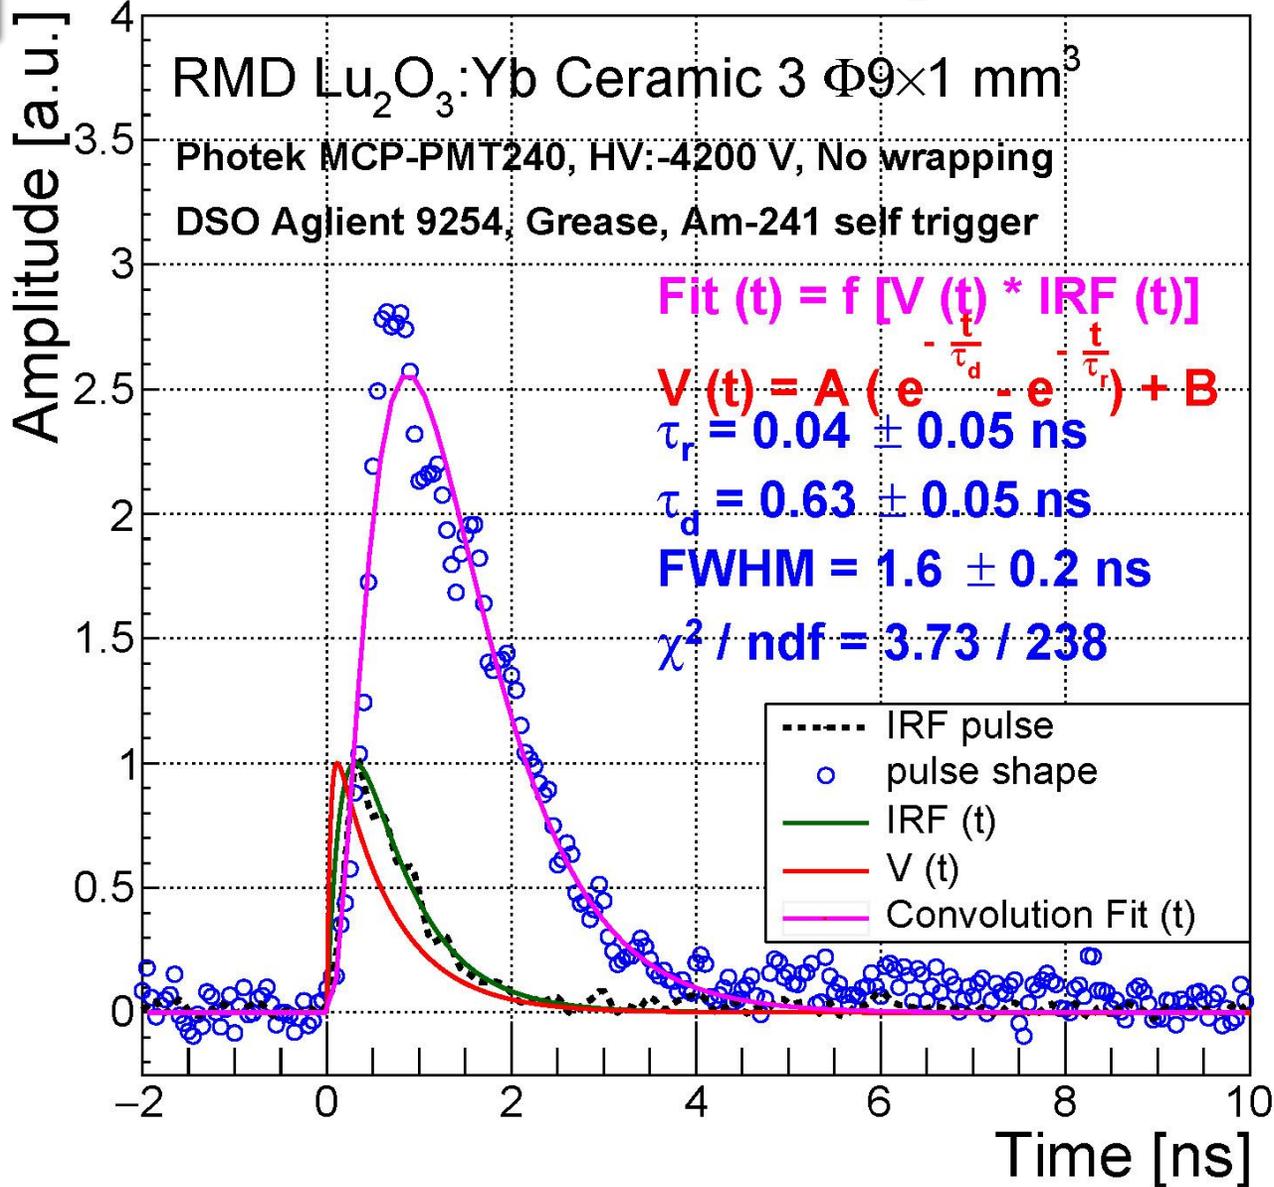

The magenta line shows the convolution fit. The numerical result of the fit after taking out the IRF are shown in blue




The result of the 0.63 ns decay time is the intrinsic decay time of  $\text{Lu}_2\text{O}_3:\text{Yb}$



# BaF<sub>2</sub>, YAP:Yb, YAG:Yb and ZnO:Ga



The intrinsic decay time of YAP:Yb, YAG:Yb and ZnO:Ga are 0.6, 0.9 & 0.4/2.8 ns, respectively  
The rise/decay time for the BaF<sub>2</sub>/BaF<sub>2</sub>:Y ultrafast light is within the IRF of the set-up

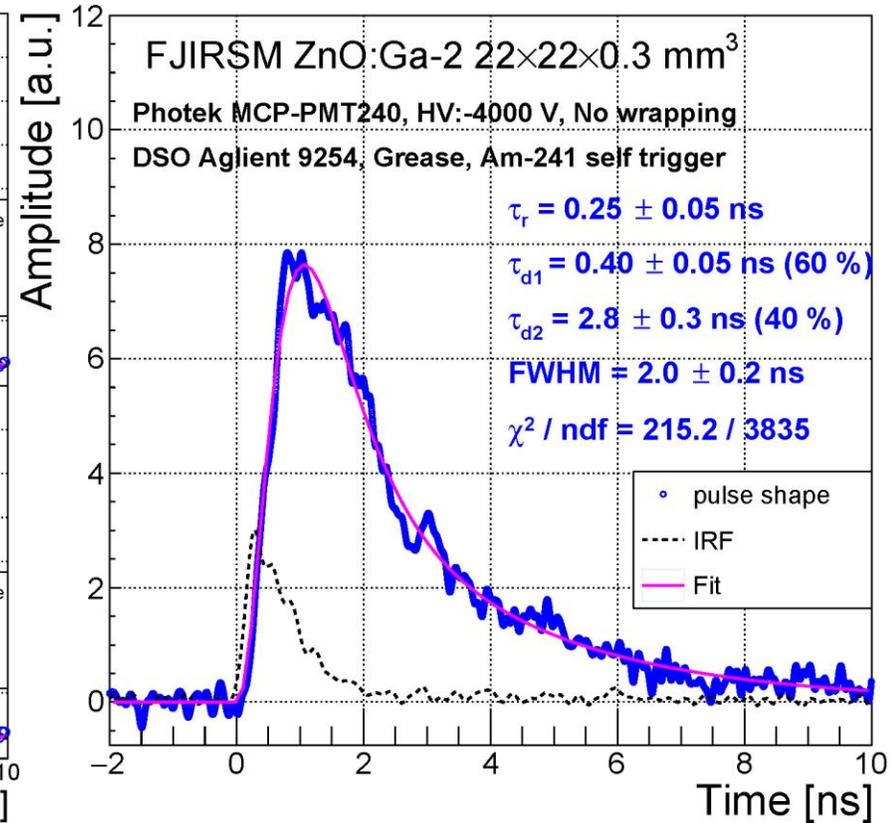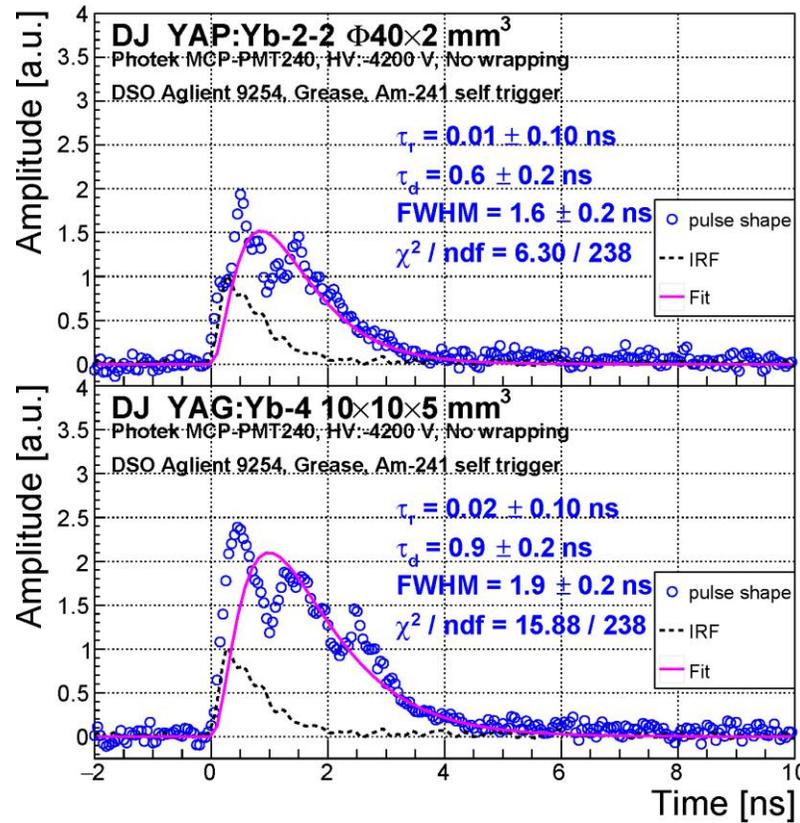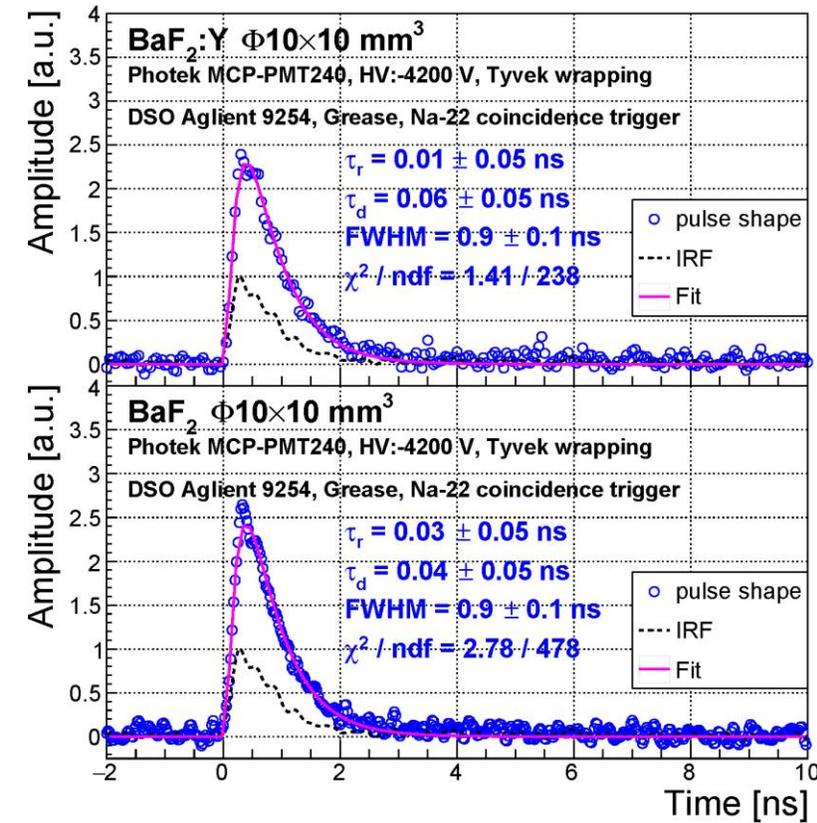



# Fast/Ultrafast Inorganic Scintillators for Imaging



arXiv: 2203.06788

	BaF <sub>2</sub>	BaF <sub>2</sub> :Y	Lu <sub>2</sub> O <sub>3</sub> :Yb	YAP:Yb	YAG:Yb	ZnO:Ga	β-Ga <sub>2</sub> O <sub>3</sub>	LYSO:Ce	LuAG:Ce	YAP:Ce	GAGG:Ce	LuYAP:Ce	YSO:Ce
Density (g/cm <sup>3</sup> )	4.89	4.89	9.42	5.35	4.56	5.67	5.94	7.4	6.76	5.35	6.5	7.2 <sup>f</sup>	4.44
Melting points (°C)	1280	1280	2490	1870	1940	1975	1725	2050	2060	1870	1850	1930	2070
X <sub>0</sub> (cm)	2.03	2.03	0.81	2.59	3.53	2.51	2.51	1.14	1.45	2.59	1.63	1.37	3.10
R <sub>M</sub> (cm)	3.1	3.1	1.72	2.45	2.76	2.28	2.20	2.07	2.15	2.45	2.20	2.01	2.93
λ <sub>1</sub> (cm)	30.7	30.7	18.1	23.1	25.2	22.2	20.9	20.9	20.6	23.1	21.5	19.5	27.8
Z <sub>eff</sub>	51.0	51.0	67.3	32.8	29.3	27.7	27.8	63.7	58.7	32.8	50.6	57.1	32.8
dE/dX (MeV/cm)	6.52	6.52	11.6	7.91	7.01	8.34	8.82	9.55	9.22	7.91	8.96	9.82	6.57
λ <sub>peak</sub> <sup>a</sup> (nm)	300 220	300 220	370	350	350	380	380	420	520	370	540	385	420
Refractive Index <sup>b</sup>	1.50	1.50	2.0	1.96	1.87	2.1	1.97	1.82	1.84	1.96	1.92	1.94	1.78
Normalized Light Yield <sup>a,c</sup>	42 4.8	1.7 4.8	0.95	0.19 <sup>d</sup>	0.36 <sup>d</sup>	2.6 <sup>d</sup> 4.0 <sup>d</sup>	6.5 0.5	100	35 <sup>e</sup> 48 <sup>e</sup>	9 32	190	16 15	80
Total Light yield (ph/MeV)	13,000	2,000	280	57 <sup>d</sup>	110 <sup>d</sup>	2,000 <sup>d</sup>	2,100	30,000	25,000 <sup>e</sup>	12,000	58,000	10,000	24,000
Decay time <sup>a</sup> (ns)	600 0.5	600 0.5	1.1 <sup>d</sup>	1.1 <sup>d</sup>	1.8 <sup>d</sup>	3.0 <sup>d</sup> 1.0 <sup>d</sup>	110 5.3	40	820 50	191 25	570 130	1485 36	75
LY in 1 <sup>st</sup> ns (photons/MeV)	1200	1200	170	34 <sup>d</sup>	46 <sup>d</sup>	980 <sup>d</sup>	43	740	240	391	400	125	318
LY in 1 <sup>st</sup> ns /Total LY (%)	9.0	64	60	60	43	49	2.0	2.5	1.2	3.3	0.7	1.4	1.3
40 keV Att. Leng. (1/e, mm)	0.106	0.106	0.127	0.314	0.439	0.407	0.394	0.185	0.251	0.314	0.319	0.214	0.334

<sup>a</sup> top/bottom row: slow/fast component; <sup>b</sup> at the emission peak; <sup>c</sup> normalized to LYSO:Ce; <sup>d</sup> excited by Alpha particles; <sup>e</sup> 0.3 Mg at% co-doping; <sup>f</sup> Lu<sub>0.7</sub>Y<sub>0.3</sub>AlO<sub>3</sub>:Ce.



# Summary




- The HEP community is developing rad-hard, fast/ultrafast and cost-effective inorganic scintillators for future HEP experiments at the energy and intensity frontiers.
- Ultrafast inorganic scintillators under development for HEP applications, such as  $\text{BaF}_2:\text{Y}$  and  $\text{Lu}_2\text{O}_3:\text{Yb}$ , may help to break the pico-second timing barrier for HEP as well as provide a GHz hard X-ray imager for future free electron laser facilities.
- Hard X-ray beams with ns bunch spacing, e.g. the APS beam in hybrid mode or the SLAC LCLS facility, are very useful for our investigation on ultrafast inorganic scintillators.

Acknowledgements: DOE HEP Award DE-SC0011925





# Cost-Effective Inorganic Scintillators for FCC-ee



## CalVision Crystal Calorimetry


- A longitudinally segmented Calvision crystal ECAL with dual readout combined with the IDEA HCAL promises excellent EM and Hadronic resolution.
- Dense, UV-transparent and cost-effective inorganic scintillators are crucial for the homogeneous hadron calorimeter (HCAL) detector concept, promising a jet mass resolution at a level of 20%/√E by dual readout for either Cerenkov and scintillation light or dual integration gate.
- Doped  $\text{PbF}_2$ ,  $\text{PbFCl}$ , BSO, titanium doped sapphire ( $\text{Al}_2\text{O}_3:\text{Ti}$ ) crystals and AFO glass have been investigated. Cost-effective inorganic glasses from RMD and Scintillex etc. are under investigation for FCC-ee

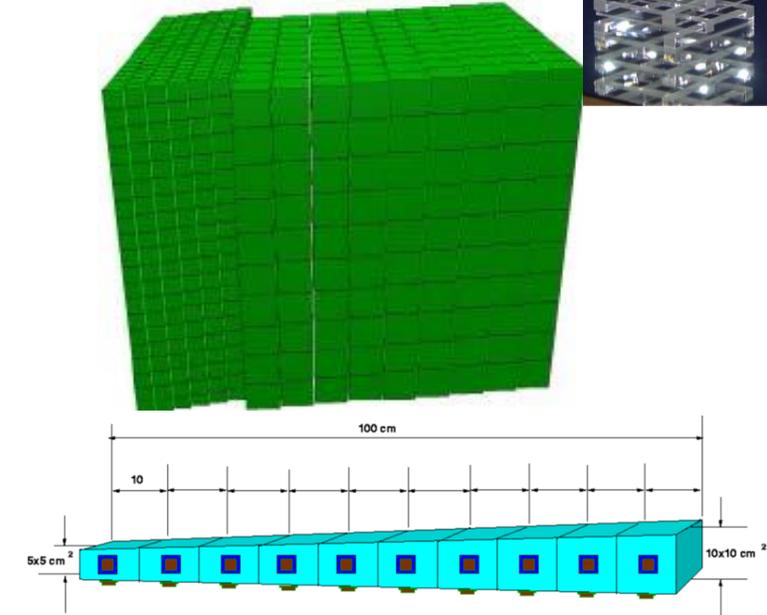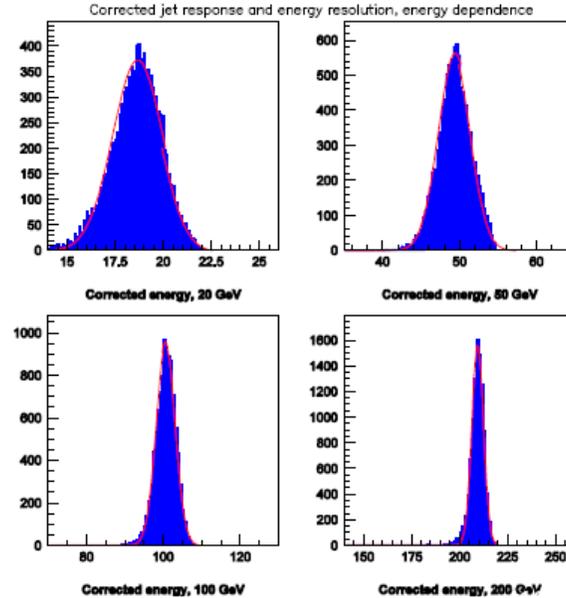

	BGO	BSO	PWO	$\text{PbF}_2$	$\text{PbFCl}$	Sapphire:Ti	AFO Glass	$\text{BaO}\cdot 2\text{SiO}_2$ Glass <sup>1</sup>	HFG Glass <sup>2</sup>
Density (g/cm <sup>3</sup> )	7.13	6.8	8.3	7.77	7.11	3.98	4.6	3.8	5.95
Melting point (°C)	1050	1030	1123	824	608	2040	980 <sup>3</sup>	1420 <sup>4</sup>	570
$X_0$ (cm)	1.12	1.15	0.89	0.94	1.05	7.02	2.96	3.36	1.74
$R_M$ (cm)	2.23	2.33	2.00	2.18	2.33	2.88	2.89	3.52	2.45
$\lambda_1$ (cm)	22.7	23.4	20.7	22.4	24.3	24.2	26.4	32.8	23.2
$Z_{\text{eff}}$ value	72.9	75.3	74.5	77.4	75.8	11.2	42.8	44.4	56.9
dE/dX (MeV/cm)	8.99	8.59	10.1	9.42	8.68	6.75	6.84	5.56	8.24
Emission Peak <sup>a</sup> (nm)	480	470	425 420	\	420	300 750	365	425	325
Refractive Index <sup>b</sup>	2.15	2.68	2.20	1.82	2.15	1.76	\	\	1.50
Relative Light Output by PMT <sup>a,c</sup>	100	20	1.6 0.4	\	2.0	0.2 0.9	2.6	5.0 4.0	3.3 6.1
LY (ph/MeV) <sup>d</sup>	35,000	1,500	130	\	150	7,900	450	3,150	150
Decay Time <sup>a</sup> (ns)	300	100	30 10	\	3	300 3200	40	180 30	25 8
d(LY)/dT (%/°C) <sup>d</sup>	-0.9	?	-2.5	\	?	?	?	-0.04	-0.37
Cost (\$/cc)	6.0	7.0	7.5	6.0	?	0.6	?	?	?



# Sapphire:Ti Emission and Transmittance

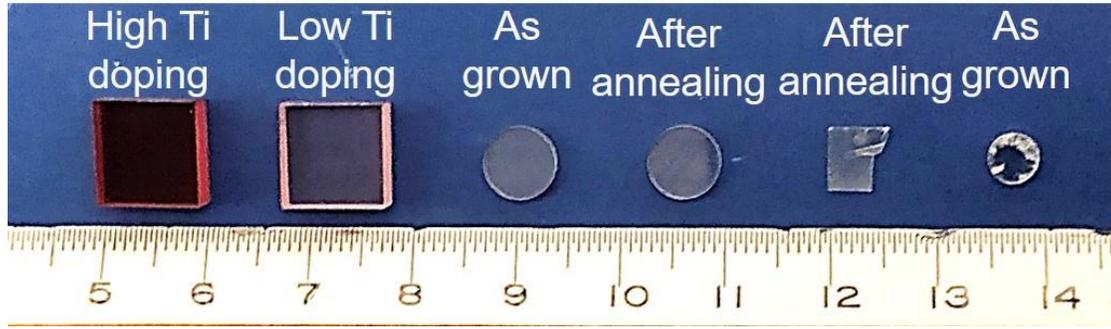

A weak emission at 325 nm with 150 ns decay time  
 A strong emission at 755 nm with 3  $\mu$ s decay time

ID	Dimension (mm <sup>3</sup> )	#	Polishing
Tongji Al <sub>2</sub> O <sub>3</sub> :Ti-1,2	10×10×4	2	Two faces
Tongji Al <sub>2</sub> O <sub>3</sub> :C-1,2	Φ7×1	2	Two faces
Tongji Lu <sub>2</sub> O <sub>3</sub> :Yb	6.4×4.8×0.4	1	Two faces
Tongji LuScO <sub>3</sub> :Yb	Φ4.8×1.3	1	Two faces

Fast @325 nm

Slow @755 nm

EWLT for Fast & Slow

Fast = 162 ns

Slow = 3.2  $\mu$ s

