



Inorganic Scintillators for Future High Energy Physics Experiments

Liyuan Zhang and Ren-Yuan Zhu

California Institute of Technology

May 24, 2024



Why Inorganic Scintillators?



arXiv: 2203.06731 and arXiv: 2203.06788

- Precision e/γ enhance physics discovery potential.
- Performance of total absorption ECAL is well understood for e/γ and jets:
 - Energy resolution achieved: $2\%/\sqrt{E} \oplus 1\%$
 - Position resolution: sub-mm can be achieved;
 - Good identification and reconstruction efficiency;
 - Excellent jet mass resolution with dual readout: C/S light or S/L gate.
- On-going Development in Caltech Crystal Lab:
 - Rad-hard LYSO:Ce crystals and LuAG:Ce ceramics (RADiCAL) for HL-LHC and FCC-hh;
 - Ultrafast BaF₂:Y and Lu₂O₃:Yb for future ultrafast calorimetry and time of flight;
 - Cost-effective ABS and DSB glasses for Higgs factory (CalVision) and HHCAL.



Crystals Used in HEP Calorimeters




Crystal	NaI:TI	CsI:TI	CsI	BaF ₂	BGO	LYSO:Ce	PWO	PbF ₂
Density (g/cm ³)	3.67	4.51	4.51	4.89	7.13	7.40	8.3	7.77
Melting Point (°C)	651	621	621	1280	1050	2050	1123	824
Radiation Length (cm)	2.59	1.86	1.86	2.03	1.12	1.14	0.89	0.93
Molière Radius (cm)	4.13	3.57	3.57	3.10	2.23	2.07	2.00	2.21
Interaction Length (cm)	42.9	39.3	39.3	30.7	22.8	20.9	20.7	21.0
Refractive Index ^a	1.85	1.79	1.95	1.50	2.15	1.82	2.20	1.82
Hygroscopicity	Yes	Slight	Slight	No	No	No	No	No
Luminescence ^b (nm) (at peak)	410	550	420 310	300 220	480	402	425 420	-
Decay Time ^b (ns)	245	1220	30 6	650 0.9	300	40	30 10	-
Light Yield ^{b,c} (photons/MeV)	38,000	63,000	1,400 420	13,680 1,560	8,000	32,000	114 40	-
d(LY)/dT ^b (%/ °C)	-0.2	0.4	-1.4	-1.9 0.1	-0.9	-0.2	-2.5	-
Experiment	Crystal Ball	BaBar BELLE BES III	KTev Mu2e	TAPS Mu2e-II	L3 BELLE	COMET CMS BTL PIONEER	CMS ALICE PANDA ePIC	A4 G-2



a. at emission peak; b. up/low row: slow/fast component; c. with QE of readout device taken out.



L3 BGO, BaBar Csl, CMS PWO ECAL

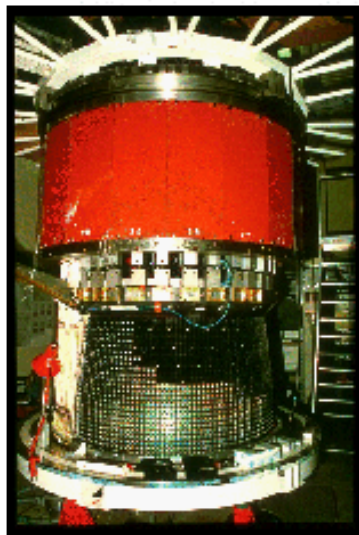

11.4k BGO

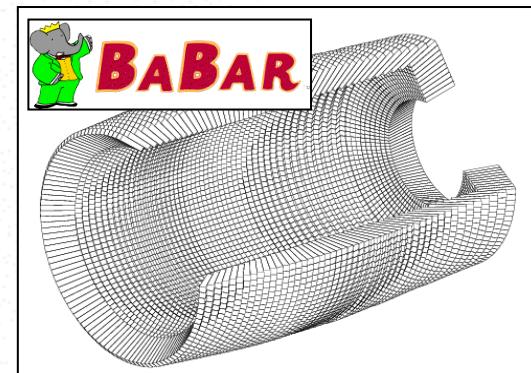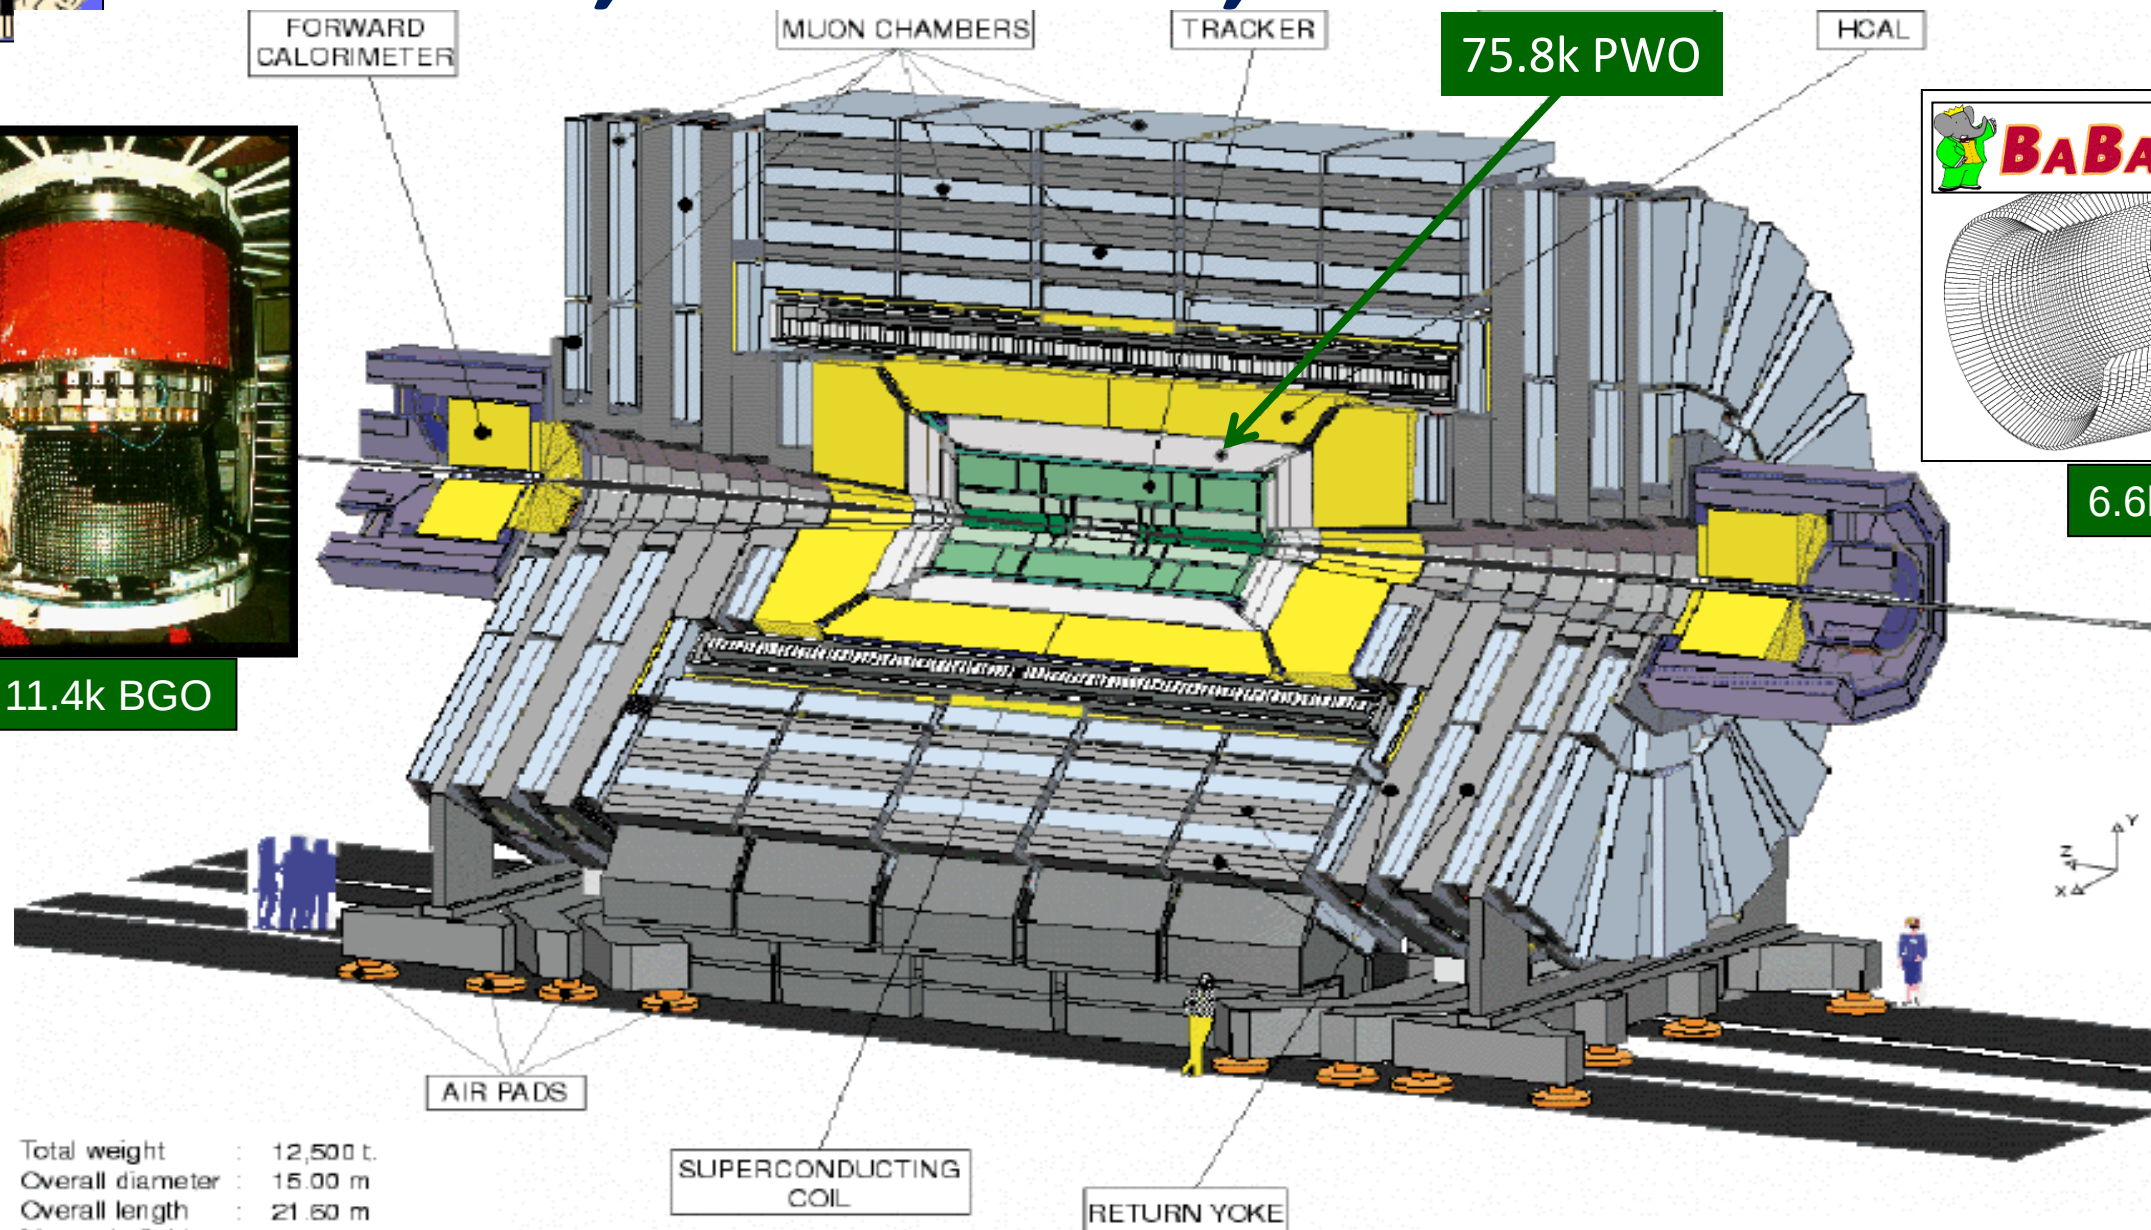

6.6k Csl:TI

Total weight : 12,500 t.
Overall diameter : 15.00 m
Overall length : 21.60 m
Magnetic field : 4 Tesla

SUPERCONDUCTING COIL

RETURN YOKE



AIR PADS



CMS H $\rightarrow \gamma\gamma$ and PWO Damage



See M. Tornago, in this conference

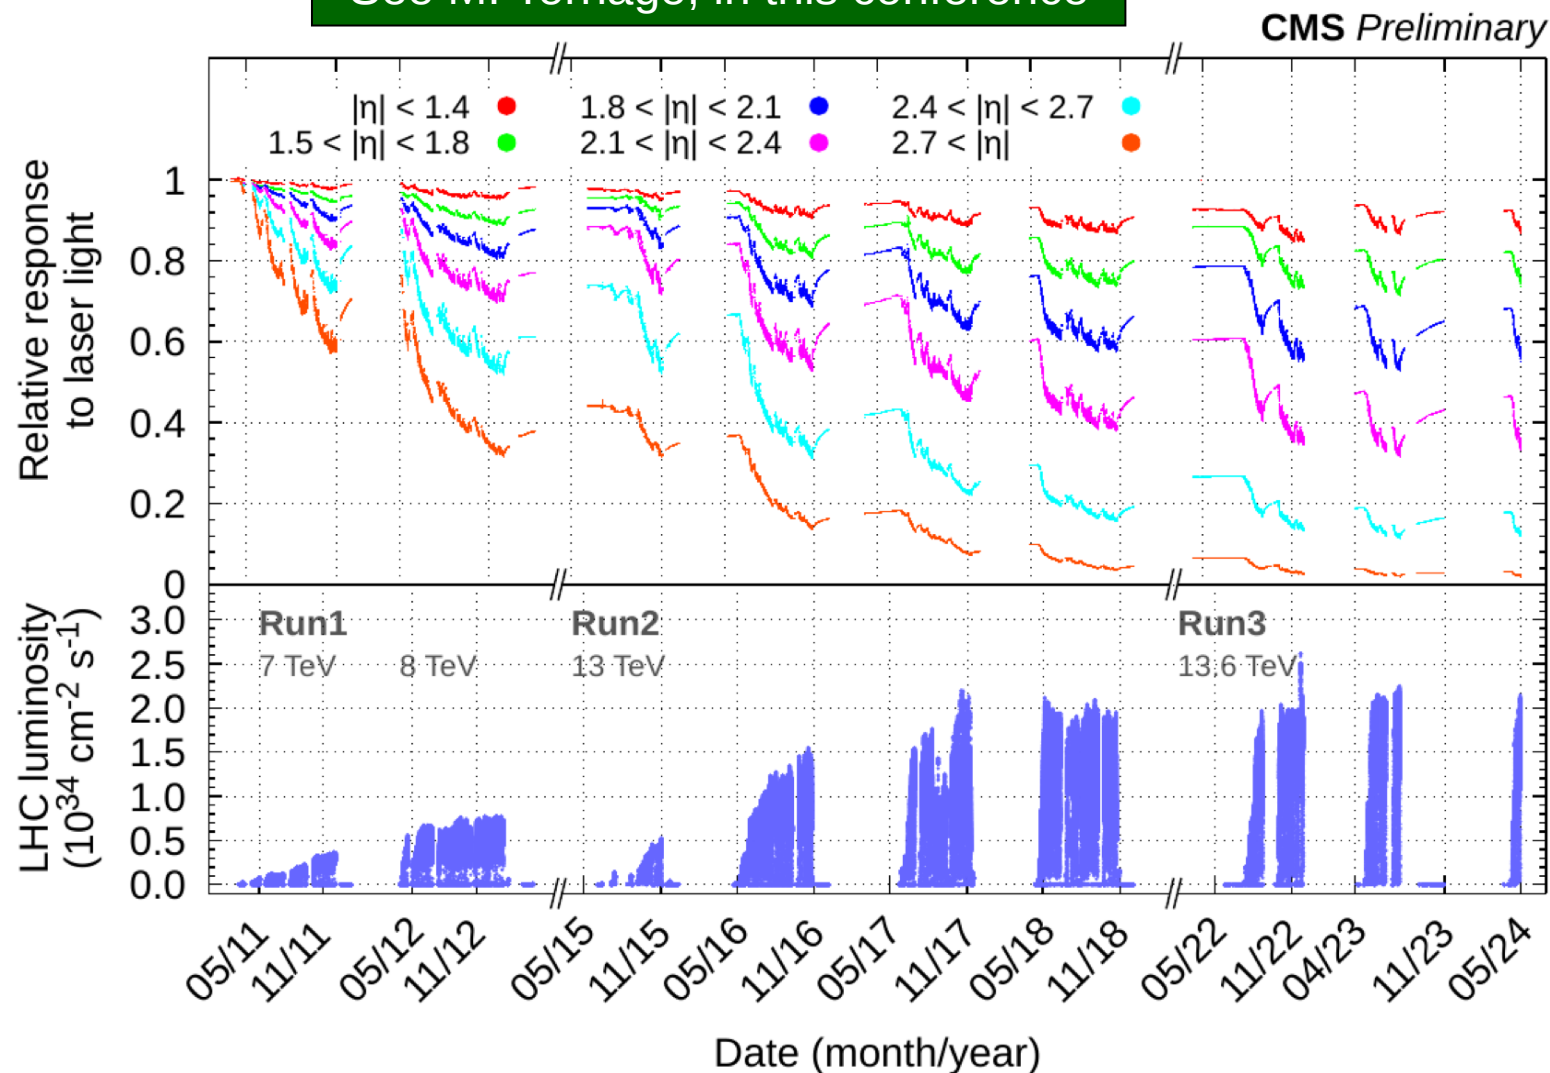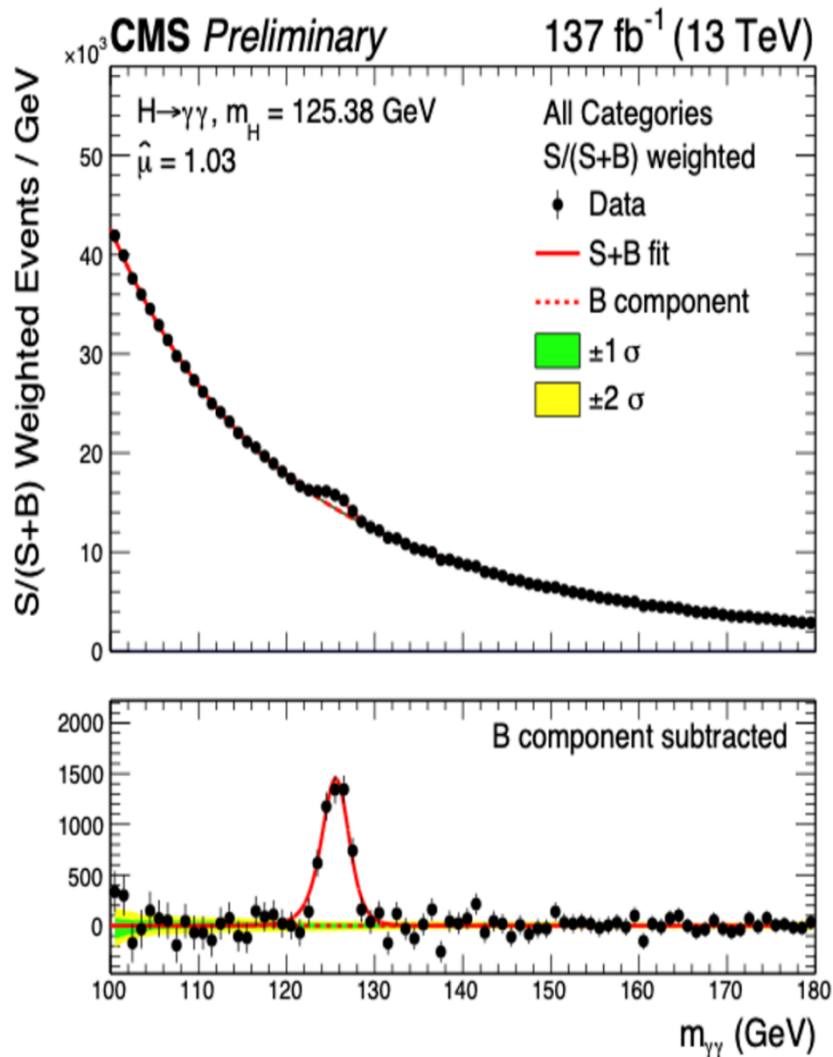

PWO damage caused by ionization dose and hadrons






PWO Damage by Ionization & Neutrons



$$\text{RIAC in PWO} = 1.4 \times 10^{-14} \times 1 \text{ MeV } n_{\text{eq}} \text{ Fluence}$$

γ -ray and hadron induced absorption explains CMS PWO monitoring data
http://www.its.caltech.edu/~rzhu/talks/ryz_161028_PWO_mon.pdf & Trans. NS. 67 (2020) 1086-1092

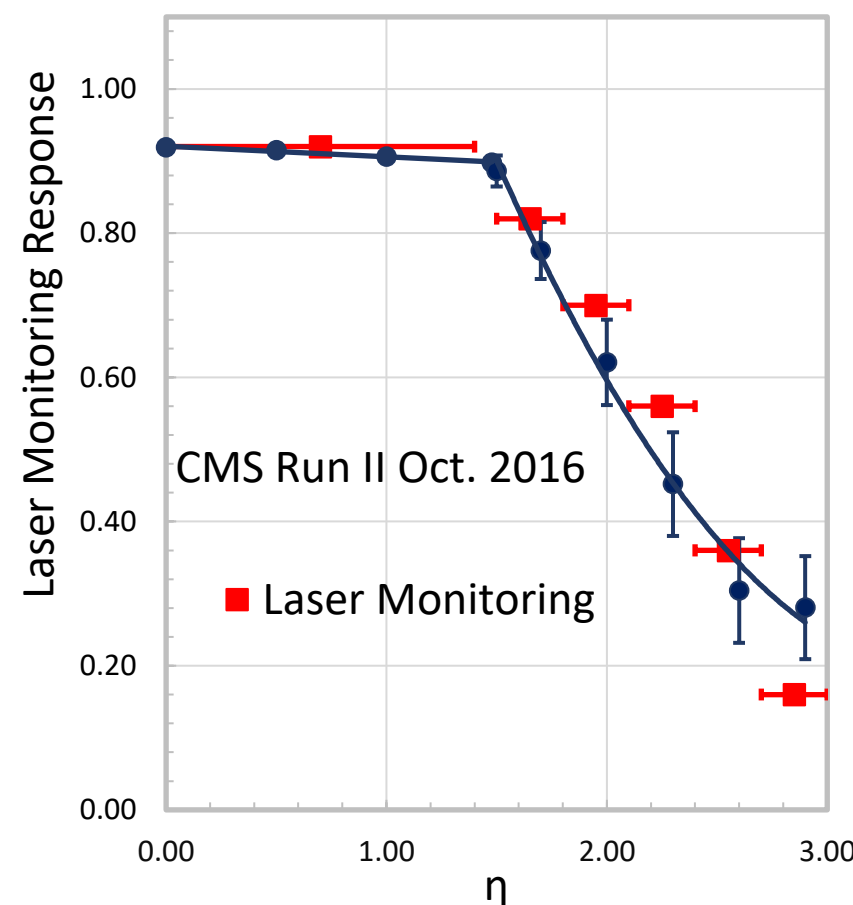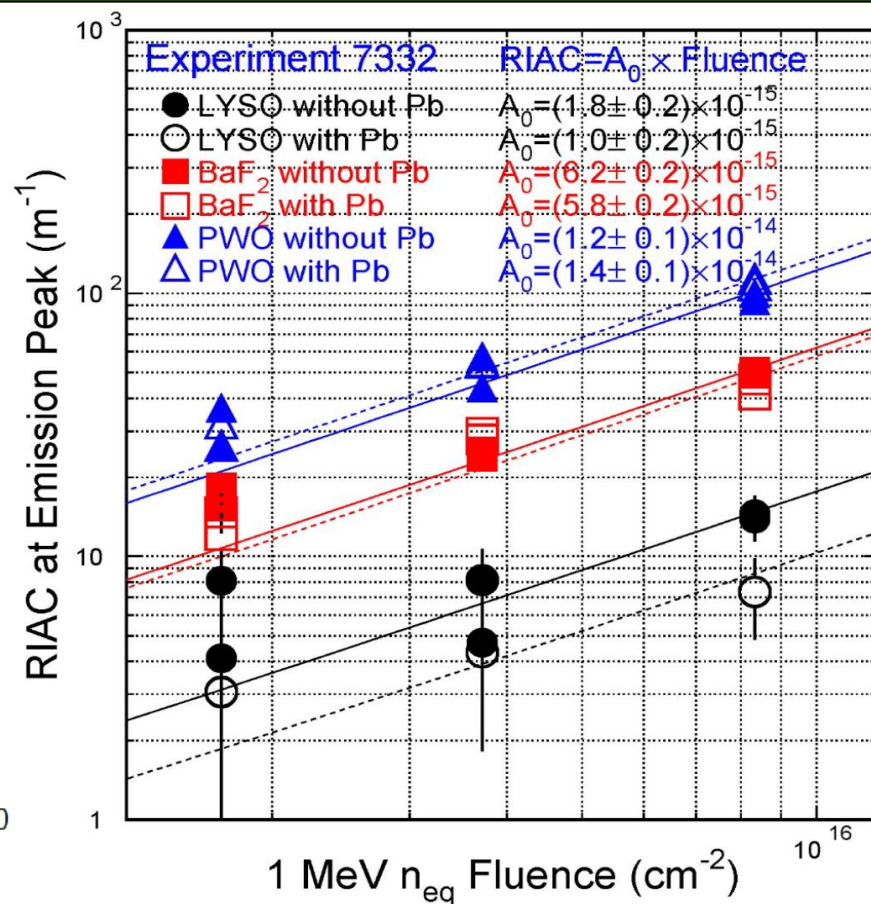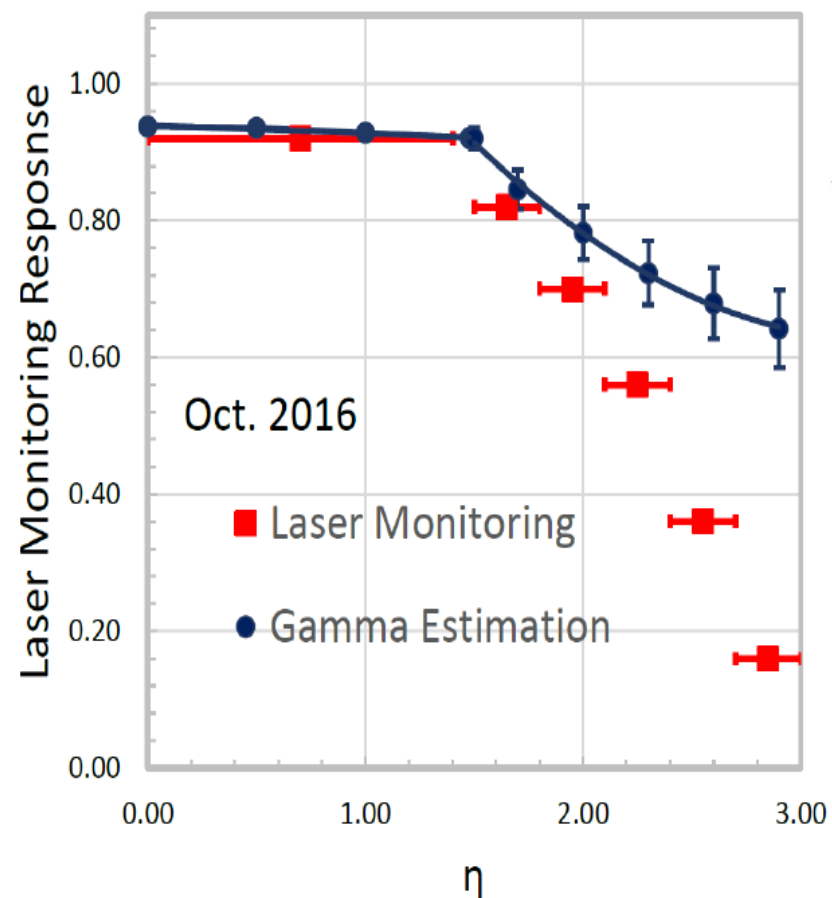



DOE Basic Research Needs Study

Priority Research Directions for Calorimetry

- Enhance calorimetry energy resolution for precision electroweak mass and missing-energy measurements;
- Advance calorimetry with spatial and timing resolution and radiation hardness to master high-rate environments;
- Develop ultrafast media to improve background rejection in calorimeters and particle identification detectors.

DOE 2019: <https://www.osti.gov/servlets/purl/1659761>

ECFA 2021: <https://cds.cern.ch/record/2784893>

Snowmass 2021: <https://arxiv.org/abs/2209.14111>




Fast/ultrafast, radiation hard and cost-effective inorganic scintillators

LYSO:Ce Radiation Hardness



IEEE TNS 63 (2016) 612-619

CMS BTL LYSO spec: RIAC < 3 m⁻¹ after 4.8 Mrad, 2.5 x 10¹³ p/cm² and 3.2 x 10¹⁴ n_{eq}/cm²

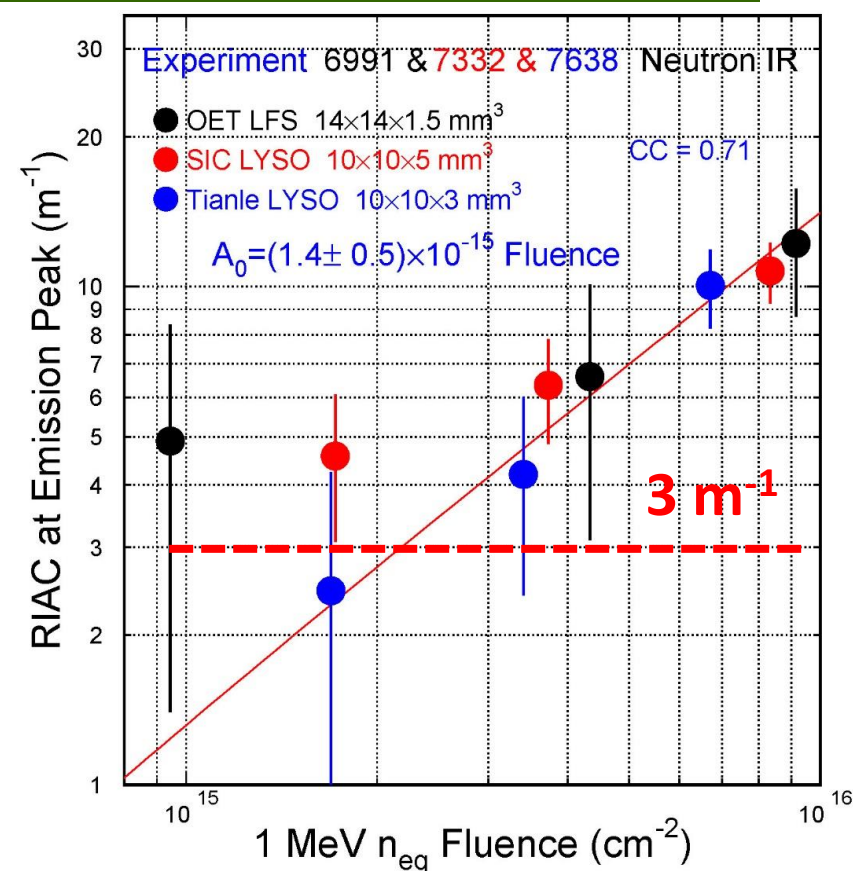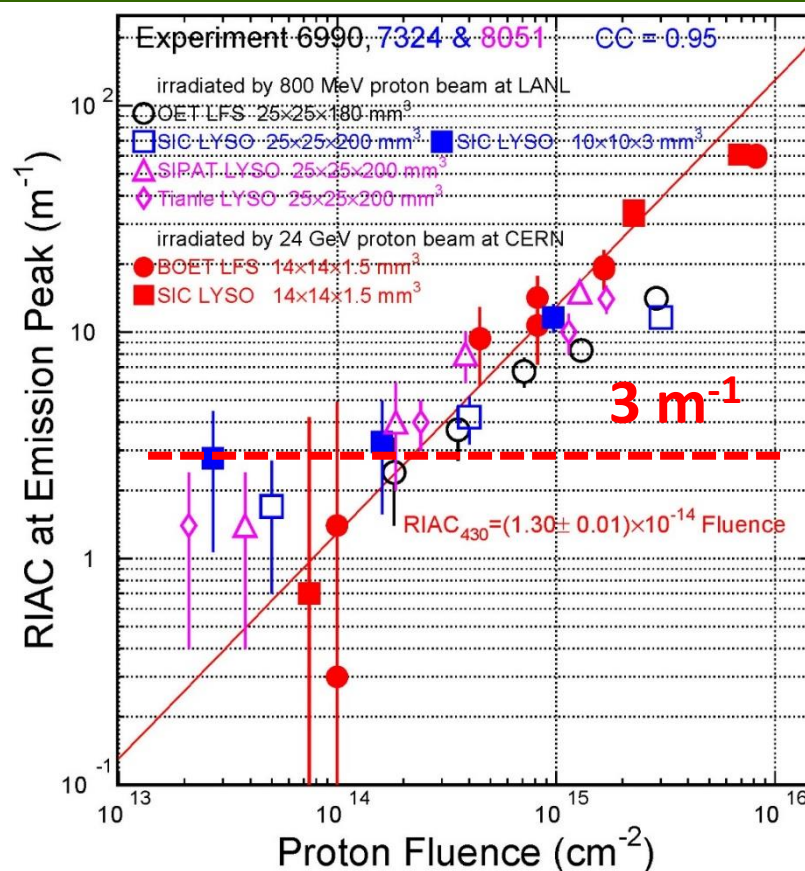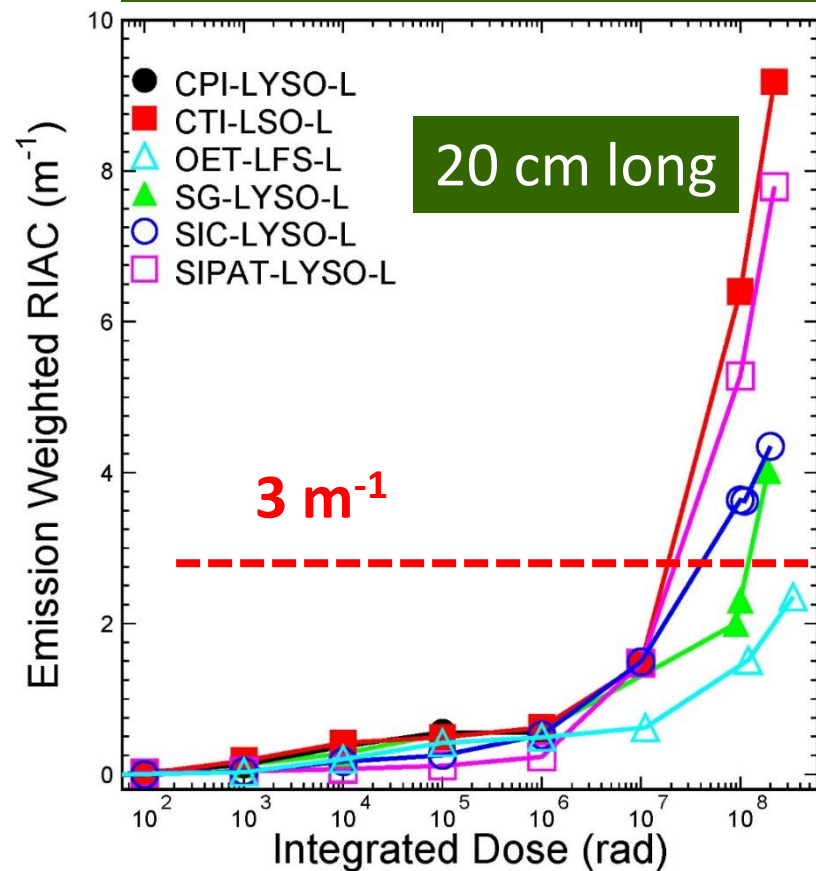

Damage induced by protons is larger than that from neutrons because of ionization energy loss in addition to displacement and nuclear breakup


LYSO:Ce for CMS MIP Timing Detector



MTD performance goal: 30-40 ps at the start degrading to < 60 ps at 3000 fb^{-1}


Barrel Timing Layer: arrays of LYSO crystal bars connected to SiPMs at both ends and readout by TOFHIR

Ultrafast inorganic scintillators would help to break the pico-second time barrier

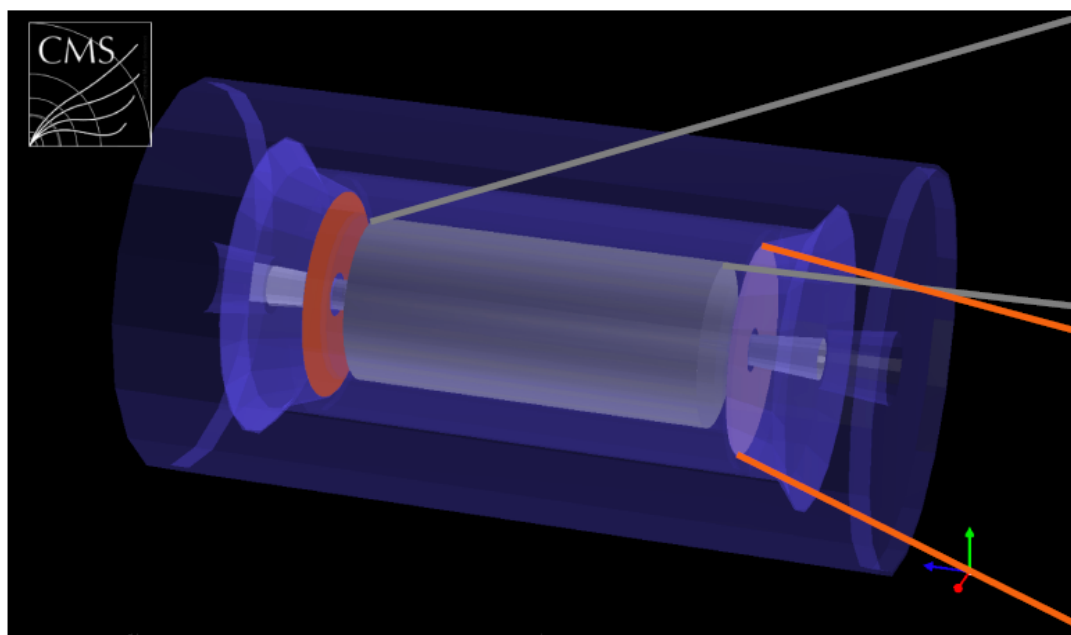


BTL: LYSO bars + SiPM read-out

- ▷ TK / ECAL interface ~ 45 mm thick
- ▷ $|\eta| < 1.45$ and $p_T > 0.7$ GeV
- ▷ Active area $\sim 38 \text{ m}^2$; 332k channels
- ▷ Fluence at 3 ab^{-1} : $2 \times 10^{14} \text{ n}_{\text{eq}}/\text{cm}^2$

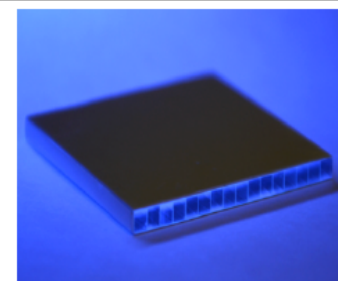

ETL: Si with internal gain (LGAD)

- ▷ On the HGC nose ~ 65 mm thick
- ▷ $1.6 < |\eta| < 3.0$
- ▷ Active area $\sim 14 \text{ m}^2$; $\sim 8.5\text{M}$ channels
- ▷ Fluence at 3 ab^{-1} : up to $2 \times 10^{15} \text{ n}_{\text{eq}}/\text{cm}^2$

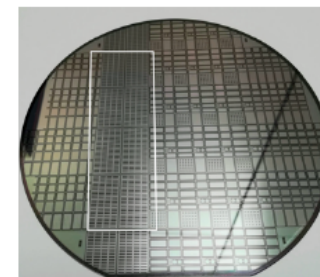

LYSO + SiPM with Thermal Electric Cooler (TEC) for CMS Barrel Timing Layer (BTL) in construction






LuAG:Ce Ceramics Radiation Hardness



IEEE TNS 69 (2022) 181-186


LuAG:Ce ceramics show a factor of two smaller RIAC values than LYSO:Ce up to $6.7 \times 10^{15} \text{ n}_{\text{eq}}/\text{cm}^2$ and $1.2 \times 10^{15} \text{ p}/\text{cm}^2$, promising for FCC-hh

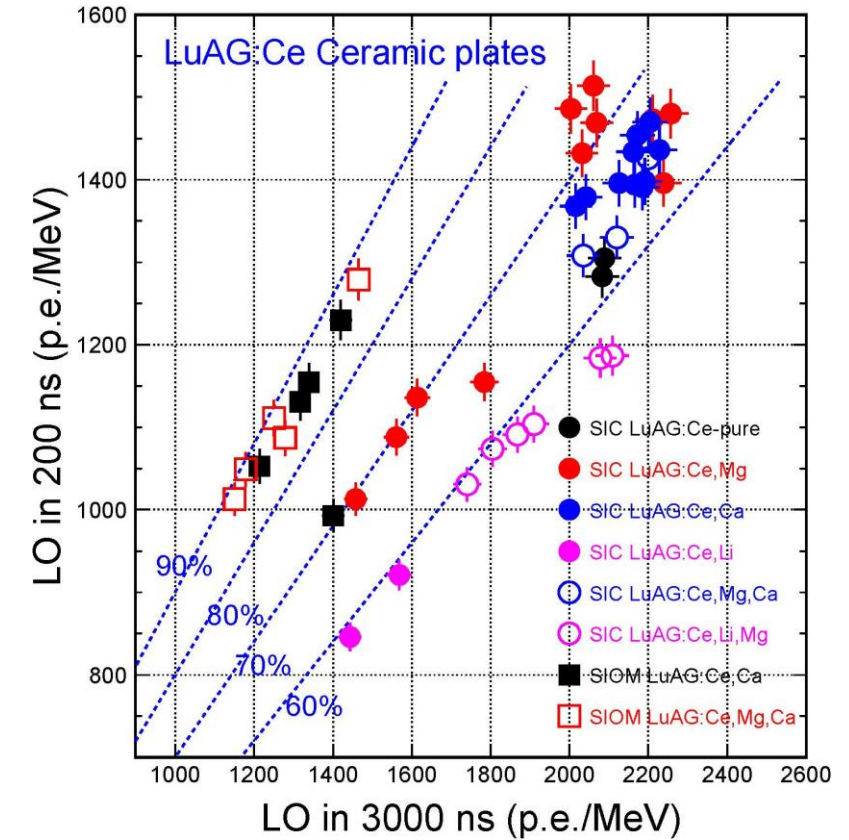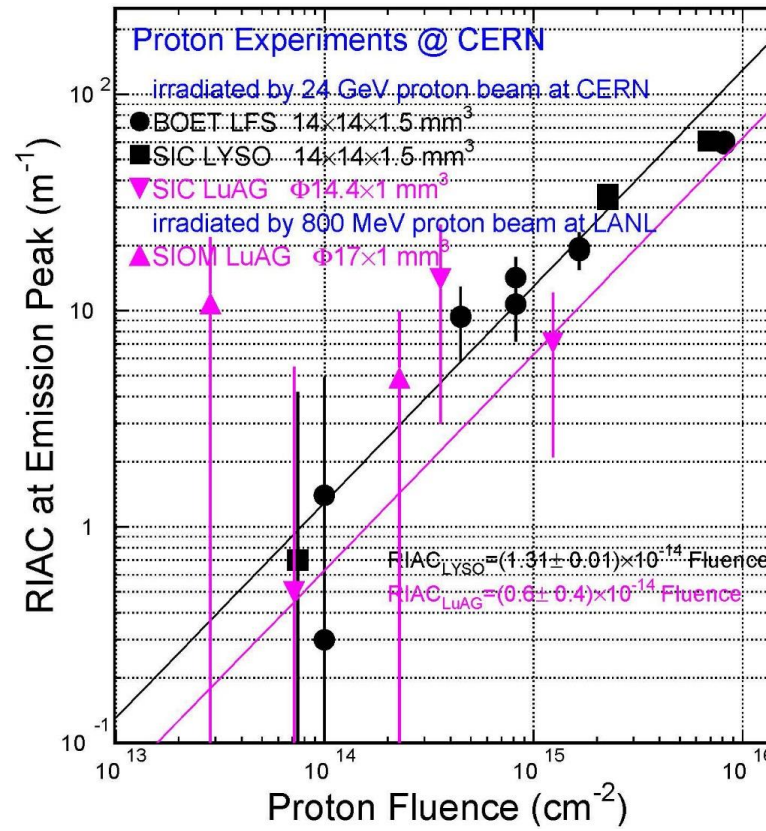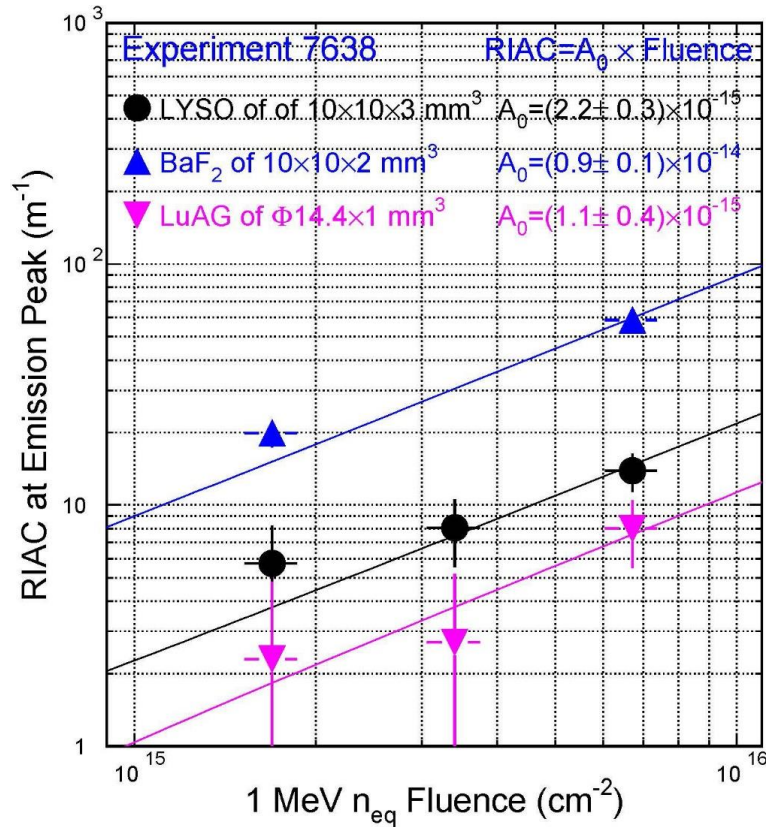

R&D on slow component suppression by Ca co-doping, and radiation hardness by $\gamma/\text{p}/\text{n}$







RADiCAL: LYSO/LuAG Shashlik ECAL

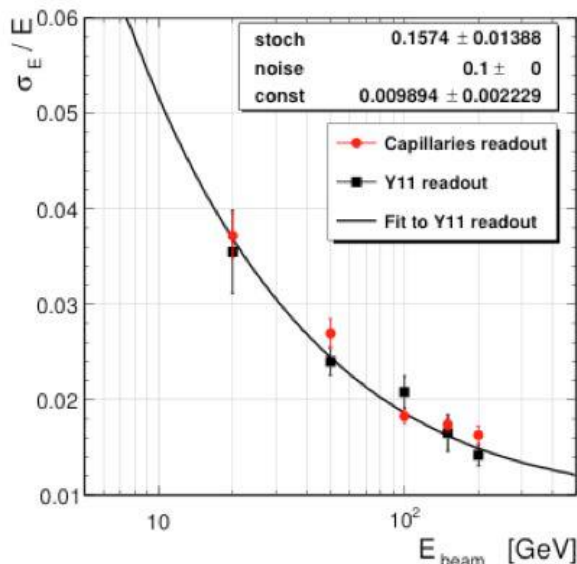

arXiv: 2203.12806
See RADiCAL Talk

RADiation hard **CAL**orimetry
Reducing light path length to
mitigate radiation damage effect
Using radiation hard materials:
LuAG:Ce ceramics excitation
matches LYSO:Ce emission

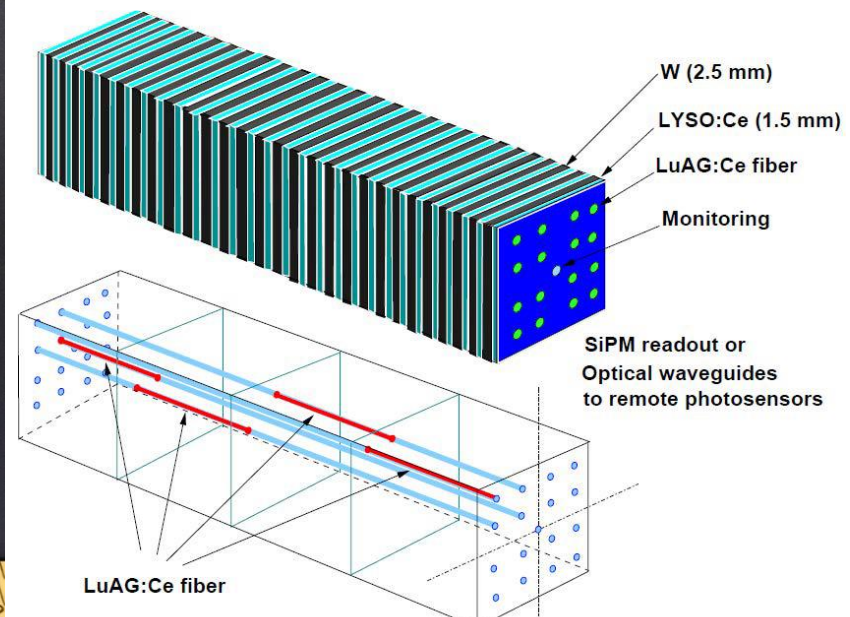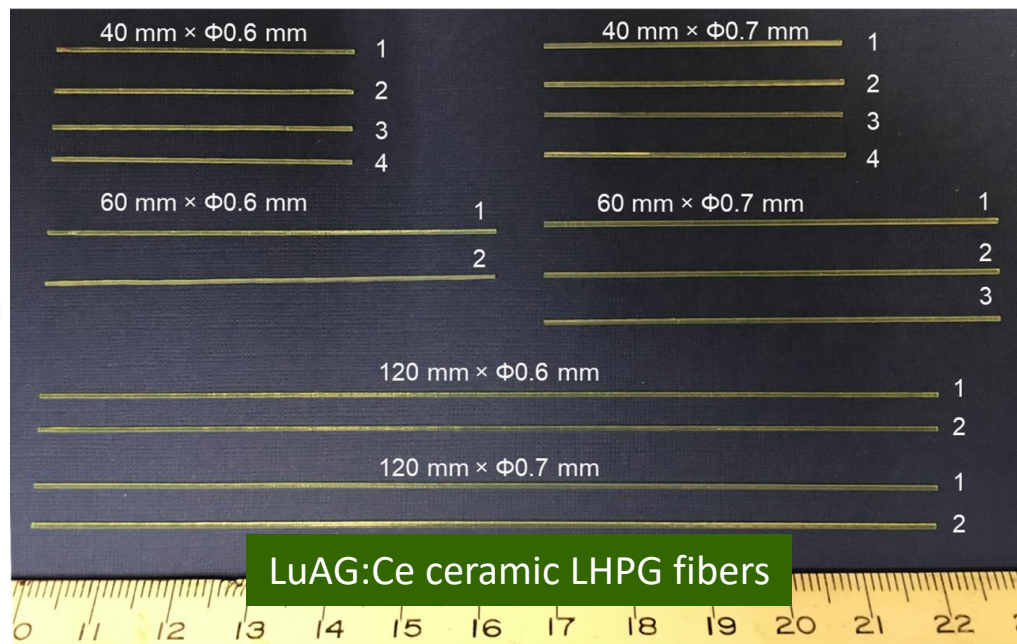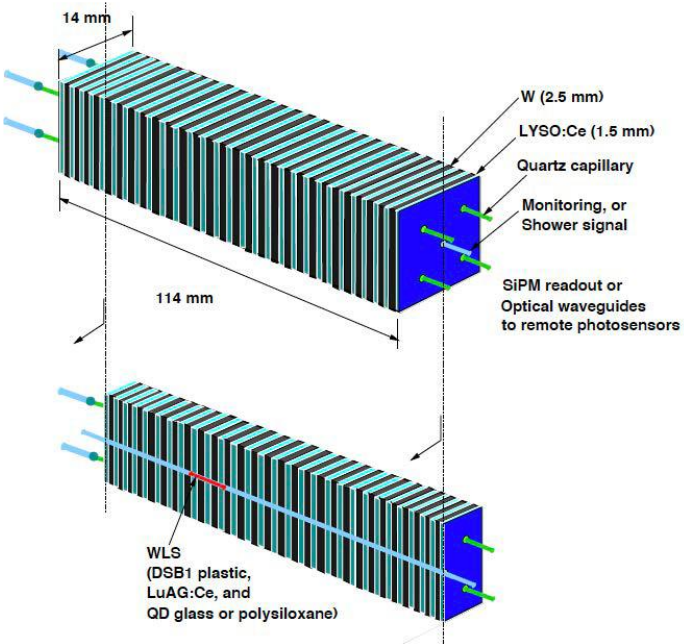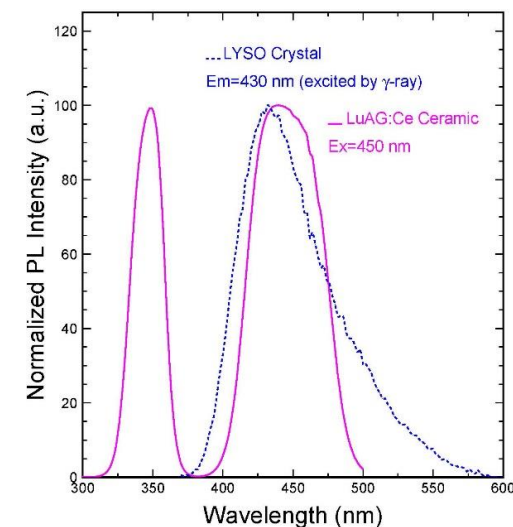





Light Output and Response Uniformity



10.1109/NSS/MIC44867.2021.9875908

Excellent longitudinal uniformity observed for a $\Phi 0.6 \times 120 \text{ mm}^3$ LuAG:Ce ceramic excited by a 420 nm LED at different location, with a solid coupling to a quartz fiber, mimicking its application in RADiCAL

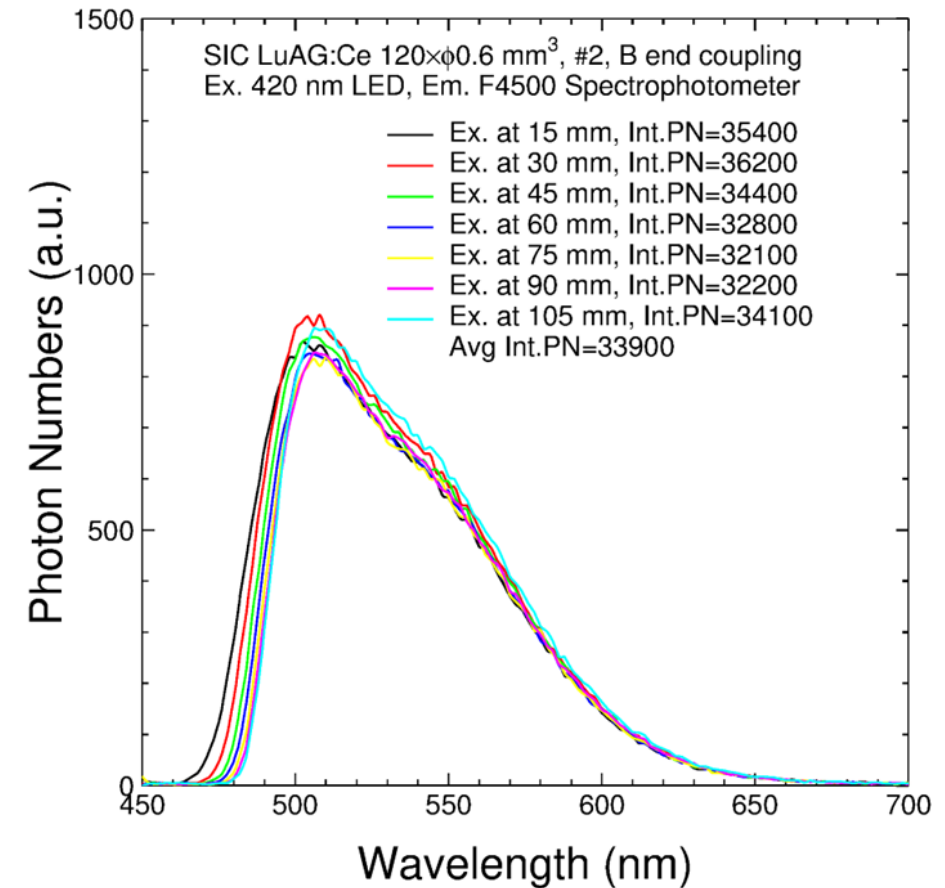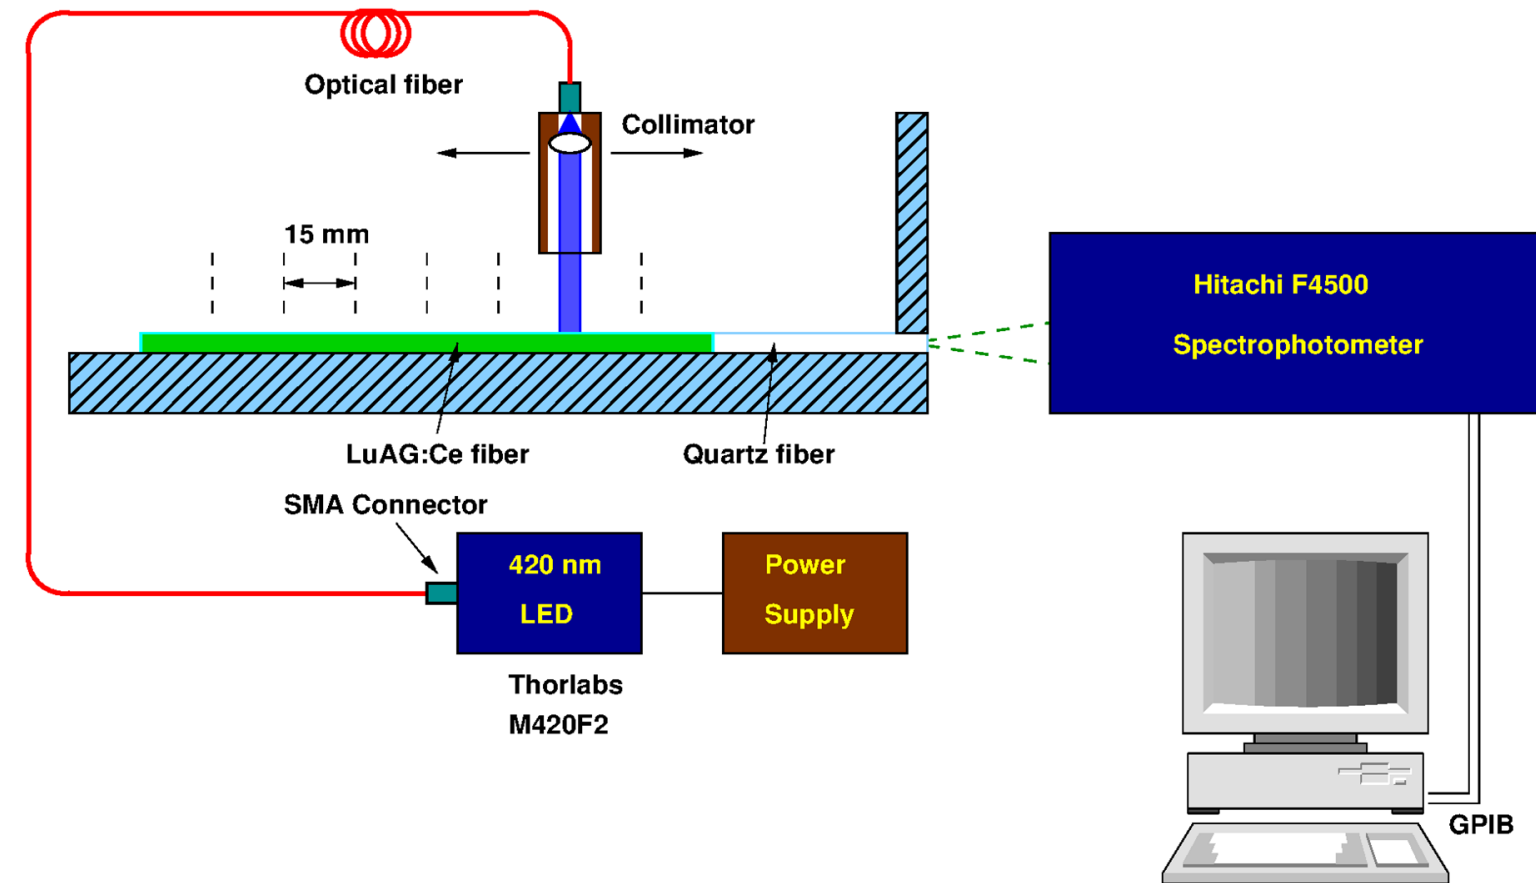



Ultrafast BaF₂:Y Calorimeter for Mu2e-II




Use ultrafast material to mitigate pile-up

• Energy resolution	$\sigma < 5\%$ (FWHM/2.36) @ 100 MeV
• Time resolution	$\sigma < 500$ ps
• Position resolution	$\sigma < 10$ mm
• Radiation hardness	
• Crystals	1 kGy/yr and a total of 10^{12} n_1 MeV equivalent/cm ² total
• Photosensors	3×10^{11} n_1 MeV equivalent/cm ² total

Mu2e-I: 1,348 CsI of 34 x 34 x 200 mm³

CsI+SiPM

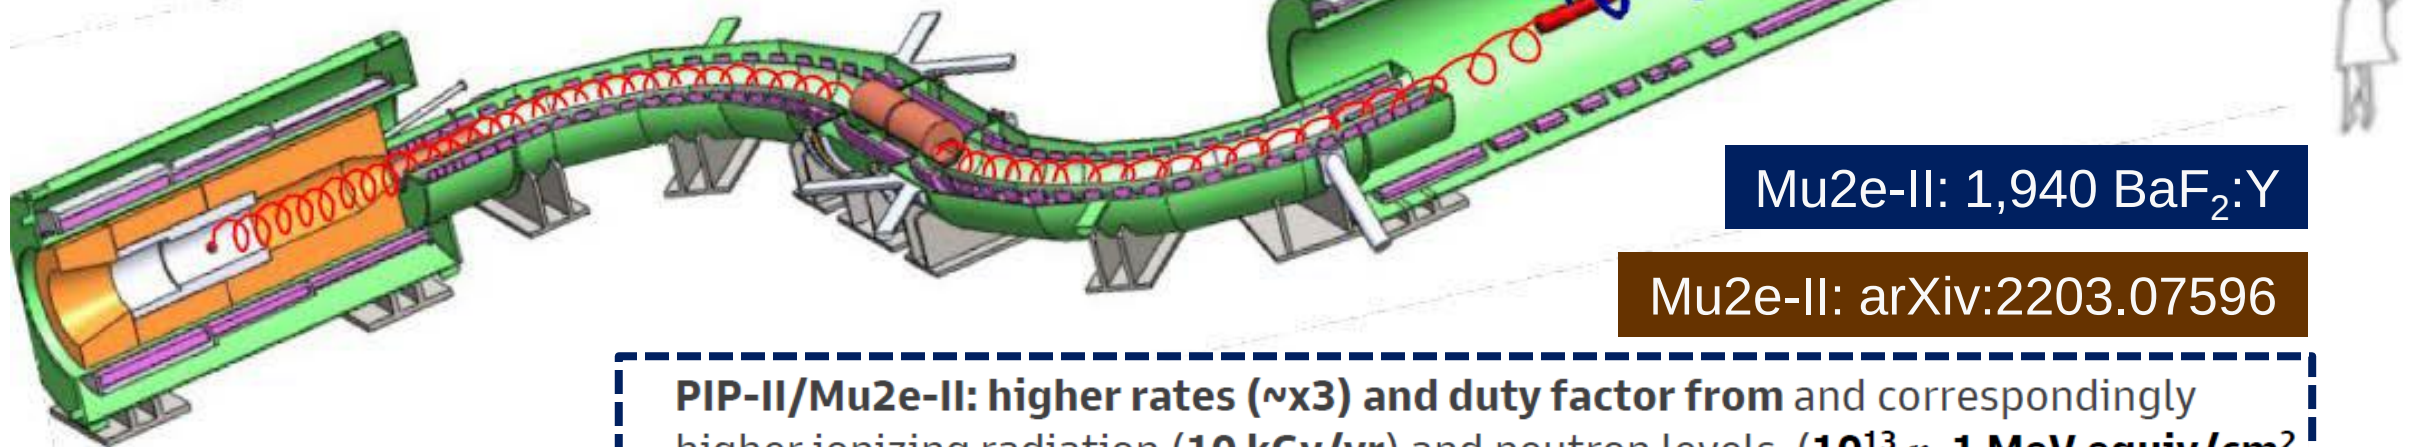

Mu2e-II: 1,940 BaF₂:Y

Mu2e-II: arXiv:2203.07596








PIP-II/Mu2e-II: higher rates ($\sim \times 3$) and duty factor from and correspondingly higher ionizing radiation (10 kGy/yr**) and neutron levels (**10^{13} n_1 MeV equiv/cm² total**), which are particularly important at the inner radius of disk 1**



BaF₂:Y for Calorimetry & Imaging



Increased F/S ratio observed in BGRI BaF₂:Y crystals: Proc. SPIE 10392 (2017)

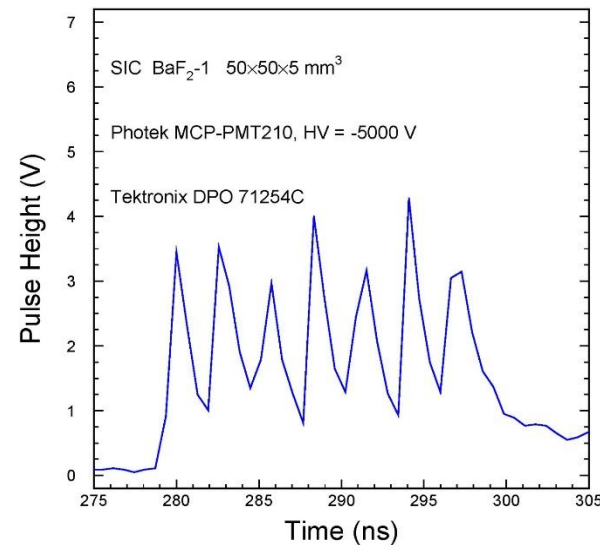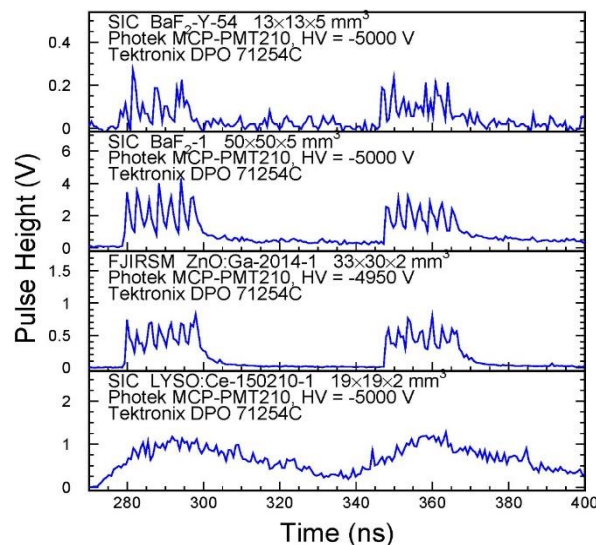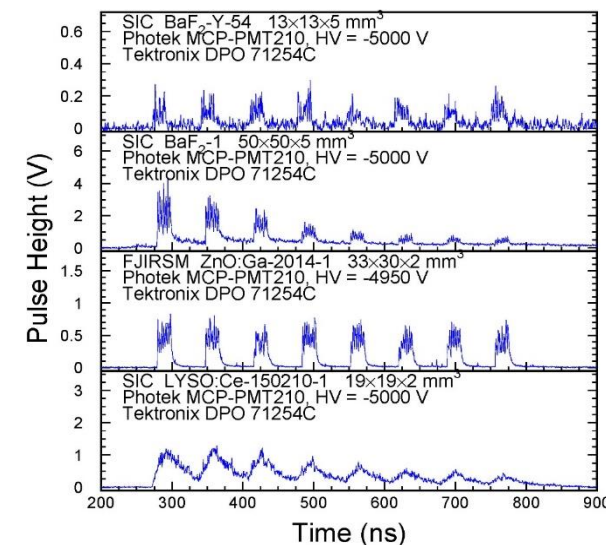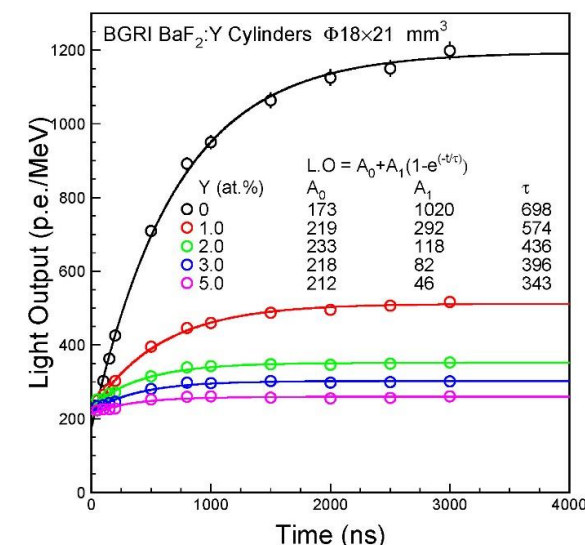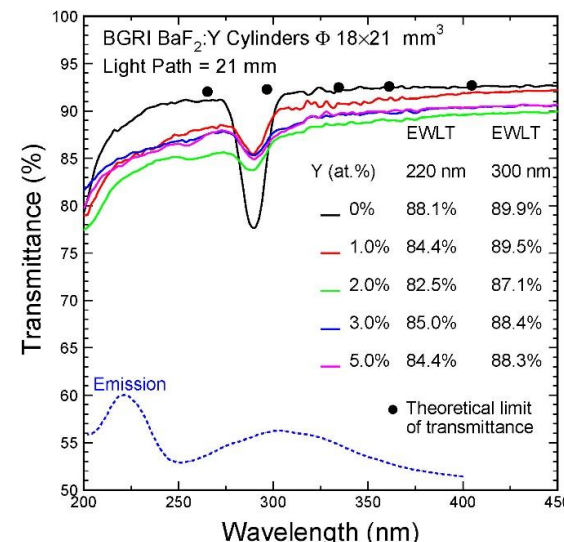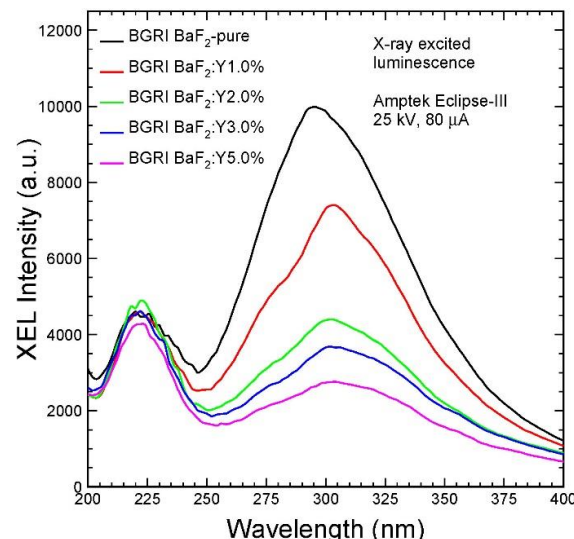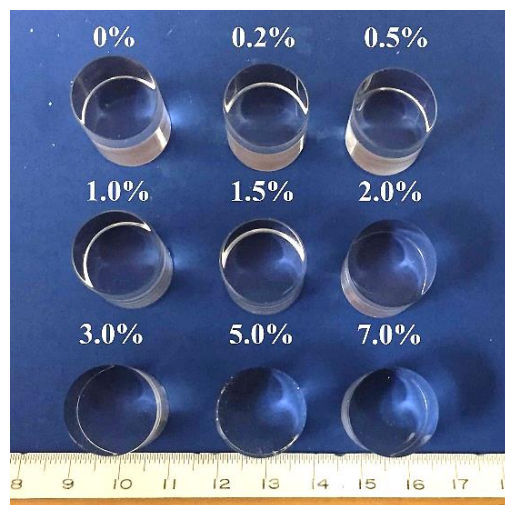

X-ray bunches with 2.83 ns spacing in septuplet are clearly resolved by ultrafast BaF₂:Y and BaF₂ crystals: for GHz Hard X-ray Imaging NIMA 240 (2019) 223-239




PDE of UV SiPM for BaF₂ and BaF₂:Y



IEEE TNS 69 (2022) 958-964

γ -ray induced readout noise is reduced by BaF₂:Y slow suppression & solar-blind PDE

Photodetector	EWPDE _{fast} (%)	EWPDE _{slow} (%)	Relative F/S _{BaF}	Relative F/S _{BaF:Y}
Hamamatsu MPPC	10.5	9.8	1/4.8	1/1.5
FBK SiPM 2021	17.8	12.7	1/3.6	1/1.1
FBK SiPM 2023-1	14.8	4.6	1/1.6	1/0.5
FBK SiPM 2023-2	14.8	5.0	1/1.7	1/0.5



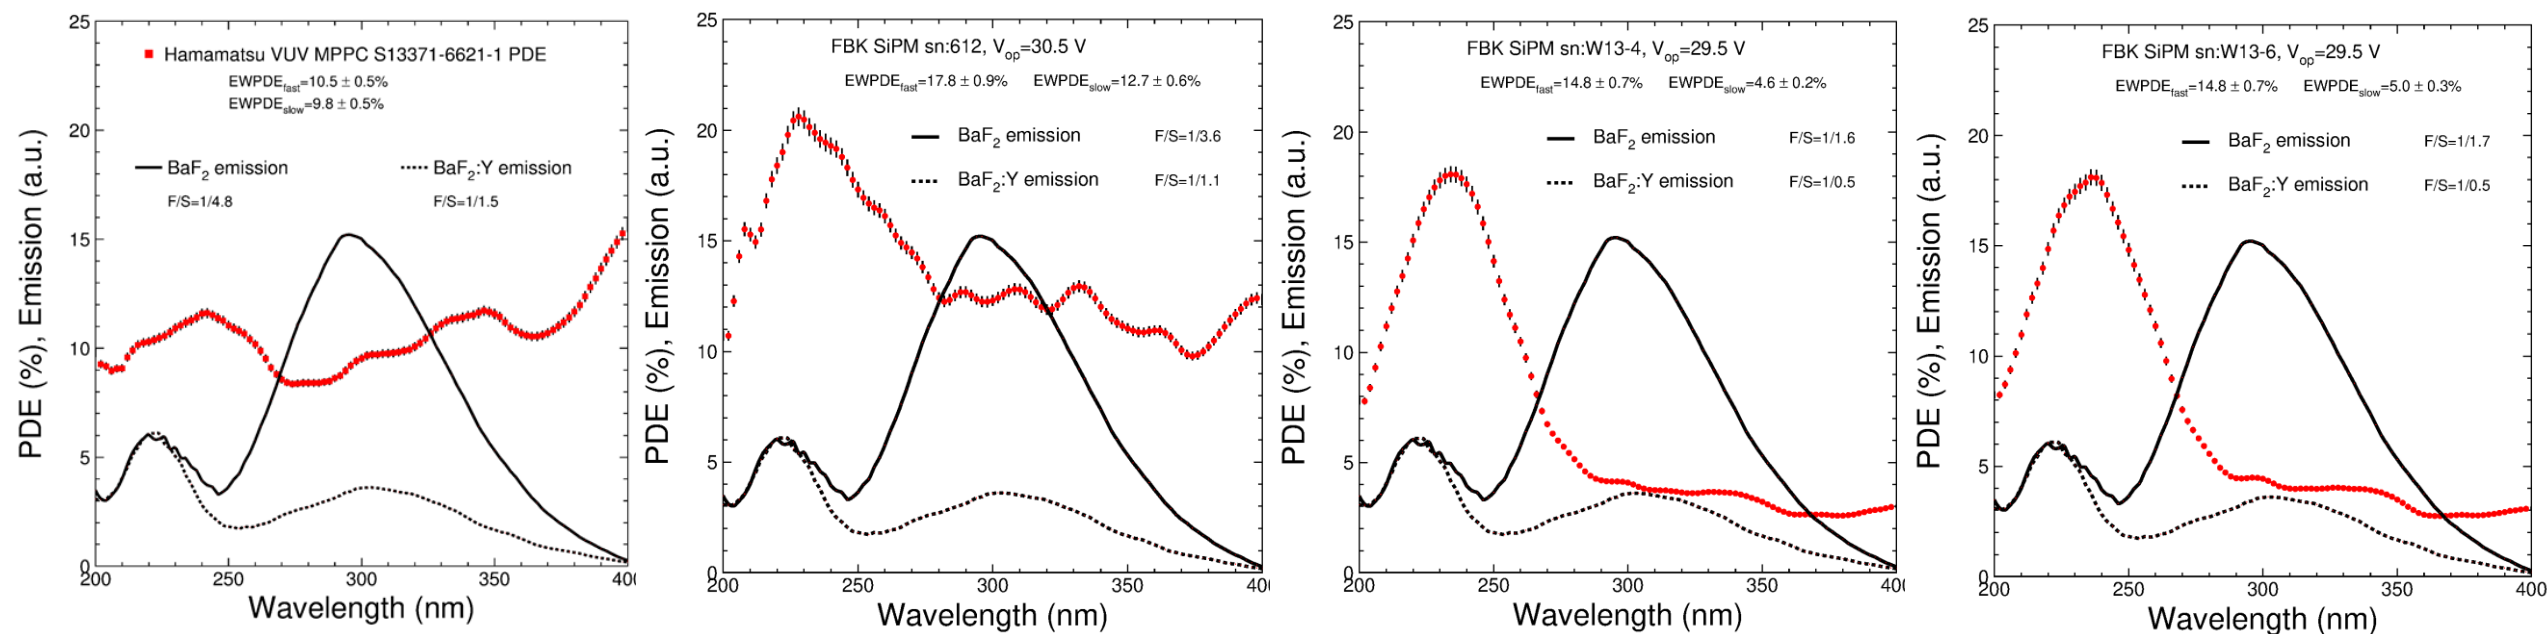




Novel $\text{Lu}_2\text{O}_3:\text{Yb}$ Ceramics



Presented in the NSS2022 conference https://www.its.caltech.edu/~rzhu/talks/NSS22_N21-03.pdf

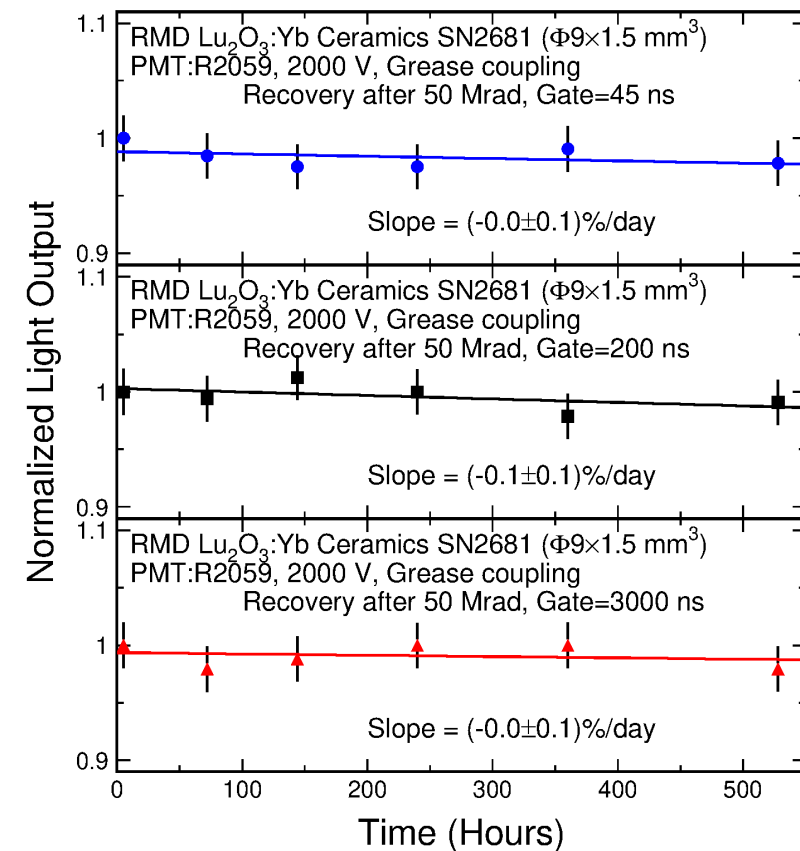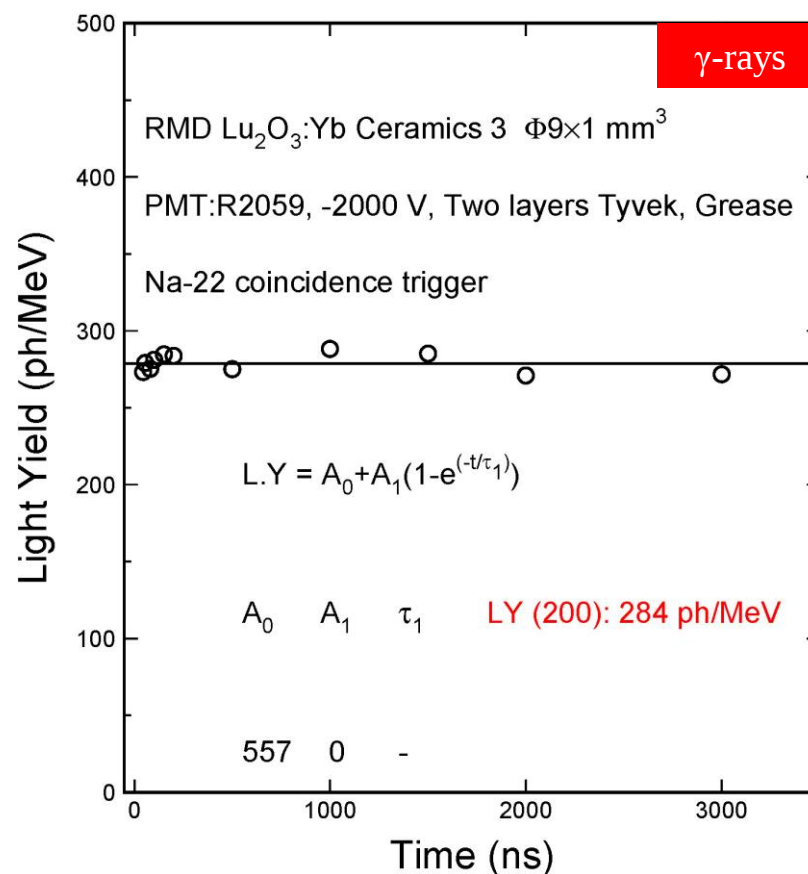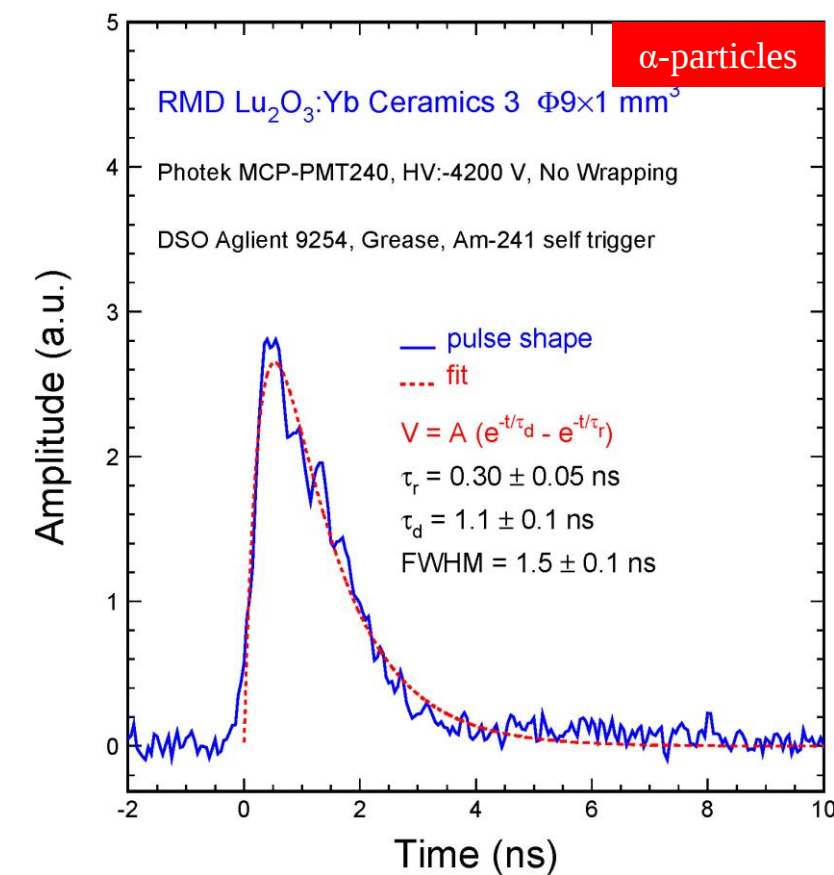




$\text{Lu}_2\text{O}_3:\text{Yb}$ ceramic of 9.4 g/cc shows an ultrafast decay time of **1.1 ns** by Am-241 with negligible slow component observed in integrated light output measurement





CalVision: Segmented Crystal ECAL

See R. Hiroski in This Conference

Followed by the IDEA DR HCAL, aiming at both EM and jet resolution

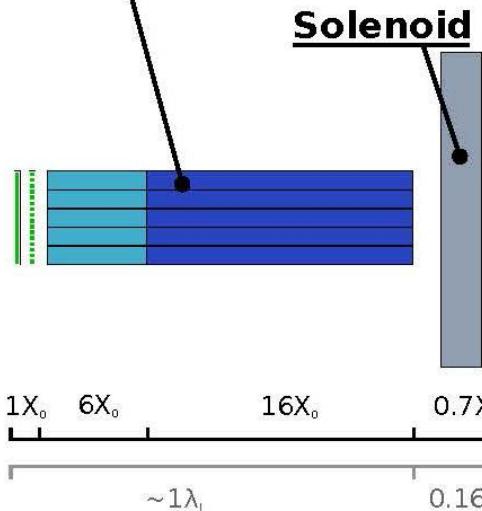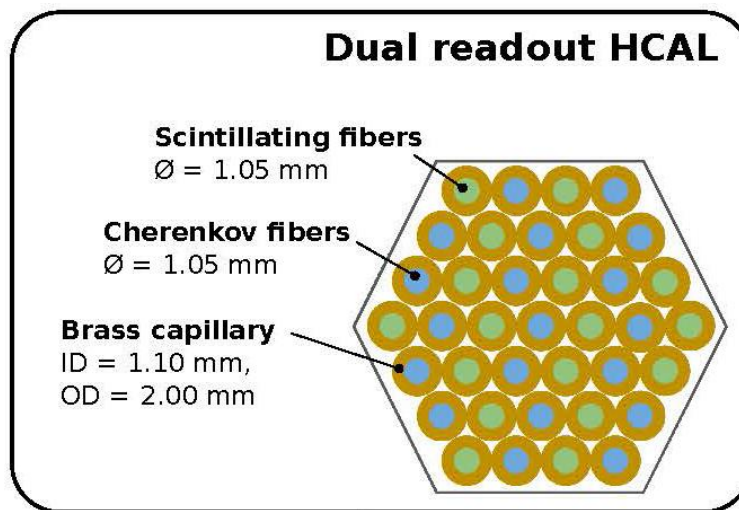
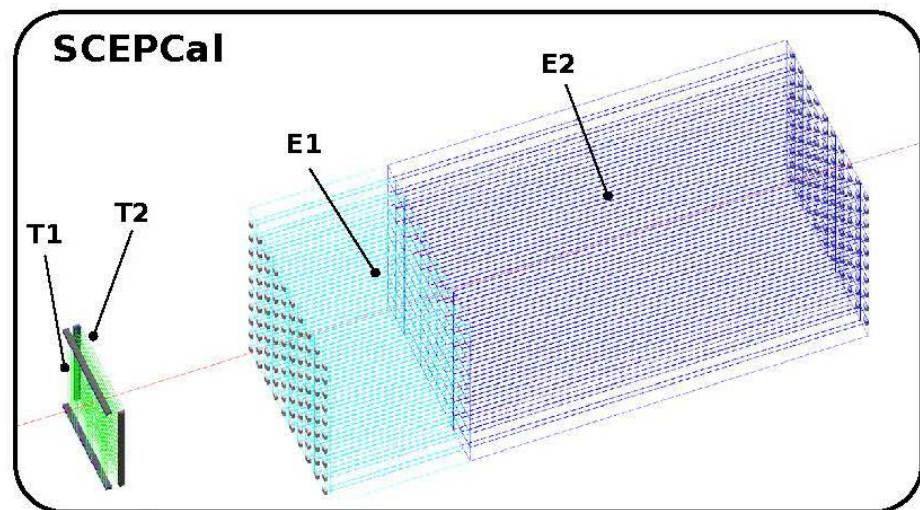


M. Lucchini et al., JINST 15 (2020) P11005

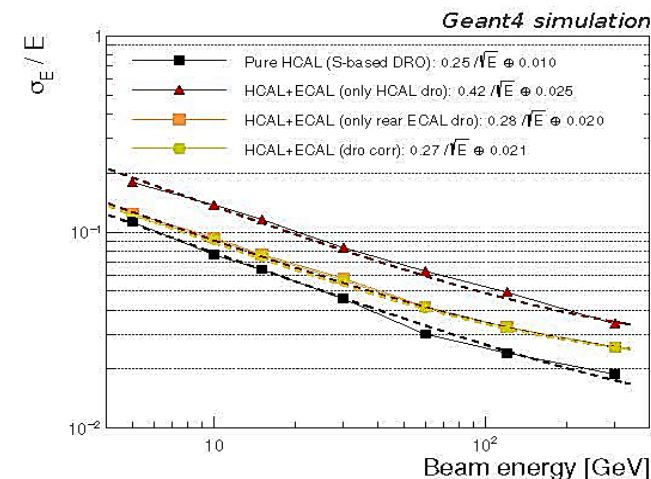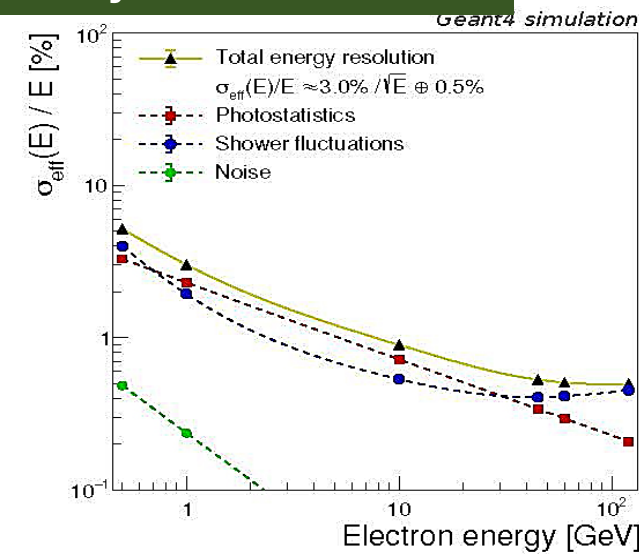




The HHCAL Concept

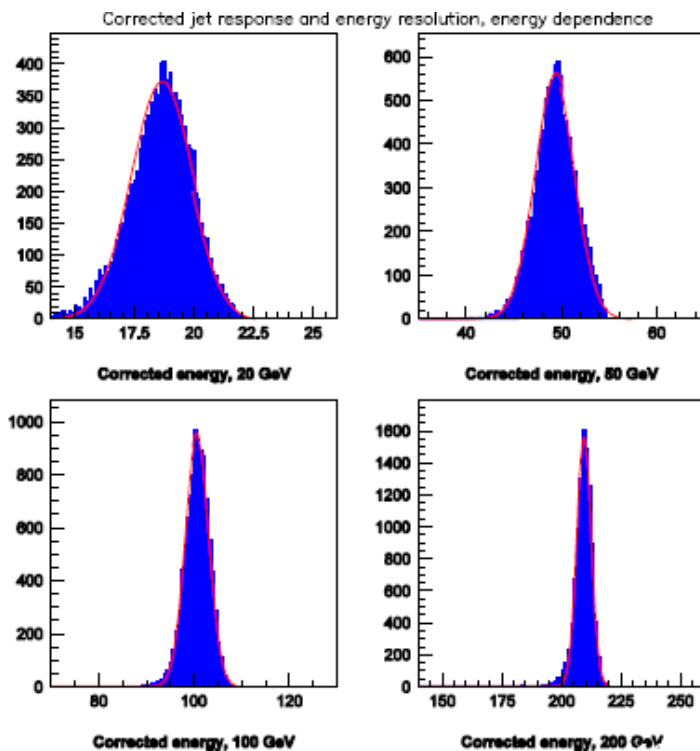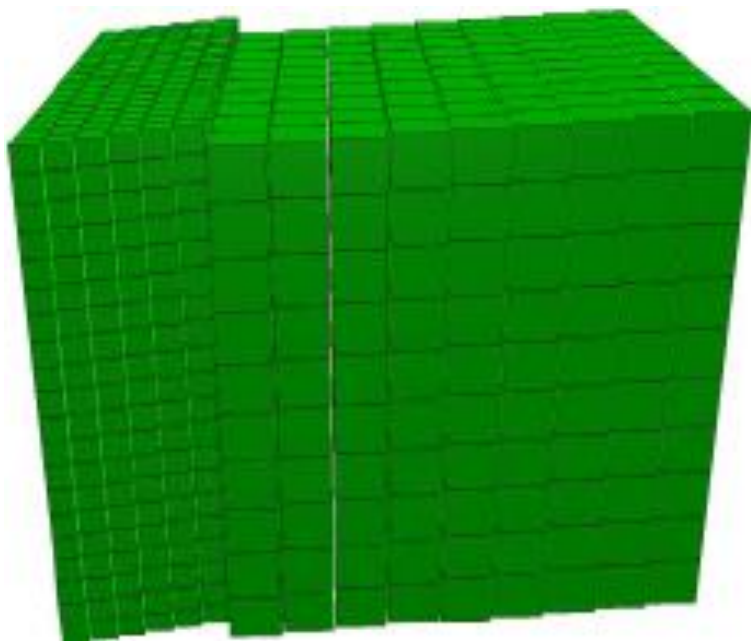


A. Para, H. Wenzel and S. McGill in
Callor2012 Proceedings and
A. Benaglia *et al.*, IEEE TNS **63** (2016)
574-579: a jet energy resolution at a
level of $20\%/\sqrt{E}$ by HHCAL with dual
readout of S/C or dual gate.
M. Demarteau, 2021 CPAD Workshop

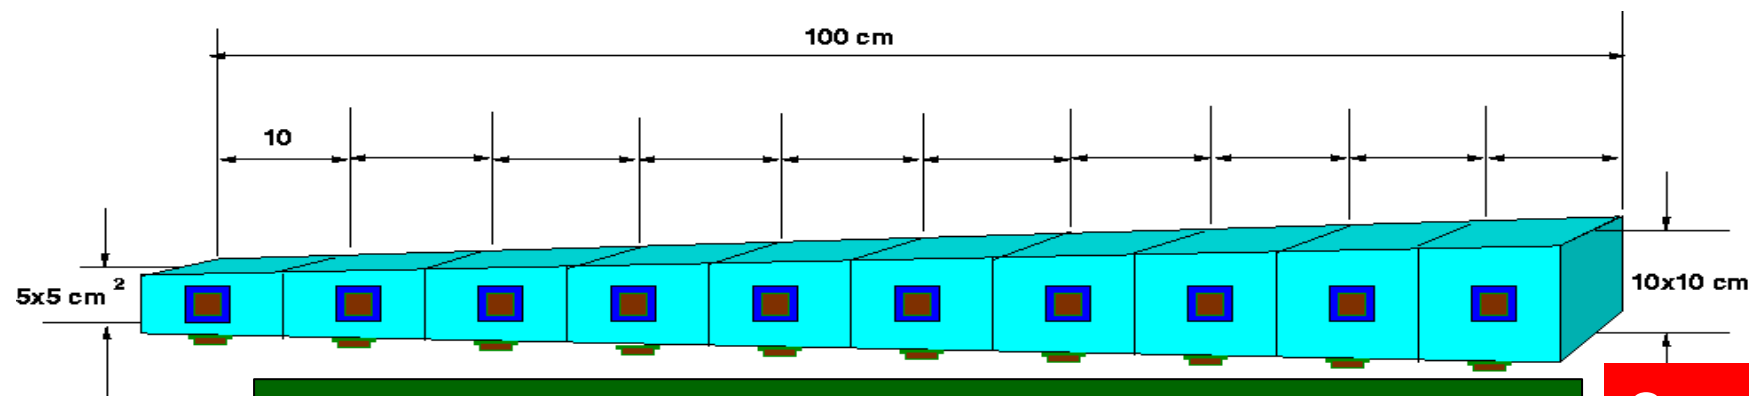






R.-Y. Zhu, ILCWS-8, Chicago: a HHCAL cell with pointing geometry

Can we afford?

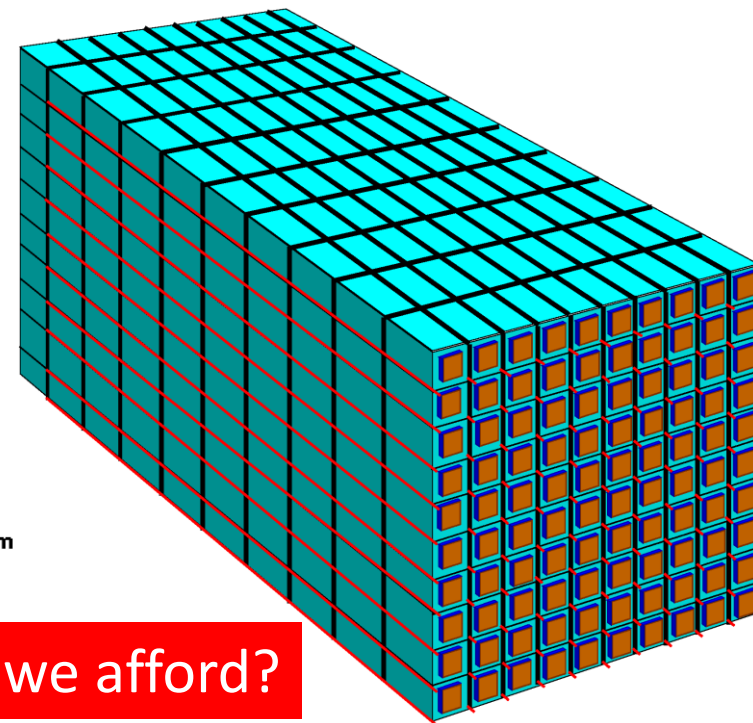







ABS ($B_2O_3-SiO_2-Al_2O_3-Gd_2O_3-Ce_2O_3$) Glass

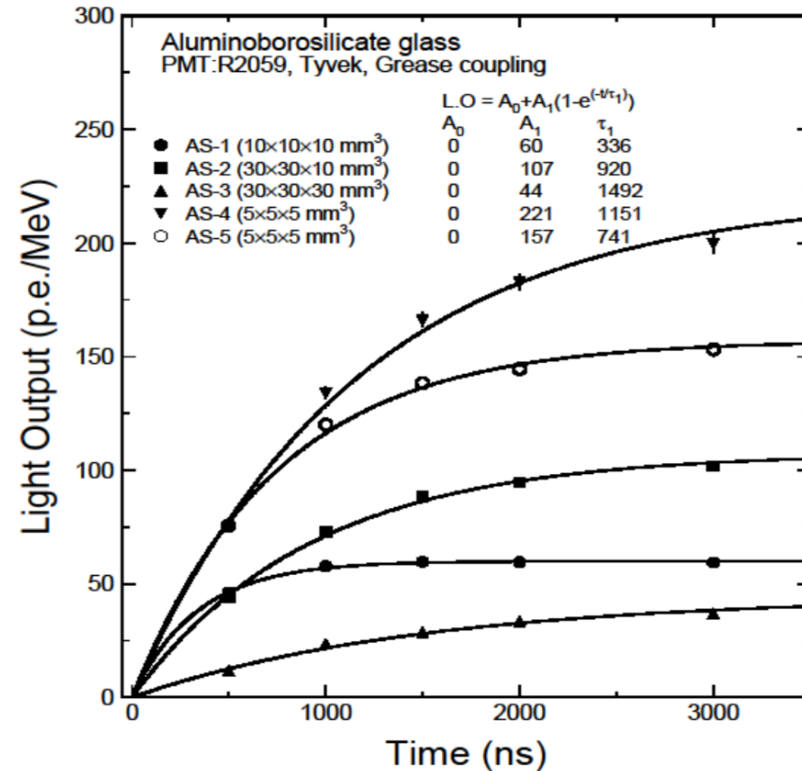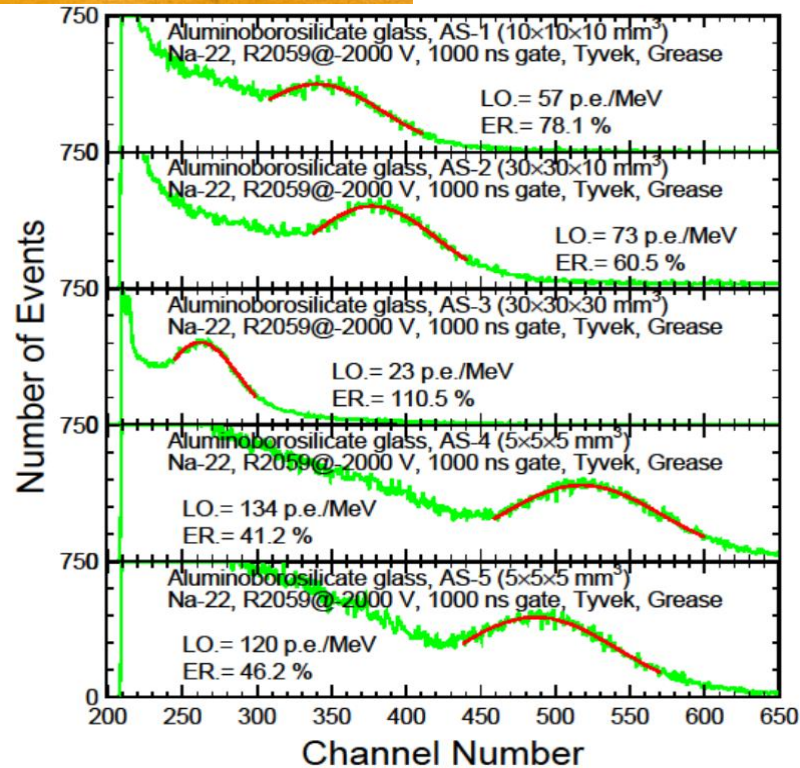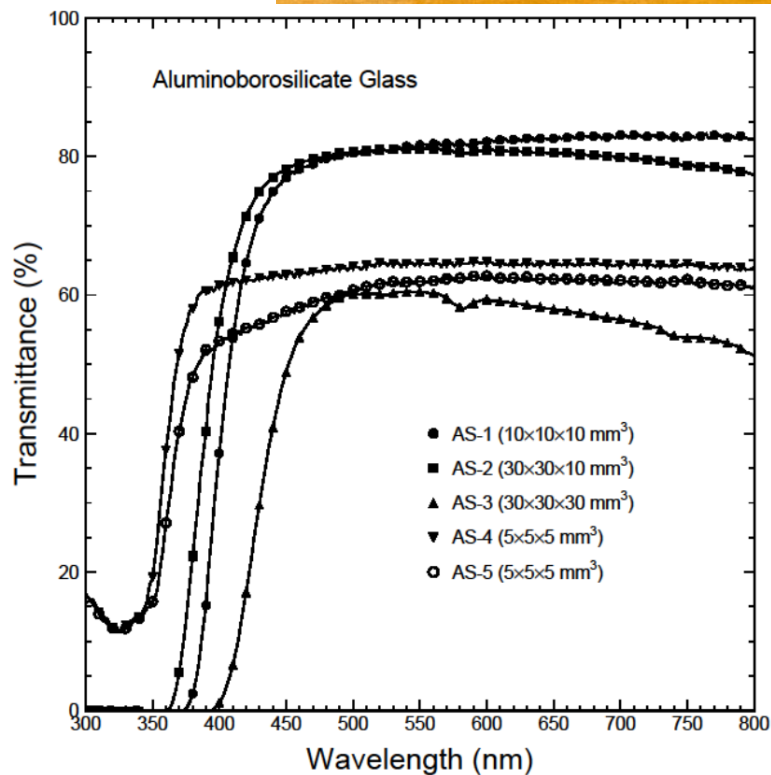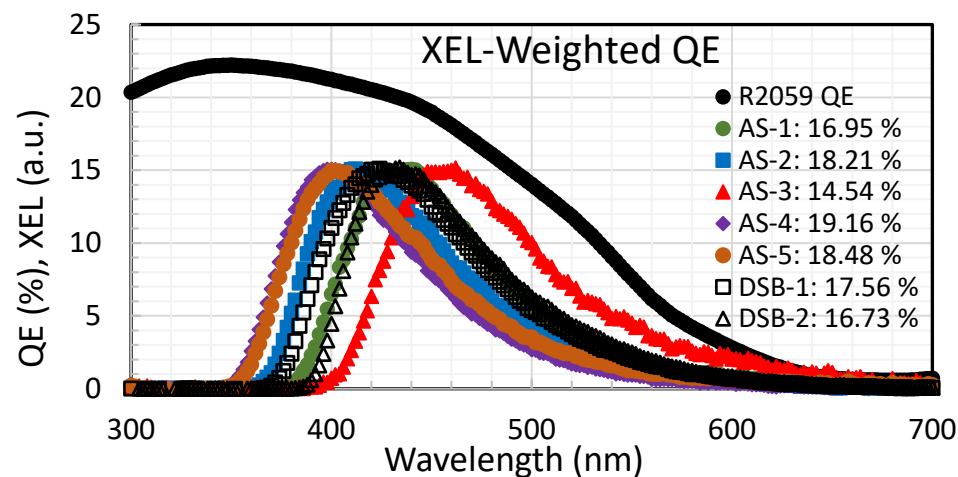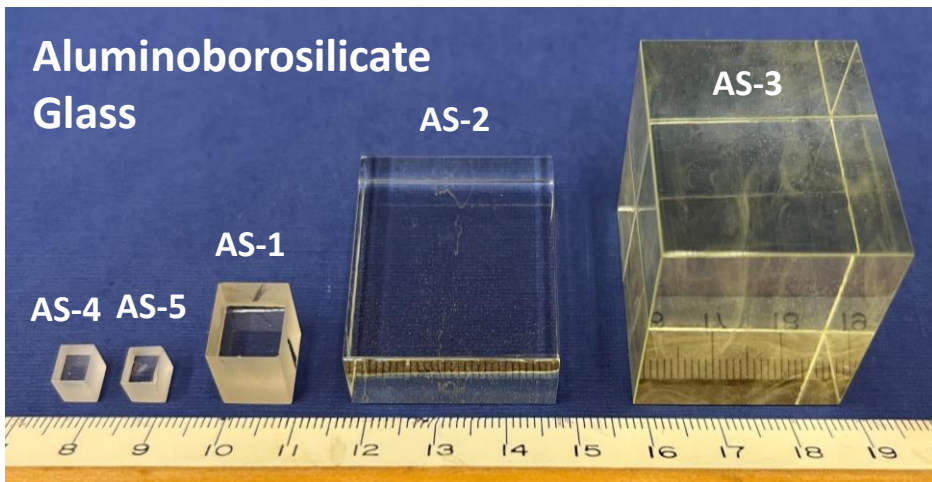



Large Size ABS and DSB Samples

See talks on glass scintillators in this conference

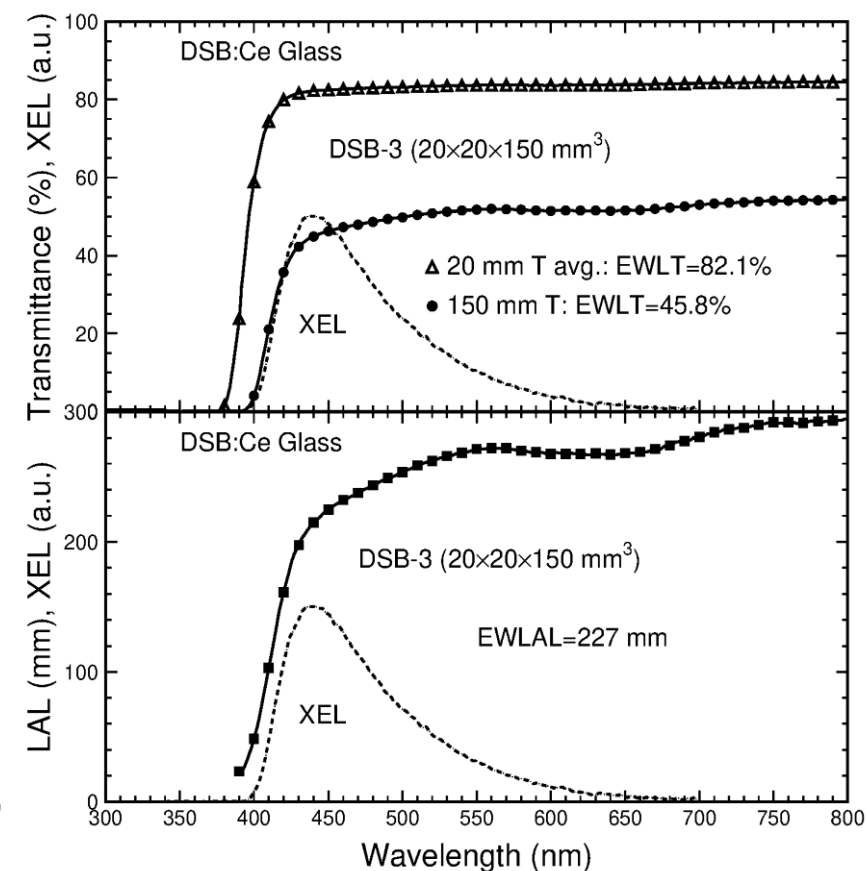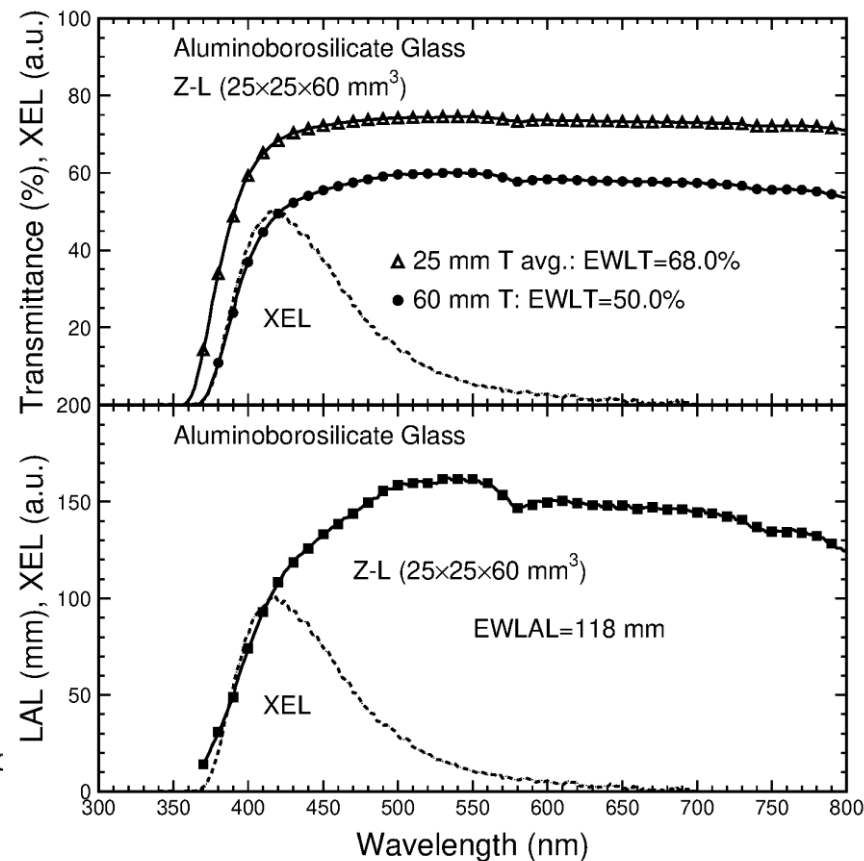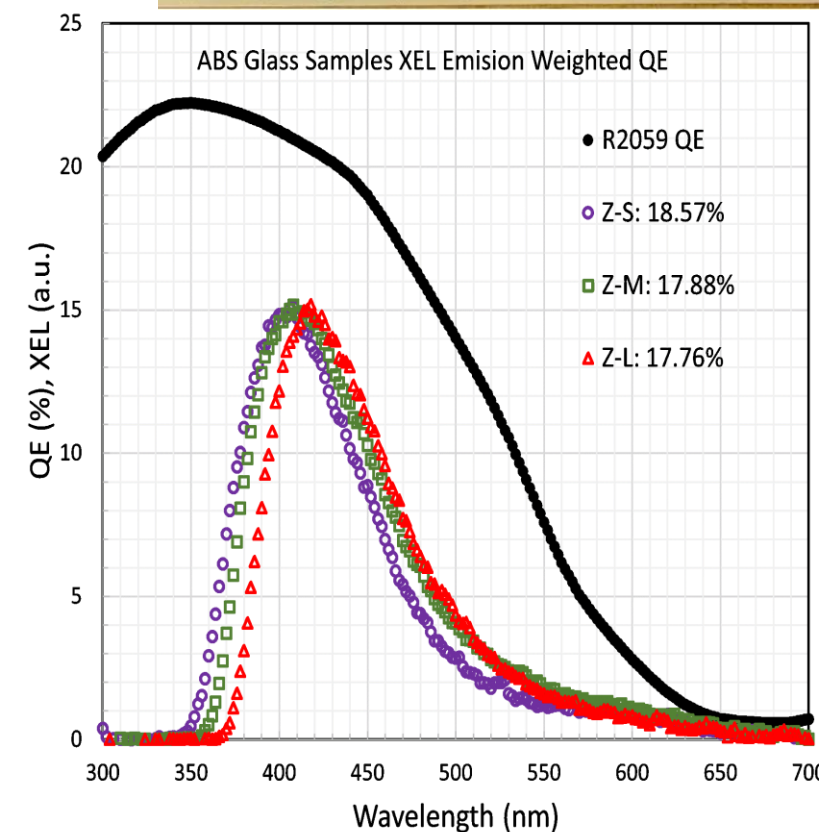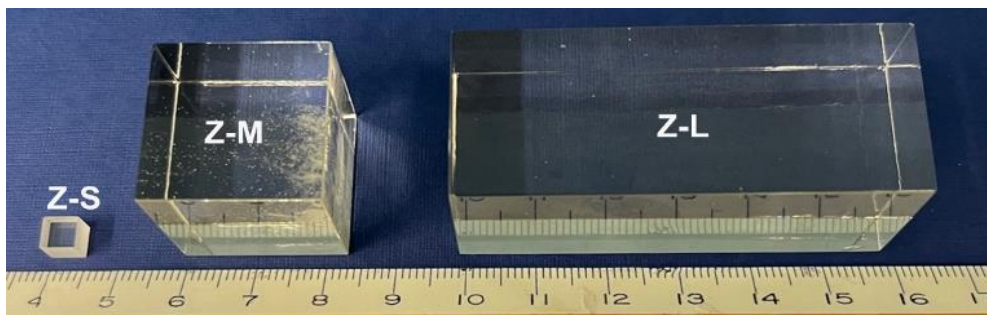



Inorganic Scintillators for HHCAL



Presented in the 9/14/2023 CalVision meeting all samples measured at Caltech

	BGO	BSO	PWO	PbF ₂	PbFCl	Sapphire:Ti	AFO:Ce Glass	DSB:Ce Glass	ABS:Ce Glass
Density (g/cm ³)	7.13	6.8	8.3	7.77	7.11	3.98	4.6	4.3	6.0
Melting point (°C)	1050	1030	1123	824	608	2040	980 ⁷	1550	?
X ₀ (cm)	1.12	1.15	0.89	0.94	1.05	7.02	2.96	2.58	1.56
R _M (cm)	2.23	2.33	2.00	2.18	2.33	2.88	2.90	3.24	2.49
λ _i (cm)	22.7	23.4	20.7	22.4	24.3	24.2	26.4	30.9	24.2
Z _{eff} value	71.5	73.8	73.6	76.7	74.7	11.1	41.4	49.5	56.6
dE/dX (MeV/cm)	8.99	8.59	10.1	9.42	8.68	6.75	6.84	6.1	8.0
Emission Peak ^a (nm)	480	470	425 420	\	420	300 750	365	420	400
Refractive Index ^b	2.15	2.68	2.20	1.82	2.15	1.76	?	?	?
LY (ph/MeV) ^c	7,500	1,500	130	\	150	7,900	450	1,360	1,150
Decay Time ^a (ns)	300	100	30 10	\	3	300 3200	40	500	740
d(LY)/dT (%/°C) ^c	-0.9	?	-2.5	\	?	?	?	0.3	?
Cost (\$/cc)	6.0	7.0	7.5	6.0	?	0.6	2.0	2.0	<1



Summary

The HL-LHC and FCC-hh require fast and radiation hard inorganic scintillators. **RADiCAL** proposes an ultra-compact, fast timing and longitudinally segmented shashlik calorimeter with LuAG:Ce ceramics as **wavelength** shifter for LYSO:Ce crystals. R&D is on-going to suppress slow components in LuAG:Ce.

Mu2e-II considers ultrafast BaF₂:Y calorimeter. R&D is on radiation hardness of BaF₂:Y and solar-blind SiPM. Industry is developing ultrafast Lu₂O₃:Yb ceramics.

CalVision proposes a dual readout longitudinally segmented crystal ECAL combined with the IDEA HCAL promising excellent EM and Hadronic resolutions for the proposed lepton Higgs factory.

Homogeneous HCAL (**HHCAL**) promises the best jet mass resolution by total absorption. Novel cost-effective heavy scintillating glass is under development.

R&D on calorimetry is being integrated in ECFA DRD6 WP3 and CPAD RDC9

Acknowledgements: DOE HEP Award DE-SC0011925 and DE-SC0024094